

SCIENTIFIC REPORTS



OPEN

Preparation of heterostructured WO_3/TiO_2 catalysts from wood fibers and its versatile photodegradation abilities

Likun Gao^{1,2}, Wentao Gan^{1,2}, Zhe Qiu^{1,2}, Xianxu Zhan³, Tiangang Qiang^{1,2} & Jian Li^{1,2}

A facile route was adopted to synthesize heterostructured WO_3/TiO_2 photocatalysts from wood fibers through a two-steps hydrothermal method and a calcination process. The prepared WO_3/TiO_2 -wood fibers were used as photocatalysts under UV irradiation for photodegradation of rhodamine B, methylene blue and methyl orange. In calcination process, the wood fibers acted as carbon substrates to prepare the WO_3/TiO_2 photocatalysts with high surface area and unique morphology. Thus, the significant enhanced photodegradation efficiency of the organic pollutants with the WO_3/TiO_2 -wood fibers under UV irradiation was obtained. The photodegradation rates are measured which confirms the highest performance of the WO_3/TiO_2 -wood fibers after calcination in comparison to the TiO_2 -wood fibers after calcination and the pure WO_3/TiO_2 after calcination. Moreover, the photodegradation efficiency of the WO_3/TiO_2 -wood fibers after calcination under visible light is high. Our results demonstrated that the WO_3/TiO_2 -wood fibers after calcination are a promising candidate for wastewater treatment in practical application.

There has been an increasing environmental problem in recent years due to global warming. From the viewpoint of the utilization of solar energy, many efforts have been devoted to develop the light-driven photocatalysts, which could decompose harmful chemicals existed in the environment by using sunlight¹. Photocatalysis is used to remove pollutants through photo-oxidation in the presence of light and photocatalyst, which can convert optical energy into the energy for chemical reactions². Semiconductor materials such as ZnO, TiO_2 , SnO_2 , and WO_3 , have been extensively studied as catalysts to degrade environment pollutants owing to their strong oxidative abilities, suitable band gaps and excellent stabilities in water solution^{3–8}. In practical, photocatalysts that are more stable, more efficient, non-toxic and capable of harvesting sunlight are highly desirable.

Markedly, TiO_2 semiconductor with the band gap of 3.2 eV is a promising photocatalyst and widely used in photodegradation of aqueous or gaseous toxic organic pollutants for water treatment and air purification due to its nontoxicity and environmental friendly properties along with stability⁹. In the photodegradation process of toxic contaminants using TiO_2 , the whole process could be insured facile and environment-friendly, which the reaction could happen at ambient temperature and pressure, and the reaction products are usually CO_2 and H_2O . It is worth noting that how to enhance photocatalytic efficiency of photocatalysts is a basic and important task, not merely for the theoretical significance but also for the advance in applications.

For the purpose of reducing the degradation and enhancement in catalytic properties, many research reported on the enhancement of toxic contaminants degradation through doping TiO_2 with extrinsic dopants such as metal oxide or metal elementary^{10, 11}. For example, after doping with V, Pt, Ag, and Au, TiO_2 semiconductor films showed obvious increase in catalytic properties^{12–15}. Liang *et al.* reported that Ce/ TiO_2 and Ag/ TiO_2 showed higher photocatalytic degradation efficiency of formaldehyde gas under UV irradiation¹⁶. Tungsten oxide (WO_3), as an important n-type semiconductor with a narrow gap (~ 2.8 eV), has drawn much attention for its unique electronic, chemical and optical properties^{17, 18}. Herein, WO_3 was selected as potential dopant to decorate the

¹Key Laboratory of Biobased Material Science & Technology (Education Ministry), Northeast Forestry University, Harbin, 150040, P.R. China. ²Research Center of Wood Bionic Intelligent Science, Northeast Forestry University, Harbin, 150040, P.R. China. ³Dehua TB New Decoration Material Co., Ltd, Huzhou, 313200, P.R. China. Xianxu Zhan, Tiangang Qiang and Jian Li jointly supervised this work. Correspondence and requests for materials should be addressed to L.G. (email: gaolknefu@163.com)

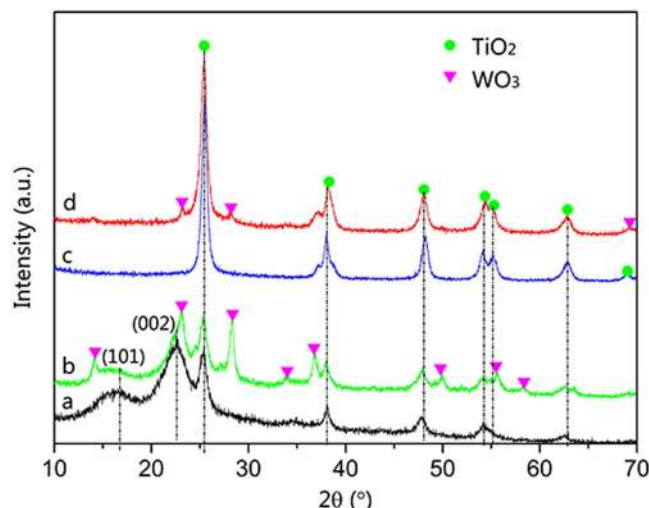


Figure 1. XRD patterns of (a) the TiO₂-wood fibers, (b) the WO₃/TiO₂-wood fibers, (c) the TiO₂-wood fibers after calcination and (d) the WO₃/TiO₂-wood fibers after calcination.

pure TiO₂. For the photodegradation, coupling TiO₂ with WO₃ can extend the optical absorption to the visible region to enhance the photocatalytic efficiency^{19–21}. The edge of the valence band and conduction band in WO₃ are lower than that in TiO₂. The differences in band edge position in the WO₃/TiO₂ photocatalyst created potential gradient at the composite interface, which would facilitate the charge separation and inhibited charge carrier recombination²².

Generally, people considered that wooden materials are always used to light a fire, and it is attributed to carbon and other components originated from cellulose, hemicellulose and lignin. In the synthesis process of photocatalysts, the presence of carbon in the wood as the substrate can lead to a relatively high surface area photocatalysts with respect to pure photocatalysts²³. Generally, the specific architectures can be obtained using hard, sacrificial or soft templates such as wood, textiles and so on^{24, 25}. Moreover, the abundant pores originated from wood intrinsic properties are beneficial to absorb gas, on the other hand, it containing plentiful hydroxide radical has emerged as a better substrate material for the growth of metal-oxide semiconductor films such as TiO₂²⁶, WO₃²⁷, CoFe₂O₄^{28, 29} and Cu₂O³⁰.

Herein, the enhanced photodegradation of organic pollutant on heterostructured WO₃/TiO₂ photocatalysts from wood fibers through a two-steps hydrothermal method and a calcination process is assumed and reported. The photodegradation of rhodamine B, methylene blue and methyl orange on the samples under UV irradiation are discussed in details.

Results

Figure 1 presents the XRD patterns of the TiO₂-wood fibers, the WO₃/TiO₂-wood fibers, the TiO₂-wood fibers after calcination and the WO₃/TiO₂-wood fibers after calcination. In Fig. 1a,b, the diffraction peaks at 14.8° and 22.5° belong to the (101) and (002) crystal planes of cellulose in the wood³¹. It can be found that all the diffraction peaks in Fig. 1 are well indexed to the standard diffraction pattern of anatase TiO₂ (JCPDS file No. 21-1272)³² and WO₃ (JCPDS file No. 75-2187)³³, indicating that the present synthesis strategy successfully achieves WO₃/TiO₂ heterostructures with high crystallinity on wood substrate. In Fig. 1a,c, the diffraction peaks at 25.5°, 38.0°, 48.3°, 54.2°, 55.3°, 62.9° and 69.0° can be perfectly identified to (101), (004), (200), (105), (211), (204) and (116) crystal planes of anatase TiO₂, respectively³². The curves in Fig. 1b,d show that all of the new diffraction peaks of the WO₃/TiO₂-wood fibers and the WO₃/TiO₂-wood fibers after calcination center at 2θ = 14.2°, 23.1°, 28.4°, 33.8°, 36.9°, 49.9°, 55.7° and 58.4° except the diffraction peaks of TiO₂, are agree with (100), (001), (200), (111), (201), (220), (221) and (400) planes of pure hexagonal WO₃^{33, 34}. Moreover, in Fig. 1c,d, the sharper diffraction peaks of WO₃ and TiO₂ suggest that calcination at 500 °C for 3 h is sufficient to crystallize pure anatase TiO₂ and hexagonal WO₃ nanostructures.

In Fig. 2, the SEM images were utilized to investigate the morphologies of the samples. It is obvious that spherical particles of TiO₂ in the TiO₂-wood fibers (Fig. 2a) are converted into rhombic type structures after calcination (Fig. 2c). As shown in Fig. 2b,d, the number of actinomorphic WO₃ flowers loaded on the surfaces of the TiO₂ spherical particles increases, which is due to the calcination at 500 °C for 3 h. Compared to the morphologies of the samples before calcination in Fig. 2a,b, the samples structures after calcination in Fig. 2c,d become more compact. This suggests formation of nanoparticles with high aspect ratio and further growth of these nanostructures in the case of the presence of wood fibers after calcination.

Based on the above results, the synthesis process of the WO₃/TiO₂ catalysts from wood fibers is illustrated in Fig. 3. After two-steps hydrothermal synthesis (A and B), the wood fibers were coated by WO₃/TiO₂ films consisted of actinomorphic WO₃ flowers and TiO₂ spherical particles. According to statistics, the carbon contents in the cellulose of wood are about 40~50%, while the cellulose is the main components of wood and the cellulose contents are about 50%. Thus, during calcination in air (C), the carbon in the wood fibers would be oxidized to

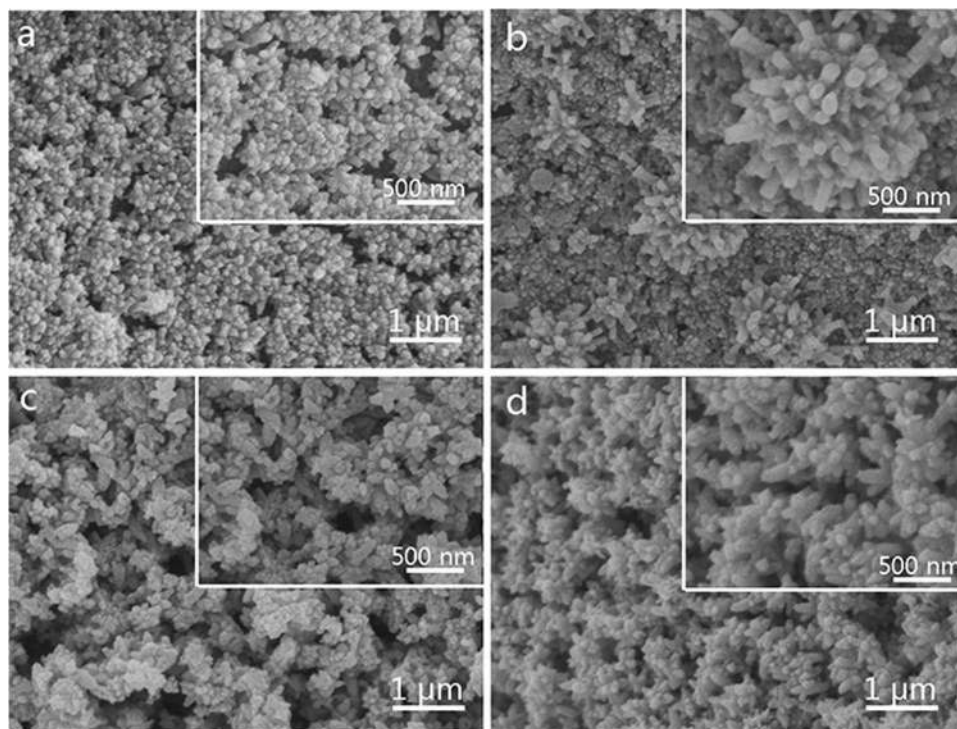


Figure 2. SEM images of (a) the TiO_2 -wood fibers, (b) the WO_3/TiO_2 -wood fibers, (c) the TiO_2 -wood fibers after calcination and (d) the WO_3/TiO_2 -wood fibers after calcination. (The inserts show the SEM images of each sample at high magnifications).

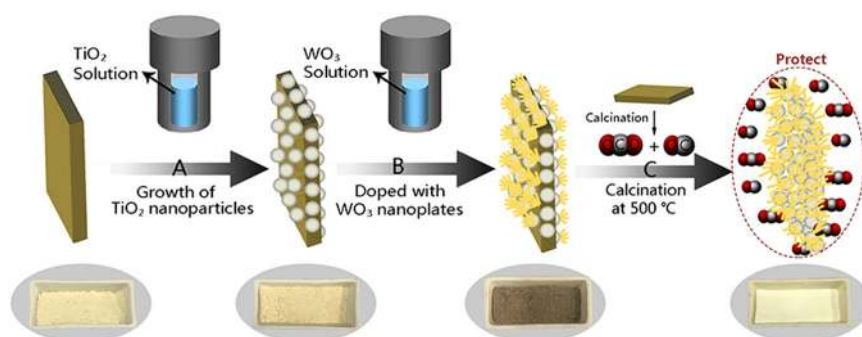


Figure 3. Synthesis scheme of the WO_3/TiO_2 catalysts from wood fibers.

CO and CO_2 gases. CO and CO_2 gases can act as reductive gases to protect the materials structures in calcination. After calcination, the wood fibers were removed leading the WO_3 flowers and TiO_2 spherical particles become more compact.

For the sake of clarification of the surface chemical composition and electronic structure, XPS analysis was applied to characterize the TiO_2 -wood fibers after calcination and the WO_3/TiO_2 -wood fibers after calcination. The wide-scan spectra in Fig. 4a show that the Ti, O, and C elements exist on the TiO_2 -wood fibers after calcination and the Ti, O, W, and C elements exist on the WO_3/TiO_2 -wood fibers after calcination. Moreover, trace amounts of carbon, which originates from the residual carbon in the structure and the adventitious hydrocarbon in the XPS instrument itself.

The Ti 2p spectrum of the TiO_2 -wood fibers after calcination in Fig. 4b shows two peaks at binding energies of 458.4 eV and 464.2 eV, which correspond to the $\text{Ti } 2p_{3/2}$ and $\text{Ti } 2p_{1/2}$ peaks, respectively. The gap between $\text{Ti } 2p_{3/2}$ and $\text{Ti } 2p_{1/2}$ lines is 5.8 eV, suggesting the existence of the Ti^{4+} oxidation state⁹. And the binding energy of $\text{Ti } 2p_{3/2}$ in the TiO_2 -wood fibers after calcination can be fitted into two components, one located at 458.67 eV, assigned to a Ti^{4+} species, and the other located at 458.37 eV, attributed to a Ti^{3+} species. With the incorporation of W species, the intensity of Ti 2p is decreased as indicated in Fig. 4a,b. This also suggests that relatively more W species are present on the surface of the structure. The slight decrease in binding energy in the WO_3/TiO_2 -wood fibers after calcination suggests that some of Ti^{4+} species are converted to a lower oxidation state, such as Ti^{3+} species; meanwhile it can be observed clearly the binding energy of Ti^{3+} increases. The peaks positions for Ti 2p in the

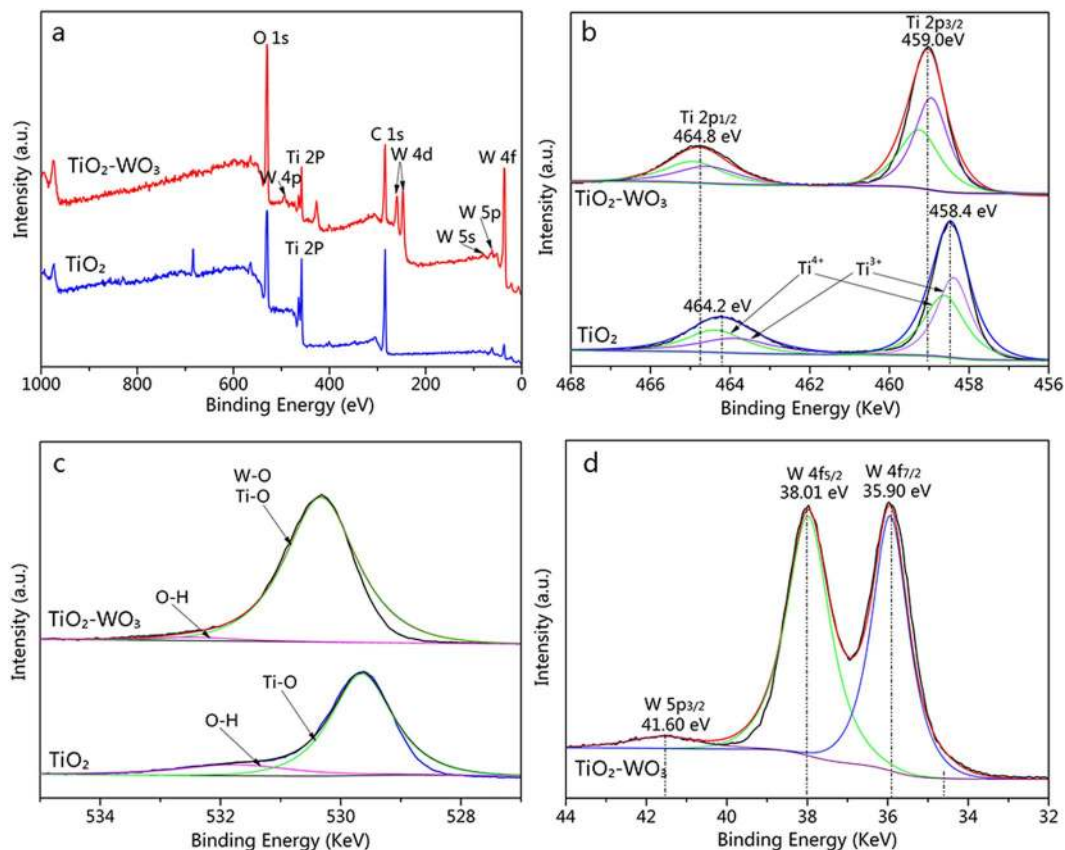


Figure 4. (a) Survey scan and (b) peaking-fitting results of Ti 2p XPS spectra of the TiO_2 -wood fibers after calcination and the WO_3/TiO_2 -wood fibers after calcination. (c) peaking-fitting results of O 1s XPS spectra of the TiO_2 -wood fibers after calcination and the WO_3/TiO_2 -wood fibers after calcination and (d) W 4f XPS spectra of the WO_3/TiO_2 -wood fibers after calcination.

WO_3/TiO_2 -wood fibers after calcination shift to higher binding energy bands than those in the TiO_2 -wood fibers after calcination. This confirms the chemical condition of TiO_2 transfers from Ti-O-Ti to Ti-O-W, which means a strong interaction between WO_3 and TiO_2 in the WO_3/TiO_2 -wood fibers after calcination.

In Fig. 4c, the O 1s band has been greatly modified with the introduction of the W species. For both the two samples, the O 1s can be fitted with two peaks. The peak at 531.75 eV in the TiO_2 -wood fibers after calcination and the peak at 532.50 eV in the WO_3/TiO_2 -wood fibers after calcination are related to the hydroxyl groups¹⁹. For the TiO_2 -wood fibers after calcination, the peak at 529.63 eV is assigned to the oxygen bound to Ti, while the O 1s region of the WO_3/TiO_2 -wood fibers after calcination with the peak at 530.33 eV contained contributions from both the Ti-O and W-O is considerably broader. This is because the Ti-O and W-O have similar binding energies³⁵.

Figure 4d shows the W 4f and the W 5p_{3/2} core level spectra recorded on the WO_3/TiO_2 -wood fibers after calcination, and the results of its fitting analysis. To reproduce the experimental data, two doublet functions are used for the W 4f component and a singlet for the W 5p_{3/2} component near 41.60 eV³⁶. One doublet contains its highest intensity peak (W 4f_{7/2}) located near 35.90 eV, which is generated by photoelectrons emitted from tungsten atoms with an oxidation state of +6; i.e. stoichiometric WO_3 . In stoichiometric WO_3 , the W atom has +6 valence electrons with 5d empty shell (d⁰ oxides). The six valence electrons of the W atom are transferred into the oxygen p-like bands and the oxygen p-like bands are completed filled. Thus, the 5d valence electron is empty and there would be a stronger interaction between the remaining electrons in W atom and the nucleus. That is, the binding energy of W 4f level of WO_3 is larger than that of metallic W³⁷. And the other peak at 38.01 eV is corresponding to W 4f_{5/2}, while the energy gap between the two peaks of W 4f_{7/2} and W 4f_{5/2} is 2.11 eV belonging to the tungsten in the W⁶⁺ valance state³⁶.

To have an insight into the effect of the wood fibers on the porous structure of the samples, BET analysis was carried out. Figure 5 shows the N₂ adsorption–desorption isotherms of the pure WO_3/TiO_2 after calcination, the TiO_2 -wood fibers after calcination and the WO_3/TiO_2 -wood fibers after calcination. These curves all exhibit small hysteresis loops, which are attributed to type IV isotherms and the representative of mesoporous materials, indicating the presence of mesopores (2–50 nm)². This result is further confirmed by the corresponding pore-size distribution curves (inset in Fig. 5). Furthermore, the isotherm profile of the WO_3/TiO_2 -wood fibers after calcination shows typical H1 type hysteresis loops in the relative pressure range from 0.4 to 0.9 according to the uniform sized spherical-particles aggregates and hysteresis loops close to H3 type from 0.9 to 1.0, indicating the presence

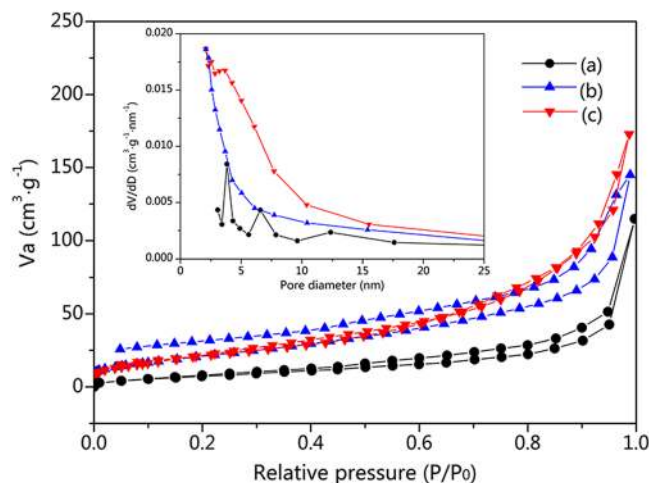


Figure 5. N_2 adsorption–desorption isotherms of (a) the pure WO_3/TiO_2 after calcination, (b) the TiO_2 -wood fibers after calcination and (c) the WO_3/TiO_2 -wood fibers after calcination. The inset shows the pore size distributions.

Sample	BET surface area (m^2/g)	Pore size (nm)	Pores volume (cm^3/g)
Pure WO_3/TiO_2 after calcination	25.98	3.83	0.17
TiO_2 -wood fibers after calcination	81.70	5.18	0.21
WO_3/TiO_2 -wood fibers after calcination	92.95	4.98	0.26

Table 1. The structure parameters of the pure WO_3/TiO_2 after calcination, the TiO_2 -wood fibers after calcination and the WO_3/TiO_2 -wood fibers after calcination.

of slit-like pores. The pore size distribution of the WO_3/TiO_2 -wood fibers after calcination exhibits a broadened pore size range (inset in Fig. 5).

BET surface areas, pore sizes and pore volumes of the WO_3/TiO_2 -wood fibers after calcination compared to the pure WO_3/TiO_2 after calcination and the TiO_2 -wood fibers after calcination are presented in Table 1. From the results shown, it is clear that the preparation of WO_3/TiO_2 in the presence of wood fibers after calcination leads to a significantly higher surface area with respect to the pure WO_3/TiO_2 obtained in the absence of wood fibers (up to approximately 3.6 times higher). The TiO_2 -wood fibers after calcination without loading WO_3 lead a relatively low surface area of $81.70 m^2/g$. That is, the method used in the study seems to produce a certain heterogeneous system with respect to wood fibers, in terms of the surface properties (surface area, pore size distribution, etc.) of obtained the WO_3/TiO_2 -wood fibers after calcination. Thus, because of its large surface area, the WO_3/TiO_2 -wood fibers after calcination provides more photocatalytic reaction sites for the adsorption of reactant molecules and increases the efficiency of the electron–hole separation, so the photocatalytic activity of the WO_3/TiO_2 -wood fibers after calcination is enhanced.

The TG and DTG curves of the pure WO_3/TiO_2 , the TiO_2 -wood fibers and the WO_3/TiO_2 -wood fibers are shown in Fig. 6. In Fig. 6a, small weight losses appear at about $50–80^\circ C$ in the samples, which correspond to a mass loss of physically adsorbed water of approximately 5%. After this peak, the DTG curves of the TiO_2 -wood fibers and the WO_3/TiO_2 -wood fibers in Fig. 6b shows three decomposition steps: (1) the first decomposition shoulder peak at about $276^\circ C$ for the TiO_2 -wood fibers, is attributed to thermal depolymerisation of hemicelluloses or pectin; (2) the major second decomposition peak at about $341^\circ C$ and $303^\circ C$ for TiO_2 -wood fibers and the WO_3/TiO_2 -wood fibers, respectively, is attributed to cellulose decomposition. Lignin is the most difficult one to decompose, and its decomposition keeps on along the whole calcination process; (3) the final decomposition peak at about $380–600^\circ C$ was attributed to all the wood components degradation gradually leading to the aromatization and carbonization. Due to the decomposition of cellulose and lignin, the maximum degradation rates of the WO_3/TiO_2 -wood fibers become lower than that of TiO_2 -wood fibers. This may be due to the catalysis of WO_3/TiO_2 composite film, which generates an accelerated pyrolysis action on wood components.

Moreover, from thermal analysis of samples we obtain information about the evolution of WO_3/TiO_2 -wood fibers system during calcination. The pure WO_3/TiO_2 obtained through hydrothermal synthesis in the absence of wood fibers leads to a total weight loss of about 19.3% after calcination at $500^\circ C$. However, the weight loss of the WO_3/TiO_2 -wood fibers after calcination at $500^\circ C$ is 45.1%, including the losses of carbon and WO_3/TiO_2 . Thus, it can be calculated that the weight loss of C in the WO_3/TiO_2 -wood fibers after calcination at $500^\circ C$ is 25.8%, that is, the residual C content is about 10.3%.

In order to investigate the light absorbance of the samples, the UV–vis diffuse reflection spectra of the TiO_2 -wood fibers after calcination and the WO_3/TiO_2 -wood fibers after calcination are depicted in Fig. 7a. As for both the TiO_2 -wood fibers after calcination and the WO_3/TiO_2 -wood fibers after calcination, it presents

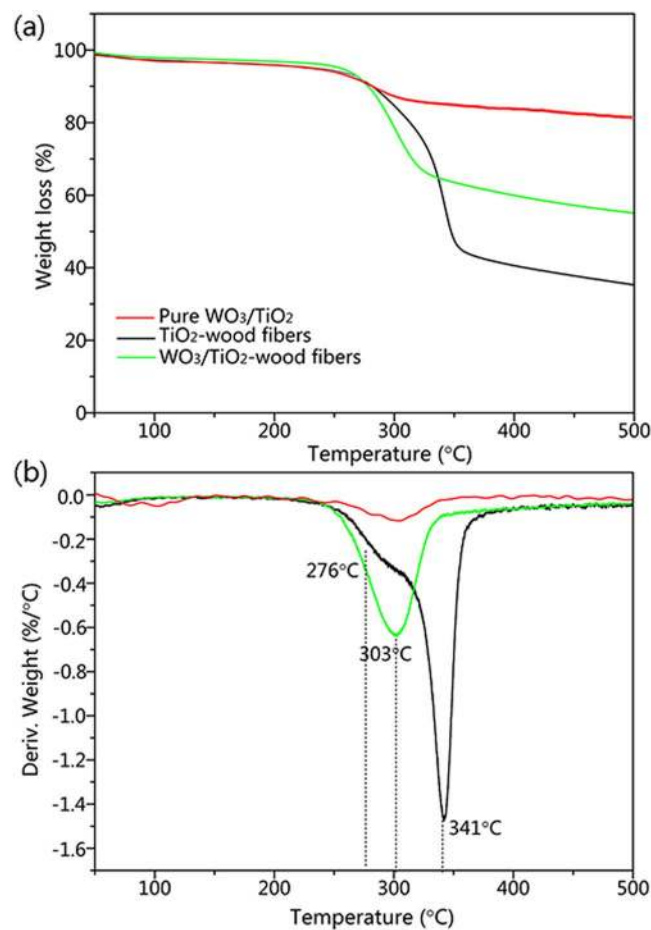


Figure 6. (a) TG profiles and (b) DTG profiles of the pure WO₃/TiO₂, the TiO₂-wood fibers and the WO₃/TiO₂-wood fibers.

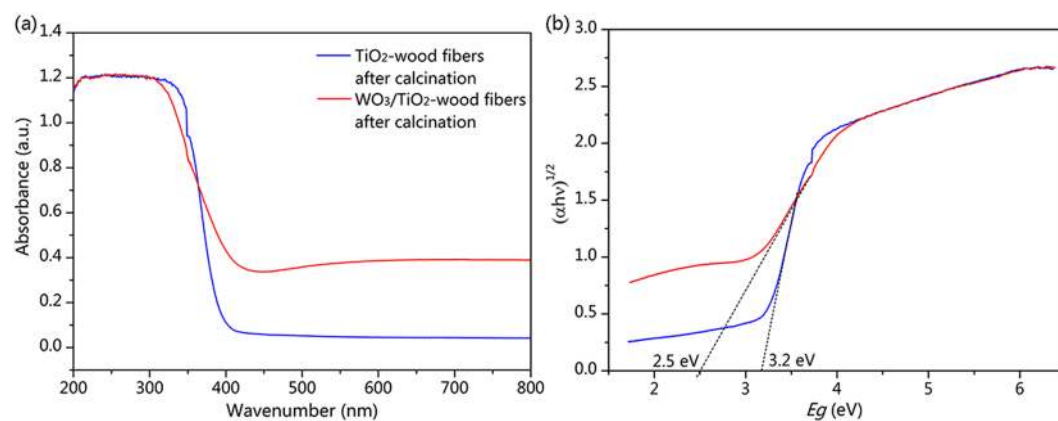


Figure 7. (a) UV-vis absorption spectra of the TiO₂-wood fibers after calcination and the WO₃/TiO₂-wood fibers after calcination, and (b) the evaluation of the optical band gap using the Tauc plot.

prominent absorptions below 380 nm wavelength, whereas the WO₃/TiO₂-wood fibers after calcination exhibits a much higher absorption, indicating more intensive effect to UV light. Moreover, the absorption wavelength of the WO₃/TiO₂-wood fibers after calcination has a comparatively red shift, indicating that doping with WO₃ can extend the optical absorption to the visible region. And the TiO₂-wood fibers after calcination and the WO₃/TiO₂-wood fibers after calcination show the absorption edges at about 396 nm and 465 nm, respectively. To calculate valence band position, the optical band gap is determined by the following Tauc equation¹³⁸:

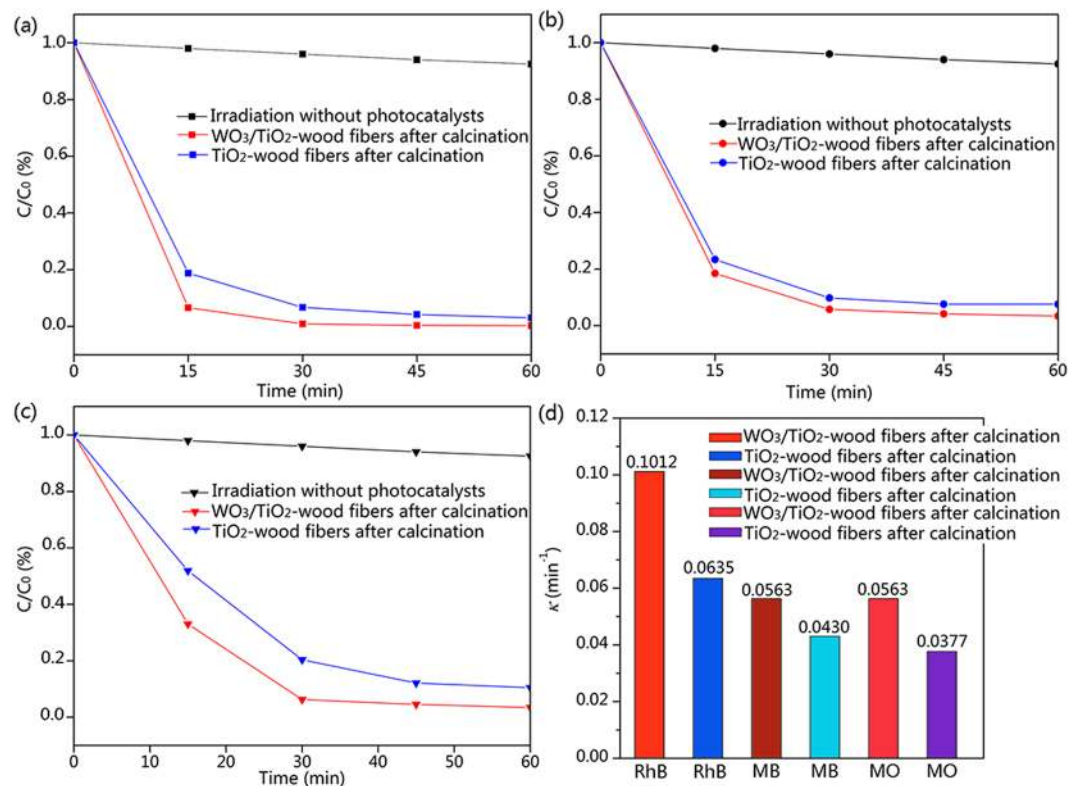


Figure 8. Concentration percent (C/C_0) of photocatalytic (a) RhB, (b) MB and (c) MO with the TiO_2 -wood fibers after calcination, the WO_3/TiO_2 -wood fibers after calcination and irradiation without photocatalysts. (d) First order rate constant k (min^{-1}) of the TiO_2 -wood fibers after calcination and the WO_3/TiO_2 -wood fibers after calcination for RhB, MB and MO.

$$(ah\nu)^n = A(h\nu - E_g) \quad (1)$$

Where A = constant, $h\nu$ = light energy, E_g = optical band gap energy, α = measure absorption coefficient, $n = 0.5$ for direct band gap, and $n = 2$ for indirect band gap materials. Because both the TiO_2 and WO_3 has direct band gap, the y axis of the Tauc plot is $(\alpha h\nu)^{1/2}$ for TiO_2 and WO_3 ^{39,40}. In Fig. 7b, the extrapolation of the Tauc plot on x intercepts gives the optical band gaps of 3.2 eV and 2.5 eV for TiO_2 and WO_3 , respectively. Therefore, the conduction band and valence band of WO_3 are more negative than the corresponding bands of TiO_2 .

The photocatalytic activities of the TiO_2 -wood fibers after calcination and the WO_3/TiO_2 -wood fibers after calcination were evaluated by degradation of RhB, MB and MO under UV (wavelength <400 nm) irradiation in order to demonstrate its potential application for wastewater treatment. Figure 8(a–c) show the relationships between concentration percent (C/C_0) and time for RhB, MB and MO degradation with 50 mg TiO_2 -wood fibers after calcination and 50 mg WO_3/TiO_2 -wood fibers after calcination. And the effects of absorption of reactant by photocatalyst and photolysis of reactant were excluded by blank experiments. The WO_3/TiO_2 -wood fibers after calcination took just 30 minutes to completely degrade RhB whereas the TiO_2 -wood fibers after calcination required 45 minutes for complete degradation of RhB. And the RhB photodegradation efficiency of the TiO_2 -wood fibers after calcination and the WO_3/TiO_2 -wood fibers after calcination were 97.2% and 99.8%, respectively. Similarly, the WO_3/TiO_2 -wood fibers after calcination spent only 45 minutes on complete degradation of MB and the MB photodegradation efficiency was 96.6%, whereas the TiO_2 -wood fibers after calcination spent 60 minutes and the MB photodegradation efficiency was 92.4%. Also for MO, the WO_3/TiO_2 -wood fibers after calcination needed 45 minutes as compared to the TiO_2 -wood fibers after calcination which needed 60 minutes for complete degradation of the dye. And the MO photodegradation efficiency of the pure WO_3/TiO_2 after calcination and the TiO_2 -wood fibers after calcination were 89.6% and 89.6%, respectively.

Figure 8d shows the first order rate constant k (min^{-1}) of the TiO_2 -wood fibers after calcination and the WO_3/TiO_2 -wood fibers after calcination for RhB, MB and MO, which was calculated by the following first order equation²⁴:

$$\ln(C_0/C) = kt \quad (2)$$

where C_0 is the initial concentration of the dye in solution and C is the concentration of dye at time t . k has maximum value of 0.1012 min^{-1} for RhB when the WO_3/TiO_2 -wood fibers after calcination is used as a catalyst and it decreased to 0.0635 min^{-1} in the case of the TiO_2 -wood fibers after calcination. Furthermore, it is 0.0563 min^{-1} for the WO_3/TiO_2 -wood fibers after calcination of MB and 0.0430 min^{-1} for the TiO_2 -wood fibers

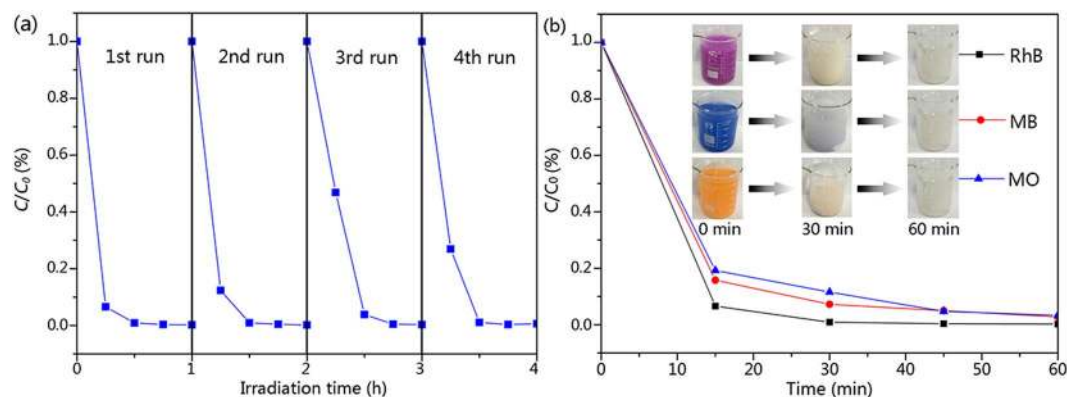


Figure 9. (a) Cycling runs in the photocatalytic degradation of RhB in the presence of 50 mg WO_3/TiO_2 -wood fibers after calcination under UV irradiation, and (b) Concentration percent (C/C_0) of photocatalytic RhB, MB and MO under visible light by 50 mg WO_3/TiO_2 -wood fibers after calcination.

after calcination. It also shows that the value of 0.0563 min^{-1} for MO in the case of the WO_3/TiO_2 -wood fibers after calcination as compared to the value of 0.0377 min^{-1} in the case of the TiO_2 -wood fibers after calcination. The presence of small pores on the surface of the WO_3/TiO_2 -wood fibers after calcination (as suggested by BET), which is highly useful for a higher value of k (min^{-1}), act as the reaction sites for the photocatalytic activity.

The WO_3/TiO_2 -wood fibers after calcination as a kind of heterogeneous photocatalyst can be easily recycled by a simple filtration. After four recycles for the photodegradation of RhB, the catalyst did not exhibit any significant loss of activity, as shown in Fig. 9a, confirming the WO_3/TiO_2 -wood fibers after calcination is not photocorroded during the photocatalytic oxidation of the dye pollutant. The stability of a photocatalyst is important to its practical application.

For verifying the response to the visible region, the photodegradation tests of the WO_3/TiO_2 -wood fibers after calcination were performed by using the 50 mg catalysts for the degradation of organic dyes under visible light (500 W xenon lamp with wavelength of 420 nm). Most interestingly, the experimental results in Fig. 9b present that, for the WO_3/TiO_2 -wood fibers after calcination, the degradation efficiency of organic dyes driven by visible light is still high, and photodegradation efficiencies for the three dyes are all over 97%, elucidating an available application of the WO_3/TiO_2 -wood fibers after calcination under visible light. Such an important and useful property for the WO_3/TiO_2 -wood fibers after calcination would greatly promote its application in a fast and facile elimination of organic pollutants under natural sunlight.

The result for the reactive nature of the WO_3/TiO_2 -wood fibers after calcination towards the photocatalytic reaction is the availability of photogenerated electrons for superoxide radical generation. Also, a large surface area and pore size provide more reactive sites for reaction, which further enhance the photocatalytic efficiency of the WO_3/TiO_2 -wood fibers after calcination. It reduces the recombination probability of photoexcited charge carriers and enhances the transport of charges.

The active species typically involved in the photodegradation include holes (h^+), hydroxyl radicals ($\bullet\text{OH}$) and superoxide radicals ($\bullet\text{O}_2^-$)^{42,43}. A series of controlled experiments of RhB photodegradation under UV light were performed over the WO_3/TiO_2 -wood fibers after calcination using different radical scavengers, as shown in Fig. 10. As a result, when TBA (scavenge $\bullet\text{OH}$) is added, the degradation rate is unchanged, while the degradation rates are dramatically decreased to 22% and 42% when BQ (scavenge $\bullet\text{O}_2^-$) and AO (scavenge h^+) are added, respectively. These suggest that the $\bullet\text{O}_2^-$ and h^+ play important roles in the photodegradation process.

To test the versatile photodegradation abilities of the samples, the photocatalytic degradation of colorless organics (phenol) has been measured. Figure 11a shows the relationships between concentration percent (C/C_0) and time for phenol degradation with 50 mg TiO_2 -wood fibers after calcination, 50 mg WO_3/TiO_2 -wood fibers after calcination, and irradiation without photocatalysts. The WO_3/TiO_2 -wood fibers after calcination took 90 minutes to completely degrade phenol. However, the TiO_2 -wood fibers after calcination could not degrade phenol. Figure 11b shows the first order rate constant k (min^{-1}) of the TiO_2 -wood fibers after calcination and the WO_3/TiO_2 -wood fibers after calcination for phenol. It shows that the k value of 0.0444 min^{-1} for phenol in the case of the WO_3/TiO_2 -wood fibers after calcination as compared to the value of 0.0006 min^{-1} in the case of the TiO_2 -wood fibers after calcination. The results indicate that the WO_3/TiO_2 -wood fibers after calcination possess versatile photodegradation abilities.

Based on the above values of optical band gap energies and the photocatalytic results, we constructed the potential energy diagrams for the WO_3/TiO_2 -wood fibers after calcination in Fig. 12. When the WO_3/TiO_2 -wood fibers after calcination are illuminated with UV light or visible light, excited electrons are generated in the conduction band of both TiO_2 and WO_3 . The photogenerated electrons in WO_3 move to the conduction band of TiO_2 easily due to the potential difference. This facile electron transfer would reduce the chance of recombination with holes formed in the valence bands of the two semiconductors. The holes migrate to the semiconductor interface either directly or after transfer from TiO_2 to WO_3 . The reduced recombination would naturally induce photo-activity enhancement²².

As shown in Fig. 12a,b, the current is divided into two cases: (a) as the $h\nu > 3.2 \text{ eV}$, that is, the photon with enough energy to excite TiO_2 . Under UV irradiation, electrons in the VB of TiO_2 are excited into the CB of TiO_2 ,

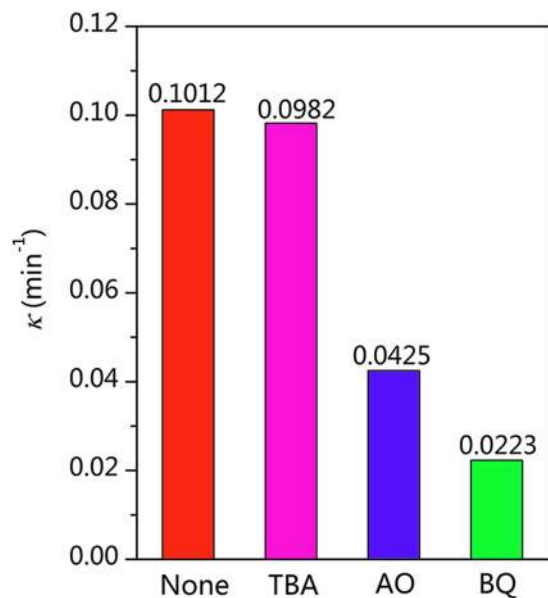


Figure 10. Effect of scavengers on the RhB photodegradation of WO_3/TiO_2 -wood fibers after calcination under UV light.

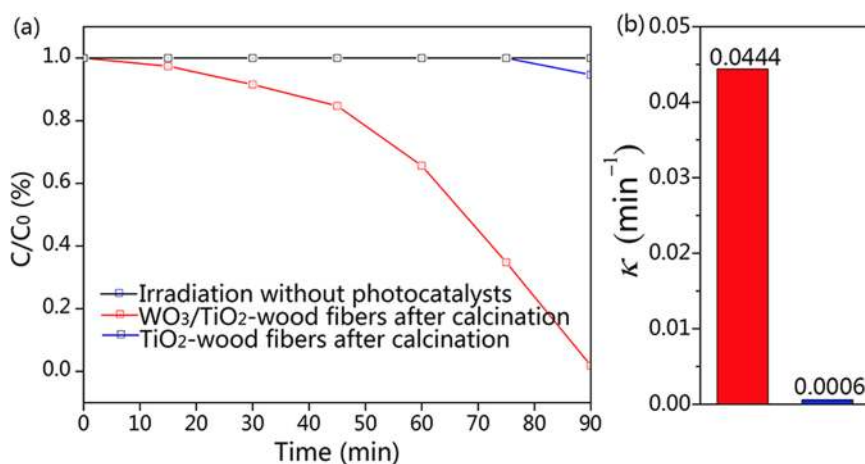


Figure 11. (a) Concentration percent (C/C_0) of photocatalytic phenol with the TiO_2 -wood fibers after calcination, the WO_3/TiO_2 -wood fibers after calcination and irradiation without photocatalysts. (b) First order rate constant k (min^{-1}) of the TiO_2 -wood fibers after calcination and the WO_3/TiO_2 -wood fibers after calcination for phenol.

and then transfer from the CB of TiO_2 to the WO_3 , because of the lower CB of WO_3 . Furthermore, the VB edge of TiO_2 is higher than that of WO_3 . The holes leaving in the VB of WO_3 can move into the valence of TiO_2 , which facilitate the electron/hole separation. Thus the photo-oxidation efficiency of the sample is increased. Thus, the lower band gap of WO_3 produces a photocatalytic effect in a wider-gap TiO_2 by increasing the charge separation and extending the energy range of photo-excitation for the system.

(b) If a photon with not enough energy to excite TiO_2 but is of enough energy to excite WO_3 , such as visible light, is incident (the $h\nu < 3.2$ eV), the hole that is created in the WO_3 valence band is excited to the conduction band of TiO_2 , while the electron is transferred to the conduction band of TiO_2 . At this point, the electron transfer increases the charge separation and the efficiency of the photocatalytic process. After separation, the electron is free to reduce the adsorbed organic compound and the hole is available to oxidize.

In both the two cases, under light illumination, the photogenerated electron-hole pairs are produced ($h\nu \rightarrow e^- + h^+$), and holes release the captured adsorbed species by leaving behind an electron ($h^+ + \text{O}_2^- \rightarrow \text{O}_2$), leading a decrease of depletion layer and an increase in the conductance. At the same time, the oxygen molecules in the ambient react with the photogenerated electrons ($\text{O}_2 + e^- \rightarrow \bullet\text{O}_2^-$), which creates additional photoinduced oxygen ions. The photoinduced oxygen ions are bound to the film much more weakly than the chemisorbed oxygen ions. Herein, the photoinduced oxygen ions are the crucial reactant taking parts in the following photochemical reactions¹². When the rate of oxygen adsorption and desorption reaches to a balance, the thickness

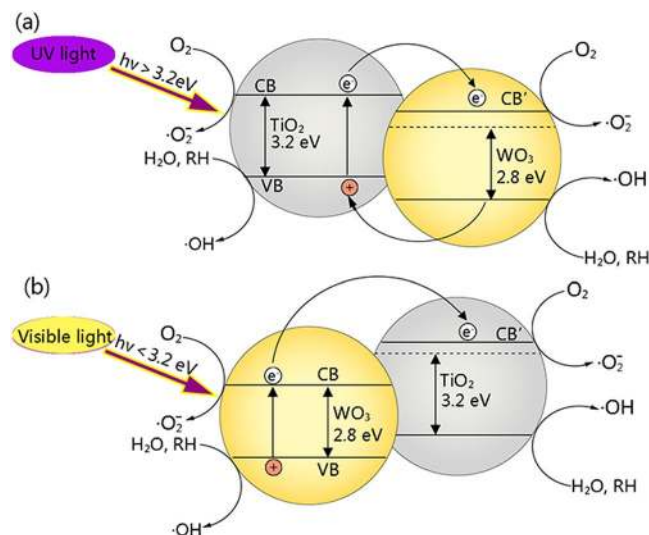


Figure 12. Photocatalytic mechanism schematic diagrams of the WO_3/TiO_2 -wood fibers after calcination as (a) the $h\nu > 3.2 \text{ eV}$, and (b) the $h\nu < 3.2 \text{ eV}$.

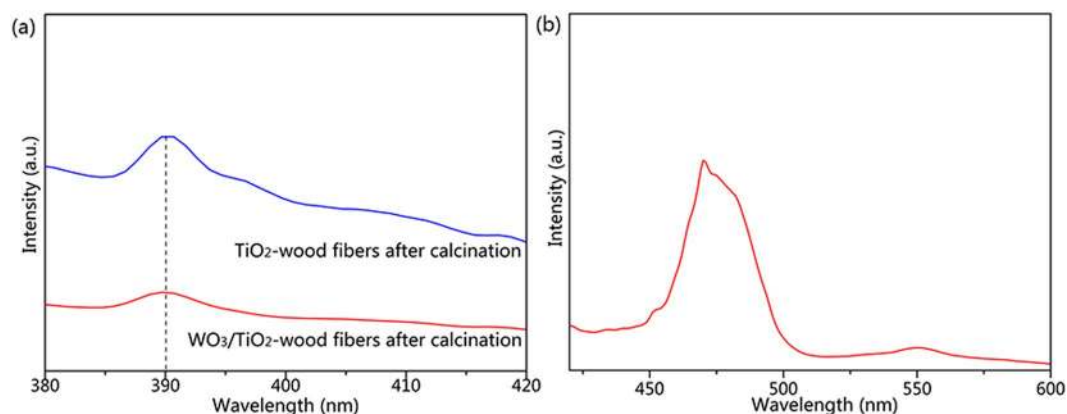


Figure 13. (a) PL spectra of the TiO_2 -wood fibers after calcination and the WO_3/TiO_2 -wood fibers after calcination in the UV light range and (b) PL spectrum of the WO_3/TiO_2 -wood fibers after calcination in the visible light range.

of the depletion layer and the conductivity of film gradually achieve a stable state, which can be regarded as the activated process of the depletion layer ($\bullet\text{O}_2^- + h\nu \rightarrow \text{O}_2$).

When the electrons and holes reach the semiconductor-environment interface, they will react with appropriate redox species (H_2O and O_2) to form reactive intermediates ($\bullet\text{OH}$ and $\bullet\text{O}_2^-$). These radicals and photo-generated holes are extremely strong oxidants which are able to oxidize all organic materials into CO_2 and H_2O , leading to the degradation of organic pollutants.

To test the above explanation, PL emission spectra were performed since they reveal the efficiency of charge carrier trapping, transfer, and separation of a charge carrier, and to understand the fate of electron-hole pairs in semiconductors. As WO_3 and TiO_2 have different emission peaks, we compared the TiO_2 -wood fibers after calcination with the WO_3/TiO_2 -wood fibers after calcination in different wavelength ranges which are shown in Fig. 13a,b. In the UV light range (Fig. 13a), the emission peak of the TiO_2 -wood fibers after calcination appears at about 390 nm, which is in accordance with the band gap of TiO_2 (3.2 eV). This peak is ascribed to a band-band PL emission phenomenon and excitonic PL resulting from surface oxygen vacancies and defects⁴⁴. In the UV light range, the PL peak intensity of the WO_3/TiO_2 -wood fibers after calcination is always lower than that of the TiO_2 -wood fibers after calcination, which indicates that the separation of photogenerated electrons and holes in the WO_3/TiO_2 -wood fibers after calcination is more efficient than that of the TiO_2 -wood fibers after calcination. In another word, the photogenerated charge recombination of the WO_3/TiO_2 -wood fibers after calcination is inhibited⁴⁵. Moreover, in Fig. 13b, the emission at 470 nm corresponding to 2.5 eV, which is approximately equal to the band-gap of the WO_3/TiO_2 -wood fibers after calcination, can be due to the transition from the conduction band of WO_3 to the conduction band of TiO_2 .

Conclusions

Herein, we combined a two-steps hydrothermal method and a calcination process to fabricate a heterostructured WO_3/TiO_2 photocatalysts from wood fibers. The wood fibers acted as carbon substrates to prepare the WO_3/TiO_2 photocatalysts with high surface area and unique morphology. The prepared WO_3/TiO_2 -wood fibers after calcination exhibit higher potential for application as an UV light or a visible light photocatalyst for degradation of organic pollutants. These studies indicate that the WO_3/TiO_2 -wood fibers after calcination with high surface area and large aspect ratio can provide more reactive sites for photocatalytic. It reduces the recombination probability of photoexcited charge carriers and also increases the transport of charges. For purpose of utilizing of solar energy, we anticipate that the WO_3/TiO_2 -wood fibers photocatalysts could be a promising photocatalyst to decompose the harmful chemicals existed in the environment.

Methods

Materials. All chemicals supplied by Shanghai Boyle Chemical Company, Limited were of analytical reagent-grade quality and used without further purification. Deionized water was used throughout the study. Wood fibers were obtained from poplar wood (*Populus ussuriensis* Kom), which is one of the most common tree species in the northeast of China. The wood fibers were oven-dried (24 h, $103 \pm 2^\circ\text{C}$) to constant weight after ultrasonically rinsing in deionized water for 30 min.

Ammonium fluorotitanate (0.4 M) and boric acid (1.2 M) were dissolved in distilled water at room temperature under vigorous magnetic stirring. Then, a solution of 0.3 M hydrochloric acid was added until the pH reached approximately 3. 75 mL of the adjusted solution and 5 g wood fibers were transferred into a 100 mL Teflon container. The autoclave was sealed and maintained at 90°C for 5 h, then allowed to naturally cool to room temperature. Finally, the TiO_2 -wood fibers were washed with distilled water and absolute ethanol for several times, dried in an oven. Thus, the TiO_2 -wood fibers were obtained.

The synthetic route of the WO_3/TiO_2 -wood fibers was as follows. Firstly, the 1.8 g of $\text{Na}_2\text{WO}_4 \cdot 2\text{H}_2\text{O}$ was dissolved into 100 ml mixed precursor solution (containing 20 ml absolute ethanol and 80 ml distilled water) at room temperature, followed by being acidified to 1.0 of pH value using the H_2SO_4 solution. The mixed solution was transferred into a stainless steel autoclave. Then the TiO_2 -wood fibers were soaked into the reaction solution. The autoclave was sealed and maintained at 110°C for 24 h, and then cooled down to room temperature. Finally, the composite films were formed on the wood fibers and then washed with distilled water and absolute ethanol for several times, and dried in an oven. Thus the WO_3/TiO_2 -wood fibers were obtained and the C content in the production was 36.6%. In both cases, the samples were calcined in flowing air at 500°C for 3 h. For comparison, the pure WO_3/TiO_2 without wood fibers after calcination was prepared.

Characterization. The morphology and microstructure were characterized by field-emission scanning electron microscopy (FE-SEM, JSM-7500F, JEOL, Japan) operating at 12.5 kV. The crystal structure of the as-prepared product was investigated by X-ray diffraction (XRD, Bruker D8 Advance, Germany) with $\text{Cu K}\alpha$ radiation of wavelength $\lambda = 1.5418 \text{ \AA}$, using a step scan mode with the step size of 0.02° and a scan rate of 4° min^{-1} , at 40 kV and 40 mA ranging from 5° to 80° . Further evidence for the composition of the product was inferred from the X-ray photoelectron spectroscopy (XPS, Thermo ESCALAB 250XI, USA), using an ESCALAB MKII X-ray photoelectron spectrometer with $\text{Mg-K}\alpha$ X-rays as the excitation source. Thermogravimetric and Differential Thermal Analysis (TG-DTA) spectra were performed using a PE-TGA7 thermogravimetric analyzer (Perkin Elmer Company) and a DTA/9050311 high temperature differential analyzer. 10 mg of the samples were taken and measured in air, and then treated in 150 ml/min of dry pure N_2 with temperatures at the rate of $10^\circ\text{C}/\text{min}$ ranging from 20°C to 800°C . Specific surface areas of the prepared products were measured by the Brunauer-Emmett-Teller (BET) method based on N_2 adsorption at the liquid nitrogen temperature using a 3H-2000PS2 unit (Beishide Instrument S&T Co., Ltd). Optical properties of the materials were characterized by the UV-vis diffuse reflectance spectroscopy (UV-vis DRS, Beijing Purkinje TU-190, China) equipped with an integrating sphere attachment, which BaSO_4 was the reference. Photoluminescence (PL) emission spectra were used to investigate the fate of photogenerated electrons and holes in the sample, and were recorded on a FluoroMax 4 fluorescence spectrometer (HORIBA Jobin Yvon Company, France). The excitation wavelength was 350 nm with the scanning speed of $600 \text{ nm}\cdot\text{min}^{-1}$. The widths of both excitation slit and emission slit were 10 nm.

Photocatalytic test. For photocatalytic tests, a certain amount of sample was dissolved in 100 ml aqueous solutions of rhodamine B (RhB), methylene blue (MB), methyl orange (MO) or phenol in glass beakers. The concentration of RhB, MB and MO was 10 mg in 1 L of H_2O , while concentration of the aqueous phenol solution was 67.2 mg/L. At first, the solution was stirred continuously in the dark for 60 minutes to establish adsorption-desorption equilibrium among the photocatalysts and dye solution, then this solution was brought into UV irradiation. A 500 W ultraviolet lamp with the wavelength range of 425 nm was used as light source. Then, the glass beaker was placed in front of the lamp during continuous magnetic stirring. 5 ml of solution was collected and centrifuged. Then UV absorption measurements were used to observe the photodegradation at specific time intervals. The absorption peaks for RhB, MB, MO and phenol were observed at 553, 664, 464 and 270 nm respectively. For stability measurements the same materials were taken from the solution and the above mentioned steps were repeated for three times. Moreover, to evaluate the role of different active species in the photocatalytic reaction, controlled experiments using different radical scavengers including ammonium oxalate (AO), tert-butyl alcohol (TBA) and 1,4-benzoquinone (BQ) were performed under UV light to scavenge the h^+ , $\bullet\text{OH}$ and $\bullet\text{O}_2^-$ species, respectively⁴².

References

- Tang, J. *et al.* Photocatalytic decomposition of organic contaminants by Bi₂WO₆ under visible light irradiation. *Catal. Lett.* **92**, 53–56, doi:10.1023/B:CATL.0000011086.20412.aa (2004).
- Tahir, M. *et al.* Large scale production of novel g-C₃N₄ micro strings with high surface area and versatile photodegradation ability. *CrystEngComm* **16**, 1825–1830, doi:10.1039/c3ce42135j (2014).
- Zhang, X. *et al.* Effect of aspect ratio and surface defects on the photocatalytic activity of ZnO nanorods. *Sci. Rep.* **4**, 4596, doi:10.1038/srep04596 (2014).
- Shao, X. *et al.* Enhanced photocatalytic activity of TiO₂-C hybrid aerogels for methylene blue degradation. *Sci. Rep.* **3**, 3018, doi:10.1038/srep03018 (2013).
- Zhu, L. *et al.* Hierarchical assembly of SnO₂/ZnO nanostructures for enhanced photocatalytic performance. *Sci. Rep.* **5**, 11609, doi:10.1038/srep11609 (2015).
- Pihosh, Y. *et al.* Photocatalytic generation of hydrogen by core-shell WO₃/BiVO₄ nanorods with ultimate water splitting efficiency. *Sci. Rep.* **5**, 11141, doi:10.1038/srep11141 (2015).
- Huang, Z. *et al.* Tungsten oxides for photocatalysis, electrochemistry, and phototherapy. *Adv. Mater.* **27**, 5309–5327, doi:10.1002/adma.201501217 (2015).
- Pan, L. *et al.* Constructing TiO₂ p-n homojunction for photoelectrochemical and photocatalytic hydrogen generation. *Nano Energy* **28**, 296–303, doi:10.1016/j.nanoen.2016.08.054 (2016).
- Gao, L. *et al.* Negative oxygen ions production by superamphiphobic and antibacterial TiO₂/Cu₂O composite film anchored on wooden substrates. *Sci. Rep.* **6**, 26055–26064, doi:10.1038/srep26055 (2016).
- Kalantar-zadeh, K. *et al.* Two dimensional and layered transition metal oxides. *Applied Materials Today* **5**, 73–89, doi:10.1016/j.apmt.2016.09.012 (2016).
- Zhang, W. *et al.* Liquid metal/metal oxide frameworks with incorporated Ga₂O₃ for photocatalysis. *ACS Appl. Mater. Inter.* **7**, 1943–1948 (2015).
- Shuang, S. *et al.* Surface plasmon enhanced photocatalysis of Au/Pt-decorated TiO₂ nanopillar arrays. *Sci. Rep.* **6** (2016).
- Park, C.-S. *et al.* Omnidirectional color filters capitalizing on a nano-resonator of Ag-TiO₂-Ag integrated with a phase compensating dielectric overlay. *Sci. Rep.* **5** (2015).
- Pandikumar, A. *et al.* TiO₂-Au nanocomposite materials embedded in polymer matrices and their application in the photocatalytic reduction of nitrite to ammonia. *Catal. Sci. Technol.* **2**(2), 345–353, doi:10.1039/C1CY00298H (2012).
- Pan, L. *et al.* Ti³⁺-defected and V-doped TiO₂ quantum dots loaded on MCM-41. *Chem. Commun.* **50**, 988–990, doi:10.1039/C3CC47752E (2014).
- Liang, W. *et al.* Photo-catalytic degradation of gaseous formaldehyde by TiO₂/UV, Ag/TiO₂/UV and Ce/TiO₂/UV. *Build. Environ.* **51**, 345–350, doi:10.1016/j.buildenv.2011.12.007 (2012).
- Deng, L. *et al.* Visible-light activate mesoporous WO₃ sensors with enhanced formaldehyde-sensing property at room temperature. *Sensor. Actuat. B: Chem.* **163**, 260–266, doi:10.1016/j.snb.2012.01.049 (2012).
- Song, J. *et al.* Oxygen-deficient tungsten oxide as versatile and efficient hydrogenation catalyst. *ACS Catal.* **5**, 6594–6599, doi:10.1021/acscatal.5b01522 (2015).
- Pan, J. H. *et al.* I. Preparation of highly ordered cubic mesoporous WO₃/TiO₂ films and their photocatalytic properties. *Chem. Mater.* **18**, 847–853, doi:10.1021/cm0522782 (2006).
- Keller, V. *et al.* Photocatalytic oxidation of butyl acetate in vapor phase on TiO₂, Pt/TiO₂ and WO₃/TiO₂ catalysts. *J. Catal.* **215**, 129–138, doi:10.1016/S0021-9517(03)00002-2 (2003).
- Xiao, M. *et al.* Synthesis and characterization of WO₃/titanate nanotubes nanocomposite with enhanced photocatalytic properties. *J. Alloy. Compd.* **470**, 486–491, doi:10.1016/j.jallcom.2008.03.003 (2009).
- Lee, W. H. *et al.* One-step formation of WO₃-loaded TiO₂ nanotubes composite film for high photocatalytic performance. *Materials* **8**, 15 (2015).
- Colón, G. *et al.* A novel preparation of high surface area TiO₂ nanoparticles from alkoxide precursor and using active carbon as additive. *Catal. Today* **76**, 91–101, doi:10.1016/S0920-5861(02)00207-9 (2002).
- Huang, Z. *et al.* W₁₈O₄₉ nanowire alignments with a BiOCl shell as an efficient photocatalyst. *Nanoscale* **6**, 8865–8872, doi:10.1039/c4nr00905c (2014).
- Huang, Z. *et al.* Mesoporous W₁₈O₄₉ hollow spheres as highly active photocatalysts. *Chem. Commun.* **50**, 10959–10962, doi:10.1039/c4cc02201g (2014).
- Gao, L. *et al.* Reversible Photocontrol of wood-surface wettability between superhydrophilicity and superhydrophobicity based on a TiO₂ film. *J. Wood Chem. Technol.* **35**, 365–373, doi:10.1080/02773813.2014.984078 (2015).
- Hui, B. *et al.* Hydrothermal deposition and photoresponsive properties of WO₃ thin films on wood surfaces using ethanol as an assistant agent. *J. Taiwan Inst. Chem. E.* **64**, 336–342, doi:10.1016/j.jtice.2016.04.031 (2016).
- Gan, W. *et al.* Fabrication of microwave absorbing CoFe₂O₄ coatings with robust superhydrophobicity on natural wood surfaces. *Ceram. Int.* **42**, 13199–13206, doi:10.1016/j.ceramint.2016.05.112 (2016).
- Gan, W. *et al.* Removal of oils from water surface via useful recyclable CoFe₂O₄/sawdust composites under magnetic field. *Mater. Design* **98**, 194–200, doi:10.1016/j.matdes.2016.03.018 (2016).
- Gao, L. *et al.* Durable superamphiphobic wood surfaces from Cu₂O film modified with fluorinated alkyl silane. *RSC Adv.* **5**, 98203–98208, doi:10.1039/C5RA19433D (2015).
- Andersson, S. *et al.* Crystallinity of wood and the size of cellulose crystallites in Norway spruce (*Picea abies*). *J. Wood Sci.* **49**, 531–537 (2003).
- Gao, L. *et al.* pH-dependent structure and wettability of TiO₂-based wood surface. *Mater. Lett.* **142**, 217–220, doi:10.1016/j.matlet.2014.12.035 (2015).
- Adhikari, S. *et al.* High efficient electrochromic WO₃ nanofibers. *Electrochim. Acta* **138**, 115–123, doi:10.1016/j.electacta.2014.06.062 (2014).
- Wang, Z. L. Splendid one-dimensional nanostructures of zinc oxide: A new nanomaterial family for nanotechnology. *ACS Nano* **2**, 1987–1992, doi:10.1021/nn800631r (2008).
- Di, Y. *et al.* Electrochromic properties of TiO₂ nanotubes coated with electrodeposited MoO₃. *Nanoscale* **5**(21), 10353–10359, doi:10.1039/c3nr03666a (2013).
- Bittencourt, C. *et al.* Ag induced modifications on WO₃ films studied by AFM, Raman and x-ray photoelectron spectroscopy. *J. Phys. D: Appl. Phys.* **37**, 3383–3391, doi:10.1088/0022-3727/37/24/005 (2004).
- Zheng, H. *et al.* Nanostructured tungsten oxide – Properties, synthesis, and applications. *Adv. Funct. Mater.* **21**(12), 2175–2196, doi:10.1002/adfm.v21.12 (2011).
- Mor, G. K. *et al.* Transparent highly ordered TiO₂ nanotube arrays via anodization of titanium thin films. *Adv. Funct. Mater.* **15**, 1291–1296, doi:10.1002/(ISSN)1616-3028 (2005).
- Shen, Y. *et al.* 6-Fold-symmetrical WO₃ hierarchical nanostructures: Synthesis and photochromic properties. *Mater. Res. Bull.* **48**, 2317–2324, doi:10.1016/j.materresbull.2013.02.083 (2013).
- Satoh, N. *et al.* Quantum size effect in TiO₂ nanoparticles prepared by finely controlled metal assembly on dendrimer templates. *Nat. Nanotechnol.* **3**, 106–111, doi:10.1038/nnano.2008.2 (2008).

41. Han, C. *et al.* *In situ* synthesis of graphitic-C₃N₄ nanosheet hybridized N-doped TiO₂ nanofibers for efficient photocatalytic H₂ production and degradation. *Nano Res.* **8**, 1199–1209, doi:10.1007/s12274-014-0600-2 (2015).
42. Huang, Z. *et al.* Synergetic promotion on photoactivity and stability of W₁₈O₄₉/TiO₂ hybrid. *Appl. Catal. B-Environ.* **147**, 167–174, doi:10.1016/j.apcatb.2013.08.038 (2014).
43. Jia, X. *et al.* Direct Z-scheme composite of CdS and oxygen-defected CdWO₄: An efficient visible-light-driven photocatalyst for hydrogen evolution. *Appl. Catal. B-Environ.* **198**, 154–161, doi:10.1016/j.apcatb.2016.05.046 (2016).
44. Zhao, S. *et al.* g-C₃N₄/TiO₂ hybrid photocatalyst with wide absorption wavelength range and effective photogenerated charge separation. *Sep. Purif. Technol.* **99**, 50–54, doi:10.1016/j.seppur.2012.08.024 (2012).
45. Hu, S. *et al.* A convenient method to prepare Ag deposited N-TiO₂ composite nanoparticles via NH₃ plasma treatment. *B. Korean Chem. Soc.* **33**, 2309–2314, doi:10.5012/bkcs.2012.33.7.2309 (2012).

Acknowledgements

This work was financially supported by the National Natural Science Foundation of China (grant no. 31470584).

Author Contributions

Jian Li, Tiangang Qiang and Xianxu Zhan conceived the project, Likun Gao designed the experiments and wrote the paper, Wentao Gan and Zhe Qiu performed the experiments. All authors reviewed the manuscript.

Additional Information

Competing Interests: The authors declare that they have no competing interests.

Publisher's note: Springer Nature remains neutral with regard to jurisdictional claims in published maps and institutional affiliations.



Open Access This article is licensed under a Creative Commons Attribution 4.0 International License, which permits use, sharing, adaptation, distribution and reproduction in any medium or format, as long as you give appropriate credit to the original author(s) and the source, provide a link to the Creative Commons license, and indicate if changes were made. The images or other third party material in this article are included in the article's Creative Commons license, unless indicated otherwise in a credit line to the material. If material is not included in the article's Creative Commons license and your intended use is not permitted by statutory regulation or exceeds the permitted use, you will need to obtain permission directly from the copyright holder. To view a copy of this license, visit <http://creativecommons.org/licenses/by/4.0/>.

© The Author(s) 2017