

Original Article

## PRODUCTION AND CHARACTERIZATION OF EXOPOLYSACCHARIDE FROM MARINE MODERATELY HALOPHILIC BACTERIUM *HALOMONAS SMYRNENSIS* SVD III

SIDDHARTH DESHMUKH<sup>1</sup>, PRADNYA KANEKAR<sup>2</sup>, RAMA BHADDEKAR<sup>1\*</sup>

<sup>1</sup>Department of Microbial Biotechnology, Rajiv Gandhi Institute of IT and Biotechnology, Bharati Vidyapeeth Deemed University, Pune-Satara Road, Katraj, Pune 411043, Maharashtra, India, <sup>2</sup>Department of Biotechnology, Modern College of Arts, Science and Commerce, Shivajinagar, Pune 411005, Maharashtra, India  
Email: neeta.bhadekar@gmail.com

Received: 24 Jun 2017 Revised and Accepted: 31 Aug 2017

### ABSTRACT

**Objective:** To study 1) Optimization of nutritional and environmental parameters to enhance the yield of EPS by *Halomonas smyrnensis* SVD III isolated from seawater, West Coast of Maharashtra, India and 2) Purification and characterization of the EPS produced.

**Methods:** The isolate was grown in Sehgal and Gibbons (SG) medium broth supplemented with 3% glucose, at 37 °C, 120 rpm for 7 d. Optimization of different parameters was carried out with one factor at a time approach. EPS was isolated from cell-free supernatant of the culture broth by centrifugation and precipitation using chilled ethanol, after removal of proteins by trichloroacetic acid (TCA) treatment. Characterization of the purified EPS was carried out with respect to fourier-transform infrared (FTIR) spectrum, <sup>1</sup>H nuclear magnetic resonance (NMR) spectrum and mass spectrometry (MS) analysis.

**Results:** Two-fold increase in the yield of EPS (23 g/l) by the selected isolate was obtained by using culture conditions as 10% inoculum size having cell density of 10<sup>7</sup> cells/ml, pH 6, incubation temperature 45 °C, 3% carbohydrate, 0.5% yeast extract as nitrogen source, 20% salt concentration and 7 d of incubation period. Characterization of the purified EPS suggested the presence of dominated glycosidic linkages and heptasaccharide nature of the molecule. As the present strain is halophilic, 20% NaCl was found to be optimum.

**Conclusion:** Optimization studies resulted in two-fold increase in the yield of EPS which is of heptasaccharide nature.

**Keywords:** *Halomonas smyrnensis* SVD III, Exopolysaccharide, Characterization of EPS by FTIR, MS, <sup>1</sup>H NMR, Glycosidic linkages, Heptasaccharide, Moderately halophilic bacterium

© 2017 The Authors. Published by Innovare Academic Sciences Pvt Ltd. This is an open-access article under the CC BY license (<http://creativecommons.org/licenses/by/4.0/>)  
DOI: <http://dx.doi.org/10.22159/ijpps.2017v9i10.20935>

### INTRODUCTION

Microbial exopolysaccharides are polysaccharides produced by microbes extracellularly as capsule or slime. These microbial EPS generally are categorized into 2 broad classes namely homopolysaccharide composed of single units of monosaccharides and heteropolysaccharide composed of two or more units of monosaccharides.

Microbial EPS are non-toxic, biodegradable and renewable in nature [1]. They play an important role in protection against desiccation [2] and also useful in forming biofilms [3, 4]. Their various applications include use as gelling agents, biosurfactants, emulsifiers, viscosifiers [5-7], biosorbents [8, 9], biologically active antimicrobials, anticancer agents and antioxidants [10-13].

Dextran is the first industrial EPS produced by *Leuconostoc mesenteroides* [14] followed by the xanthan gum which is produced by *Xanthomonas campestris* as another approved food additive [15]. Many *Bacillus* species are reported for EPS production [16-20]. Production of EPS from alkaliphilic *Vagococcus carniphilus* was investigated [21].

EPS from extremophilic microorganisms especially halophiles are comparatively less reported. Production of EPS from halophilic bacteria within extreme marine habitat along with its biological activities was reviewed [6]. *Haloferax mediterranei*, a halophilic archaeon was reported for the production of EPS with excellent rheological properties and has application in oil recovery [22, 6]. EPS from *Halomonas ventosae* and *Halomonas anticariensis* has pseudoplastic behavior [23]. Moderately halophilic *Halomonas cerina* sp. nov. was isolated from saline soils in Spain which produced EPS [24].

The yield, composition and structure of the EPS vary with the microorganism and conditions of fermentation. There are different requirements of carbon, nitrogen sources, temperature, pH, minerals etc.

for different microorganisms for EPS production. The nutritional and environmental conditions influence the yield of EPS [25]. EPS yield was found to be increased when marine bacteria were grown on limited nutrients such as phosphorous, sulphur, nitrogen and potassium [26]. During optimization of EPS, the selection of carbon source plays an important role. When growth medium was amended with sucrose, the highest EPS yield was obtained from *Hahella chejuensis* isolated from Cheju Island, Republic of Korea [27]. The haloalkaliphilic microorganism, *Halomonas alkaliantartica* strain CRSS which was isolated from a saline lake in Antarctica produced maximum EPS when acetate was used as a carbon source [28]. EPS production requires high carbon content and less nitrogen quantity in the production medium [29].

EPS is characterized by analyzing the hydrolysate of EPS by High-performance liquid chromatography (HPLC), Fourier Transform Infrared Spectroscopy (FTIR), Nuclear Magnetic Resonance (NMR) etc.

EPS from the microbial origin can be used as antiviral, antitumor and immunogenic agents and also for their functional properties like gel formation and rheology. Dextran is explored as a plasma substitute and about 6% dextran with 50,000-100,000 relative molecular weight has equivalent viscosity and colloid-osmotic properties to blood plasma. Also, it can be used as non-irritant absorbent wound dressings [30]. EPS curdlan has antitumor activity. EPS is also used in encapsulated drugs and lotion because of its gel formation property. Although polysaccharides can be seen in the preparation of vaccines, some practical issues pose difficulties in this regard such as poor immune response by polysaccharide antigens. This can be addressed by chemical modification [30]. EPS from *Halomonas maura* and *H. eurihalina* has immunomodulating activity [31-34]. *H. stenophila* produced EPS having antitumor activity [35].

Due to surfactant and bio emulsifier activity of EPS, they have importance in enhancing oil recovery. As most of the oil recovery fields

are observed in saline environments, EPS from halophiles may have an advantage. Biological activities of EPS produced from marine halophilic bacteria have been reviewed [6]. *Halomonas* is the potential genus producing EPS having efficient emulsifying activity among halophilic bacteria. *Halomonas alkaliantartica*, *H. ventose*, *H. anticariensis* and *H. maura* were found to produce EPS that are proposed to have a role as an emulsifying agent in oil recovery [36, 28, 23, 32].

As compared to other extremophiles like alkaliphiles and thermophiles, less attention has been paid to halophiles. Very few researchers have carried out optimization and characterization studies on EPS of halophiles as can be seen from the literature. The present studies were aimed at exploitation of halophiles from unexplored saline environments from West Coast of Maharashtra, India; optimization of different parameters to enhance the yield of EPS and its characterization to understand its functional groups and linkages. An attempt has been made to reach to the rationale that EPS from halophilic microorganisms could be useful for recovery of oil from the ocean where there is a saline environment. Likewise, EPS from halophiles are considered to have immunomodulatory activity. Such kinds of studies are yet to be expanded and hence halophilic bacteria were selected for EPS production.

*Halomonas smyrnensis* SVD III was isolated from ocean water of Deobaug, West Coast of Maharashtra, India [37]. The organism was found to produce EPS. Present study was carried out to investigate the effect of various parameters on EPS production by *Halomonas smyrnensis* SVD III (GeneBank accession number-KX057990) and its characterization.

## MATERIALS AND METHODS

### Chemicals and reagents

All the chemicals were of laboratory grade and purchased from Hi-media, Merck, SD Fine Chemicals Ltd. and Qualigens, India.

### Bacterial strain

*Halomonas smyrnensis* SVD III isolated from ocean water collected in Deobaug, West Coast of Maharashtra, India [37] was used in the present study. The culture was stored at 4 °C on Sehgal and Gibbons (SG) medium [38]+15% NaCl concentration for further study.

### EPS production

Inoculum was prepared for the production of EPS by growing the culture in SG medium to have a cell density of  $10^7$  cells/ml as measured by total viable count (TVC) method. The SG medium containing 3% glucose was used for the production of EPS. The composition of SG medium was casamino acids-0.75%, yeast extract-1%, potassium chloride-0.2%, trisodiumcitrate-0.3%, magnesium sulphate-2%, sodium chloride-15%, pH-7.2.

Effect of various parameters on EPS production by *Halomonas smyrnensis* SVD III was studied. The strain SVD III was cultivated in

SG medium and incubated at 37 °C, 120 rpm for 7 d. The culture was used at 10% inoculum size with  $10^7$  cells/ml for all experiments. Effect of one parameter was studied at a time keeping other parameters constant. All experiments were carried out in triplicate using 50 ml SG medium in 250 ml Erlenmeyer flask. At the end of each experiment, EPS was extracted and estimated gravimetrically.

Effect of temperature on EPS production was studied by varying the temperature as 25 °C, 37 °C and 45 °C. The most suitable temperature was selected to determine effect of pH (5, 6, 7, 8 and 9), incubation period (1 to 8 d), inoculum size (1%, 5% and 10%), concentration of NaCl (10, 15, 20 and 25%), concentration of carbon source (3%, 4%, 5% and 6% glucose) and nitrogen source (0.5%, 1%, 1.5% and 2% yeast extract) on production of EPS.

### Isolation and purification of EPS

The culture broth was centrifuged at 8000 rpm for 10 min. The cell-free culture broth (CFCB) was collected and 20% trichloroacetic acid (TCA) added to the same. CFCB was then kept on ice for 30 min to precipitate proteins followed by the centrifugation at 8000 rpm for 10 min. The supernatant was then collected in a glass tube and two volumes of chilled ethanol added. The solution was kept at 4 °C overnight to precipitate EPS [6, 30]. The amount of EPS was calculated based on dry weight estimation by gravimetric method.

### Characterization of EPS

The purified EPS was characterized using fourier-transform infrared (FTIR) spectroscopy, nuclear magnetic resonance (NMR) spectroscopy and mass spectrometry (MS) [6, 12, 18, 31].

The purified EPS was analyzed for FTIR spectroscopy analysis. The sample was analyzed between infrared spectrum 3500-400  $\text{cm}^{-1}$  using Bruker-TENSOR 37 IR spectrophotometer (USA). The purified EPS was subjected to NMR spectroscopy analysis using Bruker-Ascend 500 MHz (USA). Dimethylsulphonate (DMSO) was used as a solvent system. Applications of NMR used were  $^1\text{H}$  i.e. hydrogen-1 NMR/proton NMR in which analysis is done with respect to hydrogen-1 nuclei within the molecules of a substance, in order to determine the structure of its molecules [39]. The purified EPS was analyzed by MS using Bruker-HRMS Impact HD Q-TOF MS (USA). Parameters for this study were as follows; source type-ESI, ion polarity-positive, scan begin-50 m/z, scan end-1200 m/z.

## RESULTS

In the present study, EPS was isolated and characterized from *Halomonas smyrnensis* SVD III.

Effect of different media components on the production of EPS was investigated. Effect of carbohydrate concentration was checked by using different glucose concentration as 3%, 4%, 5% and 6%. Maximum EPS yield of 10.5 g/l was obtained at 3% glucose concentration, which decreased with increase in sugar concentration (fig. 1).

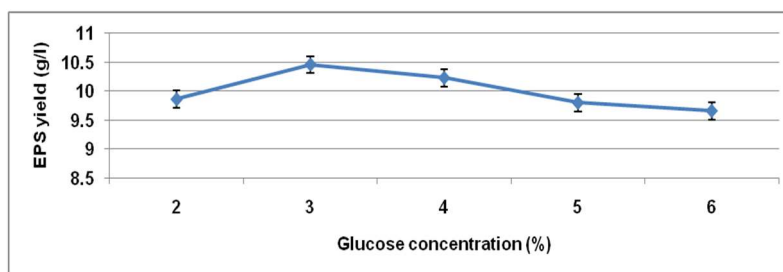


Fig. 1: Optimization of carbohydrate concentration showing 3% as the optimum concentration of glucose with 10.5 g/l yield of EPS. The number of experiments was 3 and data given in mean standard deviation (SD) and standard error (SE)

As regards effect of the incubation period, it was found that EPS yield gradually increased with incubation period up to 7<sup>th</sup> day and

then remained stationary (fig. 2). EPS yield obtained on 7<sup>th</sup> day was 10 g/l.

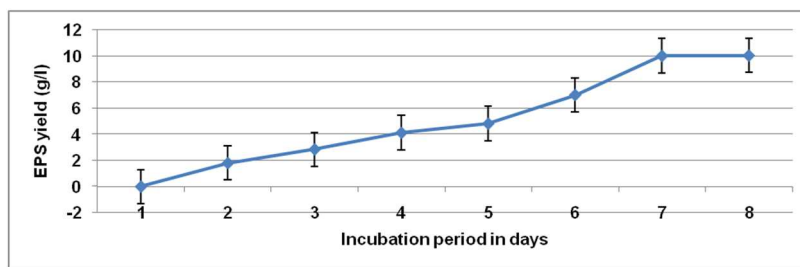


Fig. 2: Optimization of incubation period illustrating 7 d as the optimum incubation period with EPS yield of 10 g/l. The number of experiments was 3 and data given in mean SD and SE

EPS yield gradually increased with increase in inoculum size. At 10% inoculum size, EPS yield was found to be 9.75 g/l (fig. 3). Effect of different pH on EPS yield was checked and maximum EPS yield was observed at pH-6 which is 12.68 g/l followed by a gradual decrease with increase in pH value (fig. 4).

As regards effect of different salt concentrations, it was observed that maximum EPS was produced at 20% salt concentration as 10.65 g/l (Fig.5). EPS production checked at different incubation temperature indicated that at a higher temperature, the yield of EPS is increased. At 45 °C EPS yield was observed as 23.95 g/l (fig. 6).

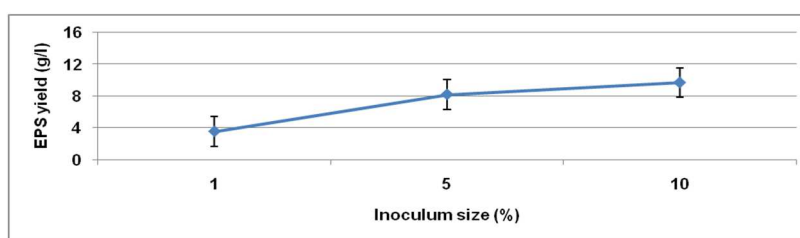


Fig. 3: Optimization of inoculum size indicating 10% inoculum size as optimum with EPS yield of 9.75 g/l. The number of experiments was 3 and data given in mean SD and SE

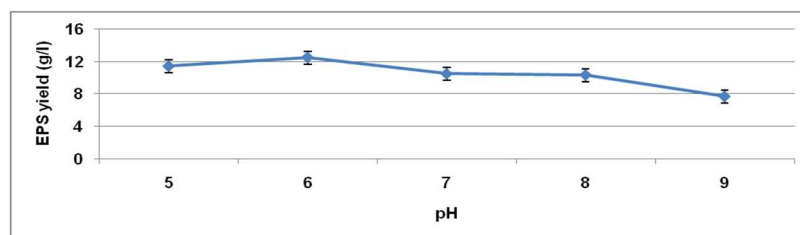


Fig. 4: Optimization of pH showing 6 as the optimum pH yielding 12.68 g/l EPS. The number of experiments was 3 and data given in SD and SE

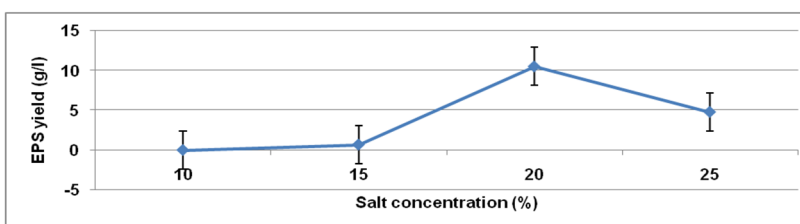


Fig. 5: Optimization of salt concentration-20% salt as the optimum with EPS yield of 10.65 g/l. The number of experiments was 3 and data given in mean SD and SE

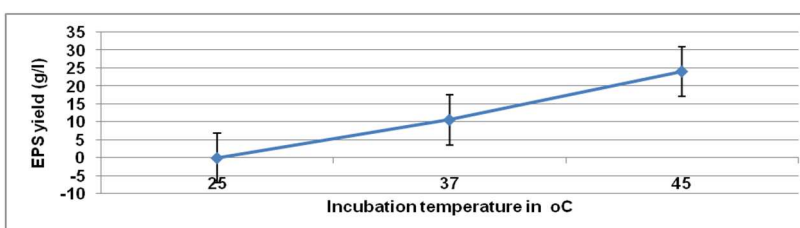


Fig. 6: Optimization of temperature indicating 45 °C temperature as the optimum with EPS yield of 23.95 g/l. The number of experiments was 3 and data given in mean SD and SE

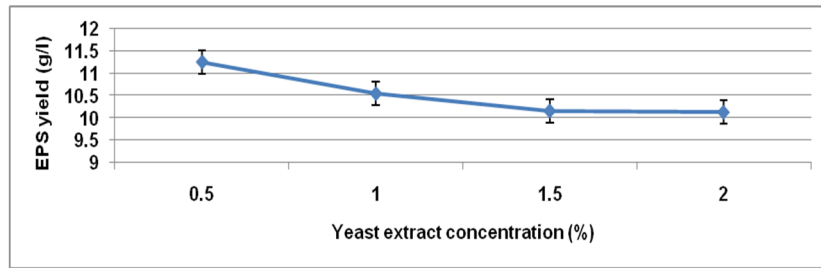


Fig. 7: Optimization of yeast extract concentration showing 0.5% yeast extract as the optimum nitrogen source yielding 11.34 g/l EPS. The number of experiments was 3 and data given in mean SD and SE

Different concentrations of yeast extract were studied for their effects on EPS yield. EPS yield was found maximum 11.34 g/l at 0.5% concentration of yeast extract (fig. 7).

Thus the optimum conditions for production of EPS by *H. smyrnensis* were found to be 3% glucose, 20% NaCl, the incubation period of 7 d, pH 6, temperature 45 °C, 0.5% yeast extract and inoculum size 10%. Under all optimum conditions, the EPS yield was 23 g/l indicating two-fold increase.

In FTIR spectra, the bands of 1770.94  $\text{cm}^{-1}$  and 1664.23  $\text{cm}^{-1}$  indicate the presence of the carbonyl group. Bands of 1122.54  $\text{cm}^{-1}$  and 1076.14  $\text{cm}^{-1}$  are dominated by glycosidic linkages (strong C-O bonds) of the polysaccharide. The band at 3320.47  $\text{cm}^{-1}$  is due to broad presence of the OH group. The  $\text{-CH}_2$  wagging is observed at

band 1334.03  $\text{cm}^{-1}$ . The band 647.08  $\text{cm}^{-1}$  is due to the out of plane bending of  $\text{-OH}$  group (fig. 8).

$^1\text{H}$  NMR spectra of the EPS sample showed the signals between the ranges of 3.659-4.932 ppm indicating protons on anomeric carbons which suggests the sample to be heptasaccharide. The signal at 3.361 ppm corresponds to the presence of protonated carbon adjacent to the electronegative group. The signal at 2.506 ppm is attributed to presence of protonated carbon adjacent to less electronegative groups (fig. 9).

Mass spectrometry suggested the presence of an oligosaccharide. The sample showed the peak at 1132.1940 which could be because of about 6-7 monosaccharide units. There are some peaks seen with the loss of 60 units suggesting the presence of sugar which has lost  $\text{C}_2\text{H}_4\text{O}_2$ . Base peak is seen at 782.4424 (fig. 10).

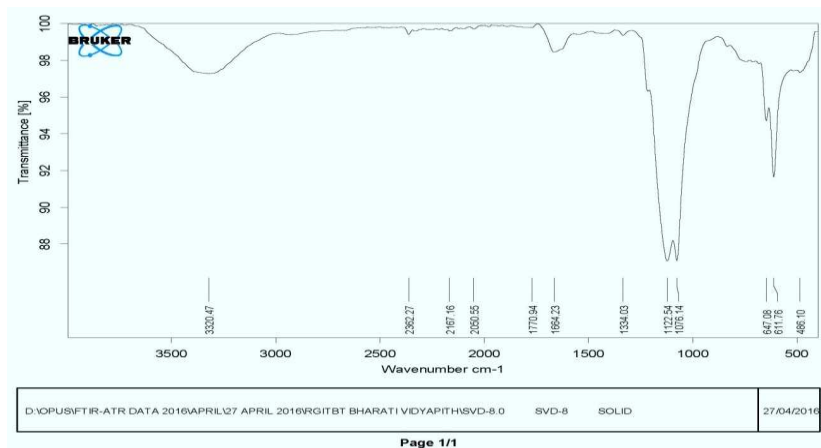


Fig. 8: Fourier transform infrared spectroscopy analysis showing glycosidic linkages between 1122 and 1076 $^{-1}$  cm, carbonyl groups between 1770 and 1664 in the EPS produced

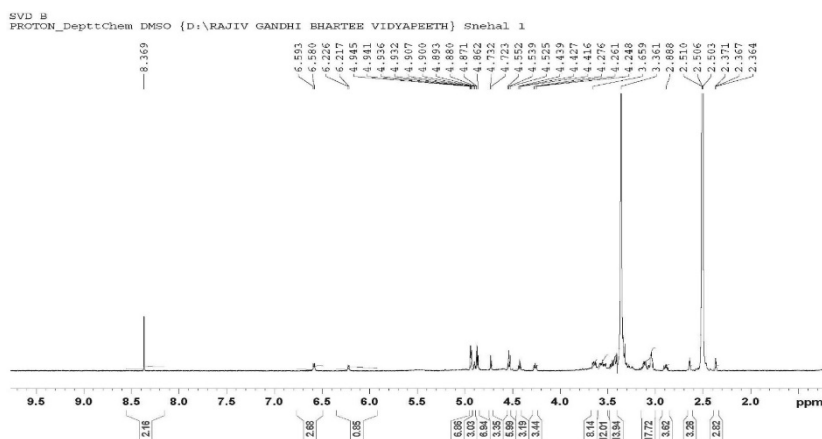
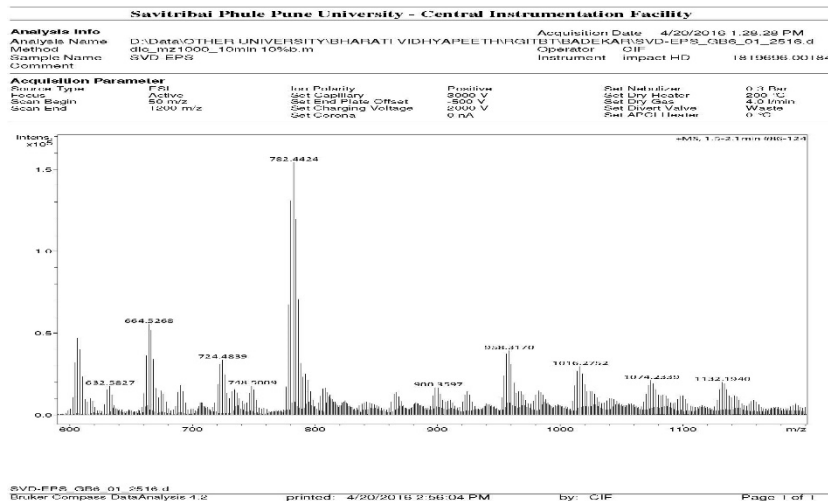


Fig. 9:  $^1\text{H}$  nuclear magnetic resonance analysis: signals between 3.659 and 4.932 showing heptasaccharide nature of the EPS



**Fig. 10: Mass spectrometry analysis indicating presence of oligosaccharide in the EPS produced**

## DISCUSSION

EPS is known to be produced extracellular during stationary phase and hence incubation period of 7 d was found to be optimum for production of EPS. It was observed that higher temperature plays a supportive role in EPS production. Halophilic microorganisms are known to grow optimally in the temperature range of 35 °C to 55 °C. In the present study also *H. smyrnensis* was found to produce maximum EPS at 45 °C. Since nitrogen is required for only growth of the organism, 0.5% yeast extract was found to be adequate for the production of EPS. As the organism *H. smyrnensis* is moderately halophilic, 20% concentration of NaCl was found to be optimum for production of EPS. EPS is a biopolymer of carbohydrates and hence 3% concentration of glucose was found to enhance the yield of EPS. *Halomonas* sp. AAD6 isolated from soil samples from Camalti Saltern area in Turkey, when grown in the presence of sucrose in defined media, produced highest EPS production levels of 1.073 g/l [40]. This strain was further identified as *Halomonas smyrnensis* sp. nov. [41]. The present strain of *H. smyrnensis* SVD III produced maximum 23.95 g/l EPS at 45 °C temperature (fig. 6). Thus the EPS production was 24 times higher than the type strain of *H. smyrnensis* sp. nov. Characterization data of the extracted EPS from type strain of *H. smyrnensis* sp. nov. Suggested that it was a levan type of EPS while the EPS produced by the present strain of *H. smyrnensis* SVD III was of heptasaccharide nature.

Optimization of production of EPS by bacteria from extreme marine habitats has been reviewed [6]. Optimization of production of EPS and its characterization from *Ophiocordyceps dipterigena* was studied [12]. Optimization of different nutrient media for the production of EPS by *Bacillus subtilis* has been described [20]. Characterization of EPS produced by *Bacillus cereus* and *Brachybacterium* species was carried out [18]. Production of EPS by alkalitolerant and halotolerant *Vagococcus carniphilus* isolated from alkaline soda lake of Lonar, India was described, production of EPS was optimized for different environmental conditions and characterized the EPS for total carbohydrate content and monosaccharides [21]. In the present study, optimization of production of EPS from *H. smyrnensis* SVD III was studied.

Production of EPS by a moderately halophilic bacterium isolated from a salt lake in Romania was described. The production of EPS was optimized for culture conditions and composition of the culture medium. The polymer was characterized by FTIR and spectrophotometrically by measuring absorption at 260 nm and fluorescence emission at 530 nm. The EPS was found to be thermostable [42]. In the present study, the EPS produced by *H. smyrnensis* SVD III was characterized by FTIR, <sup>1</sup>H NMR and MS.

In the light of work carried out on the production of EPS and its characterization from different microorganisms including halophilic

microorganisms by different researchers over the globe, the EPS produced by the present strain of *Halomonas smyrnensis* SVD III thus appears to be different from the reported halophilic microorganisms.

## CONCLUSION

*Halomonas smyrnensis* SVD III isolated from ocean water from West Coast of Maharashtra, India was found to produce 23 g/l EPS under all optimum conditions namely 3% glucose, 20% NaCl, incubation period of 7 d, pH 6, incubation temperature 45 °C, 0.5% yeast extract and inoculum size of 10%. The optimization studies resulted in two fold increase in yield of EPS. The characterization of EPS produced revealed heptasaccharide nature and dominance of glycosidic linkages (strong C-O bonds) in the polysaccharide.

## ACKNOWLEDGEMENT

The authors thank Dr. Sujata Kale of Aabasaheb Garware College, Pune for interpretation of results of FTIR, <sup>1</sup>H NMR and MS. The authors are thankful to Dr. Prabhakar Ranjekar, Ex-Director, Interactive Research School for Health Affairs, Pune, Bharati Vidyapeeth Deemed University for his encouragement and support.

## AUTHOR CONTRIBUTION

- 1) Siddharth Deshmukh: Ph. D. thesis work, conducting all the experiments, interpretation of results, writing and revising the manuscript
- 2) Pradnya Kanekar (Research co-guide): Concept and designing of experiments, interpretation of results, editing the manuscript
- 3) Rama Bhadekar (Research guide): Overall supervision on the laboratory experimental work, execution of the experimental work in the laboratory, editing the manuscript.

## CONFLICT OF INTERESTS

Declared none

## REFERENCES

1. Freitas F, Alves DA, Reis MAM. Advances in bacterial exopolysaccharides: from production to biotechnological applications. Trends Biotechnol 2011;29:388-98.
2. Bhaskar PV, Bhosle NB. Bacterial extracellular polymeric substance carrier of heavy metals in the marine food-chain. Environ Int 2006;32:191-8.
3. Hinsia SW, O'Toole GA. Biofilm formation by *Pseudomonas fluorescens* WCS365: a role for LapD. Microbiology 2006;152:1375-83.
4. İlhan Sungur E, Türetgen İ, Javaherdashti R. Monitoring and disinfection of biofilm-associated sulfate reducing bacteria on

- different substrata in a simulated recirculating cooling tower system. *Turk J Biol* 2010;34:389-97.
5. Bryan BA, Linhardt RJ, Daniels L. Variation in composition and yield of exopolysaccharides produced by *Klebsiella* sp. strain K32 and *Acinetobacter calcoaceticus* BD4. *Appl Environ Microbiol* 1986;51:1304-8.
  6. Poli A, Anzelmo G, Nicolaus B. Bacterial exopolysaccharides from extreme marine habitats: production, characterization and biological activities. *Mar Drugs* 2010;8:1779-802.
  7. Satpute SK, Banat IM, Dhakephalkar PK, Banpurkar AG, Chopade AG. Biosurfactants, bioemulsifiers and exopolysaccharides from marine microorganisms. *Biotechnol Adv* 2010;28:436-50.
  8. Martins PSO, de Almeida NF, Leite SGF. Application of a bacterial extracellular polymeric substance in heavy metal adsorption in a co contaminated aqueous system. *Braz J Microbiol* 2008;39:780-6.
  9. Moppert X, Le Costaouec T, Raquenes G, Courtois A, Simon-Colin C, Crassous P. *et al.* Investigations into the uptake of copper, iron and selenium by a highly sulphated bacterial exopolysaccharide isolated from microbial mats. *J Ind Microbiol Biotechnol* 2009;36:599-604.
  10. Onbasli D, Aslim B. Determination of antimicrobial activity and production of some metabolites by *Pseudomonas aeruginosa* B1 and B2 in sugar beet molasses. *Afr J Biotechnol* 2008;7:4614-9.
  11. Liu J, Luo J, Ye H, Sun Y, Lu Z, Zeng X. *In vitro* and *in vivo* antioxidant activity of exopolysaccharides from endophytic bacterium *Paenibacillus polymyxa* EJS-3. *Carbohydr Polym* 2010;82:1278-83.
  12. Kocharin K, Rachathewe P, Sanglier JJ, Prathumpai W. Exobiopolymer production by *Ophiocordyceps dipterigena* BCC 2073: optimization, production in bioreactor and characterization. *BMC Biotechnol* 2010;10:51.
  13. Liu CT, Chu FJ, Chou CC, Yu RC. Antiproliferative and anticytotoxic effects of cell fractions and exopolysaccharides from *Lactobacillus casei* 01. *Mutat Res* 2011;721:157-62.
  14. Crescenzi V. Microbial polysaccharides of applied interest: ongoing research activities in Europe. *Biotechnol Prog* 1995;11:251-9.
  15. Sutherland IW. Novel and established applications of microbial polysaccharides. *Trends Biotechnol* 1998;16:41-6.
  16. Patil V, Bathe GA, Patil AV, Patil RH, Sulunkea BK. Production of bioflocculant exopolysaccharide by *Bacillus subtilis*. *Adv Biotech* 2009;8:14-7.
  17. Sayem SMA, Emiliano M, Letizia C, Annabella T, Angela C, Anna Z, *et al.* Anti-biofilm activity of an exopolysaccharide from a sponge-associated strain of *Bacillus licheniformis*. *Microb Cell Fact* 2011;10:74-86.
  18. Orsod M, Joseph M, Huyop F. Characterization of exopolysaccharides produced by *Bacillus cereus* and *Brachy bacterium* sp. Isolated from Asian Sea Bass (*Latescalcarifer*). *Malays J Microbiol* 2012;8:170-4.
  19. Chen Yi-Tao, Qianq Yuan, Le-Tian Shan, Mei-Ai Lin, Dong-Qing, Cheng, *et al.* Antitumor activity of bacterial exopolysaccharides from the endophyte *Bacillus amyloliquefaciens* sp. isolated from *Ophiopogon japonicas*. *Oncol Lett* 2013;5:1787-92.
  20. Razack SA, Velayutham V, Thangavelu V. Medium optimization for the production of exopolysaccharide by *Bacillus subtilis* using synthetic sources and agro wastes. *Turk J Biol* 2013;37:280-8.
  21. Joshi AA, Kanekar PP. Production of exopolysaccharide by *Vagococcus carniphilus* MCM B-1018 isolated from alkaline Lonar lake, India. *Ann Microbiol* 2011;61:733-40.
  22. Anton J, Meseguer I, Rodriguez-Valera F. Production of an extracellular polysaccharide by *Haloferax mediterranei*. *Appl Environ Microbiol* 1988;54:2381-6.
  23. Mata JA, Bejar V, Llamas I, Arias S, Bressollier P, Tallon R, *et al.* Exopolysaccharides produced by the recently described bacteria *Halomonas ventosae* and *Halomonas anticariensis*. *Res Microbiol* 2006;157:827-35.
  24. Carmen M, Gonzalez-Domenech, Fernando Martinez-Checa, Quesada E, Bejar V. *Halomonas cerina* sp. nov., a moderately halophilic, denitrifying, exopolysaccharide-producing bacterium. *Int J Syst Evol Microbiol* 2008;58:803-9.
  25. Kumar AS, Mody K, Jha B. Evaluation of biosurfactant/bioemulsifier production by a marine bacterium. *Bull Environ Contam Toxicol* 2007;79:617-21.
  26. Sutherland IW. Biosynthesis of microbial exopolysaccharides. *Adv Microbial Phys* 1982;23:79-150.
  27. Lee HK, Chun J, Moon EJ, Ko SH, Lee DS, Lee HS, *et al.* *Hahella chejuensis* gen. nov. sp. nov., an extracellular-polysaccharide producing marine bacterium. *Int J Syst Evol Microbiol* 2001;51:661-6.
  28. Poli A, Esposito E, Oriando P, Lama L, Giordano A, de Appolonia F, *et al.* *Halomonas alkaliantarctica* sp. nov. isolated from saline lake cape russell in antarctica, an alkalophilic moderately halophilic, exopolysaccharide-producing bacterium. *Syst Appl Microbiol* 2007;30:31-8.
  29. De Vuyst L, Degeest B. Heteropolysaccharides from lactic acid bacteria. *FEMS Microbiol* 1999;23:153-77.
  30. Jenkins RO, Hall JF. Production and applications of microbial exopolysaccharides. In: Jenkins RO, Currell B, Mieras Van, Dam RC. editors. *Biotechnological innovations in chemical synthesis*. Oxford: Butterworth Heinemann; 1997. p. 193-230.
  31. Bejar V, Llamas I, Calco C, Quesada E. Characterization of exopolysaccharides produced by 19 halophilic strains of the species *Halomonas eurihalina*. *J Biotechnol* 1998;61:135-41.
  32. Arias S, Del Moral A, Ferrer MR, Tallon R, Quesada E, Bejar VM. An exopolysaccharide produced by the halophilic bacterium *Halomonas maura*, with a novel composition and interesting properties for biotechnology. *Extremophiles* 2003;7:319-26.
  33. Quesada E, Bejar V, Calvo C. Exopolysaccharide production by *Volcaniella eurihalina*. *Experientia* 1993;49:1037-41.
  34. Perez-Fernandez ME, Quesada E, Galvez J, Ruiz C. Effect of exopolysaccharide V2-7 isolated from *Halomonas eurihalina* on the proliferation *in vitro* of human peripheral blood lymphocytes. *Immunopharmacol Immunotoxicol* 2000;22: 131-41.
  35. Ruiz-Ruiz C, Srivastava GK, Carranza D, Mata JA, Llamas I, Santamaria M, *et al.* An exopolysaccharide produced by the novel halophilic bacterium *Halomonas stenophila* strain B 100 selectively induces apoptosis in human T leukaemia cells. *Appl Microbiol Biotechnol* 2011;89:345-55.
  36. Bouchotroch S, Quesada E, Del Moral A, Llamas I, Bejar V. *Halomonas maura* sp. nov., a novel moderately halophilic exopolysaccharide-producing bacterium. *Int J Syst Evol Microbiol* 2001;51:1625-32.
  37. Deshmukh SV, Kanekar PP, Bhadekar RK, Dhar SK. Exopolysaccharide producing halophilic microorganisms from West Coast of Maharashtra, India. *Int J Pharm Biol Sci* 2017;8:370-5.
  38. Sehgal SN, Gibbons NE. Effect of some metal ions on the growth of *Halobacterium cutirubrum*. *Can J Microbiol* 1960;6:165-9.
  39. Silverstein RM, Clayton BG, Morrill TC. Spectrometric identification of organic compounds. Wiley, New York; 1991.
  40. Poli A, Kazak H, Gurleyendag B, Tommonaro G, Pieretti G, Oner ET, *et al.* High-level synthesis of levan by a novel *Halomonas* species growing on defined media. *Carb Polym* 2009;78:651-7.
  41. Poli A, Nicolaus B, Denizeli AA, Yavuzturk B, Kazan B. *Halomonas smyrnensis* sp. nov. a moderately halophilic exopolysaccharide producing bacterium. *Int J Syst Evol Microbiol* 2013;63:10-8.
  42. Cojoc R, Merciu S, Oancea P, Pincu E, Dumitru L, Enache M. Highly thermostable exopolysaccharide produced by the moderately halophilic bacterium isolated from a man-made young salt lake in romania. *Pol J Microbiol* 2009;58:289-94.

#### How to cite this article

- Siddharth Deshmukh, Pradnya Kanekar, Rama Bhadekar. Production and characterization of an exopolysaccharide from marine moderately halophilic bacterium *Halomonas smyrnensis* SVD III. *Int J Pharm Pharm Sci* 2017;9(10):146-151.