



PROPERTIES OF CHITIN REINFORCES COMPOSITES: A REVIEW

M. I. Ofem^{1,*}, A. J. Anyandi² and E. B. Ene³

^{1,2,3} MECH. ENGINEERING DEPARTMENT, CROSS RIVER UNIV. OF TECHNOLOGY CALABAR, CROSSRIVER STATE. NIGERIA

E-mail addresses: ¹ ofemic@yahoo.com, ² anyandi@yahoo.com, ³ enechinelo@yahoo.com

ABSTRACT

This paper provides a review of chitin, sources, extraction, uses, applications, chitin whiskers and its preparations and the mechanical and thermal properties of chitin reinforced composites. Also reported here is the properties of CaCO₃/chitin whiskers reinforced composites. Chitin can be extracted from shrimps, crabs cell walls, yeast and green algae or from Riftia tubes with a percentage varying between 20 to 40% depending on the source. Despite the denaturing of chitin, the most widely used method of extracting chitin from seashells is the chemical method. Chitin whiskers known by different name in literature can only be prepared by using hydrochloric acid. The rod-like particles of chitin whiskers have an average lengths and widths of 200 ± 20 nm and 8 ± 1 nm respectively or more depending on the source of chitin. Chitin whiskers reinforced composites have greatly improved the mechanical and thermal properties of the composites especially at lower filler loading. The improved properties are attributed to effective stress transfer.

Key words: Chitin, mechanical, thermal, properties, biomaterials

1. INTRODUCTION

Research on nanocomposites has been on the increase, which can be attributed to their improved properties compared to neat polymers [1-2]. A class of new composites which has equally attracted research are the bio-based composite materials. This interest is based on the fundamental advantages; being renewable materials they contribute little or nothing to the depletion of energy resources and they are environmentally friendly. Another major reason for the interest is the gradual increase in the price of oil-based products and the destructive effects on the environments of these products [3]. Research into the properties of bio-based reinforced polymers has been reported [4-6]. These materials have shown good mechanical and thermal properties. One major bio material that research is ongoing is chitin.

Chitin is a naturally occurring renewable and biodegradable polysaccharide, it is a mechanically stable, nontoxic and physiologically inert polymer [7]. Chitin is a co-polymer of *N*-acetyl-glucosamine and *N*-glucosamine units, either randomly or blockly distributed throughout the biopolymer chain. When the number of *N*-acetyl-glucosamine units is higher than 50 %, the biopolymer is termed chitin, when the number of *N*-glucosamine units is higher, the term chitosan is used [8].

Being the second most abundant natural polymer after cellulose [9], it consists of 2-acetamido-2-deoxy-D-

glucose via a β (1–4) linkage. Chitin can be extracted from its sources by biological, fermentation and chemical methods [10-12]. The chemical method which is the most widely used involves acid and alkaline treatments and de-pigmentation stage to remove astaxanthine [12]. The physicochemical characteristics (crystallinity, molecular weight, moisture and ash content, protein and deacetylation degree (DD)) of chitin and its derivative chitosan can be determined using various methods [12]. Chitin whiskers (CHW), which can be produced by acid hydrolysis, are rod-like nanofibrils with dimensions of 5-70 nm in width and 150-800 nm in length [13] depending on the source. Because of their high longitudinal and transverse moduli of 150 GPa and 15 GPa, respectively, [11, 14], CHW can be used as nanofillers for reinforcement in polymers. Different techniques of producing polymer/CHW composites have been established these are casting and evaporating [15], non-aqueous solvent dispersion [16] polymer grafting [17] and freeze-drying and hot pressing [11]. Using CHW as reinforcement has greatly improved the mechanical properties especially at lower filler loading [11, 16-17]. Here we take a comprehensive review of sources of chitin and its extraction, preparation of chitin whiskers, mechanical and thermal properties of chitin reinforced composites, other properties and the biomimetic synthesis of CaCO₃ properties of chitin reinforced polymer composites.

2. CHITIN SOURCES

A shell is the hard, protective outer layer of a marine or aquatic animal, such as a mollusc. Animals with shells can be found in rivers, streams, sea or the oceans. This protective outer layer of a marine animal is referred to as exoskeleton. Examples of animals with exoskeletons are shrimps and crabs. To reduce weight and at the same time maintain high environmentally friendly physical, chemical and mechanical properties of materials, attention is focused on the properties of these exoskeleton sometimes refer to as seashells. One of the striking features of the seashells is the presence of a biodegradable polymer called chitin. Chitin, being a homopolymer of β -(1 \rightarrow 4)-linked N-acetyl-D-glucosamine is one of the most abundant renewable, natural polymers second only to cellulose [18].

Chitin can be extracted from different sources; shrimps and crabs [19-20], cell walls and structural membranes of fungi, yeast and green algae [21-22] and from Riftia tubes [11]. Most sources of chitin contain 30 to 60 % minerals, 0 to 14 % lipids, 20 to 40 % protein and 20 to 30 % chitin [23], with calcium carbonate, protein and chitin constituting about 90 % [21]. However a recent review [24] shows that chitin varies with species. Details sources of chitin, type, % content and conditions for extraction is presented in Table 1.

It has been estimated that between 10^{12} to 10^{14} tons of chitin is produced every year in the biosphere most of it in the ocean [25-26]. As per a published report of chitin production by arthropods, the total annual production in aquatic environments is estimated to be 28×10^6 , 1328×10^6 and 6×10^6 tons of chitin for freshwater, marine ecosystems and athalassohaline ecosystems respectively [27].

2.1.1 Extraction of Chitin

There are various techniques used in the extraction of chitin. Chitin can be extracted by fermentation and biological methods. While the extraction of chitin by fermentation is very expensive [28], biological extraction does not denature the chitin, is cost effective and eco-friendly [10] and recovery of protein hydrolysate with amino acid composition can be achieved [29]. Another method that has been widely reported is the chemical method [11-12, 30-31]. The chemical method for the isolation of chitin from seashells involve demineralization of inorganic matter (calcium carbonate) using dilute acid, deproteinization (protein) using alkaline solution and bleaching/decolouration using sodium chlorite and to an extent deacetylation using over 40 % concentration of NaOH or KOH to get chitosan, a derivative of chitin. The use of chemicals (high temperature, strong acid and alkaline treatment) to

isolate chitin from seashells not only result in harmful waste (acid and alkaline) to the environment and increase in cost of chitin purification, but also gives depolymerisation of the chitin there by affecting the molecular weight and viscosity after solubilisation [23,32]. These disadvantages of chemical methods of extraction led to the development of biological methods.

As stated earlier, chemical methods of chitin extraction involves demineralization using strong acid. Some of the acids that can be used include; H_2SO_4 , $HCOOH$, CH_3COOH , HNO_3 and HCl . Of these the most widely used is HCl [12, 33]. Use of HCl allows almost the complete removal of organic salts. While deproteinization is done mostly with KOH or $NaOH$, it can equally be done with proteolytic enzymes [10, 29]. Pigments are removed using sodium chlorite, hydrogen peroxide or 0.02 % of potassium permanganate at $60^\circ C$. A detailed explanation of chitin extraction by chemical method is reported by Aranaz et al., [12].

The need for a cost effective process and non-denaturing of the chitin during the extraction process, led to the development of the biological methods. A review [24] of biological methods has shown that it can replace the conventional method of chitin extraction. Synowiecki and Al-Khateeb [29] while isolating chitin from shrimp *crangomusing* enzymes, recovered protein hydrolysate having good values of protein efficiency ratio and essential amino acid. The demineralization of crab shells were carried out using lactic acid bacteria as against hydrochloric acid, while deproteinisation was done by *fungus aspergillus niger* [10]. The result shows a comparable yield % (chemical to biological method) of 28.1 to 22.6, 27.35 to 20.8 and 27.05 to 20.15 for shell to acid ratios of 1:15, 1:25 and 1:35 respectively. Most importantly the chitin obtained was partially soluble compared to the chemical method.

Using *Bacillus licheniformis* as an enzyme, the isolation of chitin from shrimp shells yielded a better viscosity quality than commercial chitin. The viscosity (soluble fraction in diluted *N*-methyl-2-pyrrolidone-LiCl at a concentration of 0.1 wt %) obtained was 80 mPa.s compared to 10 mPa.s for commercial chitin [23]. Similarly, Khanafari *et al.*, [34] comparative study of chitin and chitosan extraction from shrimp waste using chemical and biological methods, showed that the biological method were better as it consumed less energy and time, and reduced the quantity of solvent used. A one-step co-fermentation process of isolating chitin from red crab shell was developed by Jung *et al.*, [35]. This method simultaneously removed ash and protein. A schematic biological extraction method is presented in Figure 1.

Table 1: Conditions of extraction of chitin from sea sources and extracted chitin characteristics [18 (modified)]

chitin source	Acid bath 0.55M HCl Time(h)	Alkaline bath 0.3M NaOH Time(h)	H ₂ O ₂ treatment	Chitin content (%)	Type of chitin
Barnacle (Lepasanatifera)	2	4	Yes	7	α
Red crab (Portunuspuber)	5	3	Yes	10	α
Spider crab (Maia squinado)	3	3	Yes	16	α
Lobster (Homarus vulgaris)	3	3	Yes	17	α
Locust lobster (Scyllarusarctus)	2	3	Yes	25	α
Spiny lobster (Palinurus vulgaris)	3	7	Yes	32	α
Crayfish (Astacusfluviatilis)	2	3	Yes	36	α
Shrimp (Palaemonfabricius)	3	3	Yes	22	α
Squilla (Squilla mantis)	3	3	Yes	24	α
Cuttlefish (Sepia officinalis)	3	3	No	20	β
Squid (Loligo vulgaris)	3	2	No	40	β
Marbled crab(Grapsusmarmoratus)	3	3	Yes	10	α

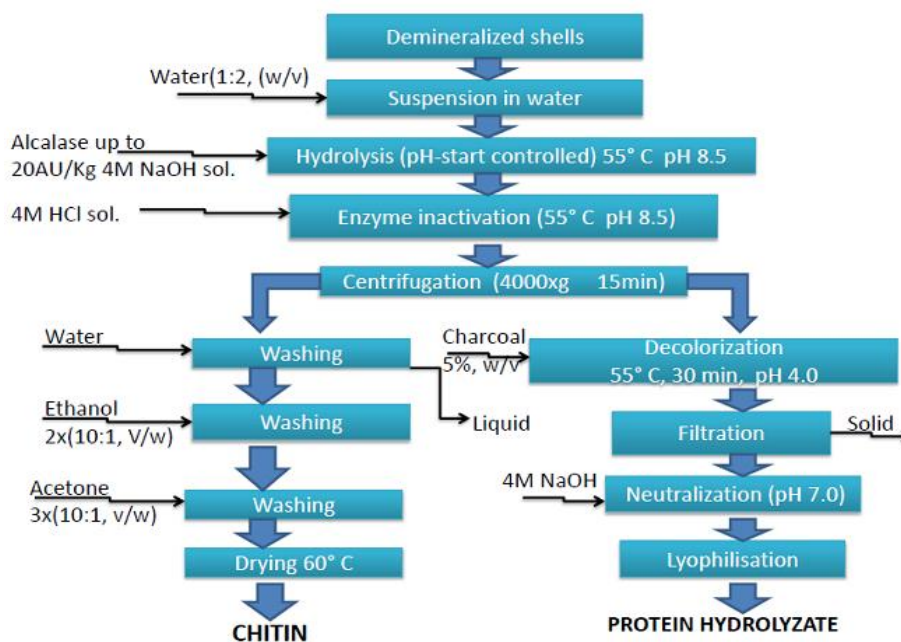


Figure 1: Flow-sheet for production of chitin and protein hydrolysate from shrimp *C. Crangon* shell waste. [29].

2.1.2 Deacetylation of Chitin

Depending on the source, three polymorphic forms of chitin are found in nature; namely α, β and γ chitins [12, 36]. The most common and extensively investigated is α-chitin because it is stable and widely found in living organisms (see Table 1). Chemical chitin is identical to cellulose but that the secondary hydroxyl on the alpha carbon atom (C-2) of the cellulose molecule is substituted with an acetamide group, also the removal of acetyl group in the alpha carbon atom results in the formation of chitosan (Figure 2). The deacetylation of chitin with NaOH or other alkaline results in the production of chitosan. Aranaz *et al.*, [12] stated two methods of chitosan preparation, depending on the level of

deacetylation. These methods are the heterogeneous deacetylation of solid chitin and homogeneous deacetylation of pre-swollen chitin under vacuum in an aqueous medium. In both cases up to 80 hours is needed to produce chitosan. In order to reduce the long processing time, and a reduction in the quantity of alkali used, Domard and Rinaldudo [37] developed a successive alkali treatment method using thiophenol in dimethylsulfoxide (DMSO). Mima *et al.*, [38] developed an intermittent water washing method while Pelletier *et al.*, [39] developed a thermo-mechanical process using a cascade reactor operating under a low alkali concentration.

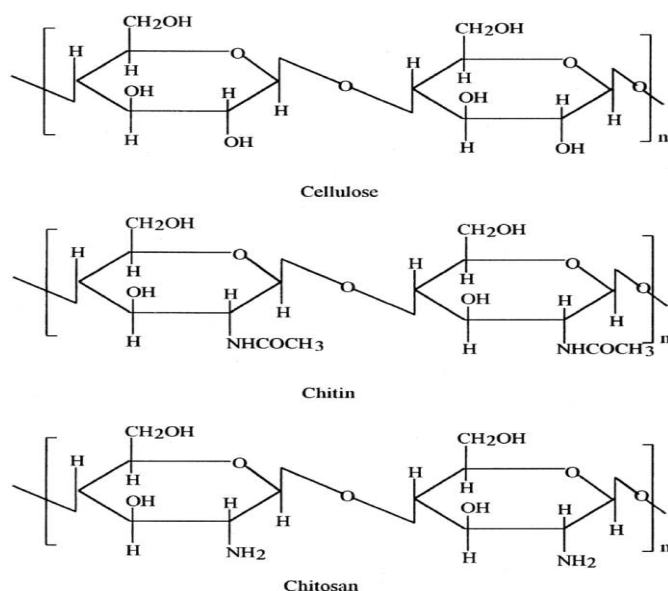


Figure 2: Chemical structures of cellulose, chitin and chitosan [40].

2.2 Chitin Whiskers

As was stated earlier chitin is known to form microfibrillar arrangements in living organisms, embedded in a non-fibrous polymer matrix of protein. CHW are known by different names in the literature such as nanocrystals, microcrystallites, nanofibrils, nanofibres or nanoparticles. Unlike cellulose whiskers which can only be prepared by strong sulphuric acid [41, 42] CHW are prepared using hydrochloric acid. Marchessault *et al* [43] was the first to report a procedure for the preparation of whiskers from chitin. In their report, purified chitin was acid hydrolysed using 2.5 N hydrochloric acid solutions under reflux for 60 minutes; the excess acid was gradually decanted, after which distilled water was added to obtain a suspension. They observed that acid hydrolyzed chitin dispersed into rod-like particles. Following their report CHW have been produced from different sources of chitin. These are crab shells [9, 15-17, 44-48], rifting tubes [11], shrimp shells [13, 30, 49-54] and squid pen [55]. Recently Ifuku *et al.*, [56] prepared chitin nanofibres from prawn shell by simple grinding without acidic chemicals. The nanofibres were 10-20 nm in width.

2.2.1 Preparation of Chitin Whiskers

In their approach in preparing CHW, Li *et al.*, [9] and Revol *et al.*, [44], purified chitin was hydrolyzed by 3 N HCl at a temperature of 104 °C for 1.5 h, then after acid hydrolysis the suspensions were diluted with deionised water, followed by centrifugation and decanting of the supernatant. This process was repeated until a colloidal state of the suspensions was observed. The crystallites were rod-like particles with average lengths and widths of 200 ± 20 nm and 8 ± 1 nm respectively.

CHW suspensions are reported to exhibit a colloidal behaviour. This behaviour was attributed to the presence of the positive charges (NH_3^+) on the surface of the CHW which was due to protonation of the amino groups of chitin in the acidic conditions [43]. Some times protonation of the amino groups is incomplete on all the CHW particles there by resulting in aggregate particles [46].

During the process of preparing nanocrystals from polymer materials, both the amorphous and the crystalline phases can be hydrolysed when strong acids are applied [57]. Due to the closed packed molecular chains in the crystalline domains of chitin, boiling chitin in HCl dissolves the amorphous phase [58] earlier than the crystalline phase. It has also been shown that the ether and the amide linkages can be broken [59]. Two important parameters that determine the particle size and yield are hydrolysis time and the concentration of HCl. Most researchers use between 2.5 to 3 N at a time frame of between 1.5 to 6 h irrespective of the source of chitin; Crab [9, 15,], rifting tubes [11], shrimp shells [13, 30, 49, 51-54] and squid pen chitin [55]. Increases in the concentration of HCl have shown to significantly destroy the chitin crystals even to the point of completely dissolving it at 8.5 N [43, 59].

Following the successful preparation of cellulose nanocrystals by Montanari *et al.*, [61] and nanofibres, Saito *et al.*, [58] using TEMPO-mediated oxidation (2,2,6,6-tetramethylpiperidine-1-oxyl radical mediated oxidation), Fan *et al.*, [60] successfully used this method to prepare chitin nanofibres and chitin nanocrystals. The addition of 5.0 mmol/g of NaClO per gram of chitin in the oxidation gave an optimum condition for the preparation of mostly individualized (Figure 3C) nanocrystals whose length and width were 340 and 8 nm respectively. After alkaline treatment of CHW, Phongying *et al.*, [54] observed that the packing structure of the CHW changed from tight crystalline to amorphous. TEM images showed that the alkaline treated CHW are a fibrous form (Figure 3A and B). Combining the results obtained from WAXD, SEM and FTIR they concluded that CHW in alkaline solution changes to form a chitosan nanoscaffold. Detailed information of CHW prepared from different sources of chitins is summarized in Table 2.

3. MECHANICAL PROPERTIES OF CHW BASED NANOCOMPOSITES

Different methods have been employed for the preparation of CHW based nanocomposites. They are casting and evaporating [30, 52, 55], freeze-drying and hot-pressing [11, 16] and polymer grafting [17].

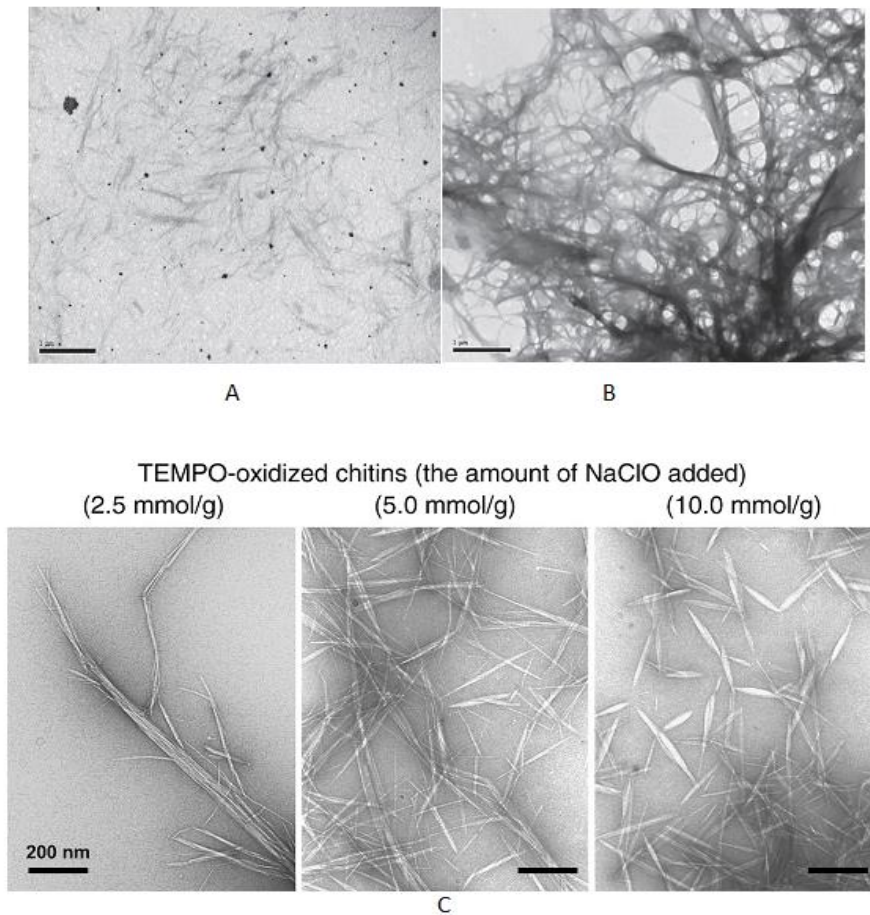


Figure 3: TEM micrographs of (a) CHW in water, (b) CHW after treatment in Alkaline [54] (c) TEM imaging of TEMPO-oxidized chitin nanocrystals prepared under different conditions [60].

Table 3 – Sizes, preparation time and temperature of CHW prepared from different sources.

Source of chitin	Width (nm)	Length (nm)	Time of hydrolysis (h)	Temperature (°C)	Reference
Shrimp	12-65	231-969	6	120	[52]
Shrimp	18-40	200-500	3	105	[30]
Shrimp	5-70	150-800	1.5	104	[54]
Shrimp	8-74	180-820	6	104	[49]
Shrimp	10-15	200-500	1.5	104	[13]
Shrimp	8-73	110-975	3	104	[51]
Crab	27-35	203-277	6	120	[46]
Crab	~20	~240	1.5	104	[17]
Crab	~15	~240	1.5	104	[47]
Crab	10-80	100-650	1.5	104	[15]
Crab	6-8	50-300	1	104	[44]
Squid pen	~10	50-300	1.5	104	[55]
Squid pen	7-70	150-800	1.5	104	[50]
Riftia tube	~18	500-1000	1.5	104	[11]

When preparing nanocomposites the technique to be used must take into account the properties of the whiskers and the matrix in addition to the desired end properties of the composite. Inaba *et al.*, [62] used starch (potato, sweet potato, kudzu, corn, wheat and mung bean) gels to form composites with chitin and collagen as

fillers. The results showed that there was an increase in the gel hardness between 90-120 % for potato, sweet potato and wheat and an increase of between 150-300 % for corn as starch concentration was increased. Similarly there was an increase between 90-300 % in cohesiveness and adhesiveness as starch concentration

increased. They attributed the increase in gel hardness to complex factors, among which are filler particle size, nature of the gel matrix, starch retrogression rate and swelling nature of the particle.

Feng *et al.*, [17] formed a chitin whisker-graft-polycaprolactone (PLC) composite using different mixtures of chitin and polycaprolactone monomer. They reported an increase in tensile strength and breaking strain while Young's modulus decreased as the PCL content was increased. β -chitin/poly(vinyl alcohol) (PVA) composite films at different ratios were formed by Peesan *et al.*, [63]. The tensile strength was found to increase from 0.7 to 5.1 MPa with an increase in β -chitin content, compared to pure β -chitin or PVA. The percentage elongation at break decreased from 165.2% to 2.9 % while the behaviour of the composite became brittle as the β -chitin content increased. Instead of using β -chitin, Junkasem *et al.* [52] and Junkasem *et al.*, [53] used α -chitin as reinforcement with PVA; their result showed better mechanical properties than Peesan *et al.*, [63].

Nair and Dufresne, [47] carried out chemical modification of crab shell CHW using three different reagents; namely phenyl isocyanate (PI), alkenyl succinic anhydride (ASA) and 3-isopropenyl-, α,α' -dimethylbenzyl isocyanate (TMI). They investigated the effect of the incorporation of these materials into a natural rubber matrix. PI and ASA were used to improve the quality of the interface between the natural rubber matrix and the CHW, while TMI helped the CHW to copolymerize with the natural rubber matrix. The chemical modification resulted in the reduction of the mechanical properties. They concluded that this "could be due to the partial or total destruction of the three-dimensional network of CHW assumed to be present in the unmodified composites."

Calcium alginate yarns and calcium alginate nanocomposite yarns containing 0.05-2.00 % w/w CHW were both prepared using a wet spinning process [30]. An increase in the tenacity of the hybrid was found at 0.015 % w/w of whiskers, reaching a maximum at 0.15 % w/w, followed by a decrease. The same trend was observed for the elongation at break. A maximum elongation at break was observed at 0.10 % w/w. They concluded that the initial rise in tenacity and elongation was due to electrostatic interactions and intermolecular hydrogen bonding between molecules and the CHW at low whiskers content, while the decrease in tenacity and elongation was attributed to the aggregation of the whiskers.

He and Ma, [64] prepared cellulose/chitin composites using a high wet method (where the spinning solution preparation method and spinning technique will have determining influence on the final properties (i.e., mechanical property and wet modulus)). The result

shows better mechanical properties when compared with crabyon fiber and normal viscose filaments. Also Zhang *et al.*, [65] successfully blended chitin/cellulose using two different coagulating systems (immersed in 5 wt % H_2SO_4 for 5 minutes, and subsequently 10 wt % glycerine for 10 minutes (H membranes) another immersed in 5 wt % $CaCl_2$, and follow the earlier steps (C membranes)) to compare mechanical properties. The tensile strength of H-membranes, in both wet and dry states, increased with an increase in chitin content and decreased with an increase in chitin content for the C membranes. Conversely the breaking elongation for C-membranes was much higher than that for H-membranes for both wet and dry specimens, as the chitin content increased. These results confirmed that there is a relatively weak interaction between cellulose and chitin for the C blend membrane, caused by an addition of chitin, and a strong interaction between cellulose and chitin in the H blends.

Four different methods of chitin film preparation were studied by Yusof *et al.*, [66]. Depending on the method, the Young's modulus varied between 1.2 and 3.7 GPa while the tensile strength was between 38.3 to 77.2 MPa and the % strain between 4.7 and 21.3 %. Ifuku *et al.*, [56] reported a Young's modulus of 2.5 GPa and a tensile strength of ~ 40 MPa for chitin film. The Young's modulus of chitin reinforced (meth) acrylic resin varied between 1.2 and ~ 5 GPa while the tensile strength was between ~ 30 and ~ 70 MPa depending on the number of the repeating units of acrylic acid resin. The mechanical properties of CHW reinforced poly vinyl alcohol (PVA) composites films with or without heat treatment have been shown to have improved compared to the original matrix [50]. The tensile strength was between ~ 60 and ~ 83 MPa while the % strain continue to decrease from 14.7 % for pure PVA film to 5.5 % for composite film having 29.6 wt % CHW

Two different techniques; freeze-drying and hot pressing and casting and evaporating were employed by Nair and Dufresne, [48] to obtain CHW reinforced natural rubber. The result shows clear evidence of the dependence of the properties on the technique used. The modulus for unvulcanized evaporated samples was higher than those of vulcanized evaporated ones, while the unvulcanized hot pressed composites were the least. Nanosized CHW forms a 3-D rigid network in the evaporated technique method; Table 3 shows a summary of the properties at different CHW content.

When soy protein was reinforced with CHW [15] there was an increase in modulus and tensile strength from 26.4 to 158 MPa and 3.3 to 8.4 MPa respectively as CHW content was increased from 0-20 wt %, while the elongation at break decreased from 205 % to 29 %. Above 20 wt % CHW, the mechanical properties

decrease. The tensile strength of CHW reinforced chitosan increases from the initial ~65 MPa for chitosan to ~84 MPa at CHW content of 2.96 %. Subsequent addition of CHW did not show any significant decrease up to 29.6 % content. The percentage elongation at break decreases from ~12 % for chitosan and level up at CHW greater or equal to 2.96 % [49]. The same behavior was observed when poly(vinyl alcohol) was used as the matrix [50].

Figure 4 shows the normalized mechanical properties of CHW reinforced polymers composites at different CHW content. The properties of pure polycaprolactone were obtained from Azevodo and Reis, [67]. From the figure there is a clear trend of decrease in strain at break as CHW increases. Most authors agreed that the initial increase in tensile strength and Young’s modulus up to a certain filler loading is an indication of strong interactions between whiskers and the matrix. These interactions restrict the motion of the matrix leading to better properties.

From Figure4B, tensile strength continues to increase subject to CHW content ≤ 20 %. At CHW content > 20 % the tensile strength either decreases or there is no significant increase. Similarly, the Young’s modulus increases up to between 20 and 25 % CHW, after which it decreases. There is a continuous decrease in strain as CHW increases. In conclusion the tensile strength and

Young modulus increases subject to CHW < 25 % content.

PAA composites have shown better mechanical properties compared with the neat polymer. Faturechi *et al*, [68] investigated the linear elastic and nonlinear hyperelastic mechanical properties of alkaline processed gelatine hydrogels at various PAA content for tissue engineering applications. The result shows that the addition of 10 wt % PAA in Gel hydrogels increases the modulus and maximum tensile strength. At PAA > 10 wt % contents a weaker mechanical strength and lower nonlinear behaviour of composite hydrogel was observed. Figure5 shows the graphical representation of their result.

Similarly, Faghihi *et al*, [69] investigated the linear and nonlinear mechanical behaviour of graphene oxide/poly(acrylic acid)/gelatine (GO/PAA/Gel) composite hydrogels having different graphene oxide nanosheet (GONS). Irrespective of the GONS content, the hydrogels showed a near linear mechanical behaviour. The hydrogels with relatively lower content of GONS (<0.3 wt %) have enhanced mechanical properties compared with those with higher content of GONS (N>0.3 wt %). On addition of 0.3 wt % GONS, both tensile strength and strain of GO (0.0 wt %)/PAA/Gel increased by 71 % and 83 % respectively. The increase was attributed to hydrogen and possible covalent bonds between GONS and polymer chains.

Table 3: Mechanical properties of CHW filled natural rubber using data obtained from tensile tests: Tensile modulus (E), conventional rubber modulus (E_{100%}), stress at break (σ_B), and elongation at break (ε_B) [48].

Sample	Processing Technique	E (MPa)	E _{100%} (MPa)	σ _B (MPa)		ε _B (%)	
				True	nominal	True	nominal
NRev	Water evaporation	1.7	1.8	25.5	2.1	248	1099
NCH2ev		5.6	2.5	21.7	2.6	213	740
NCH5ev	water evaporation	17.8	5	25	3.7	192	583
NCH10ev		-	-	-	-	-	-
NCH15ev		127	17	29.7	7.9	133	276
NCH20ev		229	23.9	9.8	126	126	252
PNRev		1.6	1.6	395	11.8	351	3252
PCH2ev		2.5	2.1	388	13.7	334	2728
PCH5ev		-	-	-	-	-	-
PCH10ev		25.9	6.8	178	10.5	283	1590
PCH15ev		52.8	11.4	128	9.4	261	1265
PCH20ev		111	15.3	20.5	5.6	130	268
NRL	Freeze drying and hot-pressing	1.1	0.71	41.6	3.4	252	1137
NCH2L		1.4	0.99	5.9	1	176	483
NCH5L		2.1	1.7	15.5	2.7	175	475
NCH10L		4.6	3.4	21.7	4.4	160	397
NCH15L		8.7	7.2	62.7	10.5	179	498
NCH20L		10.2	9.4	83.9	14.4	176	482

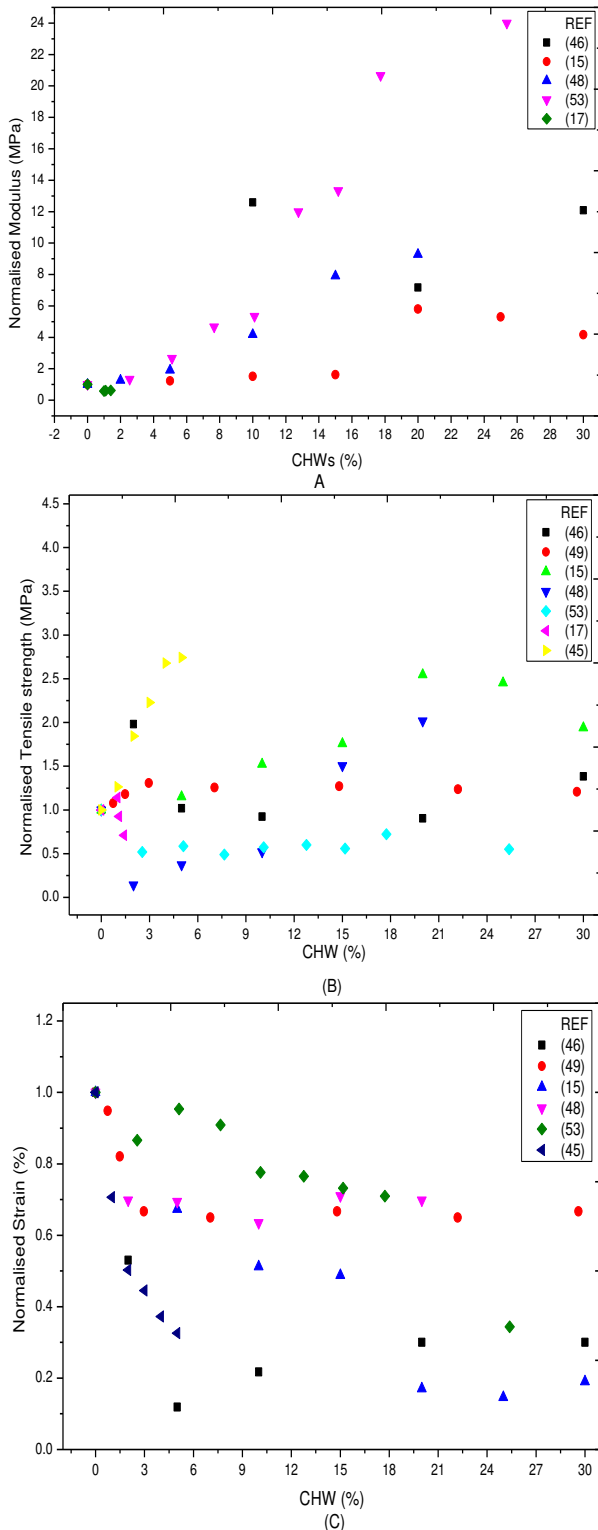


Figure 4- Normalised (against matrix) properties of CHW reinforced composites at different percentage loading of CHW (A) Modulus, (B) tensile strength and (C) strain at break.

The lower content of GONS (0.3 wt %) was well dispersed in the polymer matrix which would enhance the intermolecular interactions between the matrix and the filler. At higher amount of GONS (0.5 wt %) large agglomeration may form there by weakening the

interfacial interactions. Figure 6 shows the the tensile strength and failure strain of the composites.

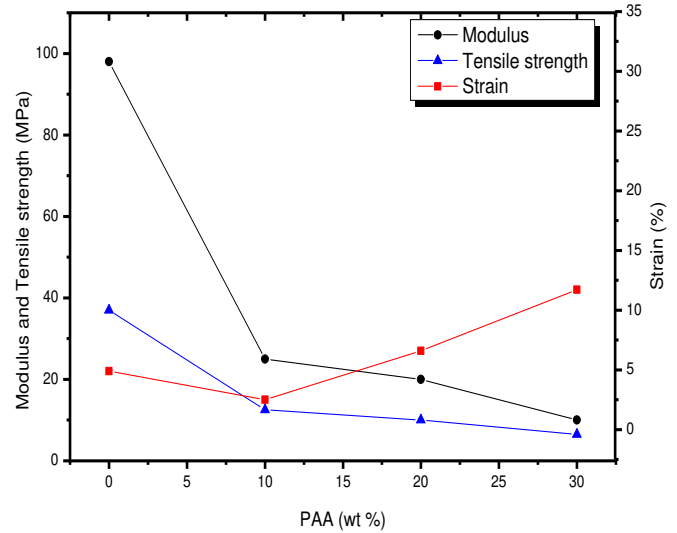


Figure5- Mechanical properties of gelatine gel reinforced PAA. [68](Modified).

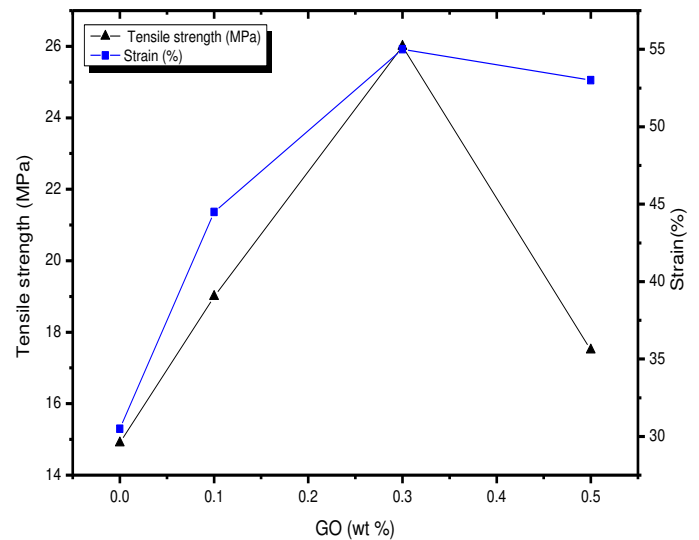


Figure6- Tensile strength (a) and tensile strain (b) of composite hydrogels having different graphene oxide nanosheet (GONS) content [69] (Modified).

Ironically cross-linked polyelectrolyte complex (PEC) membranes of cationic chitosan and anionic poly(acrylic acid) were synthesized by Smitha *et al.* [70]. Composites of chitosan (CS) and PAAc were made at different weight ratios: 90/10, 80/20, 70/30, 60/40, 50/50 and 25/75 (CS/PAAc). The membranes were post-treated to enable the formation of the polyelectrolyte complex. The 50/50 composite exhibited low methanol permeability ($3.9 \times 10^{-8} \text{ cm}^2/\text{s}$), the best physicommechanical properties and comparatively high proton conductivity ($0.038 \text{ S}\cdot\text{cm}^{-1}$). The tensile strength and elongation at break and other properties of the composites in the dry state are given in Table 5. From the table, increase in the CS weight causes

an increase in the tensile strength and a reduction in the elongation at break of the composite membranes. The enhancement was attributed to the ionic-cross-linking of the polyelectrolyte membranes.

4. THERMAL PROPERTIES

Engineering materials are subjected to changes in temperature leading to thermal expansion, melting, freezing, glass transition temperature etc. Their behaviour under these conditions determines their potential applications. Therefore the study of the thermal properties of hybrid biomaterial composites is very important. Different composites of CHW reinforced poly (vinyl alcohol) were tested for thermal properties [52, 63]. The glass transition temperatures of the composite films were found to increase with increase in CHW content, while the melting temperatures tended to shift towards lower values. As a mark of thermal stability, thermogravimetric loss in weight upon heating decreased

as CHW increased and the value was found to be between those of the pure components. Notwithstanding, improvement in thermal stability is subject to having a CHW content less than 10 % [46, 49, 50].

Some research reports that the onset decomposition temperature increased with increase in CHW content [16]. Composite films prepared by casting and evaporation from poly(styrene-co-butyl acrylate) and poly(S-co-BuA) showed an increase in storage modulus when the temperature was greater than the glass transition temperature of the matrix. At filler loadings less than 10 wt. % the mechanical properties showed no improvement but increased to ~2 GPa (from 1 GPa for pure matrix) at 20 wt. % while the addition of CHW did not affect the glass transition temperature of the composites [55]. Feng *et al.*, [17] used dynamic mechanical analysis (DMA) to determine the α -relaxation temperature of CHW-g- polycaprolactone (PCL) copolymer nanocomposites.

Table 5- Sorption characteristics, tensile strength and elongation, ion exchange capacity and methanol permeability of composites [70](Modified).

membrane	% water uptake	% methanol uptake	Tensile strength (MPa)	% elongation at break	ion exchange capacity (mequiv/g)	Methanol permeability ^a (10 ⁻⁸ cm ² /s)
PAAc	B	0.08	8.78	8	0.86	D
PEC25/75	54	0.63	21.81	7.3	1.24	4.8
PEC50/50	26	1.06	26.10	4	1.06	3.9
PEC60/40	35	1.2	24.11	5	1.18	4.1
PEC70/30	42	1.28	23.91	7	1.22	4.6
PEC80/20	80	1.29	22.81	7.5	1.16	8.2
PEC90/10	139	1.41	20.29	8	0.94	8.7
CS	c	0.39	18.07	4	0.91	D

^ameasurements carried out at 30 °C, ^bcompletely soluble, ^chighly swollen in water, ^dnot measurable.

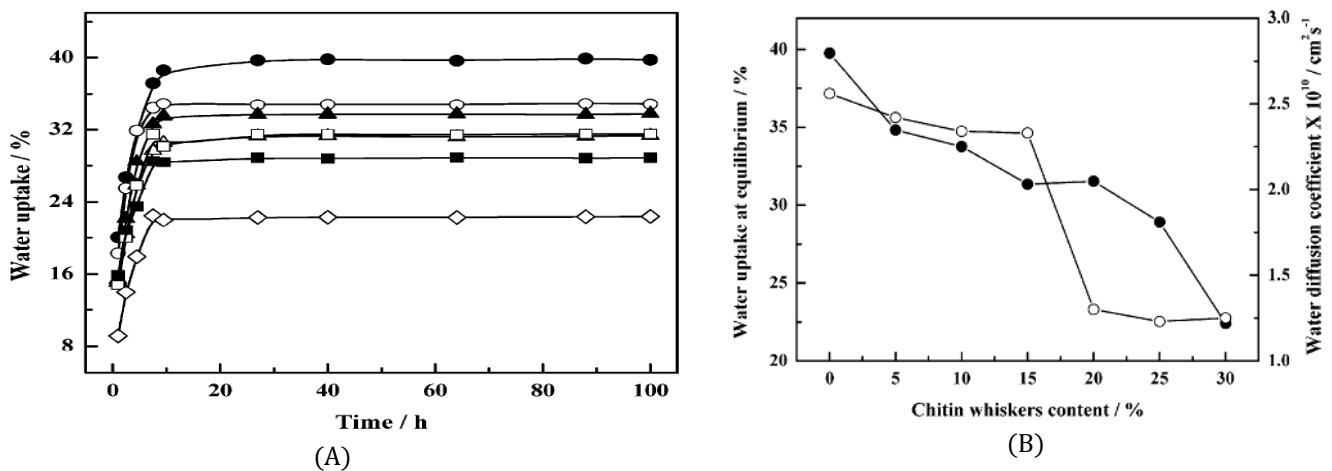


Figure 7: Water uptake at equilibrium of glycerol soy protein isolate sheet (●) and SPI/CHW composites of SPI-5(o), SPI-10 (▲), SPI-15 (Δ), SPI- 20 (□), SPI-25 (▪) and SPI-30 (◊) composite conditioned at 98 RH% as a function of time (A) and water uptake at equilibrium (●) and water diffusion coefficient (o) as a function of chitin whiskers content for composites conditioned at 98 % RH(B) [15].

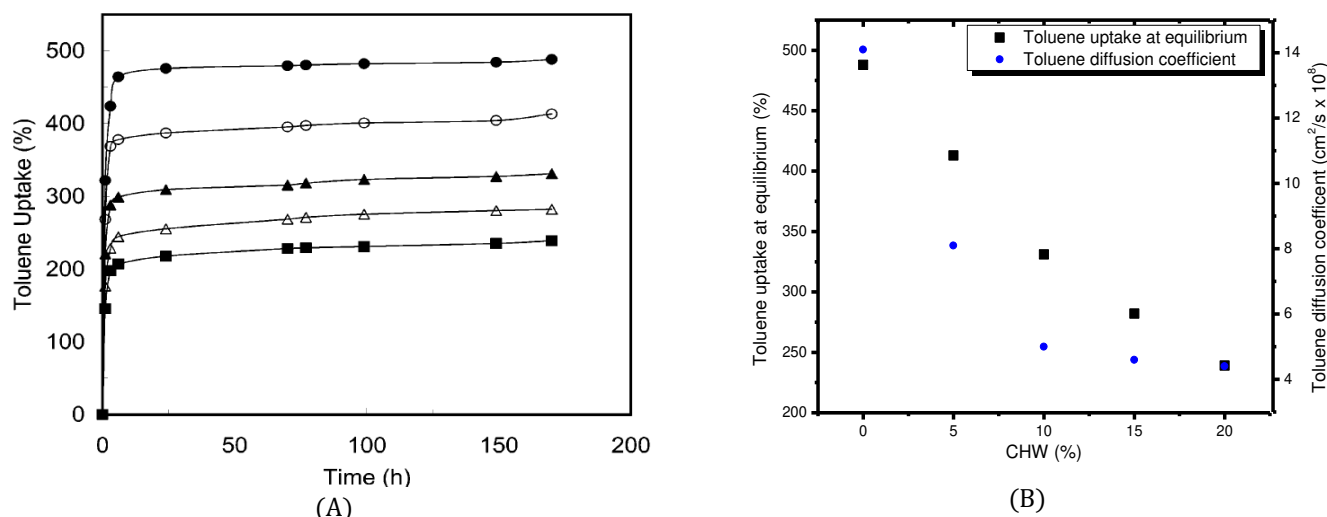


Figure 8: - Variation in toluene uptake of PNRev (●), PCH5ev (○) PCH10ev (▲), PCH15ev (Δ), and PCH20ev (□) samples as a function of time at room temperature (25 °C)(A) and toluene uptake at equilibrium and toluene diffusion coefficients in CHW/Vulcanized NR Composites immersed in toluene (B). [47]

The results showed an increase in the glass transition temperature (from -32 to -39.6 °C) as CHW content increased (from 0.99 to 1.141 %) an indication of a gradual decrease in the segmental mobility of PCL while the melting temperature and enthalpy of fusion remained relatively the same (~56 °C and ~65 J/g respectively) within the CHW content (0.99 to 1.141 %) range.

5. OTHER PROPERTIES OF CHITIN

Austin, [71] was the first to publish an extensive study on chitin solubility. This work determined solubility parameters (δ) (a numerical value based on the cohesive energy densities) for different solvents in lithium Chloride (LiCl). Solubility parameters of 10.8 for dimethyl acetamide and 11.3 for N-methyl pyrrolidinone were reported. Due to its intermolecular hydrogen bonding chitin is insoluble in most organic solvents but readily soluble in concentrated HCl, H₂SO₄ and H₃PO₄ and few other organic acid such as formic, dichloroacetic and trichloroacetic acids and strong polar solvents such as LiCl, dimethylacetamide (DMAc) and N-methyl-2-pyrrolidone (NMP) [71, 72]. The dissolution of chitin in mineral acid is accompanied by degradation. To achieve the desired solubility the degree of deacetylation and the concentration ratio between acid and chitosan must be taken into consideration. Full solubility is achieved at ≥ 85 % deacetylation [73]. A reproducible method for obtaining water-soluble chitin and the relationship between solubility and degree of deacetylation of chitin were studied [74]. The regenerated chitin, isolated at low temperature from an alkali chitin solution left at 25 °C for 48 to 77 hours, showed a very good solubility in water at 0 °C. Kubota

and Eguchi, [75] showed that alkali-chitin exhibited a lower critical solubility temperature of about 30°C.

Water swelling properties of CHW reinforced soy protein isolate (SPI) composites (using glycerol as plasticizer) were investigated by Lu *et al.*, [15]. At 25 °C the water uptake of SPI film was ~40 % that of CHW/SPI decreased as CHW content increased. For example, 20, 25 and 30 wt % CHW content had ~29 %, ~28 % and ~23 % water uptake suggesting an increase of water resistance as CHW content increased. Figure 7 shows the water uptake at equilibrium of CHW reinforced soy protein isolate (SPI) composites and the time taken to obtain maximum water uptake.

Similar results were obtained when α -chitin whisker-reinforced poly (vinyl alcohol) composite films with or without heat treatment were investigated by Sriupayo *et al.*, [50]. The uptake of toluene (Figure 8 A and B) by vulcanized natural rubber/CHW composites was investigated by Nair and Dufresne, [47]. There was an initial rapid uptake of toluene by all composites within 5h and there was a decrease in sorption rate. Neat vulcanized natural rubber uptake of toluene was 488 %, which decreased to 413, 331, 282 and 239 % at 5, 10, 15 and 20 % loading of CHW. The diffusion coefficient of toluene of neat VNR ($14.1 \times 10^{-8} \text{ cm}^2 \text{ s}^{-1}$) decreased with increasing loading of CHW to $4.4 \times 10^{-8} \text{ cm}^2 \text{ s}^{-1}$ at 20 % loading. Nair and Dufresne attributed this to the increase in stiffness of the chitin network and interactions between VNR and CHW with increased CHW loading.

6. CaCO₃/CHW HYBRID COMPOSITES

Biom mineralization is a process in which living organisms produce inorganic/organic hybrids. The production of this hybrid under different conditions has received attention in recent years. The essence of producing this

biomineral is to have a complex but environmentally friendly morphology and as well as better mechanical properties. However the understanding of these hybrids' development processes is still a subject of research. Biominerals, like the nacre of shell, have high optical and mechanical properties; these properties are closely related to their hierarchically- ordered structures [76]. It has been reported that the exoskeleton of the crayfish is composed of about 50:50 wt % of CaCO₃ and organic macromolecules such as chitin and proteins. Calcium carbonate polymorphs (calcite, vaterite or aragonite) are some of the mineral phases formed when an insoluble polymer with the help of a soluble agent of polymeric anions is induced on a substrate [77, 78]. The production of these polymorphs (calcite, aragonite, and vaterite) might be influenced by the conditions of precipitation and the presence of impurities in an aqueous solution. Of the three polymorphs, calcite is the most thermodynamically stable under ambient conditions while the least stable is vaterite. A variety of CaCO₃

crystal/chitin or chitosan based hybrid materials have been reported, some will be reviewed here. Oriented chitin films as templates were used for CaCO₃ crystallization in the presence of poly(acrylic acid), (PAA) [79]. At about 10 hours after immersing the films in the crystallization solution (ammonium carbonate vapour was slowly diffused into aqueous solution of calcium chloride) at a temperature of 5 °C small rods of about 8 μm in length of CaCO₃ crystals were observed. The rod-like CaCO₃ crystals (Figure9) increase in length to 80 μm after 50 hours of immersion. The diameter of the rod was between 10 and 30 μm. At 30 °C similar crystallization behaviour was observed. The calcite polymorph was confirmed by FTIR. Calcium carbonate was precipitated on three insoluble polymer matrices (chitin, cellulose and chitosan). Their derivatives (OH, and NH₂ were synthesized by the acetylation of hydroxyl groups following the *N*-phthaloylation of the amino group of chitosan and the acetylation of chitin respectively to prevent proton donation (see Figure10) in the presence of PAA [77].

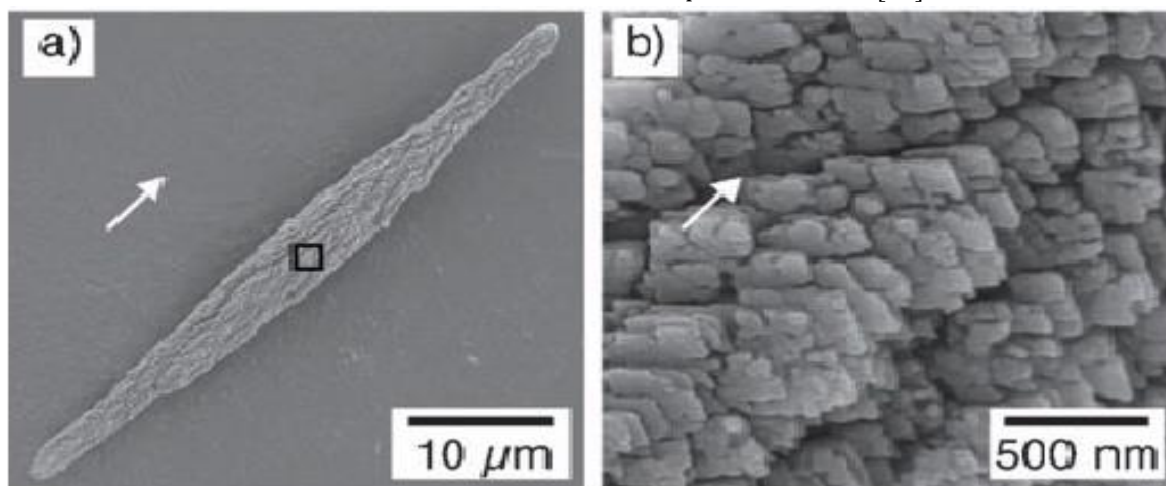


Figure9 - SEM image of the rod shape of the isolated crystal (a) and magnified image of the square area on the crystal surface in (b) [79].

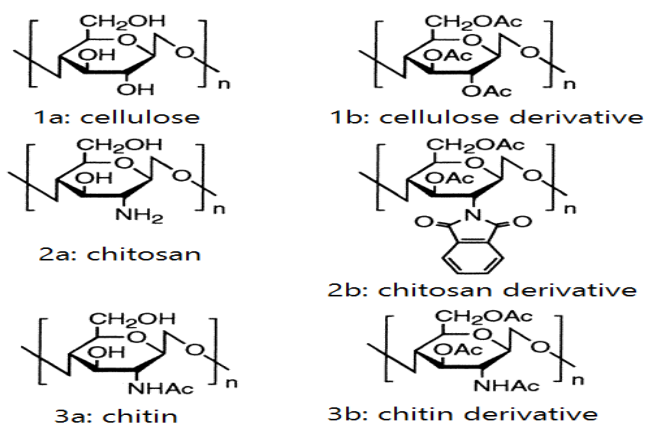


Figure 10: Structures of polymer matrixes and soluble additives [77].

The crystal growth resulted in the formation of CaCO₃ thin-film crystals of about 0.8 μm in thickness. The crystallite size as measured by X-ray was ~30 nm. No precipitation was observed for the crystallization on the insoluble polymer matrices derivatives possessing no proton-donating group (cellulose and chitin), even in the presence of PAA, but rhombohedral calcite crystals were obtained in the absence of the acidic polymer PAA. Thin films grown on chitosan consisted of mainly vaterite and those of cellulose and chitin consist of only calcite in the absence of PAA, while those grown on chitosan mainly consist of vaterite in the presence of the PAA. Polymorphs formed on the thin films developed on chitin and cellulose was independent of the concentration of PAA, where as those of chitosan were dependent. A

higher molecular weight of PAA led to less stable polymorphs.

The morphology and the crystal structure of films of calcium carbonate formed on chitosan (annealed at 100 and 260 °C) in the presence of PAA with different molecular weights at various temperatures was investigated by Kotachi *et al.*, [80] (Figure11). Granular particles were occasionally observed within the films. Irrespective of the crystal structure obtained the planar and circular appearances of the films were basically the same under all the conditions.

The diameter (Figure12) of circular chitosan films annealed at 260 °C was relatively larger than those of

100 °C baked chitosan. XRD patterns of the films deposited on 260 °C-baked chitosan in the presence of PAA (Mws = 2,000 and 250,000) at various temperatures showed the dominance of calcite peaks at lower temperature (10 °C) while aragonite dominated at higher temperature (35 °C). Weak X-rays diffraction signals for vaterite were also observed with more found on PAA, (Mw = 250,000, 10 °C and 35 °C) and non on PAA, Mw = 2,000, 10 °C. Selective production of the various polymorphs was achieved by the variation of the molecular weight of PAA, and the temperature of the solution

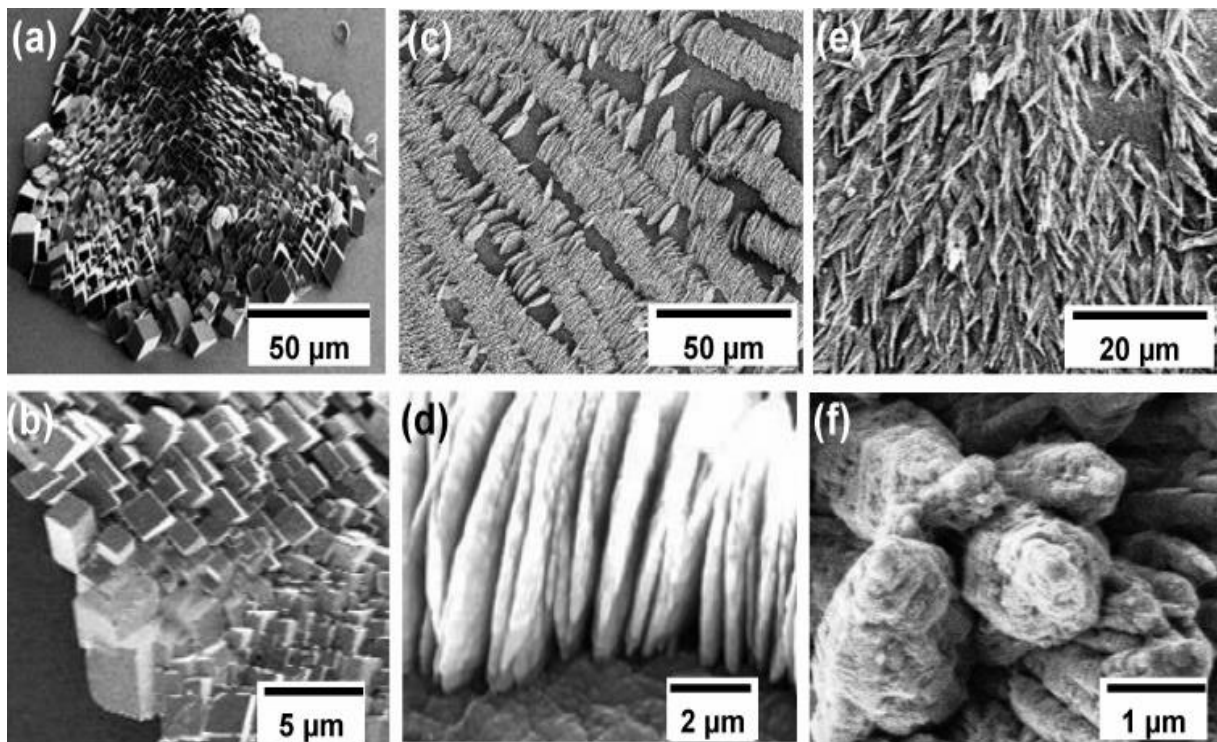


Figure11 SEM images of the development of the planar films into microarrays by the subsequent overgrowth without any additives for visual determination of the polymorphs: (a, b) calcite; (c, d) vaterite; (e, f) aragonite [80].

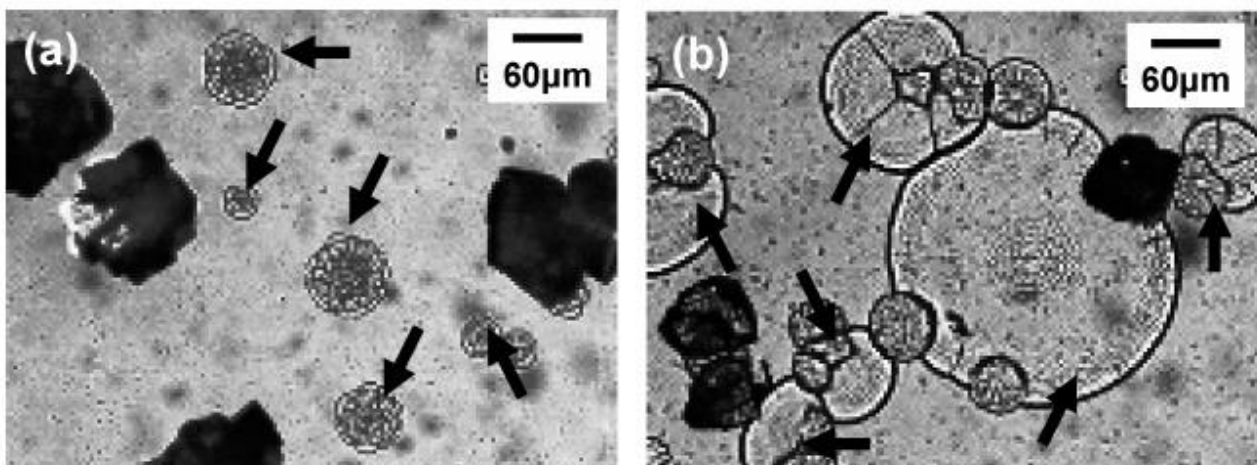


Figure12 - Optical micrographs of calcium carbonate grown at 10 °C with 2.4×10^{-3} wt % PAA250k on 100 °C (a) and 260 °C baked (b) chitosan. Arrows indicate planar films. Black shadows are granular particles [80].

Yamamoto *et al.*, [78] used 5 wt % of CHW prepared by acid hydrolysis to prepare CaCO₃/chitin-whisker hybrids, when the suspension was converted to a gel by exposing it to ammonium carbonate vapour. The chitin gel was used as a template and CaCO₃ crystals were allowed to form for 30 days. Formation of spherical CaCO₃ crystals started after 3 days without the existence of amorphous CaCO₃. The crystals gradually increased in size until the gel matrix was filled with CaCO₃ crystals after 30 days. Scanning electron microscopy image of the hybrid showed the presence of CaCO₃ crystals in the gel matrix while Raman spectra, FTIR and XRD revealed calcite crystals.

7. CONCLUSIONS

Chitin is one of the biomaterials that is abundant and cheap. The availability of this material made the research interesting both to the industry and researchers. Been cheap and abundant, researchers are able to generate products and materials add value to humanity. Chitin especially in the whiskers form can add value to humanity when properly process. This article was aimed at reviewing the sources of chitin, its extraction, and the mechanical and thermal properties of CHW reinforced composites were also reviewed. The effect of CaCO₃ growth on CHW/Polymer composites was also investigated. Depending on the source, three polymorphic forms of chitin are; namely α , β and γ chitins are found in nature. The most common and extensively investigated is α -chitin because is stable and widely found in living organisms. The tensile properties of composites are improved by the addition of CHW. A clear trend of decrease in strain at break as CHW increases was established. Authors agreed that the increase in Young's modulus and tensile strength up to a certain percentage CHW loading is an indication of strong interactions between whiskers and the matrix. Above this percentage CHW loading the tensile strength either decreases or there is no significant increase. The same trend was observed for the Young's modulus, while the strain continues to decrease as CHW increases.

REFERENCES

- [1] Aldousiri B, Dhakal HN, Onuh S, Zhang ZY, Bennett N and Richardson MOW. Effect of layered silicate reinforcement on the structure and mechanical properties of spent polyamide-12 nanocomposites. *Composites Part B: Engineering*; 43:1363-1367. (2012).
- [2] Ha S, Rhee K, Park SJ and Lee JH. Temperature effects on the fracture behaviour and tensile properties of silane-treated clay/epoxy nanocomposites. *Composites Part B: Engineering*; 41:602-607. (2010).
- [3] Toro P, Quijada R, Arias J and Yazdani-Pedram M. Mechanical and Morphological Studies of Poly (propylene)-Filled Eggshell Composites. *Macromolecular Materials and Engineering*; 292:1027-1034. (2007).
- [4] Masoodi R, El-Hajjar RF, Pillai KM and Sabo R. Mechanical characterization of cellulose nanofiber and bio-based epoxy composite. *Materials and Design*; 36:570-576. (2012).
- [6] Campanella A, La Scala J and Wool R. Fatty Acid-Based Comonomers as Styrene Replacements in Soybean and Castor Oil-Based Thermosetting. *Journal of Applied Polymer Science*; 119:1000-1010. (2011).
- [7] Erman E, Stanzione J, Reno K, Wool R and Miller M. Pyrolyzed Chicken Feather Fibers for Biobased Composite Reinforcement. *Journal of Applied Polymer Science*; 128:983-989. (2013).
- [8] Muzzarelli RAA., Ed. *Chitin nanofibrils. In: Chitin and Chitosan, Opportunities and Challenges*, New Age International, New Delhi, India (2005).
- [9] Khor E and Lim LY. Implantable applications of chitin and chitosan. *Biomaterials* ; 24: 2339-2349. (2003)
- [10] Li J, Revol J. F. Marchessault RH. Effect of degree of deacetylation of chitin on the properties of chitin crystallites. *Journal of Applied Polymer Science*; 65:373-380. (1997).
- [11] Das S and Ganesh EA. Extraction of Chitin from Trash Crabs (*Podophthalmus vigil*) by an Eccentric Method. *Journal of Biological Sciences*; 2: 72-75. (2010).
- [12] Morin A and Dufresne A. Nanocomposites of chitin whiskers from *Riftia* tubes and poly (caprolactone). *Macromolecules*; 35:2190-2199. (2002).
- [13] Aranaz I, Mengibar M, Harris R, Panos I, Miralles B, Acosta N, Galed G and Heras A. Functional characteristics of Chitin and Chiosan. *Current Chemical Biology*; 3:203-230. (2009).
- [14] Wongpanit P, Sanchavanakit N, Pavasant P, Bunaprasert T, Tabata Y and Rujiravanit R. Preparation and characterization of chitin whisker-reinforced silk fibroin nanocomposite sponges. *European Polymer Journal*; 43: 4123-4135. (2007).
- [15] Xu W, Mulhern PJ, Blackford BL, Jericho MH and Templeton I. A new atomic force microscopy technique for the measurement of the elastic properties of biological materials. *Scanning Microscopy*; 8 :499-506. (1994).
- [16] Lu Y, Weng L and Zhang L. Morphology and properties of soy protein isolate thermoplastics reinforced with chitin whiskers. *Biomacromolecules*, 5: 1046-1051. (2004).
- [17] Wu X, Torres F. G., Vilaseca F and Peijs TJ. Influence of the Processing Conditions on the Mechanical Properties of Chitin Whisker Reinforced Poly (caprolactone) Nanocomposites. *Journal of Biobased Materials BioEnergy*, 1:341-350. (2007).
- [18] Feng L, Zhou Z, Dufresne A, Huang J, Wei M and An L. Structure and Properties of New Thermo foaming Bionanocomposites Based on Chitin Whisker-Graft-Polycaprolactone. *Journal of Applied Polymer Science* (2009); 112:2830-2837.
- [19] Rhazi M, Desbrieres J, Tolaimate A, Alagui A and Vottero P. Investigation of different natural sources of chitin:

- influence of the source and deacetylation process on the physicochemical characteristics of chitosan. *Polymer International*; 49:337-344. (2000).
- [20] Ifuku S, Nogi M, Yoshioka M, Morimoto M, Yano H and Saimoto H. Fibrillation of dried chitin into 10-20 nm nanofibers by a simple grinding method under acidic conditions. *Carbohydrate Polymers* 81:134-139. (2010;)
- [21] Minke R and Blackwell J. The structure of α -chitin. *Journal of Molecular Biology*; 120:167-181. (1978).
- [22] Mathur N. K, and Narang C. K. Chitin and Chitosan, Versatile Polysaccharides from Marine Animals. *Journal of Chemical Education*: 67:938-942 (1990).
- [23] Cárdenas G, Cabrera G, Taboada E, Miranda SP. Chitin characterization by SEM, FTIR, XRD, and ¹³C cross polarization/mass angle spinning NMR. *Journal of Applied Polymer Science* (2004); 93:1876-1885.
- [24] Waldeck J, Daum G, Bisping B, and Meinhardt F. Isolation and molecular characterization of chitinase-deficient *Bacillus licheniformis* strains capable of deproteinization of shrimp shell waste to obtain highly viscous chitin. *Applied and Environmental Microbiology*, 72:7879-7885. (2006).
- [25] Kaur S and Dhillon GS. Recent trends in biological extraction of chitin from marine shell wastes: a review. *Critical Reviews in Biotechnology*, 1:1-18. (2013).
- [26] Kaur S, Dhillon GS. The versatile biopolymer chitosan: potential sources, evaluation of extraction methods and applications. *Critical Reviews in Microbiology*; 40: 155-175. (2014).
- [27] Poulicek, M and C. Jeuniaux. Chitin biodegradation in marine environments: An experimental approach. *Biochemical Systematic and Ecology*; 19:385-394. (1991).
- [28] Cauchie HM. Chitin production by arthropods in the hydrosphere. *Hydrobiologia* 470: 63-96. (2002);
- [29] Tröger C and Niranjana K. Sustainable Chitin extraction and Chitosan modification for application in the food industry. *International conference on Food innovation*, (2010).
- [30] Synowiecki J, Al-Khateeb NA. The recovery of protein hydrolysate during enzymatic isolation of chitin from shrimp *Crangon crangon* processing discards. *Food Chemistry* 68:147-152. (2000).
- [31] Watthanaphanit A, Supaphol P, Tamura H, Takura S and Rujiravanit R. Fabrication, structure and properties of Chitin Whiskers-Reinforced Alginate Nanocomposite Fibers. *Journal of Applied Polymer Science*; 110:890-899. (2008).
- [32] Al Sagheer F. A, Al-Sughayer, Muslim S and Elsabe MZ. Extraction and characterisation of chitin and chitosan from marine sources in Arabia Gulf. *Carbohydrate Polymers*; 77:410-419. (2009).
- [33] Dhillon G. S., Kaur S, Brar SK, Verma M. Green synthesis approach: extraction of chitosan from fungus mycelia. *Critical Reviews in Biotechnology*; 33:379-403. (2013).
- [34] Percot A, Viton C, Domard A. (2003). Characterization of shrimp shell deproteinization. *Biomacromolecules*, 4:1380-1385. (2003).
- [35] Khanafari A, Marandi, R and Sanatei S. Recovery of chitin and chitosan from shrimp waste by chemical and microbial methods. *Iranian Journal of Environmental Health Science and Engineering*; 5(1):19-24
- [36] Jung WJ, Jo GH, Kuk JH, Kim KY, Park RD. Extraction of chitin from red crab shell waste by cofermentation with *Lactobacillus parasei* subsp. *Tolerans* KCTC-3074 and *Serratiamacrescens* FS-3. *Applied Microbial and Physiology*; 71:234-237. (2006).
- [37] Zeng J, He Y, Li S and Wang Y. Chitin Whiskers: An Overview. *Biomacromolecules*; 13:1-11. (2012).
- [38] Domard AI and Rinadudo M. Preparation and characterization of fully deacetylated chitosan. *Journal of Biological Macromolecules*; 5: 49-52. (1983).
- [39] Mima S, Miya M, Iwamoto R and Yoshikawa S. Highly Deacetylated Chitosan and Its Properties. *Journal of Applied Polymer Science*; 28: 1909-1917. (1983).
- [40] Pelletier A, Lemire I, Sygusch J, Chornet E and Overend RP. Chitin/chitosan transformation by thermo-mechanochemical treatment including characterization by enzymatic depolymerisation. *Biotechnology and Bioengineering* 36:310-315. (1990);
- [41] Majeti NV and Kumar R. A Review of chitin and chitosan applications. *Reactive and Functional Polymers*; 46:1-27 (2000).
- [42] Favier V, Chanzy H and Cavaille JY. Polymer Nanocomposites Reinforced cellulose whiskers. *Macromolecules* 28-6365-6367. (1995);
- [43] Dufresne A, Kelerhals MB and Witholt B. Transcrystallization in Mcl-PHAs/Cellulose Whiskers Composites. *Macromolecules*; 32:7396-7401. (1999).
- [44] Marchessault RH, Morehead RR and Walter NM. Liquid Crystal Systems from Fibrillar Polysaccharides. *Nature*. ; 184:632-633. (1959).
- [45] Revol JF and Marchessault RH. In vitro chiral nematic ordering of chitin crystallites. *International Journal of Biology Macromolecules*; 15:329-335 (1993).
- [46] Chang PR, Jian RJ, Yu JG and Ma XF. Starch-based composites reinforced with novel chitin nanoparticles. *Carbohydrate Polymer*; 80:420-425. (2010).
- [47] Hariraksapitak, P and Supaphol, P. Preparation and Properties of α -Chitin-Whisker-Reinforced Hyaluronan-Gelatin Nanocomposite Scaffolds. *Journal Of Applied Polymer Science* 117: 3406-3418. (2010);
- [48] Nair KG and Dufresne A. Crab shell chitin whisker reinforced natural rubber nanocomposites. 1. Processing and swelling behaviour. *Biomacromolecules A*; 4:657-665. (2003).
- [49] Nair KG and Dufresne A. Crab shell chitin whisker reinforced natural rubber nanocomposites. 2. Mechanical behaviour. *Biomacromolecules B*; 4: 666-674. (2003).
- [50] Sriupayo J, Supaphol P, Blackwell J and Rujiravanit R. Preparation and characterization of α -chitin whisker-reinforced chitosan nanocomposite films with or without heat treatment. *Carbohydrate Polymer A*; 62: 130-136. (2005).
- [51] Sriupayo J, Supaphol P, Blackwell J and Rujiravanit R. Preparation and characterization of α -chitin whisker-reinforced poly(vinyl alcohol) nanocomposite films with or without heat treatment. *Polymer B*; 46: 5637-5644, (2005).

- [52] Goodrich JD and Winter WT. α -Chitin Nanocrystals Prepared from shrimp shells and their specific surface area measurement. *Biomacromolecules*; 8:252-257. (2007).
- [53] Junkasem J, Rujiravanit R, Grady BP and Supaphol P. X-ray diffraction and dynamic mechanical analyses of α -chitin whisker-reinforced poly(vinyl alcohol) nanocomposite nanofibers. *Polymer International*; 59:85-91. (2010).
- [54] Junkasem J, Rujiravanit R and Supaphol P. Fabrication of α -chitin whisker-reinforced poly (vinyl alcohol) nanocomposite nanofibers by electrospinning. *Nanotechnology* 17:4519-4528. (2006);
- [55] Phongying S, Aiba S and Chirachanchai S. Direct chitosan nanoscaffold formation via chitin whiskers. *Polymer* 48:393-400. (2007).
- [56] Paillet M and Dufresne A. Chitin whisker reinforced thermoplastic nanocomposites. *Macromolecules*; 34: 6527-6530, (2001).
- [57] Ifuku S, Nogi M, Nogi M, Abe K, Yoshioka M, Morimoto M, Saimoto H and Yano H. Simple preparation method of chitin nanofibers with a uniform width of 10–20 nm from prawn shell under neutral conditions. *Carbohydrate Polymer*; 84:762-764. (2011).
- [58] Habibi Y, Lucia LA, and Rojas OJ. Cellulose nanocrystals: chemistry, self-assembly, and application. *Chemical Review*; 110: 3479-3500. (2010).
- [59] Saito Y, Putaux JL, Okano T, Gaill F and Chanzy H. Structural aspects of the swelling of β -chitin in HCl and its conversion into α -chitin. *Macromolecules*; 30:3867-3873. (1997).
- [60] Clark GL and Smith AF. X-ray diffraction studies of chitin, chitosan and derivatives. *Journal of Physical Chemistry*; 40:863-879. (1936).
- [61] Fan YM, Saito T and Isogai A. Chitin nanocrystals prepared by Tempo-Mediated oxidation of α -chitin. *Biomacromolecules* 9:192-198. (2008);
- [62] Montanari S, Rountani M, Heux L and Vignon MR. Topochemistry of carboxylated cellulose nanocrystals resulting from tempo-mediated oxidation. *Macromolecules*; 38:1665-1671, (2005).
- [63] Inaba H, Hoshizawa M, Fujiwara A, Matsumura Y and Mori T. Textural Properties Of Starch Gels Filled With Collagen and Chitin. *Journal of Texture Studies*; 26:577-586. (1995).
- [64] Peesan M, Rujiravanit R, and Supaphol P. Characteristics of beta-chitin/poly (vinyl alcohol) blend films. *Polymer Testing*; 22:381-387. (2003).
- [65] He C and Ma B. The spinning, Structure, and properties of Cellulose/Chitin blend filaments through HWM method. *Polymer Advanced Technology*; 21:496-505. (2010).
- [66] Zhang L, Guo J and Du Y. Morphology and properties of cellulose/chitin blends membranes from NaOH/Thiourea aqueous solution. *Journal of Applied Polymer Science* 86:2025-2032. (2002).
- [67] Yusof NL, Lim LY and Khor E. Flexible chitin films: structural studies. *Carbohydrate Research*; 339:2701-2711. (2004).
- [68] Azevedo MC and Reis RL. Development and properties of polycaprolactone / hydroxyapatite composite biomaterials. *Journal of Materials Science: Materials in Medicine*; 14:103-107. (2003)
- [69] Faturechi R, Karimi A, Hashemi A, Yousefi H, Navidbakhsh M. Influence of poly(acrylic acid) on the mechanical properties of composite hydrogels. *Advances in Polymer Technology*; 33:21487-21493. (2014).
- [70] Faghihi S, Karimi A, Jamadi M, Imani R and Salarian R. Graphene oxide / poly (acrylic acid) / gelatin nanocomposite hydrogel: Experimental and numerical validation of hyperelastic model. *Material Science and Engineering: C* 38:299-305. (2004);
- [71] Smitha B, Sridhar S and Akhan AA. Polyelectrolyte Complexes of Chitosan and Poly(acrylic acid) As Proton Exchange Membranes for Fuel Cells. *Macromolecules*; 37:2233-2239. (2004).
- [72] Austin PR, *Chitin solvents and solubility parameters, in Chitin and Chitosan and Related Enzymes*, ed. by Zikakis JP. Academic Press, Orlando, FL, pp. 227–237 (1984).
- [73] Rinaudo M. Chitin and chitosan: Properties and applications. *Progress in Polymer Science* 2006; 31: 603-632
- [74] No, HK and Meyers SP. Preparation and Characterization of Chitin and Chitosan: A Review. *Journal of Aquatic Food Product Technology*, 4(2):27-52. (1995).
- [75] Sannan T, Kurita K and Iwakura Y. Studies on Chitin, 2. Effect of Deacetylation on Solubility. *Macromolecular Chemistry and Physics*, 177: 3589-3600. (1976).
- [76] Kubota N and Eguchi Y. Facile preparation of water-soluble N-acetylated chitosan and molecular weight dependence of its water-solubility. *Polymer Journal*; 29:123-127. (1997).
- [77] Suzuki M, Saruwatari K, Kogure T, Yamamoto Y, Nishimura T, Kato T and Nagasawa H. An Acidic matrix protein, Pif, is a key macromolecule for Nacre formation. *Science* 325:1388-1390. (2009);
- [78] Hosoda N and Kato T. Thin-Film Formation of Calcium Carbonate Crystals: Effects of Functional Groups of Matrix Polymers. *Chemistry of Materials*; 13: 688-693. (2001).
- [79] Yamamoto Y, Nishimura T, Saito T and Kato T. CaCO₃/chitin-whisker hybrids: formation of CaCO₃ crystals in chitin-based liquid-crystalline suspension. *Polymer Journal*, 42:583-596. (2010).
- [80] Nishimura T, Ito T, Yamamoto Y, Yoshio M. and Kato, T. Macroscopically ordered polymer/CaCO₃ hybrids prepared by using a liquid-crystalline template. *Angewandte International Edition*; 47:2800-2803. (2008).
- [81] Kotachi A, Miura T and Imai H. Polymorph Control of Calcium Carbonate Films in a Poly (acrylic acid)/Chitosan System. *Crystal Growth and Design*, 6:1635-1641 (2006).