

 Open access • Journal Article • DOI:10.1051/JPHYS:01985004604064900

Radius of gyration of a polyion in salt free polyelectrolyte solutions measured by S. A. N. S. — [Source link](#)

M. Nierlich, François Boué, Alain Lapp, R. Oberthur

Published on: 01 Apr 1985 - Journal De Physique (Société Française de Physique)

Topics: Radius of gyration, Persistence length and Gyration

Related papers:

- [Remarks on polyelectrolyte conformation](#)
- [Small angle neutron scattering by semi-dilute solutions of polyelectrolyte](#)
- [Characteristic lengths and the structure of salt free polyelectrolyte solutions. A small angle neutron scattering study](#)
- [Light scattering by dilute solutions of salt-free polyelectrolytes](#)
- [Electrostatic Persistence Length of a Wormlike Polyelectrolyte](#)

Share this paper:    

View more about this paper here: <https://typeset.io/papers/radius-of-gyration-of-a-polyion-in-salt-free-polyelectrolyte-4fim7pmhaq>



HAL
open science

Radius of gyration of a polyion in salt free polyelectrolyte solutions measured by S. A. N. S.

M. Nierlich, François Boué, A. Lapp, R. Oberthur

► **To cite this version:**

M. Nierlich, François Boué, A. Lapp, R. Oberthur. Radius of gyration of a polyion in salt free polyelectrolyte solutions measured by S. A. N. S.. *Journal de Physique*, 1985, 46 (4), pp.649-655. 10.1051/jphys:01985004604064900 . jpa-00210005

HAL Id: jpa-00210005

<https://hal.archives-ouvertes.fr/jpa-00210005>

Submitted on 1 Jan 1985

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

Classification
 Physics Abstracts
 61.25H — 61.40K

Radius of gyration of a polyion in salt free polyelectrolyte solutions measured by S.A.N.S.

M. Nierlich, F. Boué, A. Lapp

L.L.B., CEN-Saclay (*), 91191 Gif-sur-Yvette Cedex, France

and R. Oberthur

I.L.L., 156 X, Centre de Tri, 38042 Grenoble Cedex, France

(Reçu le 29 mai 1984, révisé le 16 novembre, accepté le 6 décembre 1984)

Résumé. — On a étudié des solutions de polyélectrolytes (NaPSS) en absence de sel ajouté. La diffusion de neutrons aux petits angles a permis de mesurer le rayon de gyration (R_g) du polyion grâce au marquage spécifique (deutération) de chaînes associé à une méthode d'extrapolation qui permettent d'extraire le facteur de forme de la fonction de corrélation totale. En supposant que le modèle de chaîne à longueur de persistance tient compte de la flexibilité locale du polyion, on a extrait des valeurs de la longueur de persistance b_l à partir de R_g : R_g et b_l décroissent quand la concentration en polyions augmente. On distingue deux domaines de concentration : à faible concentration, R_g $c_p^{-1/2}$ et b_l c_p^{-1} et à forte concentration, R_g $c_p^{-1/4}$ et b_l $c_p^{-1/2}$. Le calcul de Le Bret pour la contribution électrostatique à la longueur de persistance décrit bien ces deux régimes.

Abstract. — In this paper measurements of the radius of gyration of a polyion in salt free semi-dilute polyelectrolyte solutions are presented. We have used neutron scattering to extract the form factor of a single polyelectrolyte chain from the total correlation function by using a specific labelling associated with an extrapolation method. Assuming that the wormlike chain model takes into account the local flexibility of the chain due to electrostatic interactions along the chain, we have extracted, from the radii of gyration, values for the persistence length b_l . Both R_g and b_l decrease with increasing polyion concentration, c_p . We can distinguish two concentration régimes : at low concentration, R_g decreases as $c_p^{-1/2}$ and b_l as c_p^{-1} and at high concentration R_g decreases as $c_p^{-1/4}$ and b_l as $c_p^{-1/2}$.

These two régimes for the variation of b_l with c_p are well described by a calculation of Le Bret for the electrostatic contribution to the persistence length of the polyion.

1. Introduction.

In solutions of polyelectrolytes, made from linear flexible polymers, an essential parameter is the polymer chain rigidity which is strongly influenced by the ionic strength and in particular by the polyelectrolyte concentration [1]. Electrostatic repulsions between charges along the chain will affect the local flexibility of the polyelectrolyte and will tend to increase the global size of the polyion. This global size may be estimated by the measurement of the mean square radius of gyration. The aim of this paper is to report such measurements obtained by small angle neutron scattering on salt free polyelectrolyte solutions. The only variable quantity is the concentration of the

polyions, c_p (in moles of monomer units per liter) and we study the variation of the radius of gyration of the polyion with c_p .

In salt free and dilute solution, the polyions are assumed to be stretched by electrostatic repulsion. The concentration c^* (equal to M/R_g^3 where M and R_g are the molecular weight and the radius of gyration of the polyion) which defines the boundary between the dilute and the semi-dilute regimes is very low [2, 3] : it is then difficult to reach the dilute regime using neutron scattering and we work with semi-dilute solutions. In that case, the total monomer correlation function $S_T(q)$ reflects the effect of the internal structure of the polyion $S_1(q)$ as well as the effect of the interchain correlations $S_2(q)$. Neutron scattering is then a privileged tool to observe one polyion among the others [3, 4] : a specific labelling

(*) Laboratoire commun CEA-C.N.R.S.

(deuteration for neutron scattering) associated with an extrapolation method allows these two contributions to be separated. This method was already described in reference [3], and in reference [5] in a detailed manner. Here, we recall it briefly. We work at a fixed concentration of a mixture of deuterated (sodium polystyrene sulfonate : NaPSS_D) and hydrogenated (NaPSS_H) polymer in solution in a mixture of x_D D₂O, $(1 - x_D)$ H₂O, x_D being the mole fraction of D₂O necessary to match the scattering length density of the hydrogenated chains. In that case, the total monomer correlation function is :

$$S_T(q) = Y_D S_1(q) + Y_D^2 S_2(q). \quad (1)$$

Y_D being the monomer fraction of labelled chains. The extrapolation of $S_T(q)/Y_D$ to zero mole fraction of labelled chains, at fixed total monomer concentration c_p of the polyelectrolyte, leads to $S_1(q)$. $S_2(q)$ is given by the slope of these extrapolations. From $S_1(q)$, we can obtain, according to the q range, either the radius of gyration of the polyion or additional conformation parameters [5]. In reference [3], measurements of the radius of gyration of a low molecular weight NaPSS have been reported and for the first time tested the method but the experimental conditions were not adequate : in particular, the mole fraction of D₂O used in this first experiment did not match the hydrogenated polymer. We have now corrected this error and made new experiments with a similar molecular weight of NaPSS over a large range polyion concentration. In addition, assuming the wormlike chain model for the polyelectrolyte chain, we extract, from R_g , a persistence length b_t which reflects the flexibility of the chain at small distances : the variation of b_t with c_p is then obtained.

2. Experiments.

2.1 SAMPLES. — The characteristics of the samples are summarized in table I.

Sodium polystyrene sulfonate has been prepared

by one of us at the C.R.M. in Strasbourg by sulfonation of polystyrene using the method of Vink [6] : this method leads to a fully charged chain. Molecular weight distributions have been measured first by GPC in THF on the neutral polymer [7], then by aqueous GPC on the sulfonated polymer. Their polydispersity is characterized by the ratio M_w/M_n where M_w is the weight average molecular weight and M_n the number average molecular weight. The polydispersities after sulfonation are higher than those of the neutral polymer.

After freeze-drying, chemical analysis shows that some water always remains : the given concentrations are corrected for this amount of residual water. The range of the total concentration c_p extends between 0.0817 M and 0.563 M (1 M = 1 mole/liter).

2.2 DETERMINATION OF x_D . — Solutions are made from a mixture of NaPSS_H and NaPSS_D in a mixture of D₂O and H₂O. The suitable value of x_D for the extinction of the scattering of the hydrogenated chain is 0.485 ± 0.005 . It is obtained by the relation

$$x_D = \frac{\sum \frac{b_i}{V^2} - \tilde{\rho}_{H_2O}}{\tilde{\rho}_{D_2O} - \tilde{\rho}_{H_2O}} \quad (2)$$

where $\sum b_i = 50.89$ fm is the total scattering length of the NaPSS monomer (C₈H₇SO₃Na);

$V_2 = 108.2$ cm³/mole is the partial molar volume of the NaPSS monomer [8];

$\tilde{\rho}_{H_2O} = -0.56 \times 10^{10}$ cm⁻² and $\tilde{\rho}_{D_2O} = 6.36 \times 10^{10}$ cm⁻² are the scattering length densities of light and heavy water at 25 °C. An experimental measurement of x_D has been made for a slightly different polystyrene sulfonate during the experiment reported in reference [5] : the obtained value is 0.487. We have finally chosen for the sample used here the lower value of $x_D = 0.485 \pm 0.05$ which seems more reasonable due to the uncertainty in the degree of sulfonation.

Table I. — Characteristics of the sodium polystyrene sulfonates. The characteristics of hydrogenated and deuterated parent polystyrene used for the sulfonation are described in reference [7].

Origin	Deuterated	Hydrogenated
	C.R.M. Strasbourg	C.R.M. Strasbourg
Polydispersity of parent polystyrene	$\frac{M_w}{M_n} = 1.10 \pm 0.05$	$\frac{M_w}{M_n} = 1.05 \pm 0.05$
Molecular weight of NaPSS	26 000	30 200
Rate of sulfonation	98 %	95 %
Water content after freeze drying (w/w)	12.8 % \pm 3 %	10.9 % \pm 3 %
Polydispersity after sulfonation	1.15	1.13

2.3 NEUTRON MEASUREMENTS. — The S.A.N.S. instrument used is D 11 at the I.L.L. in Grenoble : the sample detector distance was 10.6 m with an incident wavelength of 9.90 Å which gave a q range from 4.43×10^{-3} to $2.27 \times 10^{-2} \text{ \AA}^{-1}$.

2.4 EXTRAPOLATION OF $S_1(q)$ FROM $S_T(q, Y_D)$. — We use formula (1) to plot $S_T(q, Y_D)/Y_D$ as a function of Y_D for each value of q . The curves must appear as straight line which was always the case using four values of Y_D . Representative extrapolations are shown in figure 1 for two values of q and c_p .

3. Measure of the radius of gyration.

The form factor $S_1(q)$ is extracted from the total scattering function $S_T(q)$ using equation (1) : $S_1(q)$ contains all information on the dimension of an isolated polyion in solution.

First, we use the classical method to extract the radius of gyration from the form factor $S_1(q)$, the Zimm plot :

$$S_1^{-1}(q) = 1 + q^2 R_g^2/3. \tag{3}$$

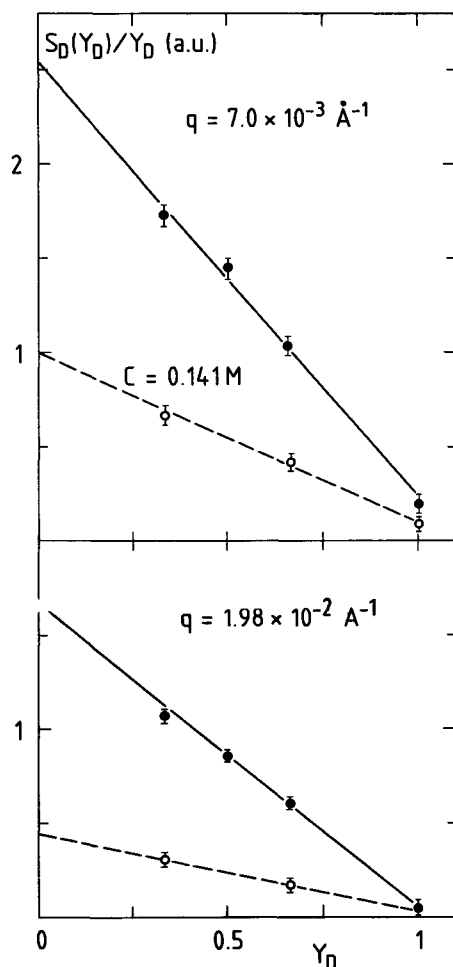


Fig. 1. — Scattering functions $S_D(Y_D, q)/Y_D$ as a function of Y_D for two q values, for $c_p = 0.563 \text{ M}$ (●) and $c_p = 0.141 \text{ M}$ (◐). The extrapolation of the straight line to $Y_D = 0$ yields $S_1(q)$.

The obtained values of the radius of gyration are tabulated in the first column of table II. However, these values of R_g greatly depend on the range over which the extrapolation has been performed : the Zimm plot representation gives a good linearization of the scattering function only for Gaussian coils with a Schulz-distribution of their molecular weight and a polydispersity $M_w/M_n = 2$. If M_w/M_n approaches 1, then more and more deviations occur from linearity, especially if qR_g exceeds 1 [9, 11]. With the obtained values of R_g and the experimental q range, however, qR_g extends between 0.7 and 2.1 for all the studied concentrations : hence, in this case a Zimm plot is not recommended and another plot which takes the conformation of the polyion into account must be used to obtain a better estimate of R_g .

Because the conformation of the polyion which changes with the concentration of polyions is yet unknown, we can consider only the two extreme conformations, a rod at low concentration and a Gaussian coil at high concentration, to extract R_g .

In both cases, for monodisperse or only slightly polydisperse systems, the Berry plot is more suitable for the linearization of the scattering curve in the range $qR_g, 0.7-2$ [9]. $S_1^{-1/2}(q)$ versus q^2 gives a straight line of slope R_g .

$$S_1^{-1/2}(q) = 1 + q^2 R_g^2/6. \tag{4}$$

Figure 2 shows the behaviour of $S_1^{-1/2}(q)$ for all the samples.

We remark that the first five points fall well below the straight line which well fits all the following points. A straight line including these first five points leads to a $R_g > R_{grod} = 93 \text{ \AA}$ (see Table II), which is

Table II. — Radius of gyration obtained from :

- The Zimm plot : $S_1^{-1}(q) = 1 + \frac{q^2 R_g^2}{3}$.
- The Berry plot $S_1(q)^{-1/2} = 1 + \frac{q^2 R_g^2}{6}$.

C M	R_g Å Zimm plot	R_g Å Berry plot
0.0817	94 ± 6	81 ± 5
0.123	77 ± 6	65 ± 5
0.208	62 ± 5	57 ± 3
0.338	61 ± 3	55 ± 4
0.404	63 ± 2	54 ± 3
0.484	55 ± 3	53 ± 3
0.563	56 ± 3	52 ± 3

$R_{grod} = 93 \text{ \AA}$.
 $R_{g\theta} = 34 \text{ \AA}$.

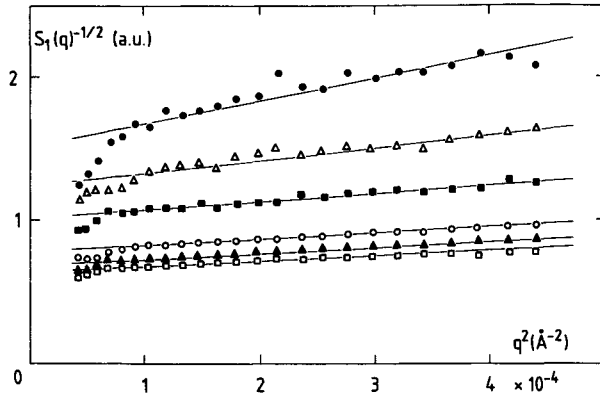


Fig. 2. — Berry plot of $S_1(q)$ for all the samples : ● $c_p = 0.0817$ M; △ $c_p = 0.123$ M; ■ $c_p = 0.208$ M; ○ $c_p = 0.338$ M; ▲ $c_p = 0.404$ M; □ $c_p = 0.484$ M. The units for $S_1(q)$ are arbitrary.

obviously unrealistic. We believe that these points correspond to an overscattering at small angles : this has always been observed in all our polyelectrolytes (see for example Fig. 2 of Ref. [2]). We think that this scattering does not depend on the purity of the solution but mainly on the chemical preparation of the sample : up to now, we did not succeed in eliminating it.

The new radii of gyration are reported in the second column of table II.

We can see in there that :

— The Zimm plot yields higher values and the Berry plot lower values.

— The gap between these two sets of R_g which is large for the lower concentrations (13 % for $c_p = 0.087$) is reduced for the higher concentrations (6 % for $c_p = 0.563$). This is well explained by the decrease of R_g with c_p : at high c_p , R_g is smaller and $(qR_g)_{\max}$ is of the order of 1 and in that case, the results from the two plots, Zimm and Berry, are very similar [9]. Since at high concentrations the two values are equal to within the uncertainty of the two plots and since at low concentrations, the Berry plot fits better the quasi rod conformation, we decide to discuss the Berry plot values.

4. Variation of R_g with c_p .

Figure 3 shows the variation of R_g with the concentration of polyions : it shows a continuous decay as c_p increases. At low concentration, an important decrease of R_g is observed with increasing concentration whereas at high concentration, this decrease is slowed down. To compare these experimental values with the two limiting cases, we can calculate :

— First, the radius of gyration of the totally stretched chain of length $L = Np$ where N and p are the number and the repeat distance of monomers along the chain. We take $R_g = L/\sqrt{12}$ which gives with $p = 2.22$ Å the repeat distance of an isotactic

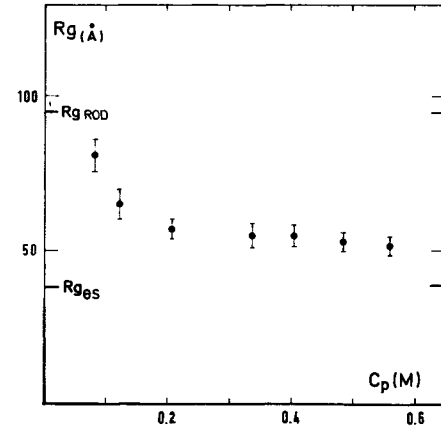


Fig. 3. — Variation of the radius of gyration with the concentration of polyions. The radius of gyration is extracted from the Berry plot : $S_1^{-1/2}(q)$ versus q^2 .

polystyrene chain [20], and $N = 122$, $L = 271$ Å and $R_g = 78$ Å.

— Second, the radius of gyration of the parent polystyrene in theta solvent which using the expression $\langle R_g^2 \rangle_z^{1/2} = 0.27 M_w^{0.506}$ [10], gives $R_g = 32$ Å.

Introducing the polydispersity $M_w/M_n = 1 + U = 1.15$, we obtain for the rod [11]

$$\langle R_g^2 \rangle_z^{1/2} = \left[\frac{(1+3U)(1+2U)}{(1+U)^2} \right]^{1/2} \frac{L}{\sqrt{12}} = 93 \text{ Å} \quad (5)$$

and for the coil

$$\langle R_g^2 \rangle^{1/2} = \left[\frac{1+2U}{1+U} \right]^{1/2} \langle R_g^2 \rangle_z^{1/2} = 34 \text{ Å}. \quad (6)$$

A double logarithmic plot of R_g as a function of c_p allows two concentration regimes to be distinguished (Fig. 4) :

— In a low concentration regime, the first three points appear close to a line of slope 0.48 ± 0.05 . The behaviour is then :

$$R_g \propto c_p^{-1/2}.$$

For the lowest studied concentration of this regime the polyion is very extended but not totally stretched :

$$R_g/R_{grod} = 0.87.$$

This ratio could approach one at lower concentrations or if we have slightly overestimated R_{grod} (the actual chain conformation has to be taken into account).

— In a high concentration regime another straight line could be plotted of slope 0.20 ± 0.08 . The decay of R_g with the increase of c_p can be roughly taken as :

$$R_g \propto c_p^{-1/4}.$$

Let us remark that for the highest studied concentration, the overall size of the corresponding neutral polymer is not yet reached : $R_g/R_{gneutral} = 1.53$.

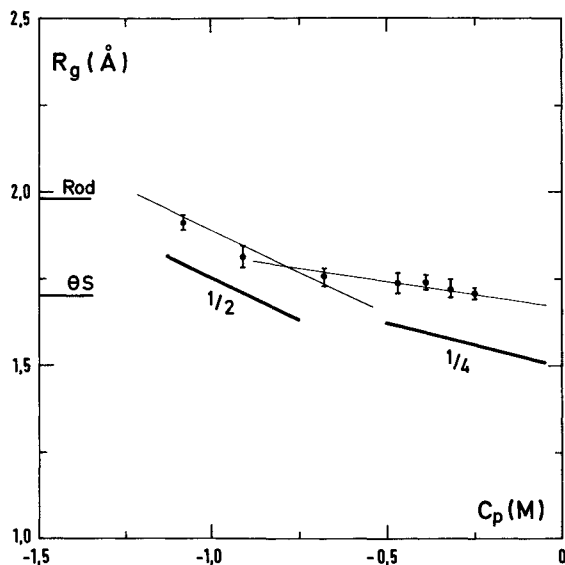


Fig. 4. — Double logarithmic plot of R_g versus c_p .

4. Discussion.

The wormlike chain description.

These results show that the two possible extreme conformations of the polyion, rod and Gaussian coil conformation of the θ -state of polystyrene (λ) have not been observed and we are dealing only with intermediate conformations of a polyion having a more

or less local stiffness. Such a chain is classically described by the wormlike chain model which allows a continuous transition from rod to Gaussian coil [12]. This model requires two parameters for its characterization, the persistence length b_t and the contour length L . When L/b_t is small, the chain is very stiff and rodlike, and when L/b_t is large, the chain is Gaussian.

The radius of gyration of such a chain is given by [13] :

$$\langle R_g^2 \rangle = b_t^2 \left[\frac{x}{3} - 1 + \frac{2}{x} - \frac{2}{x^2} (1 - \exp(-x)) \right] \quad (7)$$

with $x = L/b_t$.

For $L/b_t \ll 1$, equation (7) leads to

$$R_g^2 = \frac{L^2}{12} \quad (8)$$

which is the radius of gyration of a rod of length L .

For $L/b_t \gg 1$, equation (7) leads to

$$R_g^2 = b_t L/3 \quad (9)$$

which is the radius of gyration of a Gaussian coil.

Equations (8) and (9) are the extreme conditions for the dimension of the polyion.

Equation (7) is only valid for monodisperse samples and appropriate corrections have to be made for polydisperse samples [11]. A molecular weight distribution, approximated by the continuous Schulz-distribution, leads to

$$\langle R_g^2 \rangle_z (M_w, U) = \frac{1 + 2U}{1 + U} \frac{L b_t}{3} \left\{ 1 - \frac{1 + U}{1 + 2U} \frac{3 b_t}{L} \left(1 - \frac{2 b_t}{L} \right) - \frac{(1 + U)^2}{1 + 2U} \frac{6 b_t^3}{L^3} \left[1 - \left(1 + \frac{U}{1 + U} \frac{L}{b_t} \right)^{-1/U} \right] \right\} \quad (10)$$

where $U = M_w/M_n - 1$, and $\langle R_g^2 \rangle_z$ is the z-average of the mean square radius of gyration as obtained from the scattering data of polydisperse samples.

According to equation (10), R_g depends on three parameters, b_t , L and U . U can be obtained from table I and two unknown parameters remain. With this single experiment, we have no means to know exactly the value of L but a maximum value can be evaluated. The NaPSS molecule of molecular weight 26 000 consists of $N = 122$ monomers with a repeat distance of $p = 2.5 \text{ \AA}$ (if the polymer is in a l_1 -helix (Zig-Zag) conformation [20]), so the maximum contour length is $L = 305 \text{ \AA}$.

Table III presents, in the first two columns, a comparison of values of the persistence length b_t obtained with formula (7), $U = 0$, and formula (10), $U = 0.15$. The effect of the variation of L is shown in the last two columns with $p = 2.5 \text{ \AA}$, $L = 305 \text{ \AA}$ and $p = 2.22 \text{ \AA}$, $L = 271 \text{ \AA}$.

It appears, from comparison of columns 1 and 2, that the value of b_t strongly depends on the polydispersity. We thus want to stress that the knowledge of the polydispersity is absolutely necessary to extract the persistence length, especially for the rod limit. It also appears that the extraction of b_t is very sensitive to both the absolute value of R_g and the error on R_g . At low concentrations, R_g is close to the value of the radius of gyration of the rod for which b_t must be infinite and a weak variation of R_g in this range leads to a large variation of b_t : for example for $c = 0.0817$, the error in R_g is 10 % but the error in b_t is 50 %.

The variation of b_t with the concentration of polyions is shown in figure 5, for the two sets of values corresponding to $U = 0.15$. The plots b_t versus $c_p^{-1/2}$ appear linear for the higher concentration and at an infinite concentration these two straight lines converge to one value of b_t which is the persistence

Table III. — Persistence length as a function of polyelectrolyte concentration extracted from R_g for various assumptions. The first two columns of b_t show the influence of the polydispersity, the last two columns the remaining uncertainty due to the unknown contour length of the polyion.

c_p M	b_t Å	b_t Å	b_t
	$L = 305$ Å $U = 0$	$L = 305$ Å $U = 0.15$	$L = 271$ Å $U = 0.15$
0.0817	594 ± 404	139 ± 42	318 ± 160
0.123	85 ± 26	59 ± 15	80 ± 22
0.208	51 ± 10	39 ± 6	49 ± 9
0.338	46 ± 10	35 ± 7	44 ± 10
0.404	43 ± 7	33 ± 5	41 ± 7
0.484	41 ± 7	32 ± 5	39 ± 6
0.563	39 ± 6	30 ± 5	37 ± 6

length of the neutral polymer : we found 12 Å, in agreement with different determinations [5, 14]. At low concentrations, a pronounced deviation from this law $b_t \propto c_p^{-1/2}$ is observed : a log log plot of b_t as a function of c_p indicates a concentration dependence close to c_p^{-1} .

In conclusion, these data indicate two clear features :

— at low concentrations :

$$b_t \propto c_p^{-1}$$

— and at high concentrations :

$$b_t \propto c_p^{-1/2}.$$

During the last few years, theoretical estimates of the persistence length have been given. The total persistence length b_t which gives some idea of the local stiffness of the polyion is the sum of two contributions : b_p the intrinsic persistence length of the neutral backbone and b_e the electrostatic contribution arising from the interactions between charges along the flexible backbone : $b_t = b_p + b_e$.

The electrostatic contribution to the persistence length b_e has been calculated by several workers [15, 16, 18, 19].

T. Odijk [15] and J. Skolnick and M. Fixman [16], assuming that the charges interact through a Debye-Hückel potential, have found :

$$b_e = \frac{1}{12} Q N^2 h(y) \quad (11)$$

where Q is the Bjerrum length ($Q = (e^2)/\epsilon_0 kT = 7.13$ Å in water), $y = KL$ with L the contour length of the polyion and K^{-1} the Debye-Hückel screening length related to the concentration through the relation :

$$K^2 = 8 \pi Q c \quad (12)$$

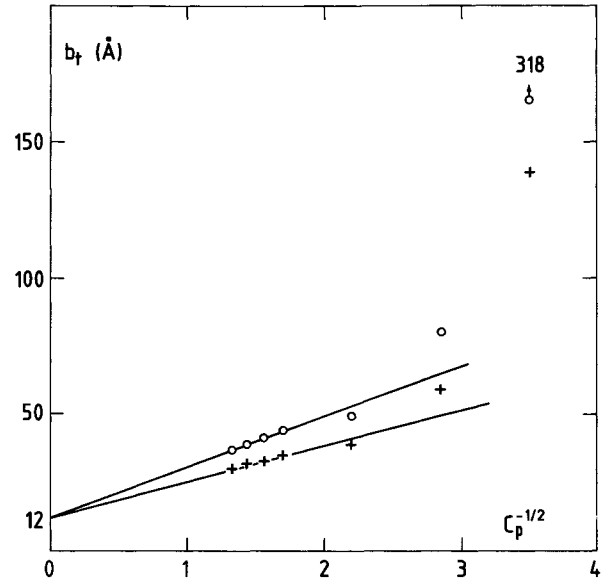


Fig. 5. — Variation of the total persistence length b_t with the concentration of polyions. The values of b_t are extracted from R_g using equation (10) with :

$$+ U = 0.15 \quad \text{and} \quad L = 305 \text{ Å}$$

$$\circ U = 0.15 \quad \text{and} \quad L = 271 \text{ Å}.$$

where c is the concentration of the non condensed counter ions.

In the case of the rod limit

$$h(y) = e^{-y}(y^{-1} + 5y^{-2} + 8y^{-3}) + 3y^{-2} - 8y^{-3}. \quad (13)$$

If the two following conditions are obeyed :

— $Kb_t \gg 1$, which is true for polyelectrolytes near the rod limit or at least for polyelectrolytes having a high intrinsic stiffness.

— The counter ion condensation model applies [17].

Formula (11) gives

$$b_e = \frac{1}{4 K^2 Q}. \quad (14)$$

Then, the persistence length b_e , depends on the concentration through K^2 : relations (14) and (12) give a c_p^{-1} dependence for b_e .

This c_p^{-1} dependence is found experimentally for the lower concentrations but a departure from this law appears for the higher concentrations. This deviation could be related to the fact that for this kind of flexible polyelectrolyte having a small intrinsic stiffness, the condition $Kb_t \gg 1$ is not fully satisfied (for the smallest concentration $Kb_t \sim 12$ and for the highest $Kb_t \sim 4$). In addition, the values of b_e calculated with equation (14) are smaller than those found experimentally (Fig. 6). As the condition $Kb_t > 1$ is not fulfilled for these concentrations, formula (11) will be perhaps more suitable for calculating b_e .

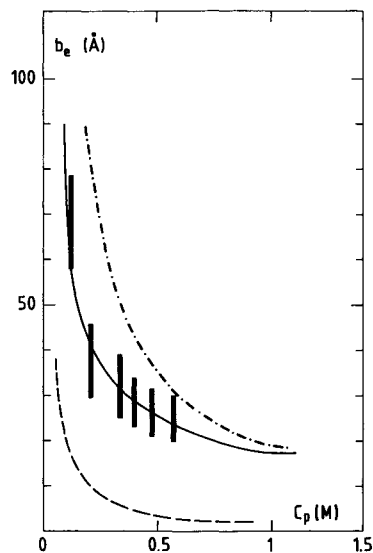


Fig. 6. — Calculated values of the electrostatic persistence length by Le Bret (—) and Odijk [(- - -) $b_e = 1/4 K^2 Q$ (- · - · -) $b_e = (1/12) QN^2 h(\gamma)$ with $N = 122$ and $L = 271$ Å] are compared to experimental values $b_e = b_t - b_p$ with $b_p = 12$ Å.

These new values are reported on figure 6 where one can see that they also disagree with experimental values.

More recently, Fixman [18] and Le Bret [19] have

performed new calculations of b_e . Le Bret has integrated the complete Poisson-Boltzmann equation for a toroid. The results cannot be put into a simple analytical form but numerical calculations made by Le Bret (reported in Fig. 4 of Ref. [5]) lead to two concentration régimes for the variation of b_e with c_p : at low concentration $b_e \propto c_p^{-1}$ and at high concentration $b_e \propto c_p^{-1/2}$ (for more details see Ref. [19] and [5]).

First, these two concentration régimes agree with the experimental determination and, moreover, calculated and experimental values are in good agreement: this is shown in figure 6 which gives the comparison between b_e experimental, $b_{e \text{ Odijk}}$ and $b_{e \text{ Le Bret}}$.

In reference [5], we report results concerning NaPSS of a larger molecular weight and we have extracted b_t from a fit between the experimental curves $S_1(q)$ and the calculated correlations functions for a worm-like chain [21-23]: these two sets of b_t , extracted from R_g and from $S_1(q)$ at high q are in good agreement.

Acknowledgments.

We wish to thank M. Le Bret for his helpful collaboration and especially for the calculation of the electrostatic persistence length. We are indebted to M. Rawiso, G. Jannink and G. Weill for various discussions and G. Jannink for a careful criticism of the manuscript.

References

- [1] DE GENNES, P. G., *Scaling concepts in polymer physics*, Cornell University Press. (Ithaca and London).
- [2] NIERLICH, M., WILLIAMS, C., BOUÉ, F., COTTON, J. P., DAOUD, M., FARNOUX, B., JANNINK, G., PICOT, C., MOAN, M., WOLFF, C., RINAUDO, M., DE GENNES, P. G., *J. Physique* **40** (1979) 701.
- [3] WILLIAMS, C., NIERLICH, M., COTTON, J. P., JANNINK, G., BOUÉ, F., DAOUD, M., FARNOUX, B., PICOT, C., DE GENNES, P. G., RINAUDO, M., MOAN, M., WOLFF, C., *J. Polym. Sci. Polym. Lett. Ed* **17** (1979) 379.
- [4] AKCASU, C., *J. Polym. Sci. Polymer Phys. Ed* **18** (1980) 863.
- [5] NIERLICH, M., BOUE, F., OBERTHUR, R., LAPP, A., Submitted to *J. Colloid Polym. Sci.*
- [6] VINK, H., *Makromol. Chem.* **182** (1981) 279.
- [7] LAPP, A., STRAZIELLE, C., Submitted to *Makromol. Chem.*
- [8] ISE, N., OKUBO, T., *J. Amer. Chem. Soc.* **90** (1968) 4527.
- [9] KIRSTE, R. G. and OBERTHUR, R. C., *Small Angle X-ray scattering*, Chapter 12 Edited by O. Glatter and O. Kratky (Academic Press, London) 1982.
- [10] COTTON, J. P., *J. Physique Lett.* **41** (1980) L-231.
- [11] OBERTHUR, R., *Makromol. Chem.* **179** (1978) 2693.
- [12] KRATKY, O., POROD, G., *Rec. Trav. Chem. Pays-Bas* **68** (1949) 1106.
- [13] BENOIT, H., DOTY, P., *J. Phys. Chem.* **57** (1953) 958.
- [14] RAWISO, M., BENOIT, H., DUPLESSIX, R., PICOT, C., WEILL, G., Submitted to *Macromolecules*.
- [15] ODIJK, T., *J. Polym. Sci., Polym. Phys.* **15** (1977) 477.
- [16] SKOLNICK, J. and FIXMAN, M., *Macromol.* **10** (1977) 944.
- [17] MANNING, G. S., *J. Chem. Phys.* **51** (1969) 924.
- [18] FIXMAN, M., *J. Chem. Phys.* **76** 12 (1982) 6346.
- [19] LE BRET, M., *J. Chem. Phys.* **76** 12 (1982) 6243.
- [20] BIRSHTEIN, T. M., PTITSYN, O. B., *Conformations of Macromolecules* (Interscience Publishers, New York) 1966, p. 62-63.
- [21] SHARP, P., BLOOMFIELD, V. A., *Biopolymers* **6** (1968) 1201.
- [22] DES CLOIZEAUX, J., *Macromolecules* **7** (1974) 649.
- [23] YOSHIZAKI, T. and YAMAKAWA, H., *Macromolecules* **13** (1980) 1518.