

Restoration of Endodontically Treated Teeth with Carbon Fibre Posts — A Prospective Study

• Bruce Glazer, DDS, B.Sc.D., Dip. Prosth. •

A b s t r a c t

Background: A prospective study was started in 1995 to evaluate the success of carbon fibre reinforced epoxy resin (CFRR) posts used to restore endodontically treated teeth. All the teeth in the study had lost more than 50% of their coronal structure.

Methods: Fifty-nine carbon fibre Composiposts cemented with Metabond and built up with Core Paste cores were placed into the teeth of 47 patients. Each tooth received a full-coverage restoration (porcelain fused to metal crown) and was followed for 6.7-45.4 months (average = 28.0 months, standard deviation = 10.7).

Results: Results for 52 teeth in 42 patients were analyzed. There were no fractures. The overall failure rate was 7.7% and the cumulative survival rate was 89.6% at the end of the follow-up period. The only statistically significant finding ($p = 0.04$) was that posts in lower premolars were at higher risk of failure.

Conclusion: CFRR posts are among the most predictable systems available today. CFRR posts in the upper anterior teeth are associated with a higher success rate and longer life than those placed in premolars, especially lower premolars. This study contributes to the growing body of evidence that supports the use of CFRR posts in the restoration of endodontically treated teeth.

MeSH Key Words: carbon; dental prosthesis design; post and core technique

© J Can Dent Assoc 2000; 66:613-8
This article has been peer reviewed.

There is no consensus on the best procedure for restoring endodontically treated teeth. However, retrospective studies¹⁻⁶ do identify factors that affect the success rate. Tooth location in the arch,¹⁻³ type of occlusion,² amount of remaining dentin³ and type of abutment¹ affect the selection of a restorative approach that will produce a favourable outcome. Yet in spite of this evidence, a recent survey⁷ calls into question dentists' patterns of restoring endodontically treated teeth in the United States.

Failure rates averaging 2% per year have been reported²⁻⁶ for both single crowns and retainers for fixed partial dentures. The 1992 Hatzikyriakos¹ study reported dramatic differences in failure rate over 3 years between complete coverage restorations functioning as single crowns (5.5%) and those functioning as fixed partial denture abutments (16.4%). The reported causes of failure were debonding, post fracture, caries and root fracture. Because of the excellent adhesion of dentinal bonding agents to tooth structure, when used with resin core build-ups or in conjunction with luting cements, the threat of fracture as the chief failure mode in endodontically treated teeth is increasing.⁸

Corrosion caused by dissimilar metals, area variation and stress, first reported in 1970⁹ is just now being implicated as a source of fracture potential in post-endodontic restorations.¹⁰ In addition to established factors, the composition of the post system may play a pivotal role in restorative success. To address this concern, a carbon fibre post system was introduced in Europe in 1990. A carbon-epoxy composite post was reinforced with long carbon unidirectional, high-performance fibres stretched parallel to the axis of the post.¹¹ The fibres represented 64% of the structural volume and the matrix, which bound the fibres together, was an epoxy resin.

King and Setchell¹² showed that prefabricated carbon fibre posts exhibit properties comparable with, and in some cases better than, those of prefabricated metal posts, and McDonald and colleagues¹³ found no difference in fracture resistance among unrestored endodontically treated teeth, teeth with stainless steel posts and teeth with carbon fibre posts. However, in 1997, a laboratory-based study¹⁴ demonstrated that teeth restored with a carbon fibre post system exhibited inferior strength compared with other established metallic post systems



Figure 1: Composipost and core paste showing 2.0-mm ferrule.



Figure 3: ISO 90, ISO 100 and ISO 120 University of Montreal Endoposts and matching drill sets.

when subjected to a single-angled compression load. Subsequent studies of the carbon fibre post system¹⁵⁻¹⁷ do not agree on its efficacy. This confusion led to the initiation of the study reported here to evaluate the success of a carbon fibre post system used to retain an intracoronal foundation to restore endodontically treated teeth.

Materials and Methods

Patients in this study were referred by their dentist or treating specialist. All those who received a carbon fibre post and resin core restoration followed by a full-coverage restoration (porcelain fused to metal) between September 21, 1995, and November 26, 1998, were enrolled in the study. However, 5 patients were later excluded because of relocation or inability to locate them. Patients were recalled annually, although some received more frequent recalls due to ongoing dental needs.

Success or failure of the restorative tooth complex was evaluated by the author. When a patient was unable to return, a follow-up visit was arranged with the referring dentist, who was provided with the criteria for judging success or failure by telephone. The classification of failure as either biological or mechanical was based on findings of an unpublished cast post pilot study, carried out in 1990-93.



Figure 2: #1, #2, #3 Composiposts and matching drill sets.

The crown preparation varied from a full chamfer to a feather finish depending on the height and thickness of the remaining dentin, but there was always a minimum 2.0-mm ferrule of dentin¹⁸ as measured with a periodontal probe (Fig. 1). Crown lengthening or extrusion procedures or both¹⁸ were used when the height of the remaining supragingival dentin (ferrule) was < 2.0 mm. A biological width of 2.0 mm was the ultimate goal after periodontal surgery and/or orthodontics. Christensen's guidelines,^{19,20} that a core needs post retention only when more than 50% of the tooth's coronal structure has been destroyed, were followed.

Removal of the gutta percha for post preparation²¹ was accomplished with Gates Glidden drills (Premier Dental (Canada), Markham, ON) at least 48 hours after obturation.²² This was followed by refining of the canal space using the drill sets provided in Composipost or University of Montreal Endopost kits (Biodent, Québec, QC). A minimal apical seal of 5.0 mm of gutta percha filling was retained in the apical root portion.²¹ Canals were not prepared to receive a predetermined size of post; rather the gutta percha was removed and the post that best fit the remaining space was used in each tooth.²³ For the Composipost no. 1 (Recherches Techniques Dentaire [RTD], Grenoble, France), which was used in most cases, slight refining at the top of the pulp chamber was required; no additional preparation was required for University of Montreal Endo-posts (RTD, Grenoble, France).

The Composiposts were cylindrical with grooves around the circumference and a 2-stepped shank section tapering to a conical seating face for stabilization (Fig. 2). The University of Montreal Endopost had a distinctive smooth conical profile (Fig. 3). The posts were placed in the canal to mark the length needed to project into the resin core, then removed and cut with a diamond disc. The head of the carbon post should extend through the composite resin core to the surface of the preparation to prevent thin, unsupported areas of resin from fracturing during provisional restoration or on removal of the final impression.²⁴

In preparation for the subsequent core build-up a copper band (Moyco Industries, Inc. Philadelphia, PA) was selected to fit snugly around the remaining dentin and its height was

marked so that the carbon fibre post projected 1.0 mm beyond the edge of the band. It was then cut with scissors to the correct height. The opposing arch was prepared to ensure proper retention and resistance according to Shillingburg.²⁵

The root canal was scrubbed for 10 seconds with C&B Metabond (Parkell, Farmingdale, NY) dentin conditioner on a felt brush (Pinnacle Products Inc., Lakeville, MN). The canal was then washed with water and dried with air and paper points (Henry Schein, Port Washington, NY). C&B Metabond was mixed according to the manufacturer's instructions. (The powder chosen from the Metabond kit was the tooth-coloured radio-opaque product.) The post was moistened with the mixed liquid and the cement was quickly loaded into Accudose Needle Tubes (Centrix Inc., Shelton, CT), placed in a Centrix syringe and injected into the canal. Once the canal was filled with cement, a lentulo (Spiral Fillers RA, Caulk, Dentsply, Milford, DE) was inserted to the depth of the canal to ensure proper coating of the root canal walls. The carbon post was then placed to the precut depth. Brushes were dipped in fresh monomer and the coronal surface of the tooth was cleaned of excess cement.

The Metabond was allowed to set undisturbed for 10 minutes, then the copper band was placed around the tooth and the dentin was etched with 37% phosphoric acid. Two-step Tenure (Den-Mat Corporation, Santa Maria, CA) was placed on all tooth surfaces and light-cured for 30 seconds. Core Paste (Den-Mat Corporation, Santa Maria, CA) was mixed in equal amounts, and a Centrix syringe was used to extrude the resin core material within the copper band; undercuts helped retain the core material. Pressure was applied with a gloved finger over a mylar strip until the resin hardened.

After 10 minutes, the band was removed and final preparations were made with Gingitage burs (Vic Pollard Dental Diamond Drills, Westlake, CA). The Gingitage burs prepared the tooth and refined the tissue if more ferrule was needed. The final impression was made and the tooth temporized (Luxatemp, DMG, Zenith Brand Division, Foremost Dental Mfg. Co., Hamburg, Germany) pending delivery of the crown. All crowns were porcelain fused to metal and final cementing was completed with Flecks Crown and Bridge cement (Mizzy Inc., Cherry Hill, NJ).

The restoration was deemed successful if the complete crown was still cemented to the underlying tooth-core complex at follow-up, without any biological or mechanical breakdown. Biological failure was defined as the presence of pathology due to caries, periodontal disease or endodontic failure. Mechanical failure was the debonding of any part of the tooth-post-core-crown complex or the presence of fracture. The presence of periodontal disease was identified as increasing mobility and pocket depth in any of the 6 readings on the restored teeth. Radiographs were taken during annual recall.

All restorative procedures were completed by one investigator with over 30 years of clinical experience. In 6 cases, the success of the restorations was determined by the referring dentist; one of the failures was reported by the referring endodontist.

Table 1 Sample characteristics

Patients	
Number	42
% Female	57.1
Age	
% under 45 years (<i>n</i> = 13)	31.0
% 45-65 years (<i>n</i> = 21)	50.0
% over 65 years (<i>n</i> = 8)	19.0
Mean age at date of post insertion (<i>n</i> = 52)	54.1 years (SD=14.4, range 17-83)
Teeth	
Number	52
% maxillary teeth	71.2
% mandibular teeth	28.8
% incisors	30.8
% canines	25.0
% premolars	44.2
Post type (<i>n</i> = 52)	
Composipost (%)	
#1 (<i>n</i> = 37)	71.2
#2 (<i>n</i> = 1)	1.9
Total (<i>n</i> = 38)	73.1
Endopost (%)	
size #90 (<i>n</i> = 10)	19.2
size #100 (<i>n</i> = 4)	7.7
Total (<i>n</i> = 14)	26.9

SD = Standard deviation.

Note: 7 cases were excluded from the analysis because they were not seen at follow-up.

Table 2 Distribution of cases by prosthetic status and tooth type

	Single	FPD abutment	
Maxillary	Number of cases	Number of cases	Overall %
Incisor	8	8	30.8
Canine	3 (1)	7	19.2
Premolar	5 (1)	6	21.2
Mandibular			
Incisor	—	—	0.0
Canine	2	1	5.8
Premolar	9 (1)	3 (1)	23.1
Total number	27 (3)	25 (1)	
Overall %	51.9%	48.1%	

() = No. of failed carbon fibre posts
FPD = fixed partial denture

Statistical Methods

Data were analyzed using the SPSS statistical software system (SPSS Inc., Chicago, IL). Dates were entered as day, month, year, using the 15th of the month when only month and year were known. Variables were created for tooth type, event status (i.e., post failure vs. non-failure), and time to event, and were assigned numerical values. Time-to-event was defined as the time, in months, between the date of insertion

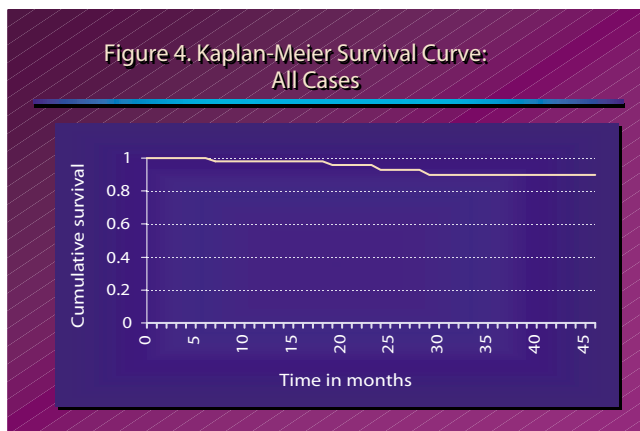


Figure 4: Kaplan-Meier survival curve for all cases.

of the post and either the date of failure of the restoration or the date of the last recall. If a patient was not seen at one or more recall appointments, he or she was excluded from the analysis. Censored observations were cases for which failure did not occur during the observation period. However, censored observations contributed time to the analysis.

The unit of analysis was the tooth and teeth were referred to as cases. Survival analysis, used to determine the probability of failure or the survival rate, was performed at 3 levels (univariate, bivariate and multivariate) using the Kaplan-Meier method, the log-rank test, the Breslow (or generalized Wilcoxon) test and Cox regression. At the bivariate and multivariate levels, the following independent variables were assessed: patient's sex and age, tooth type and location, post type and prosthetic status.

It was assumed that subjects were treated similarly whether they entered the study early or late, that hazard rate did not change with time, and that those lost to follow-up were not significantly different from those included in the analysis.

Results

Characteristics of the Sample

A total of 59 carbon fibre reinforced epoxy resin posts with extracoronary coverage were placed in the mouths of 47 patients. Of these, 5 patients and 7 "cases" were excluded from analysis. Patients were monitored by recall for 6.7-45.4 months (average = 28.0 months, standard deviation [SD] = 10.7 months). The first post was inserted on September 21, 1995, and the last on November 26, 1998. Table 1 shows the distribution of cases by patient characteristics, tooth and post type. Table 2 shows the distribution by prosthetic status and tooth type together with the number of failed restorations. Upper incisors were the most commonly treated tooth type, followed by lower premolars and upper premolars. No molars required posts during the 3.75 years of the study.

Failure occurred in 3 teeth with single crown restorations and one fixed partial denture abutment. Of these, 2 were in lower premolars, one in an upper premolar and one in an upper canine (Table 2).

Table 3 Summary of Kaplan-Meier analysis

Variable	Mean survival time in months (SE)	95% Confidence Interval
Sex		
male	41.0 (2.1)	37.0-45.0
female	43.9 (1.4)	41.1-46.6
Age		
< 45yrs	42.2 (1.9)	38.6-45.8
45-65 yrs	42.8 (2.1)	38.7-46.9
> 65 years	All observations censored	All observations censored
Tooth location		
Anterior	44.6 (1.3)	42.0-47.2
Posterior (premolar)	39.4 (2.2)	35.1-43.7
Tooth location (dental arch)		
Maxillary	44.0 (1.4)	41.3-46.6
Mandibular	38.7 (2.3)	34.2-43.2
Tooth type		
Incisor	All observations censored	All observations censored
Canine	42.9 (2.9)	37.3-48.6
Premolar	39.4 (2.2)	35.1-43.7
Prosthetic status		
Single	41.3 (2.0)	37.3-45.2
FPD abutment	44.9 (1.0)	42.9-46.9
Post type		
Composipost	41.5 (1.6)	39.4-45.7
Endopost	All observations censored	All observations censored

SE = Standard error of the mean.
 Note: Survival estimates cannot be computed if all observations are censored.

Univariate Analysis

For the 4 failures reported (7.7% of all cases), 2 were biologic (periapical pathology) and 2 were mechanical (1 core debonding and 1 crown debonding). Average time to failure was 20.0 months (SD = 9.5, median = 21.9, range 7.0-29.3).

The Kaplan-Meier survival curve for all cases is shown in Fig. 4. The cumulative survival rate at the end of the follow-up period was 89.6%, with a mean survival time of 43.4 months (95% confidence interval [CI], 41.0-45.8).

Bivariate Analysis

Table 3 summarizes the mean survival times and confidence intervals for bivariate analyses using the Kaplan-Meier method. Although survival rates for carbon fibre posts placed in anterior teeth in the maxillary arch (canines in particular) and fixed partial denture abutments were higher than for those placed in posterior teeth (premolars in particular), in the mandibular arch and in single teeth, the differences were not statistically significant (Table 4). Similarly, gender and age differences in carbon fibre post survival rates were not statistically significant. However, mean survival time was shorter for premolar teeth (39 months) than for anterior teeth (45 months). Pairwise comparisons of the different tooth types, carried out

Table 4 Summary of log rank and Breslow tests

Variable	Log-rank test statistic (p value)	Breslow statistic (p value)
Sex	0.07 (0.791)	0.19 (0.666)
Age (< 45 vs. 45-65 yrs)	0.02 (0.895)	0.04 (0.846)
Anterior-posterior (premolar) tooth location	2.22 (0.136)	1.11 (0.293)
Maxillary-mandibular tooth	1.03 (0.311)	0.61 (0.433)
Tooth type (canine vs. premolar)	0.51 (0.475)	0.07 (0.790)
Prosthetic status	1.02 (0.312)	1.46 (0.227)
Post type	1.42 (0.234)	1.36 (0.244)

Table 5 Summary of Cox regression analysis

Variable	Coefficient	SE	Significance
Sex (0 = male; 1 = female)	-0.73	1.13	0.518
Age (1 = 65 or younger; 0 = 65+ years)	13.34	406.80	0.974
Prosthetic status (1 = single; 2 = FPD abutment)	1.42	1.31	0.276
Post type (0 = Compositpost; 1 = Endopost)	13.80	477.77	0.977
Tooth type (1 = upper incisor 2 = upper canine; 3 = upper premolar; 5 = lower canine; 6 = lower premolar)	0.50	0.24	0.040

using the log-rank test, revealed a statistically significant difference in the 3-year survival rates of lower premolars compared with upper incisors.

Multivariate Analysis

Table 5 summarizes results from the Cox regression analysis to examine the joint influence of predictor variables on the carbon fibre post system. The following variables were included in the Cox regression model: sex, age, prosthetic status, post type and tooth type. Tooth type was found to be statistically significant, adjusting for other factors in the model. In other words, posts in lower premolars were at higher risk of failure than the other tooth types studied. None of the other variables was significant.

Discussion

This study may have lacked the power necessary to detect a statistical significance for the comparisons made. The results

suggest that the use of carbon reinforced resin posts in premolars, especially lower premolars, may be associated with a higher failure rate and shorter longevity than in anterior teeth. However, the ability to generalize these results is limited due to several factors: the length of follow-up was shorter than other similar studies; the number of cases was small; and post insertions took place over a long period (3 years). Nevertheless, the results indicate a 3-year survival rate of 90% for the carbon fibre-based post system used to restore endodontically treated teeth. Two of the 3 shortcomings of this study could be overcome by continuing to follow the cohort and reanalyzing the data in 5 and 10 years.

The mechanical failures included one resin core that debonded from the remaining dentin in an upper cuspid. The carbon post was replaced using the special removal system available from the manufacturer, an advantage over many existing post systems.²⁶

As a result of the use of techniques that minimize cement failure and have been shown to be retentive,^{27,28} all of the carbon fibre posts used in this study remained cemented to the radicular dentin.

Clinical Implications

As in previous studies,¹⁵⁻¹⁷ the CFRR post showed no fractures. The placement technique is less invasive than with some other post systems due to a shorter post length of 7.0-8.0 mm, with less chance of perforation, and posts may be replaced if biologic or mechanical failure occurs.

The greater biologic failure rate among premolars compared with anterior teeth may reflect a more complex root canal system. ❖

Acknowledgments: Special thanks to Dr. Herenia Lawrence and Dr. Robert Hawkins for their help in statistical analysis of the data. This study was partly funded by Biodent, Parkell and Den-Mat.

Dr. Glazer is staff prosthodontist at the Toronto Hospital (General Division) and an associate in dentistry at the University of Toronto.

Correspondence to: Dr. Bruce Glazer, Anesthesia in Dentistry, 712-1881 Yonge St., Toronto ON M4S 3C4. E-mail: bglazer@istar.ca.

The author has no declared financial interest in any company manufacturing the types of products mentioned in this article.

References

- Hatzikyriakos AH, Reisis GI, Tsingos N. A 3-year post operative clinical evaluation of posts and cores beneath existing crowns. *J Prosthet Dent* 1992; 67:454-8.
- Bergman B, Lunquist P, Sjogren U, Sundquist G. Restorative and endodontic results after treatment with cast posts and cores. *J Prosthet Dent* 1989; 61:10-5.
- Sorensen JA, Martinoff JT. Intracoronal reinforcement and coronal coverage: a study of endodontically treated teeth. *J Prosthet Dent* 1984; 51:780-4.
- Mentink AG, Meeuwissen R, Kayser AF, Mulder J. Survival rate and failure characteristics of the all metal post and core restoration. *J Oral Rehabil* 1993; 20:455-61.
- Morgano SM, Milot P. Clinical success of cast metal posts and cores. *J Prosthet Dent* 1993; 70:11-6. Review.
- Weine FS, Wax AH, Wenckus CS. Retrospective study of tapered, smooth post systems in place for 10 years or more. *J Endod* 1991; 17:293-7.

7. Scurria MS, Shugars DA, Hayden WJ, Felton DA. General dentists patterns of restoring endodontically treated teeth. *JADA* 1995; 126:775-9.
8. McLean A. Predictably restoring endodontically treated teeth. *J Can Dent Assoc* 1998; 64:782-7. Review.
9. Mateer RS, Reitz CD. Corrosion of amalgam restorations. *J Dent Res* 1970; 49:399-407.
10. Glantz PO, Nilner K. The devitalized tooth as an abutment in dentitions with a reduced but healthy periodontium. *Periodontology* 2000 1994; 4:52-7.
11. Duret B, Duret F, Reynaud M. Long-life physical property preservation and postendodontic rehabilitation with the Composipost. *Compend Contin Edu Dent* 1996; 17(Suppl 20):S50.
12. King PA, Setchell DJ. An in vitro evaluation of a prototype CFRC prefabricated post developed for the restoration of pulpless teeth. *J Oral Rehabil* 1990; 17:599-609.
13. McDonald AV, King PA, Setchell DJ. In vitro study to compare impact fracture resistance of intact root-treated teeth. *Int Endod J* 1990; 23:304-12. Review.
14. Sidoli GE, King PA, Setchell DJ. An in vitro evaluation of a carbon fiber-based post and core system. *J Prosthet Dent* 1997; 78:5-9.
15. Fredriksson M, Astback J, Pamenius M, Arvidson K. A retrospective study of 236 patients with teeth restored by carbon fiber-reinforced epoxy resin posts. *J Prosthet Dent* 1998; 80:151-7.
16. Martinez-Insua A, da Silva L, Rilo B, Santana U. Comparison of the fracture resistance of pulpless teeth restored with a cast post and core or carbon-fiber post with a composite core. *J Prosthet Dent* 1998; 80:527-32.
17. Isidor F, Odman P, Brondum K. Intermittent loading of teeth restored using prefabricated carbon fiber posts. *Int J Prosthodont* 1996; 9:131-6.
18. Assif D, Pilo R, Marshak B. Restoring teeth following crown lengthening procedures. *J Prosthet Dent* 1991; 65:62-4. Review.
19. Christensen GJ. When to use fillers, build-ups or posts and cores. *J Am Dent Assoc* 1996; 127:1397-8.
20. Christensen GJ. Posts: Necessary or unnecessary? *J Am Dent Assoc* 1996; 127:1522-4, 1526.
21. Portell FR, Bernier WE, Lorton L, Peters DD. The effect of immediate versus delayed dowel space preparation on the integrity of the apical seal. *J Endod* 1982; 8:154-60.
22. Mattison GD, Delivannis PD, Thacker RW Jr, Hassell JK. Effect of post preparation on the apical seal. *J Prosthet Dent* 1984; 51:785-9.
23. Lloyd PM, Palik JF. The philosophies of dowel diameter preparation: a literature review. *J Prosthet Dent* 1993; 69:32-6. Review.
24. Walton JN, Ruse ND, Glick N. Apical root strain as a function of post extension into a composite resin core. *J Prosthet Dent* 1996; 75:499-505.
25. Shillingburg HT, Jacobi R, Brackett S. Fundamentals of Tooth Preparations. Chicago: Quintessence Publishing Co. Inc.; 1987.
26. Sakkal S. Carbon-fiber post removal technique. *Compend Contin Edu Dent* 1996; 17(Suppl 20):S86.
27. Standlee JP, Caputo AA. Endodontic dowel retention with resinous cements. *J Prosthet Dent* 1992; 68:913-7.
28. Tjan AH, Nemetz H. Retention of posts cemented with resin based luting agents. *Oral Health* 1993; 83(Nov):9-14.

**C D A R E S O U R C E
C E N T R E**

CDA members can order the Resource Centre's information package on endodontically treated teeth by contacting us at tel.: **1-800-267-6354** or **(613) 523-1770**, ext. 2223; fax: **(613) 523-6574**; e-mail: **info@cda-adc.ca**.