

Selective photoelectrochemical oxidation of glycerol to high value-added dihydroxyacetone

Liu, Dong; Liu, Jin-Cheng; Cai, Weizheng; Ma, Jun; Yang, Hong Bin; Xiao, Hai; Li, Jun; Xiong, Yujie; Huang, Yanqiang; Liu, Bin

2019

Liu, D., Liu, J.-C., Cai, W., Ma, J., Yang, H. B., Xiao, H., ... Liu, B. (2019). Selective photoelectrochemical oxidation of glycerol to high value-added dihydroxyacetone. *Nature Communications*, 10(1). doi:10.1038/s41467-019-09788-5

<https://hdl.handle.net/10356/102872>

<https://doi.org/10.1038/s41467-019-09788-5>





© 2019 The Author(s). This article is licensed under a Creative Commons Attribution 4.0 International License, which permits use, sharing, adaptation, distribution and reproduction in any medium or format, as long as you give appropriate credit to the original author(s) and the source, provide a link to the Creative Commons license, and indicate if changes were made. The images or other third party material in this article are included in the article's Creative Commons license, unless indicated otherwise in a credit line to the material. If material is not included in the article's Creative Commons license and your intended use is not permitted by statutory regulation or exceeds the permitted use, you will need to obtain permission directly from the copyright holder. To view a copy of this license, visit <http://creativecommons.org/licenses/by/4.0/>.

ARTICLE

<https://doi.org/10.1038/s41467-019-09788-5>

OPEN

Selective photoelectrochemical oxidation of glycerol to high value-added dihydroxyacetone

Dong Liu ¹, Jin-Cheng Liu ², Weizheng Cai¹, Jun Ma³, Hong Bin Yang^{1,4}, Hai Xiao ², Jun Li ², Yujie Xiong³, Yanqiang Huang⁵ & Bin Liu¹

It is highly profitable to transform glycerol – the main by-product from biodiesel production to high value-added chemicals. In this work, we develop a photoelectrochemical system based on nanoporous BiVO₄ for selective oxidation of glycerol to 1,3-dihydroxyacetone – one of the most valuable derivatives of glycerol. Under AM 1.5G front illumination (100 mW cm⁻²) in an acidic medium (pH = 2) without adsorbed oxidant, the nanoporous BiVO₄ photoanode achieves a glycerol oxidation photocurrent density of 3.7 mA cm⁻² at a potential of 1.2 V versus RHE with 51% 1,3-dihydroxyacetone selectivity, equivalent to a production rate of 200 mmol of 1,3-dihydroxyacetone per m² of illumination area in one hour.

¹School of Chemical and Biomedical Engineering, Nanyang Technological University, 62 Nanyang Drive, Singapore 637459, Singapore. ²Department of Chemistry and Key Laboratory of Organic Optoelectronics & Molecular Engineering of Ministry of Education, Tsinghua University, Beijing 100084, China. ³Hefei National Laboratory for Physical Sciences at the Microscale, Collaborative Innovation Center of Chemistry for Energy Materials (iChEM), School of Chemistry and Materials Science, University of Science and Technology of China, Hefei 230026, China. ⁴Institute for Materials Science and Devices, Suzhou University of Science and Technology, Suzhou 215009, China. ⁵State Key Laboratory of Catalysis, Dalian Institute of Chemical Physics, Chinese Academy of Sciences, Dalian 116023, China. Correspondence and requests for materials should be addressed to H.X. (email: haixiao@tsinghua.edu.cn) or to Y.X. (email: yjxiong@ustc.edu.cn) or to B.L. (email: liubin@ntu.edu.sg)

Increasing global energy demand and environmental concern drive the development of fuels and building-block chemicals production from renewable feedstocks and green energy sources^{1–6}. Biodiesel manufactured from vegetable oils and animal fats has become increasingly attractive because of its environmental benefits^{7–10}, which is now produced at million tonnes of oil equivalent per year. Production of 100 pounds of biodiesel brings out 10 pounds of glycerol as a by-product. With increase in global biodiesel consumption, efficient utilization of glycerol becomes an urgent and highly profitable market^{11–17}. Glycerol has many oxidation derivatives, among which, 1,3-dihydroxyacetone (DHA) is most valuable. DHA is widely used in cosmetic, pharmaceutical, fine chemical, and food industries, which costs US \$150 per kg while the price for crude and refined glycerol is only US \$0.11 and US \$0.66 per kg, respectively^{18,19}. Commercial DHA is mainly produced via a microbial fermentation process, which is complex, time-consuming, and subject to substrate inhibition^{15,20}. Besides, selective catalytic conversion of glycerol to DHA could be achieved by thermal oxidation or electrochemical oxidation on noble metal catalysts (e.g., Pt, Pd, Ag, and Au) with adsorptive oxidants^{21–28}, which are not only cost-intensive, but also produce DHA at very low production rates with poor DHA selectivities.

Photoelectrochemical oxidation provides another promising approach, which combines both renewable feedstock and green energy source together to make building-block chemical and clean fuel at the same time. In this study, we demonstrate that photoelectrochemical oxidation of glycerol to DHA could be achieved with high selectivity at ambient temperature and pressure on porous BiVO₄. At pH = 2, under AM 1.5G front illumination (100 mW cm⁻²), the porous BiVO₄ photoanode is able to produce about 200 mmol of DHA per m² of illumination area in 1 h at a potential of 1.2 V vs. RHE without the requirement of adsorptive oxidant. Based on isotope labeling experiments and density functional theory (DFT) calculations, we deduce a possible reaction mechanism of selective photoelectrochemical oxidation of glycerol to DHA on BiVO₄.

Results

Synthesis and structural characterization of BiVO₄ photoanode. BiVO₄ photoanode was prepared by reacting BiOI nanoflake arrays that were electrochemically grown on fluorine-doped tin dioxide (FTO) glass with vanadyl acetylacetonate at elevated temperatures. Supplementary Fig. 1 shows the typical scanning electron microscopy (SEM) image of the as-prepared BiVO₄ photoanode, which displays porous, interconnected nanoflake arrays. High-resolution transmission electron microscopy (HRTEM) image shows that the main exposed facet of the BiVO₄ nanoflake is (112). The BiVO₄ nanoarrays are phase-pure with monoclinic scheelite structure (Supplementary Fig. 2). The bandgap of the BiVO₄ nanoarrays was measured to be ~2.5 eV (Supplementary Fig. 3).

Photoelectrochemical performance of BiVO₄ photoanode. Photoelectrochemical (PEC) performance of BiVO₄ photoanode was first evaluated in 0.5 M Na₂SO₄ electrolyte with pH adjusted from 2 to 12 under one sun illumination (AM 1.5 G, 100 mW cm⁻²). Figure 1 shows the current density-potential profiles under dark and illumination conditions. Without the addition of glycerol in the reaction medium, the photocurrent density resulting from water oxidation via front illumination is nearly identical, reaching ~1 mA cm⁻² at 1.23 V vs. RHE independent of pH. When glycerol was introduced, the photocurrent density dramatically increased, accompanying with a clear onset shift towards lower potentials, indicating easier oxidation of glycerol than water. The photocurrent

density approaches 4 mA cm⁻² at 1.23 V vs. RHE at pH = 2. Increase in pH greatly decreases photocurrent and at the same time increases the onset potential, suggesting that proton could directly influence the catalytic oxidation reaction. Further increasing pH to more than 10 caused photocorrosion of BiVO₄ (Supplementary Fig. 4).

Figure 1d–f and Supplementary Fig. 5 show the chopped photocurrent profiles recorded at 1.0 and 0.6 V vs. RHE, respectively in an H-type cell. In the absence of glycerol, each on–off cycle of photocurrent produces a transient spike, which is induced by the diffusion and accumulation of photogenerated holes at the surface of BiVO₄ due to the slow kinetics of water oxidation reaction (Supplementary Fig. 6 and Supplementary Note 1)²⁹. The stable photocurrent density reaches 0.1 and 1.0 mA cm⁻² at 0.6 and 1.0 V vs. RHE, respectively at pH = 2. Adding 0.1 M of glycerol not only dramatically increases the photocurrent density to 1.8 and 3.4 mA cm⁻² at 0.6 and 1.0 V vs. RHE, but also at the same time greatly reduces the photocurrent spike. This comparison suggests faster reaction kinetics of glycerol oxidation as compared to water oxidation. Additionally, increase in reaction pH greatly reduces the photocurrent density, which can be attributed to the better glycerol adsorption on BiVO₄ at lower pH (Supplementary Fig. 7 and Supplementary Note 2). Enhanced adsorption of glycerol on BiVO₄ at lower pH shall result in easier transfer of photogenerated holes for further oxidation reactions, which therefore diminishes the chopped photocurrent spikes.

To gain information on the charge and mass transfer processes, electrochemical impedance spectroscopy (EIS) studies were performed under different applied biases with light illumination. An equivalent circuit based on charge carrier trapping mechanism was employed to analyze the EIS data (Fig. 2c)^{30,31}. The equivalent circuit includes a space-charge capacitance, C_{sc} and a surface state capacitance, CPE_q. R_Ω is the series resistance, R_t is the resistance that represents the trapping of holes in the surface states, and R_s is the charge and mass transfer resistance from surface states to solution. For the EIS spectra collected without glycerol, as shown in the Bode (Fig. 2a) and Nyquist plots (Supplementary Fig. 8a), the frequency peak decreases and shifts to higher frequency with increasing bias, leading to decreased faradaic resistance and improved surface reaction rate. After adding glycerol, the frequency peak shifts to higher frequency, but the impedance semicircle becomes larger with increasing bias (Fig. 2b and Supplementary Fig. 8b). The increased R_s in PEC glycerol oxidation with increasing bias could be attributed to the poor desorption of the oxidation products³². We further calculated the total resistance, R_{total} via R_{total} = R_Ω + R_t + R_s (Supplementary Fig. 8c and Supplementary Note 3), and compared with the resistance estimated from the current density-potential profile (R_{total} = dV/dJ⁻¹) as shown in Fig. 2d. At potentials prior to H₂O oxidation onset, R_{total} is found to be orders of magnitude higher for PEC water oxidation as compared to that for PEC glycerol oxidation.

To probe the charge carrier dynamics, we performed transient open-circuit voltage decay (OCVD) measurements. Figure 3a compares the OCVD profiles of the BiVO₄ photoanode measured in 0.5 M Na₂SO₄ aqueous solution at various pH, from which, we were able to estimate the lifetimes of photogenerated charge carriers (Fig. 3b). It is found that decrease in reaction pH slightly increases recombination rate of photogenerated electron–hole pairs. The photoresponse spectra of the porous BiVO₄ nanoarray photoanode were further assessed as shown in Fig. 3c, d, which resemble well with the light absorption spectrum of BiVO₄ (Supplementary Fig. 3). In the absence of glycerol at pH = 2, the incident photon-to-current conversion efficiency (IPCE) approaches ~20% at 400 nm and 1.23 V vs. RHE. The addition

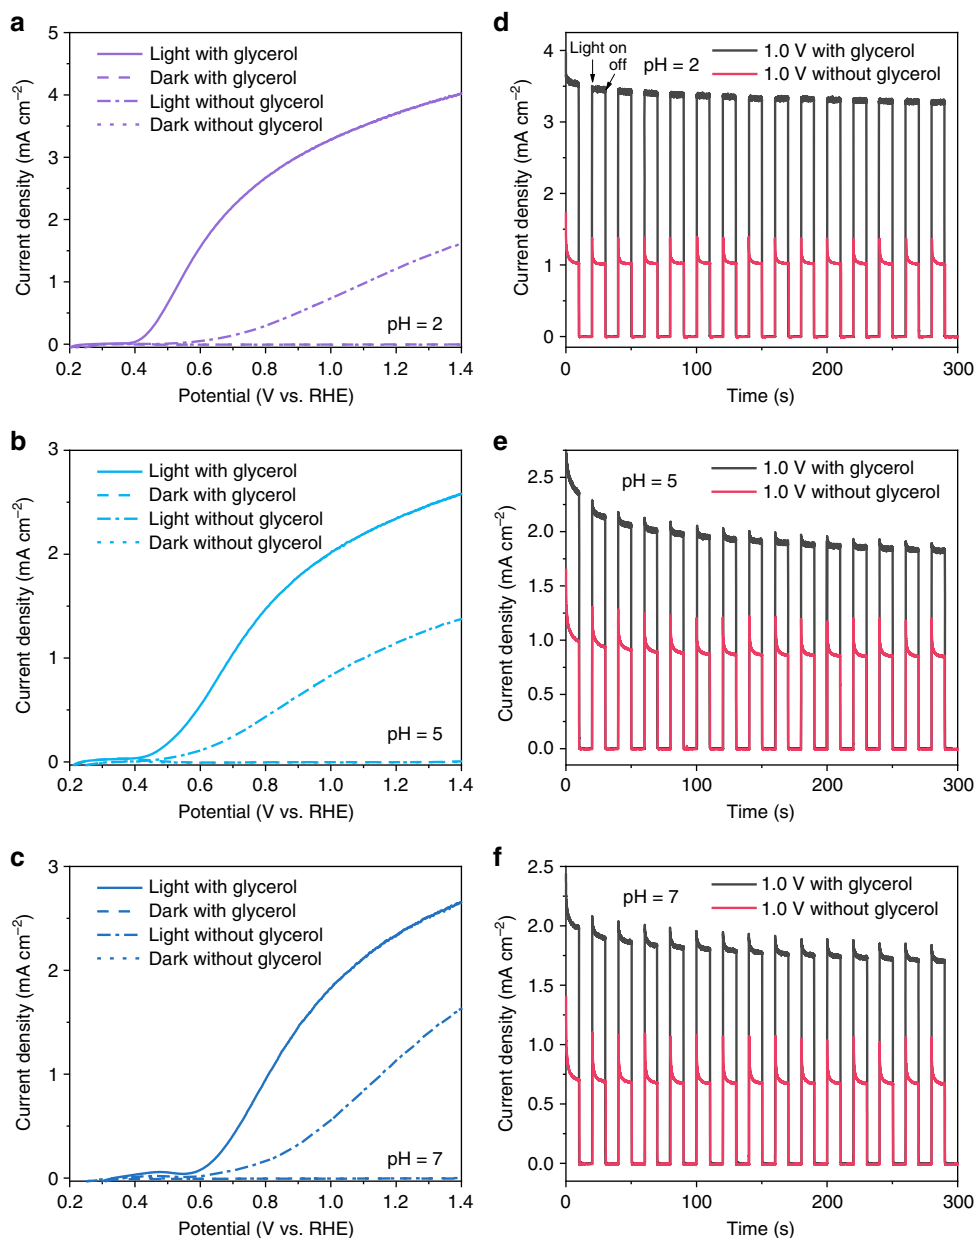


Fig. 1 Photoelectrochemical performances. **a–c** Current density–potential profiles of BiVO₄ photoanode measured in 0.5 M Na₂SO₄ at various pH in an H-type cell under dark and AM 1.5 G, 100 mW cm⁻² illumination. **d–f** Chopped photocurrent density–time profiles of BiVO₄ photoanode at 1.0 V vs. RHE in 0.5 M Na₂SO₄ at various pH with and without glycerol. Source data are provided as a Source Data file

of glycerol significantly increases the IPCE across the entire light absorption region of BiVO₄, reaching 80% at 400 nm and 1.23 V vs. RHE, which is consistent with the change in photocurrent density. Furthermore, increase in reaction pH decreases IPCE (Fig. 3d) as a result of impaired binding of glycerol on BiVO₄ as discussed previously.

Selective photoelectrochemical oxidation of glycerol. The photoelectrochemical stability of the porous BiVO₄ nanoarray photoanode was assessed by measuring photocurrent as a function of reaction time at various applied potentials. As shown in Supplementary Fig. 9, the BiVO₄ photoanode exhibits excellent long-time stability against photocorrosion at pH = 2 with stable photocurrent densities. Following, the photooxidation of glycerol was carried out at 0.8–1.2 V vs. RHE to analyze the oxidation products and faradaic efficiency (Supplementary

Fig. 10). The products consist of formic acid, glyceric acid, DHA, and trace amount of glycolic acid. Figure 4a and Supplementary Fig. 11 show the production rate and selectivity of oxidation products at various pH. With increase in applied potential, the production rate of the oxidation products also increases. At pH = 2, DHA becomes the preferred oxidization product with selectivity and overall faradaic efficiency approaching ~50% in the liquid products and ~30%, respectively, independent of applied potential. At a potential of 1.2 V vs. RHE, the production rate of DHA reaches as high as about 200 mmol per m² of illumination area in 1 h, and the total carbon balance is about 91.3%, in which the glycerol-to-DHA conversion selectivity is 63.6% (Supplementary Table 1). CO₂ and CO could also be detected from further oxidation of liquid products together with H₂O₂ and O₂ from water oxidation. Total charge-to-chemical balance is about 90.21%. Besides DHA, glyceric acid was also produced as a by-product, resulting in the overall selectivity of

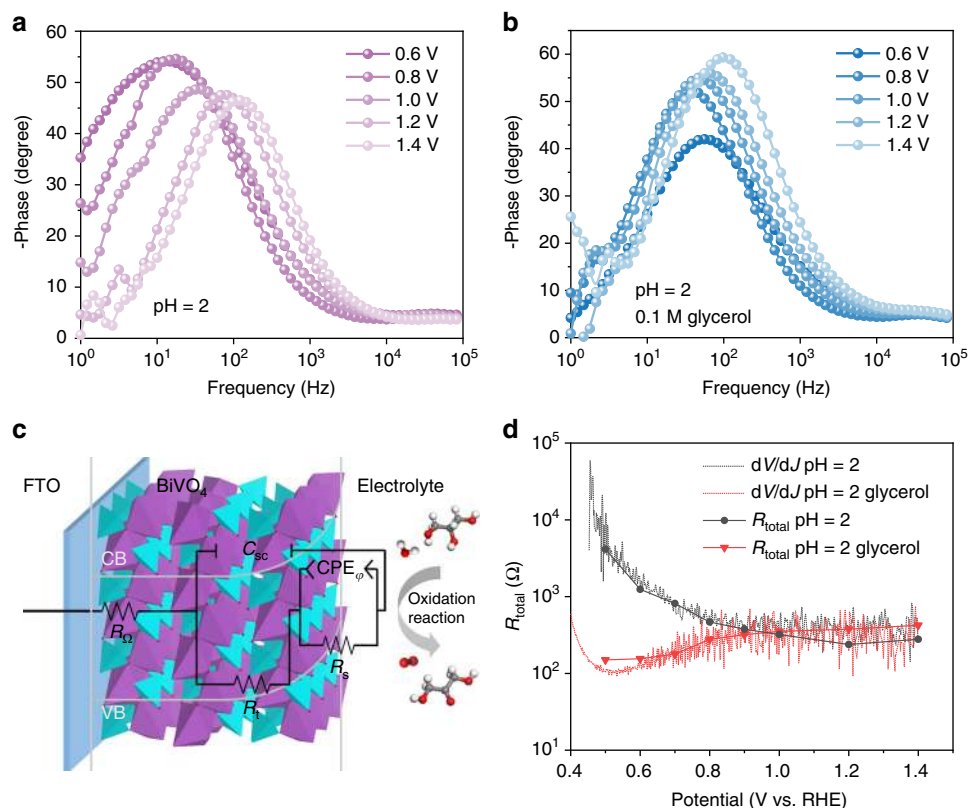


Fig. 2 Charge and mass transfer processes. **a, b** The Bode plots measured at different potentials under AM 1.5 G, 100 mW cm^{-2} illumination without and with the presence of glycerol. **c** Equivalent circuit used to conceptualize the BiVO_4 photoanode in PEC reactions. **d** R_{total} calculated from dV/dJ^{-1} of current density-potential profiles and from EIS data with and without glycerol under illumination

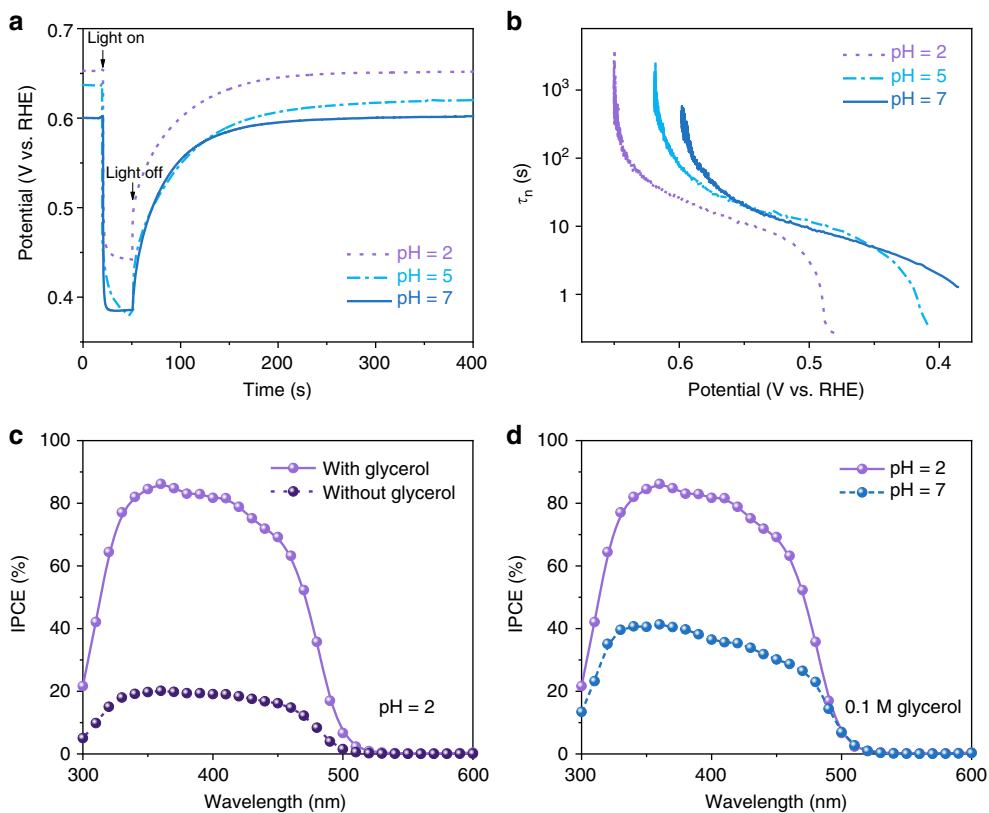


Fig. 3 Charge carrier dynamics. **a, b** Transient OCVD profiles and lifetimes of photogenerated charge carriers of porous BiVO_4 nanoarray photoanode in $0.5 \text{ M Na}_2\text{SO}_4$ at various pH. **c, d** Incident photon-to-current conversion efficiency spectra of porous BiVO_4 nanoarray photoanode

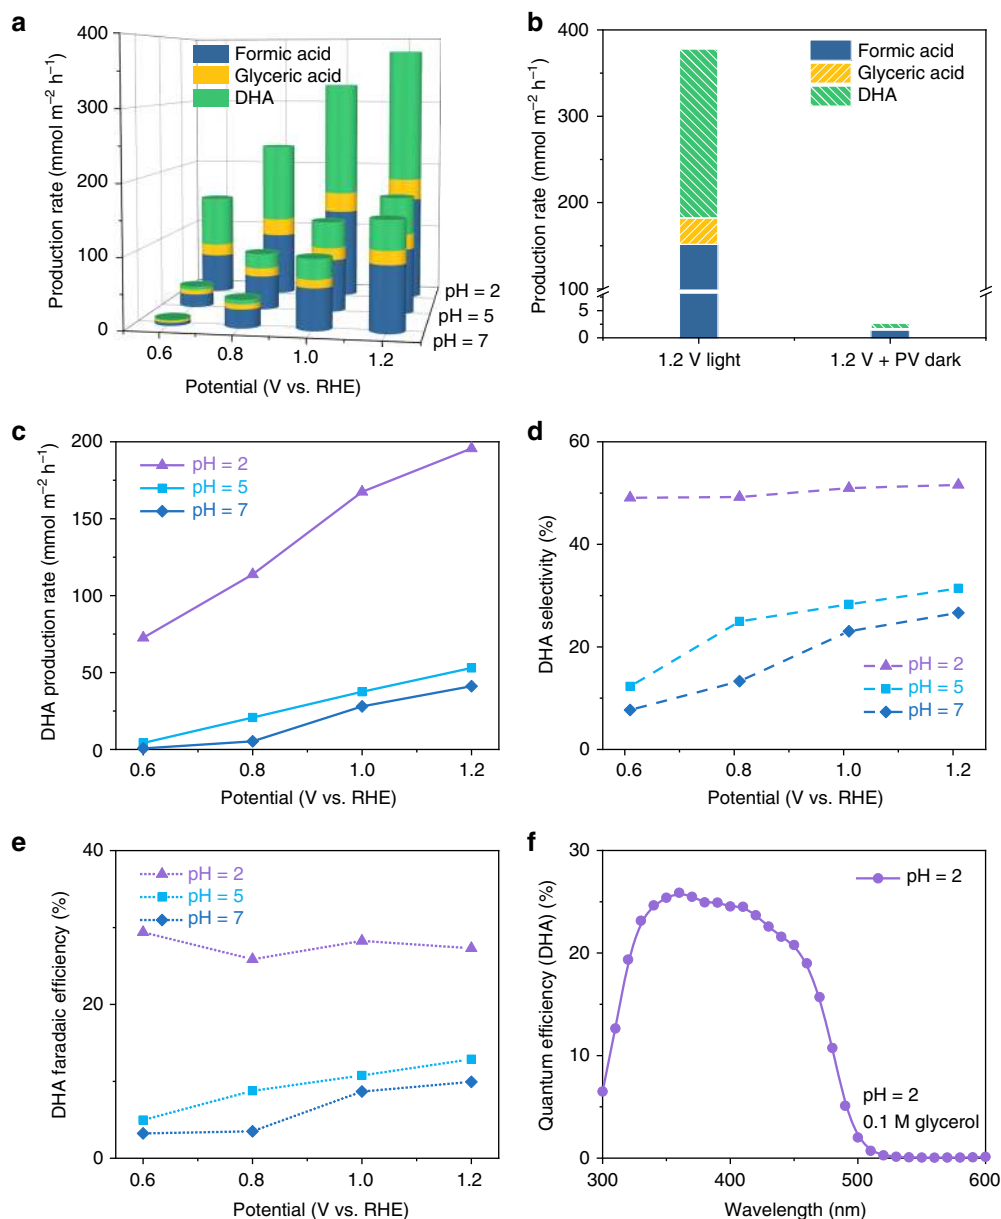


Fig. 4 Selective photoelectrochemical oxidation of glycerol. **a** Photoelectrocatalytic production rate of oxidation products on BiVO₄ photoanode at reaction pH of 2, 5, and 7, respectively in 1 h. **b** Production rate of oxidation products at pH = 2 and 1.2 V vs. RHE under illumination or 1.375 V vs. RHE in dark, respectively. **c–e** Production rate, selectivity, and faradaic efficiency of DHA produced in an H-type cell at pH = 2, 5, and 7. **f** Incident photon-to-DHA conversion efficiency spectrum acquired at pH = 2 and 1.23 V vs. RHE

high value-added glycerol derivatives (DHA + glyceric acid) approaching ~60%. Increase in pH decreases not only the photocurrent, but also the selectivity towards high value-added oxidation products (Fig. 4c–e). At pH = 12, glycerol was almost completely oxidized to formic acid with a faradaic efficiency close to 99% (Supplementary Fig. 12). Both photocurrent and production rate of DHA increase notably with increase of glycerol concentration (Supplementary Fig. 13). Without light illumination, glycerol could only be oxidized to DHA by BiVO₄ at very low efficiency after applying additional bias (Fig. 4b and Supplementary Fig. 14). Porous BiVO₄ nanoarray photoanode could produce DHA with higher rate and selectivity than BiVO₄ film photoanode as porous nanoarrays possess larger surface area and more abundant active sites (Supplementary Fig. 15 and Supplementary Note 4). In addition, porous BiVO₄ nanoarrays also showed advantages in selective glycerol oxidation as

compared to other semiconductor nanomaterials (Supplementary Fig. 16 and Supplementary Note 5).

Reaction mechanism. To probe the reaction mechanism, we conducted isotope-labeling experiments and electron spin resonance (ESR) measurements. Supplementary Fig. 17 displays the liquid chromatography mass spectrometry (LC-MS) results of photoelectrochemical glycerol oxidation in oxygen isotope labeled electrolyte with H₂O containing 10% H₂¹⁸O. The results show that ¹⁸O can be detected in the target product DHA in the form of C₃H₆O₂¹⁸ONa (Supplementary Table 2 and Supplementary Note 6), indicating that the isotope oxygen in DHA comes from water in the electrolyte. It can thus be speculated that oxidation of β-hydroxy to carbonyl group during photoelectrochemical glycerol oxidation to DHA would be accomplished by an addition

and substitution reaction. The adsorbed glycerol on BiVO₄ photoanode would be oxidized into radicals by photogenerated holes (Supplementary Tables 3, 4 and Supplementary Notes 7, 8) 33–35. Room temperature ESR spectra indicate that after adding glycerol in this system, instead of hydroxyl radicals, glycerol radicals could be detected (Supplementary Fig. 18 and Supplementary Note 9). Driven by the energetic holes, the glycerol radicals could react with water from electrolyte to form unstable gem-diol intermediates, followed by dehydration to produce the carbonyl group, during which the isotope oxygen might be left in the products^{35,36}. As a conclusion, we infer that the oxidation of glycerol to DHA could occur via the following steps as shown in Supplementary Fig. 19 and Supplementary Note 10, including adsorption of glycerol on BiVO₄ photoanode, oxidation of adsorbed glycerol to radicals by photogenerated holes, reaction with water, and dehydration. Glyceric acid and formic acid could also be formed via this similar pathway, resulted from the further oxidation of glyceraldehyde.

As shown in Supplementary Fig. 7, glycerol could be better adsorbed on BiVO₄ at lower pH, which shall result in an easier charge transfer and enhanced catalysis to photoelectrochemically convert glycerol into glycerol derivatives when decreasing reaction pH. Besides, acidic environment can also suppress the reaction towards acid products, which might further reduce the consumption of DHA as well as suppress the production of formic acid³⁷. The adsorption of glycerol on BiVO₄ and the reaction pathways of the glycerol oxidation were verified by DFT calculations on the (112) facets of BiVO₄—the main exposed crystal facets of the BiVO₄ photoanode studied in this work (Supplementary Fig. 1c). As shown in the DFT results, the terminal and middle hydroxyl groups of glycerol adsorb spontaneously on the bismuth site of BiVO₄ with strong electrostatic attraction between Bi³⁺ and oxygen of hydroxyls (Fig. 5, Supplementary Fig. 20, and Supplementary Note 11). Subsequently, the adsorbed glycerol is oxidized by the photo-generated holes in BiVO₄ to form radicals (Supplementary Figs. 21 and 22). The tertiary radical on the middle carbon is 0.18 eV more stable than the terminal radical, which explains the good selectivity towards DHA production during photoelectrochemical oxidation of glycerol on BiVO₄. The photo-assisted reaction is critical for the production of DHA as only formic acid could be detected in the final liquid product under dark condition. BiVO₄ provides a suitable bandgap of ~2.5 eV that endows photo-generated holes with sufficient energy to overcome the energy requirement for the formation of radicals, which is ~1.5 eV. Thereafter, the radicals react with water, followed by dehydration to eventually form DHA.

Finally, incident photon-to-DHA quantum efficiency (QE-DHA) was evaluated by multiplying IPCE with faradaic efficiency of DHA as shown in Fig. 4f. In the reaction medium with pH = 2, a 25% photon-to-DHA conversion efficiency can be achieved at a wavelength of 400 nm.

Discussion

In summary, we have demonstrated an efficient and stable photoelectrochemical system based on porous BiVO₄ nanoarrays for selective oxidation of glycerol to high value-added DHA. In an H-type cell at pH = 2, the porous BiVO₄ nanoarray photoanode is able to produce 56 mmol_{g_{catalyst}}⁻¹ h⁻¹ of DHA at a potential of 1.2 V vs. RHE under AM 1.5 illumination (100 mW cm⁻²). Based on isotope labeling and DFT calculations, we deduced a possible reaction mechanism of selective photoelectrochemical oxidation of glycerol to DHA on BiVO₄. This study not only provides an evidence of the reaction process of selective photoelectrochemical oxidation of glycerol to DHA, but also presents a broad research

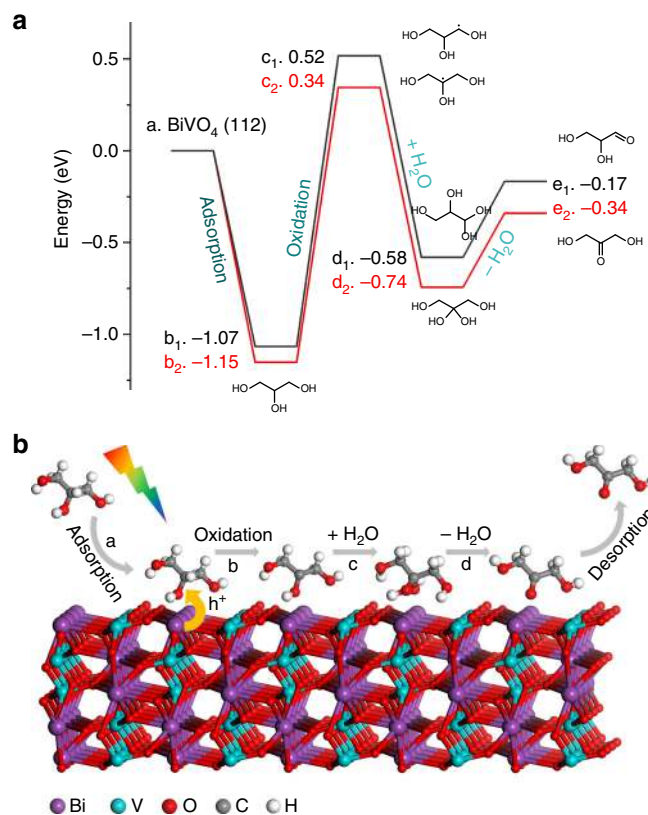


Fig. 5 Reaction mechanism. **a** Energy profile of glycerol oxidation on BiVO₄. 1 (black) and 2 (red) stand for reactions that take place at the terminal and middle carbon, respectively. **b** Schematic illustration showing PEC glycerol oxidation to DHA

perspective for the utilization of solar light to produce high value-added chemicals from renewable feedstocks.

Methods

Synthesis of BiVO₄ photoanode. All chemicals were purchased from Sigma-Aldrich and used without further purification. BiVO₄ photoanode was prepared by reacting BiOI nanoflake arrays with vanadyl acetylacetonate³⁸. Firstly, BiOI nanoflake arrays were grown on conductive fluorine-doped SnO₂ (FTO, 14 Ω cm, 1 × 1 cm²) by a three-electrode cathodic electrodeposition at -0.1 V vs. Ag/AgCl for 5 min in a mixed solution of 50 mL of 0.04 M Bi(NO₃)₃ and 0.4 M KI aqueous solution with pH adjusted to 1.7 by adding HNO₃ and 20 mL of 0.23 M benzoquinone ethanol solution. Subsequently, 0.1 mL of vanadyl acetylacetonate dimethyl sulfoxide solution (0.4 M) was added onto the BiOI nanoflake arrays, followed by heating to 723 K in ambient environment at a ramp rate of 2 K min⁻¹. After 2 h, the resultant product on FTO was cooled to room temperature and washed by NaOH solution.

Sample characterizations. SEM images were taken on a JEOL JSM-6700F field emission scanning electron microscope operated at 5 kV. HRTEM image was taken on a JEOL JEM-2100F field-emission transmission electron microscope operated at 200 kV. X-ray powder diffraction (XRD) patterns were recorded using a Philips X'Pert Pro Super X-ray diffractometer with Cu Kα radiation (λ = 1.54178 Å). UV-vis diffuse reflectance spectrum was recorded in the spectral region of 300–600 nm on a Shimadzu SolidSpec-3700 spectrophotometer. The bandgap of BiVO₄ was determined based on the Tauc plot. BiVO₄ photocatalysts used in this work were scraped from the BiVO₄ nanoarray-FTO glass.

Fourier transform infrared spectroscopy (FTIR) measurements were carried out in the attenuated total reflection (ATR) configuration using a Nicolet iN10 MX spectrometer equipped with a Ge ATR crystal and a DTGS KBr detector. All spectra were measured with a resolution of 1 cm⁻¹ and presented in absorbance $A = -\log(R/R_0)$, where R and R_0 are the reflectance spectra of BiVO₄ samples treated in electrolyte of different pH with and without glycerol. After soaked in the electrolyte with and without glycerol at different pH for 10 min, the BiVO₄ samples were washed by the electrolyte without glycerol. After dried with N₂ flow, the BiVO₄ samples were pressed into intimate optical contact with the Ge crystal for ATR-FTIR measurements.

Room-temperature ESR spectra of BiVO₄ photocatalysts were collected on a JEOL JES-FA200 ESR spectrometer (300 K, 9.063 GHz, X-band). Microwave power employed was 1 mW and sweep width was set from 319.3 to 329.3 mT. Modulation frequency and modulation amplitude were 100 kHz and 0.35 mT, respectively. 5,5-Dimethyl-1-pyrroline N-oxide (DMPO) was used as the spin-trapping agent. 0.5 mg BiVO₄ photocatalysts were dispersed in 2 mL 0.5 M Na₂SO₄ electrolyte (pH = 2) with or without 0.1 M glycerol, then 60 μL DMPO aqueous solution (0.2 M) was added into the solution for ESR measurement.

Photoelectrochemical characterization. Photoelectrochemical measurements were conducted on an electrochemical workstation (CHI 760E) in a sealed H-type glass cell. Nafion 212 proton exchange membrane was used to separate the anode from the cathode chamber. The simulated solar illumination was obtained from a 300 W Xenon lamp with an AM 1.5G filter (100 mW cm⁻²). The porous BiVO₄ nanoarrays grown on FTO were front illuminated and used as the working electrode, while Ag/AgCl electrode and Pt sheet were used as the reference and counter electrode, respectively. The electrolyte contains 0.5 M Na₂SO₄ aqueous solution with pH adjusted to 2, 5, 7, 10, and 12 using 1 M NaOH solution or 0.5 M H₂SO₄ solution. Photocurrent was recorded from 0.2 to 1.4 V vs. RHE at a scan rate of 10 mV s⁻¹ with and without the presence of 0.1 M glycerol.

The photoresponse of the BiVO₄ photoanode was studied by measuring photocurrent densities under chopped light irradiation (light on/off cycles: 20 s) at 0.6 and 1.0 V vs. RHE in 0.5 M Na₂SO₄ at various pH with and without glycerol. The photoelectrochemical impedance spectra were collected in a frequency range of 1~10⁵ Hz with an amplitude of 5 mV under AM 1.5 G, 100 mW cm⁻² illumination, from 0.6 V to 1.4 V vs. RHE. Mott-Schottky plots were measured at 1000 Hz under dark and AM 1.5 G, 100 mW cm⁻² illumination with potential varied from -0.3 to 0.6 V vs. RHE.

OCVD measurements were carried out with light illumination on and off. After turning off the light, the average lifetime of photogenerated charge carriers (τ_n) was estimated according to:

$$\tau_n = \frac{k_B T}{e} \left(\frac{dV_{oc}}{dt} \right)^{-1} \quad (1)$$

where τ_n is the potential dependent lifetime, k_B is Boltzmann's constant, T is the temperature in K, e is the single electron charge, and V_{oc} is the open-circuit voltage at time t .

IPCE was measured under monochromatic irradiation under one sun illumination (AM 1.5 G, 100 mW cm⁻²) equipped with a monochromator at 1.23 V vs. RHE:

$$\text{IPCE} = \frac{[(\frac{1240}{\lambda}) \times (J_{\text{light}} - J_{\text{dark}})]}{P} \times 100\% \quad (2)$$

where λ is the wavelength, J_{light} is the photocurrent density under irradiation, J_{dark} is the current density under dark condition, and P is the incident light power density.

Photoelectrocatalysis characterizations. To quantitatively analyze the oxidation products, the photoelectrochemical oxidation was performed in a sealed H-type cell at a potential of 0.6, 0.8, 1.0, and 1.2 V vs. RHE for 1 h without the addition of adsorbent oxidant. After reaction, 1 mL of solution was taken out from the cell and analyzed using high performance liquid chromatography (HPLC) to calculate the glycerol conversion and yields of the products using an Agilent 1260 chromatograph equipped with a Hi-Plex H (300×d-7 mm, 8 μm) column and MWD and RID detector. The external quantum efficiency of photon-to-DHA was calculated based on IPCE and faradaic efficiency of DHA.

Selectivity of DHA was calculated based on:

$$\begin{aligned} \text{Selectivity(DHA)} &= \frac{n_{\text{DHA}}}{n_{\text{all}}} \times 100\% = \frac{n_{\text{DHA}}}{n_{\text{GA}} + n_{\text{DHA}} + n_{\text{FA}} + n_{\text{GLA}} + n_{\text{LA}}} \times 100\% \\ &= \frac{c_{\text{DHA}}}{c_{\text{GA}} + c_{\text{DHA}} + c_{\text{FA}} + c_{\text{GLA}} + c_{\text{LA}}} \times 100\% \end{aligned} \quad (3)$$

where n_{DHA} , n_{GA} , n_{FA} , n_{GLA} , and n_{LA} are the yield of DHA, glyceric acid, formic acid, glycolic acid, and lactic acid, respectively. c is the product concentration detected by HPLC.

Production rate of DHA was calculated according to:

$$\text{Production rate(DHA)} = \frac{c_{\text{DHA}} \times V}{t} \quad (4)$$

$$\text{Production rate per unit area(DHA)} = \frac{c_{\text{DHA}} \times V}{t \times A} \quad (5)$$

where V is the volume of reaction solution, t is the reaction time, and A is the area of photoanode.

Faradaic efficiency was calculated by:

$$\begin{aligned} \text{Faradaic efficiency(DHA)} &= \frac{\text{Number of holes to oxidize glycerol to DHA}}{\text{Number of all collected photogenerated holes}} \times 100\% \\ &= \frac{e_{\text{DHA}} \times n_{\text{DHA}} \times N}{Q/n} \times 100\% \\ &= \frac{2 \times e_{\text{DHA}} \times V \times N}{Q/n} \times 100\% \end{aligned} \quad (6)$$

where e_{DHA} is the number of holes required to oxidize one glycerol molecule to DHA, N is Avogadro's constant, Q is the quantity of electric charge, and n is the elementary charge.

External quantum efficiency of DHA was calculated by:

$$\begin{aligned} \text{QE(DHA)} &= \frac{\text{Number of holes to oxidize glycerol to DHA}}{\text{Number of incident photons}} \times 100\% \\ &= \text{IPCE} \times \text{Faradaic efficiency(DHA)} \times 100\% \end{aligned} \quad (7)$$

Carbon balance was calculated based on:

$$\text{Carbon balance} = \frac{n_{\text{GA}} + n_{\text{DHA}} + \frac{n_{\text{FA}}}{3} + \frac{n_{\text{GLA}}}{3/2} + \frac{n_{\text{CO}_2}}{3} + \frac{n_{\text{CO}}}{3}}{n_{\text{glycerol}}} \times 100\% \quad (8)$$

The LC-MS measurements were carried out on a LTQ Orbitrap XL Hybrid Ion Trap-Orbitrap Mass Spectrometer with IonMax ESI (electrospray ionization) Source. 0.5 M of Na₂SO₄ solution containing 10% H₂¹⁸O was used as the electrolyte with pH adjusted to 2 by 0.5 M of H₂SO₄. After 2 h of PEC reaction, the products with electrolyte were collected. Before LC-MS measurements, the products were extracted by SPE (Solid Phase Extraction Cartridges) column to remove inorganic salts. Hypersil GOLD column (3 μm particle size) and ESI Na⁺ source were used in the LC-MS measurements.

Computational details. All DFT calculations were performed with VASP 5.3.5^{39,40}. Spin-polarized DFT with Perdew-Burke-Ernzerhof (PBE) flavor of generalized gradient approximation were employed⁴¹. Iterative solutions of the Kohn-Sham equations were expanded in plane-wave basis sets defined by a kinetic energy cutoff of 400 eV. The convergences of energy and force were set as 10⁻⁶ eV and 0.02 eV Å⁻¹, respectively. Single gamma point sampling was used for the Brillouin Zone integration. The BiVO₄(112) surface was modeled by a p(2×2) supercell with three VO₄ layers as shown in Supplementary Fig. 20a. The calculated interlayer distance is 3.10 Å, which is in good agreement with HRTEM results. A vacuum region of 15 Å was set between the periodically repeated slabs to avoid artificial interactions. The charge density differences were evaluated using the formula $\Delta\rho = \rho_{\text{slab+ads}} - \rho_{\text{slab}} - \rho_{\text{ads}}$, where ρ_{slab} , ρ_{ads} , and $\rho_{\text{slab+ads}}$ are the electron densities of BiVO₄(112) slab, adsorbate, and the adsorption configuration, respectively.

Data availability

All data supporting the findings in the article as well as the Supplementary Information files are available from the corresponding authors on reasonable request. The source data underlying Fig. 1 and Supplementary Figs. 5, 10a-c, and 18 are provided as a Source Data file.

Received: 14 July 2018 Accepted: 22 March 2019

Published online: 16 April 2019

References

- Bender, T. A., Dabrowski, J. A. & Gagné, M. R. Homogeneous catalysis for the production of low-volume, high-value chemicals from biomass. *Nat. Rev. Chem.* **2**, 35–46 (2018).
- Lewis, N. S. & Nocera, D. G. Powering the planet: chemical challenges in solar energy utilization. *Proc. Natl. Acad. Sci. USA* **103**, 15729–15735 (2006).
- Li, W. et al. Integrated photoelectrochemical solar energy conversion and organic redox flow battery devices. *Angew. Chem. Int. Ed.* **55**, 13104–13108 (2016).
- Nocera, D. G. Solar fuels and solar chemicals industry. *Acc. Chem. Res.* **50**, 616–619 (2017).
- Caes, B. R., Teixeira, R. E., Knapp, K. G. & Raines, R. T. Biomass to furanics: renewable routes to chemicals and fuels. *ACS Sustain. Chem. Eng.* **3**, 2591–2605 (2015).
- Caspeta, L., Buijs, N. A. A. & Nielsen, J. The role of biofuels in the future energy supply. *Energy Environ. Sci.* **6**, 1077–1082 (2013).
- Issariyakul, T. & Dalai, A. K. Biodiesel from vegetable oils. *Renew. Sustain. Energy Rev.* **31**, 446–471 (2014).
- Knothe, G., Van Gerpen, J. H. & Krahl, J. *The Biodiesel Handbook* (AOCS Press, Champaign, Illinois, USA, 2005).
- Lee, A. F., Bennett, J. A., Manayil, J. C. & Wilson, K. Heterogeneous catalysis for sustainable biodiesel production via esterification and transesterification. *Chem. Soc. Rev.* **43**, 7887–7916 (2014).

10. Pradhan, A. et al. Energy life-cycle assessment of soybean biodiesel revisited. *Trans. ASABE* **54**, 1031–1039 (2011).
11. Haider, M. H. et al. Efficient green methanol synthesis from glycerol. *Nat. Chem.* **7**, 1028–1032 (2015).
12. Morales, M. et al. Environmental and economic assessment of lactic acid production from glycerol using cascade bio- and chemocatalysis. *Energy Environ. Sci.* **8**, 558–567 (2015).
13. Bagheri, S., Julkapli, N. M. & Yehye, W. A. Catalytic conversion of biodiesel derived raw glycerol to value added products. *Renew. Sustain. Energy Rev.* **41**, 113–127 (2015).
14. Pagliaro, M., Ciriminna, R., Kimura, H., Rossi, M. & Della Pina, C. From glycerol to value-added products. *Angew. Chem. Int. Ed.* **46**, 4434–4440 (2007).
15. Katryniok, B. et al. Selective catalytic oxidation of glycerol: perspectives for high value chemicals. *Green Chem.* **13**, 1960–1979 (2011).
16. Lam, C. H., Bloomfield, A. J. & Anastas, P. T. A switchable route to valuable commodity chemicals from glycerol via electrocatalytic oxidation with an earth abundant metal oxidation catalyst. *Green Chem.* **19**, 1958–1968 (2017).
17. Zalineeva, A. et al. Self-supported Pd₂Bi catalysts for the electrooxidation of glycerol in alkaline media. *J. Am. Chem. Soc.* **136**, 3937–3945 (2014).
18. Kumar, G. S. et al. Stabilized glycerol dehydrogenase for the conversion of glycerol to dihydroxyacetone. *Chem. Eng. J.* **276**, 283–288 (2015).
19. Quispe, C. A. G., Coronado, C. J. R. & Carvalho, J. A. Glycerol: production, consumption, prices, characterization and new trends in combustion. *Renew. Sustain. Energy Rev.* **27**, 475–493 (2013).
20. Ma, L., Lu, W., Xia, Z. & Wen, J. Enhancement of dihydroxyacetone production by a mutant of *Gluconobacter oxydans*. *Biochem. Eng. J.* **49**, 61–67 (2010).
21. Ciriminna, R., Palmisano, G., Della Pina, C., Rossi, M. & Pagliaro, M. One-pot electrocatalytic oxidation of glycerol to DHA. *Tetrahedron Lett.* **47**, 6993–6995 (2006).
22. Ning, X. et al. Promoting role of bismuth and antimony on Pt catalysts for the selective oxidation of glycerol to dihydroxyacetone. *J. Catal.* **335**, 95–104 (2016).
23. Kwon, Y., Birdja, Y., Spanos, I., Rodriguez, P. & Koper, M. T. M. Highly selective electro-oxidation of glycerol to dihydroxyacetone on platinum in the presence of bismuth. *ACS Catal.* **2**, 759–764 (2012).
24. Schunemann, S., Dodekatos, G. & Tüysüz, H. Mesoporous silica supported Au and AuCu nanoparticles for surface plasmon driven glycerol oxidation. *Chem. Mater.* **27**, 7743–7750 (2015).
25. Ribeiro, L. S. et al. Pd, Pt, and Pt–Cu catalysts supported on carbon nanotube (CNT) for the selective oxidation of glycerol in alkaline and base-free conditions. *Ind. Eng. Chem. Res.* **55**, 8548–8556 (2016).
26. Hirasawa, S., Watanabe, H., Kizuka, T., Nakagawa, Y. & Tomishige, K. Performance, structure and mechanism of Pd–Ag alloy catalyst for selective oxidation of glycerol to dihydroxyacetone. *J. Catal.* **300**, 205–216 (2013).
27. Garcia, A. C. et al. Strong impact of platinum surface structure on primary and secondary alcohol oxidation during electro-oxidation of glycerol. *ACS Catal.* **6**, 4491–4500 (2016).
28. Garcia, A. C., Birdja, Y. Y., Tremiliosi-Filho, G. & Koper, M. T. M. Glycerol electro-oxidation on bismuth-modified platinum single crystals. *J. Catal.* **346**, 117–124 (2017).
29. Dotan, H., Sivula, K., Gratzel, M., Rothschild, A. & Warren, S. C. Probing the photoelectrochemical properties of hematite (α -Fe₂O₃) electrodes using hydrogen peroxide as a hole scavenger. *Energy Environ. Sci.* **4**, 958–964 (2011).
30. Klahr, B., Gimenez, S., Fabregat-Santiago, F., Bisquert, J. & Hamann, T. W. Electrochemical and photoelectrochemical investigation of water oxidation with hematite electrodes. *Energy Environ. Sci.* **5**, 7626–7636 (2012).
31. Klahr, B., Gimenez, S., Zandi, O., Fabregat-Santiago, F. & Hamann, T. Competitive photoelectrochemical methanol and water oxidation with hematite electrodes. *ACS Appl. Mater. Interfaces* **7**, 7653–7660 (2015).
32. Heo, N., Jun, Y. & Park, J. H. Dye molecules in electrolytes: new approach for suppression of dye-desorption in dye-sensitized solar cells. *Sci. Rep.* **3**, 1712 (2013).
33. Palmisano, G. et al. Advances in selective conversions by heterogeneous photocatalysis. *Chem. Commun.* **46**, 7074–7089 (2010).
34. Kongjao, S., Damronglerd, S. & Hunsom, M. Electrochemical reforming of an acidic aqueous glycerol solution on Pt electrodes. *J. Appl. Electrochem.* **41**, 215–222 (2011).
35. Zhang, M. et al. Oxygen atom transfer in the photocatalytic oxidation of alcohols by TiO₂: oxygen isotope studies. *Angew. Chem. Int. Ed.* **48**, 6081–6084 (2009).
36. Vaz, A. D. N. & Coon, M. J. On the mechanism of action of cytochrome P450: evaluation of hydrogen abstraction in oxygen-dependent alcohol oxidation. *Biochemistry* **33**, 6442–6449 (1994).
37. Hu, W., Knight, D., Lowry, B. & Varma, A. Selective oxidation of glycerol to dihydroxyacetone over Pt–Bi/C catalyst: optimization of catalyst and reaction conditions. *Ind. Eng. Chem. Res.* **49**, 10876–10882 (2010).
38. Kim, T. W. & Choi, K.-S. Nanoporous BiVO₄ photoanodes with dual-layer oxygen evolution catalysts for solar water splitting. *Science* **343**, 990–994 (2014).
39. Kresse, G. & Furthmüller, J. Efficiency of ab-initio total energy calculations for metals and semiconductors using a plane-wave basis set. *Comput. Mater. Sci.* **6**, 15–50 (1996).
40. Kresse, G. & Furthmüller, J. Efficient iterative schemes for ab initio total-energy calculations using a plane-wave basis set. *Phys. Rev. B* **54**, 11169–11186 (1996).
41. Perdew, J. P., Burke, K. & Ernzerhof, M. Generalized gradient approximation made simple. *Phys. Rev. Lett.* **77**, 3865–3868 (1996).

Acknowledgements

This work was supported by the funds from the Singapore Ministry of Education Academic Research Fund (AcRF) Tier 1: RG115/18, RG115/17 and RG9/17, Tier 2: MOE2016-T2-2-004, the National Key Projects for Fundamental Research and Development of China (2017YFA0207301, 2016YFA0202804), the Strategic Priority Research Programme of the Chinese Academy of Sciences (XDB17020400), and the National Nature Science Foundation of China (21725102).

Author contributions

D.L. and B.L. conceived the project and designed the experiments. B.L. supervised the project. D.L. carried out experiments and data analysis. J.-C.L., H.X., and J.L. performed numerical calculation. W.C., J.M., and H.B.Y. contributed to catalyst characterization. Y. X. and Y.H. contributed to the manuscript preparation. D.L. and B.L. together wrote the manuscript. All authors commented on the final manuscript.

Additional information

Supplementary Information accompanies this paper at <https://doi.org/10.1038/s41467-019-09788-5>.

Competing interests: The authors declare no competing interests.

Reprints and permission information is available online at <http://npg.nature.com/reprintsandpermissions/>

Journal peer review information: *Nature Communications* thanks the anonymous reviewers for their contribution to the peer review of this work. Peer reviewer reports are available.

Publisher's note: Springer Nature remains neutral with regard to jurisdictional claims in published maps and institutional affiliations.



Open Access This article is licensed under a Creative Commons Attribution 4.0 International License, which permits use, sharing, adaptation, distribution and reproduction in any medium or format, as long as you give appropriate credit to the original author(s) and the source, provide a link to the Creative Commons license, and indicate if changes were made. The images or other third party material in this article are included in the article's Creative Commons license, unless indicated otherwise in a credit line to the material. If material is not included in the article's Creative Commons license and your intended use is not permitted by statutory regulation or exceeds the permitted use, you will need to obtain permission directly from the copyright holder. To view a copy of this license, visit <http://creativecommons.org/licenses/by/4.0/>.

© The Author(s) 2019