

## Studies of copper valence states with Cu $L_3$ x-ray-absorption spectroscopy

M. Grioni,\* J. B. Goedkoop, R. Schoorl, F. M. F. de Groot, and J. C. Fuggle  
*Research Institute for Materials, University of Nijmegen, 6525-ED Nijmegen, The Netherlands*

F. Schäfers and E. E. Koch  
*Berliner Elektronenspeicherring-Gesellschaft für Synchrotronstrahlung m.b.H (BESSY), Lentzeallee 100,  
 D-1000 Berlin 33, West Germany*

G. Rossi, J.-M. Esteve, and R. C. Karnatak  
*Laboratoire pour l'Utilisation du Rayonnement Electromagnetique (LURE), F-91405 Orsay CEDEX, France*  
 (Received 7 March 1988)

We have used x-ray-absorption spectroscopy to study a series of compounds in which Cu assumes a formal valence between 0 and 3. We find that the shape, the threshold energy, and the intensity of the Cu  $L_3$  absorption edge is strongly influenced by the chemical state of the Cu atoms. We use the Cu  $2p$  x-ray-absorption spectra of a large number of Cu compounds, including sulfides, oxides, La-Sr-Cu-O compounds, a phthalocyanine complex, and various minerals to show that the presence of a strong  $2p$ - $3d$  excitonic transition is a fingerprint of the Cu( $d^9$ ) contribution to the ground state. A simple ionic picture is generally inadequate to describe these compounds.

### I. INTRODUCTION

The nature of the electronic structure and bonding in Cu compounds is a matter of intrinsic interest which has gained added impetus since the discovery of high-temperature superconductivity in a class of Cu oxides. If Cu compounds were purely ionic then Cu<sup>0</sup>, Cu<sup>I</sup>, Cu<sup>II</sup>, and Cu<sup>III</sup> compounds would have the configurations (Ar) $3d^{10}4s^1$ , (Ar) $3d^{10}4s^0$ , (Ar) $3d^9 4s^0$ , and (Ar) $3d^8 4s^0$ , respectively. However, Cu belongs to the group-*B* metallic elements, which are much more electronegative than the group-*A* metals, i.e., the effective nuclear charge felt by the  $4s$  electrons is larger in elements such as Cu, Zn, etc. than in Na, Ca, etc. As a consequence group-*B* elements show enhanced affinity for highly polarizable anions<sup>1</sup> and a marked tendency to covalency.<sup>2</sup> Further, as recognized for many decades,<sup>2</sup> the covalency in compounds of the group-*B* metals increases with increasing valency, i.e., the sharing of electrons between metal and ligand atoms can lead to nonintegral values for the number of electrons on the metal atoms. It should also be noted that inorganic chemists have for several decades known that the  $3d^{10}$  configuration of Cu<sup>I</sup> should not be regarded as inert but that the  $d$  electrons are also important for bonding in these compounds.<sup>3</sup> Thus, a discussion of whether Cu is present as Cu<sup>0</sup>, Cu<sup>+</sup>, Cu<sup>2+</sup>, or Cu<sup>3+</sup> in a given compound is rather sterile as it is probably never present in precisely these ionic states. A discussion of whether Cu is monovalent (Cu<sup>I</sup>), divalent (Cu<sup>II</sup>), etc. may be relevant when the partner elements in a compound have variable valence,<sup>3</sup> but most relevant is simply the question of the weights of the Cu configurations  $d^8$ ,  $d^9$ ,  $d^{10}$ , and  $d^{10} 4s^1$ .

High-energy spectroscopies [x-ray photoelectron spectroscopy (XPS), x-ray-absorption spectroscopy (XAS), Auger-electron spectroscopy (AES), and bremsstrahlung isochromat spectroscopy (BIS)] are well suited to provide

information on these points, as proved, for instance, by the breakthroughs obtained in studies of the lanthanides and of transition-metal compounds.<sup>4-12</sup> XAS, in particular, offers several advantages over the other techniques, not only because of its site selectivity, which it shares with XPS core-level studies, but also because of the role of selection rules, which often lead to a simpler theoretical treatment of the data.<sup>12-15</sup> In addition, the surface sensitivity of XAS in the photoyield mode is, to some extent, tunable. We use the total-electron-yield mode which probes a layer some hundreds of angstroms thick, so that the surface cleanliness is less critical, and which gives a strong signal so that measurement times are short. The situation is particularly clearcut for the  $2p$  ( $L_{2,3}$ ) absorption edge of Cu as transitions to the  $3d$  states are possible in Cu<sup>II</sup> (and Cu<sup>III</sup>) but not in Cu<sup>I</sup> compounds. In this paper we underline the potential utility of Cu  $L_3$  XAS for determination of the Cu ground-state configuration and we give some examples of a qualitative exploitation of the technique.

### II. EXPERIMENT

Measurements of the Cu  $L_2$  and  $L_3$  edges were made at the Berliner Elektronenspeicherring-Gesellschaft für Synchrotronstrahlung (BESSY) and les Anneux de Collisions de l'Accélérateur Linéaire (ACO) storage rings using synchrotron radiation. The radiation was in both cases monochromatized using double-crystal monochromators equipped with beryl crystals,<sup>16,17</sup> which gave an energy resolution of  $\sim 400$  meV at the Cu  $L_3$  edges ( $\sim 932$  eV) and absorption spectra were collected in the total-yield mode. The vacuum during the XAS measurements was often as low as  $2 \times 10^{-10}$  torr, but this could only be achieved after bakeout, and in some cases where the compounds were sensitive to heat, the bakeout procedure was

omitted and the pressure was  $\sim 10^{-9}$  torr. XPS studies were made in ultrahigh vacuum using monochromatized Al  $K\alpha$  radiation from a large-solid-angle (0.1 sr) quartz-crystal monochromator custom built by Vacuum Science Workshop.  $\text{Cu}_2\text{O}$ ,  $\text{CuFeS}_2$  (chalcopyrite),  $\text{CuS}$  (covellite),  $\text{Cu}_{1.8}\text{S}$  (digenite),  $\text{Cu}_2\text{S}$  (chalcocite),  $\text{Cu}_3\text{As}$  (domeykite), and  $\text{Cu}_3\text{AsS}_4$  (enargite) were natural minerals. For these samples, and Cu metal, a clean surface, as shown by XPS, was prepared by scraping the surface in vacuum.  $\text{La}_2\text{CuO}_4$  and  $\text{La}_{1.8}\text{Sr}_{0.2}\text{CuO}_4$  were sintered disks and were not baked. XPS showed that these samples were free of surface carbon, hydroxide, and other detectable impurities after thorough scraping. The commercial CuO powder samples and ground powder samples of the minerals malachite ( $\text{Cu}_2[(\text{OH})_2\text{CO}_3]$ ), turquoise ( $\text{CuAl}_6[\text{OHPO}_4]_4 \cdot 3\text{H}_2\text{O}$ ) chrysocolla ( $\text{CuSiO}_3 \cdot n\text{H}_2\text{O}$ ), and diopside [ $\text{Cu}_3(\text{Si}_3\text{O}_9) \cdot 3\text{H}_2\text{O}$ ] were pressed on to an Al sample holder. XPS showed the presence of some carbon on the CuO surface, but this should not influence the XAS spectra, where the probing depth is larger than in XPS. We had no access to methods to detect loss of water from the minerals which contain water, but include the spectra for completeness. Beam damage is in principle feasible for these samples, but the photon doses are smaller in this experiment than in XPS and no time dependence of the spectra was detected.

### III. RESULTS AND INTERPRETATION

For the present discussion it is sufficient to consider the Cu  $L_3$  edge. Figure 1 shows the Cu  $L_3$  absorption edges of CuO (formally  $\text{Cu}^{\text{II}}$ ),  $\text{Cu}_3\text{As}$  (formally  $\text{Cu}^{\text{I}}$ ) and Cu metal (formally  $\text{Cu}^0$ ). The relative intensities of the spectra have been normalized to the peak height, after subtraction of a sloping background which was extrapolated from the linear region below the threshold.

The spectra of Fig. 1 exhibit important differences related to the different configuration of Cu atoms in the three samples. The  $L_3$  edge of CuO has a strong peak at 931.3 eV. The origin of this feature is now well understood: a Cu  $2p$  electron is excited from the  $2p$  level to the empty  $3d$  bands, but the effect of the Coulomb interaction between the strongly localized  $2p$  hole and the rather small Cu  $3d$  orbital is to localize the extra  $3d$  electron. The final state is thus a "core exciton," in some ways like a Frenkel exciton.<sup>18,19</sup> Similar peaks are expected whenever a core electron is excited into a narrow ( $d$  or  $f$ ) band and have been found in many rare-earth<sup>14</sup> and transition-metal compounds. The observation that the Cu  $L_3$  XAS peak of CuO is below the XPS binding energy (marked with a vertical arrow) is itself proof that the peak is not a density-of-states feature, although the density of states of CuO does show a sharp peak just above the Fermi level. The intensity of this peak is related to the total amount of Cu  $3d$  character in the unoccupied states.

The spectra of "monovalent" Cu in  $\text{Cu}_3\text{As}$  and Cu metal do not show such a peak because the  $d$  shell is essentially full. The absorption edge is  $\sim 3$  times weaker on an absolute scale<sup>20</sup> because the matrix elements for the  $2p$ - $4s$  transitions are smaller than those for the  $2p$ - $3d$  process<sup>21</sup> and the  $4s$  bands are broad (although see comments

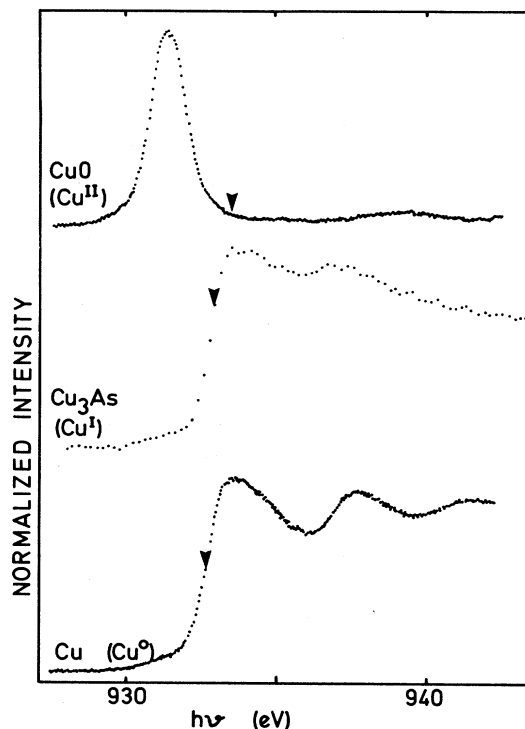


FIG. 1. XAS spectra of Cu,  $\text{Cu}_3\text{As}$ , and CuO at the Cu  $L_3$  edge. The arrows mark the position of the main peak Cu  $L_3$  peak binding energy in XPS, relative to  $E_F$ , and the combined error limits for alignment of XPS and XAS energy scales are  $\sim 0.5$  eV. The spectra have been arbitrarily scaled to give the same peak height.

in the next paragraph). Because the  $4s$  wave function is more extended than that of the  $3d$  orbital, the core-hole potential has much less effect on the spectral shape and the observed XAS of Cu bears a close resemblance to the calculated total density of Cu states<sup>22-25</sup> (although the  $L_3$  absorption only probes  $s$  and  $d$  states). Also, the XAS threshold energy is in agreement with the Cu  $2p_{3/2}$  binding energy as determined by XPS.

The data in Fig. 1 support the idea that one could use the presence of a sharp peak in the Cu  $L_3$  spectrum, below the XPS threshold, as a measure of the amount of unoccupied Cu  $3d$  character in the initial states. However, in answering this question we must be careful to define what we mean by a  $d$  count. The problem may be illustrated by comparison with Ni. Ni is well known to have approximately 9.4 electrons per atom in the bands with predominantly Ni  $d$  character, but because of hybridization with the  $s$  states the  $3d$  character in the occupied " $d$  band" only adds up to 8.8 electrons per atom.<sup>26</sup> Likewise, for Cu metal where the Cu " $3d$  band" itself is clearly full, analysis shows  $3d$  character adding up to 9.6  $3d$  electrons per Cu atom.<sup>27</sup> The  $\sim 0.4$   $3d$  holes of Cu metal must contribute to the intensity of the  $L_{2,3}$  edges in Cu. This partly explains why the Cu  $L_3$  edge of bulk copper is much more intense than the structures which occur above the large peak in CuO and which probably result from transitions into  $4s$  states not hybridized with Cu  $3d$  states. However, it is probably not the whole explanation

as the extra intensity extends to high energies above  $E_F$  where no  $3d$  weight can be expected.

We present in Figs. 2 and 3 spectra from a wide range of Cu compounds. First, we consider Fig. 2 where the spectra of many compounds with nominally monovalent, or zero valent Cu are collected. Few of these bear much resemblance to the spectra of divalent Cu in CuO, while all of the  $\text{Cu}^{\text{II}}$  compounds shown in Fig. 3 do show a large peak. Note that of all the spectra in Fig. 2, only CuS and  $\text{Cu}_{1.8}\text{S}$  show real intensity below the arrows marking the Cu  $2p_{3/2}$  binding energies found by XPS. At least for CuS there is indication from the crystal structure that  $\frac{1}{3}$  of the Cu atoms could be described as  $\text{Cu}^{\text{II}}$  (Ref. 28, p. 907) (the shoulder at  $\sim 931$  eV in  $\text{Cu}_2\text{S}$  is probably due to CuO impurity). For the rest of the materials the structure in the Cu  $L_3$  edges can probably be explained by structure in the single-particle density of

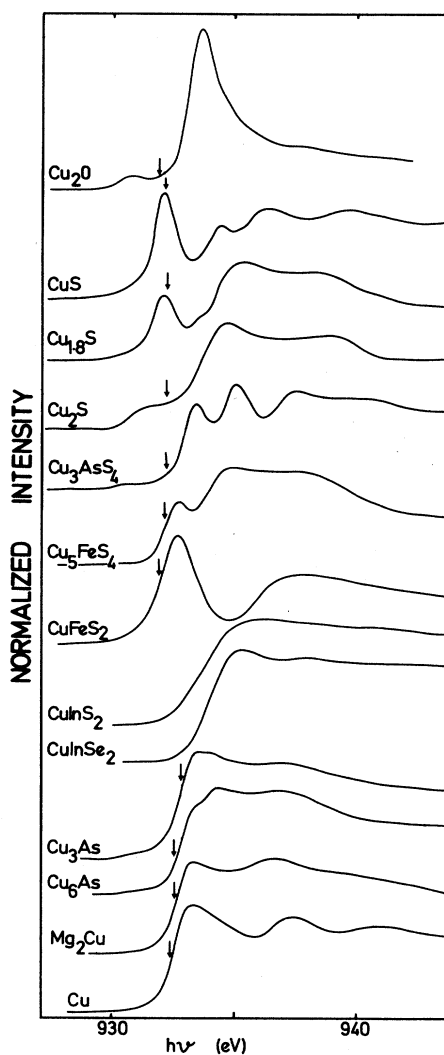


FIG. 2. Cu  $L_3$  XAS spectra of Cu compounds. The spectra have been arbitrarily scaled to give the same peak heights, except for  $\text{Cu}_2\text{O}$ , which was clearly stronger than the other materials. The arrows mark the main XPS  $L_3$  binding energies, as for Fig. 1.

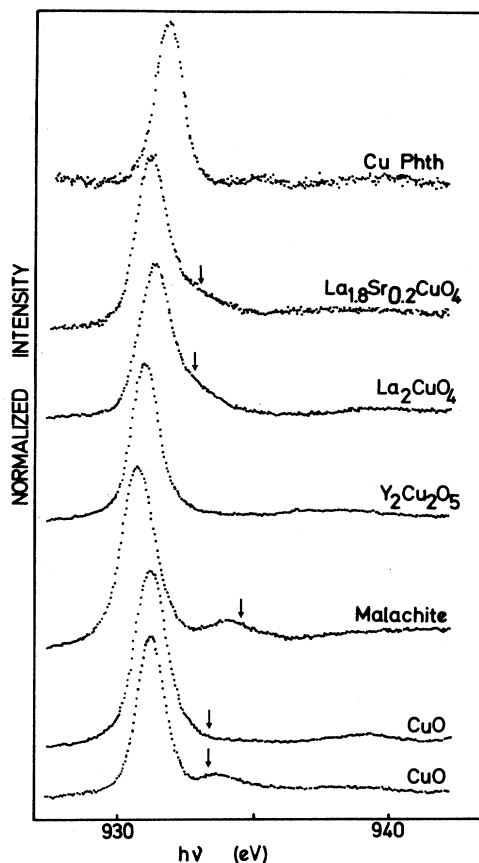


FIG. 3. Cu  $L_3$  XAS spectra of some divalent Cu compounds. Arrows mark the Cu  $L_3$  peak binding energies in XPS, as for Fig. 1.

states appropriate to the Cu site and some of these details will be discussed more fully in later publications.

The spectrum of  $\text{Cu}_2\text{O}$  in Fig. 2 is one of the most complicated to interpret and illustrates very well the dangers of equating a single atomic configuration,  $d^{10}$ , with a particular valence,  $\text{Cu}^{\text{I}}$ . The small peak in the spectrum at 931 eV is a spurious feature, attributed to CuO impurities because of its energy and the variation in intensity from sample to sample. The peak at 933.7 eV is asymmetric and is followed by a plateau with weak structure on its high-energy side. Recent augmented-spherical-wave (ASW) band-structure calculations indicate an amount of  $d$  character in the unoccupied states that is unusually large for a  $\text{Cu}^{\text{I}}$  compound and show a sharp peak in the conduction bands.<sup>25</sup> We thus attribute the large intensity of this peak a few electron volts above threshold to the  $2p$ - $3d$  channel. The amount of unoccupied  $d$  character, and hence, the strength of the XAS peak, is certainly related to the unusual structure of  $\text{Cu}_2\text{O}$  in which the Cu is linearly coordinated to only two oxygen nearest neighbors.<sup>29</sup>

Figure 3 gives the Cu  $L_3$  spectra of a number of  $\text{Cu}^{\text{II}}$  compounds. A strong peak is always observed just below the threshold as defined by the XPS binding energy. In every case we attribute this peak to  $2p$ - $3d$  character in the excitations which dwarves the  $2p$ - $4s$  signal. Many of the

spectra in Fig. 3 exhibit small peaks and tails on the high-binding-energy side of the main peaks. In some cases these may be attributed to structure in the unoccupied density of states. However, we do not wish to attach undue significance to these peaks because we found small variations in the peaks from one sample to another. An example of this is CuO, itself, where some commercial samples exhibited a small peak at  $\sim 934$  eV.

For CuO,  $Y_2Cu_2O_5$ ,  $La_2CuO_4$ , and malachite, as well as for turquoise, chrysocolla, and diopside the formal Cu valence derived from the stoichiometry is clearly 2 and we would expect a strong contribution of the Cu  $d^9$  configuration to the ground state, even if some of the minerals probably lose some of their water of crystallization in the vacuum. This expectation is reflected in the intensity of the observed peaks (only a representative sample is shown in Fig. 3, but all showed the strong peak). Note, however, that even in CuO the number of Cu  $3d$  electrons has been estimated from XPS satellite intensities to be as high as 9.3.<sup>9,30</sup> Without a satisfactory method of absolute normalization of the spectra, and a standard for which we have absolutely reliable values for the number of Cu  $3d$  holes in the ground state, we can only say that these spectra indicate a large and probably majority contribution of the Cu  $3d^9$  configuration to the ground state. The same is true of Cu in Cu-phtalocyanine (CuPc) which has been the subject of some debate<sup>31-33</sup> and will be further discussed elsewhere. The formal oxidation number of Cu in  $La_{1.85}Sr_{0.15}CuO_4$  is larger than 2 but we see no evidence for a Cu  $d^8$  contribution to the ground state in this spectrum. (See, e.g., Refs. 34-36 for further discussion of this point.)

#### IV. CONCLUDING REMARKS

We have reported the  $L_3$  XAS spectra of a large number of compounds in which Cu has an oxidation number of 0, 1, 2, or 3. We always find a sharp peak in the spectra when the oxidation number of the Cu is 2 or more. We attribute the sharp peak to transitions with largely  $2p \rightarrow 3d$  character. Because the peak is always found below the threshold as defined by XPS, we do not believe

it can be explained by density-of-states (DOS) effects alone (although we would expect divalent Cu to have a high density of unoccupied Cu  $3d$  states just above  $E_F$ ). In principle, the strength of this peak could be used as a monitor of the amount of Cu  $3d$  character in the unoccupied states. We note that the strength of the  $L_3$  edges in  $Cu^0$  and  $Cu^I$  compounds is too great to be explained by  $2p \rightarrow 4s$  transitions alone and we attribute part of the intensity of these edges to Cu  $3d$  character in the unoccupied states as a result of  $3d-4s$  hybridization. This is particularly true for  $Cu_2O$ , where the extra intensity is all very close to threshold. In other materials, such as Cu, unexplained intensity continues to much higher energies and cannot all be accounted for by Cu  $3d$  character in the unoccupied states. However, the case of  $Cu_2O$  illustrates very clearly that the atomic configuration labels Cu  $d^9$ , Cu  $d^{10}$ , and Cu  $d^{10} 4s$  should not be applied too literally to  $Cu^0$ ,  $Cu^I$ , and  $Cu^{II}$  compounds.

#### ACKNOWLEDGMENTS

We are grateful to the Laboratoire pour l'utilisation du Rayonnement Electromagnetique (LURE) technical staff for their valuable aid and to the Group Anneau du Laboratoire de l'accélérateur Linéaire, Orsay, for their help in operating the machine, and also the the Berlin Elektronenspeicherring für Synchrotronstrahlung for access to facilities. We also thank Mr. P. Bariand, curator of the Mineralogy Collection of the Université Pierre et Marie Curie, Paris, for his generous loan of samples, without which this work would not have been possible, and A. A. Menovsky for a sample of  $Y_2Cu_2O_5$ . Discussions with G. A. Sawatzky were always exciting and much appreciated. This work was supported financially by the Netherlands Foundation for Chemical Research (SON) with financial aid from the Netherland Organization for the Advancement of Pure Research (ZWO), the Foundation for Fundamental Research into Material (FOM) and the Committee for the European Development of Science and Technology (CODEST) program and by the Centre Nationale de la Recherche Scientifique (CNRS), France.

\*Permanent address: Laboratoire pour l'Utilisation du Rayonnement Electromagnetique (LURE), Bâtiment 209d F-91405 Orsay CÉDEX, France.

<sup>1</sup>See e.g., S. Ahrland, J. Chatt, and N. R. Davies, *Rev. Chem. Soc.* **11**, 265 (1958); R. G. Pearson, *J. Am. Chem. Soc.* **85**, 3533 (1963); *Science* **151**, 172 (1966).

<sup>2</sup>K. Fajans and G. Joos, *Z. Phys.* **23**, 1 (1923); K. Fajans, *Naturwissenschaften* **11**, 165 (1923); *Z. Krystallogr.* **61**, 18 (1924).

<sup>3</sup>See N. V. Sidgwick, *The Chemical Elements and their Compounds* (Clarendon, Oxford, 1950), p. 103.

<sup>4</sup>For a recent review, see *Narrow-Band Phenomena*, edited by J. C. Fuggle, G. A. Sawatzky, and J. W. Allen (Plenum, New York, 1988).

<sup>5</sup>J. C. Fuggle, F. U. Hillebrecht, J.-M. Esteva, R. C. Karnatak, O. Gunnarsson, and K. Schönhammer, *Phys. Rev. B* **27**, 4637 (1983); O. Gunnarsson, K. Schönhammer, J. C. Fuggle, F. U.

Hillebrecht, J.-M. Esteva, R. C. Karnatak, and B. Hillebrand, *ibid.* **28**, 330 (1983); J. C. Fuggle, *Physica B* **130**, 56 (1985); and references therein.

<sup>6</sup>J. W. Allen, S. J. Oh, O. Gunnarsson, K. Schönhammer, M. B. Maple, M. S. Torikachvili, and I. Lindau, *Adv. Phys.* **35**, 275 (1986), and references therein.

<sup>7</sup>A. Fujimori, *Phys. Rev. B* **27**, 3992 (1983); **28**, 2881 (1983); **28**, 4489 (1983).

<sup>8</sup>A. Kotani and Y. Toyozawa, *J. Phys. Soc. Jpn.* **35**, 1073 (1973); **35**, 1082 (1973).

<sup>9</sup>G. v. der Laan, C. Westra, and G. A. Sawatzky, *Phys. Rev. B* **23**, 4369 (1981).

<sup>10</sup>G. A. Sawatzky, in *Studies in Inorganic Chemistry*, edited by J. Schoonman (Elsevier, Amsterdam, 1983), Vol. 3, p. 3.

<sup>11</sup>G. van der Laan, J. Zaanen, G. A. Sawatzky, R. Karnatak, and J.-M. Esteva, *Phys. Rev. B* **33**, 4253 (1986).

<sup>12</sup>G. van der Laan, J. Zaanen, G. A. Sawatzky, R. Karnatak,

- and J.-M. Esteva, *Solid State Commun.* **56**, 673 (1985).
- <sup>13</sup>B. T. Thole, R. D. Cowan, G. A. Sawatzky, J. Fink, and J. C. Fuggle, *Phys. Rev. B* **31**, 6856 (1985).
- <sup>14</sup>B. T. Thole, G. van der Laan, J. C. Fuggle, G. A. Sawatzky, R. C. Karnatak, and J.-M. Esteva, *Phys. Rev. B* **32**, 5107 (1985), and references therein.
- <sup>15</sup>G. van der Laan, B. T. Thole, G. A. Sawatzky, J. C. Fuggle, R. Karnatak, J.-M. Esteva, and B. Lengeler, *J. Phys. C* **19**, 817 (1986).
- <sup>16</sup>M. Lemonnier, O. Collet, C. Depautex, J.-M. Esteva, and D. Raoux, *Nucl. Instrum. Methods* **152**, 109 (1978).
- <sup>17</sup>J. Feldhaus, F. Schifers, and W. Peatman, *Proc. SPIE* (to be published).
- <sup>18</sup>S. T. Pantelides, *Phys. Rev. B* **11**, 2391 (1975).
- <sup>19</sup>H. P. Hjalmarson, H. Büttner, and J. D. Dow, *Phys. Rev. B* **24**, 6010 (1981).
- <sup>20</sup>We have not yet been able to devise a reliable, absolute normalization procedure for XAS in the total-yield mode. The signal is dependent not only on known factors, such as the number of photons transmitted by the monochromator and the atomic concentration of copper, but also on intricate, material-dependent details of the cascade processes following core-hole creation and the escape depths of electrons of a multitude of different kinetic energies. Even the pre-edge background is due to absorption from all the atomic species present so that it is necessary to rely on independent measurements and assumptions regarding the atomic cross sections (e.g., for O) and the solid-state effects. Moreover, the measured edge-background ratio for given material depends on the experimental conditions (e.g., angle between sample normal and the detector, rocking-curve adjustments in the monochromator, etc.). The value quoted for the relative intensity is an average estimate from several measurements in which the measurement conditions (angles, etc.) are kept similar. It is obtained by scaling Cu II and Cu or Cu I spectra to the same intensity over background several electron volts above the edge. A similar value is obtained by scaling the Cu and CuO spectra in the same preedge background intensity, after a correction is made for O absorption in CuO and after edge and/or background variations in different measurements are averaged out. Given the inaccuracies in both methods, not too much importance should be attached to the exact number, which just expresses the fact that  $I(\text{white line}) > I(\text{step}) \gg I(2p-4s \text{ in CuII})$ .
- <sup>21</sup>R. D. Cowan, in *The Theory of Atomic Structure and Spectra* (University of California, Berkeley, 1981).
- <sup>22</sup>D. van der Marel, G. A. Sawatzky, R. Zeller, F. U. Hillebrecht, and J. C. Fuggle, *Solid State Commun.* **50**, 47 (1984).
- <sup>23</sup>W. Speier, J. C. Fuggle, R. Zeller, B. Ackerman, K. Szot, F. U. Hillebrecht, and M. Campagna, *Phys. Rev. B* **30**, 6921 (1984).
- <sup>24</sup>L. A. Grunes, *Phys. Rev. B* **27**, 2111 (1983).
- <sup>25</sup>M. Czyzyk (private communication).
- <sup>26</sup>J. C. Fuggle, F. U. Hillebrecht, R. Zeller, Z. Zolnierrek, P. A. Bennett, and C. Freiburg, *Phys. Rev. B* **27**, 2145 (1983) and references therein; L. Hodges, H. Ehrenreich, and N. D. Lang, *Phys. Rev.* **152**, 505 (1966).
- <sup>27</sup>A. R. Williams and N. D. Lang, *Phys. Rev. Lett.* **40**, 954 (1978).
- <sup>28</sup>See, e.g. A. F. Wells, in *Structural Inorganic Chemistry*, 4th ed. (Clarendon, Oxford, 1975), p. 30.
- <sup>29</sup>See also S. L. Hubert, B. A. Bunker, F. C. Brown, and P. Pianetta, *Phys. Rev. B* **30**, 2120 (1984).
- <sup>30</sup>Z. X. Shen, J. W. Allen, J. J. Yeh, J. S. Kang, W. Ellis, W. Spicer, I. Lindau, and M. B. Maple, P. D. Dalichaouch, M. S. Torikachvili, J. Z. Sun, and T. H. Geballe, *Phys. Rev. B* **36**, 8414 (1988).
- <sup>31</sup>M. Iwan, E. E. Koch, T. C. Chiang, D. E. Eastman, and F. J. Himpsel, *Solid State Commun.* **34**, 57 (1980).
- <sup>32</sup>E. E. Koch, Y. Jugnet, and F. J. Himpsel, *Chem. Phys. Lett.* **116**, 7 (1985).
- <sup>33</sup>S. Lee, M. Yudkowsky, W. P. Halperin, M. Y. Ogawa, and B. M. Hoffman, *Phys. Rev. B* **35**, 5003 (1987).
- <sup>34</sup>N. Nücker, J. Fink, B. Renker, D. Ewert, P. J. W. Weijs, and J. C. Fuggle, *Jpn. J. Appl. Phys. Suppl.* **26-3**, 1015 (1987); J. C. Fuggle, P. J. W. Weijs, R. Schoorl, G. A. Sawatzky, J. Fink, N. Nücker, P. J. Durham, and W. Temmerman, *Phys. Rev. B* **37**, 123 (1988); M. Grioni, J. C. Fuggle, P. J. W. Weijs, J. B. Goedkoop, G. Rossi, F. Schaefer, J. Fink, and N. Nücker, *J. Phys. (Paris)* **48**, C9-1189 (1987).
- <sup>35</sup>F. Baudelet, G. Collin, E. Dartyge, A. Fontaine, G. P. Kappler, G. Krill, J. P. Itie, J. Jegoudez, M. Maurer, P. Monod, A. Revcoleschi, H. Tolentino, G. Tourrillon, and M. Verdaguer, *J. Phys. (Paris)* (to be published).
- <sup>36</sup>A. Bianconi, A. Congiu Castellano, S. Della Longa, M. De Santis, A. Di Cicco, K. Garg, P. Delogu, A. Gargano, A. Clozza, R. Giorgi, P. Lagarde, A. M. Flank, and A. Marcelli, *J. Phys. (Paris) Colloq.* **48**, C9-1179 (1987).