

 Open access • Journal Article • DOI:10.2174/1874088X01004020009

## Study of the Bandgap of Synthesized Titanium Dioxide Nanoparticules Using the Sol-Gel Method and a Hydrothermal Treatment~!2009-10-14~!2009-10-30~!2010-01-27~!

— [Source link](#) 

Sergio Valencia, Juan M. Marín, Gloria Restrepo

**Published on:** 17 Feb 2010 - The Open Materials Science Journal

**Topics:** Titanium dioxide and Sol-gel

Related papers:

- [Study of the Bandgap of Synthesized Titanium Dioxide Nanoparticules Using the Sol-Gel Method and a Hydrothermal Treatment](#)
- [Electrochemical Photolysis of Water at a Semiconductor Electrode](#)
- [Titanium Dioxide Nanomaterials: Synthesis, Properties, Modifications, and Applications](#)
- [A low-cost, high-efficiency solar cell based on dye-sensitized colloidal TiO<sub>2</sub> films](#)
- [Photocatalysis on TiO<sub>2</sub> Surfaces - Principles, Mechanisms, and Selected Results](#)

Share this paper:    

View more about this paper here: <https://typeset.io/papers/study-of-the-bandgap-of-synthesized-titanium-dioxide-4qjnpjyfs7>

# Study of the Bandgap of Synthesized Titanium Dioxide Nanoparticules Using the Sol-Gel Method and a Hydrothermal Treatment

Sergio Valencia, Juan Miguel Marín and Gloria Restrepo\*

*Applied Physical Chemistry Processes, University of Antioquia, Medellin, Colombia*

**Abstract:** In this work optical properties of titanium dioxide nanoparticles were studied. Titanium dioxide nanoparticles were synthesized by the sol-gel method followed by a hydrothermal treatment using tetraisopropyl orthotitanate (TIOT) and 2-propanol. The synthesized samples were characterized by X-ray diffraction (XRD), UV-Vis diffuse reflectance spectroscopy (UV/DRS) and nitrogen adsorption-desorption methods. The bandgap energy was obtained using the Kubelka-Munk reemission function. The catalyst synthesized with a molar ratio of  $R_1$  (water/TIOT) = 3.5 and  $R_2$  (2-propanol/TIOT) = 15 has a predominately anatase phase. It also has a high photo degradation of methyl orange compared to TiO<sub>2</sub> Degussa P-25. A shift band gap energy of 3.27 was observed.

**Keywords:** Titanium dioxide, hydrothermal treatment, sol-gel method, band gap.

## 1. INTRODUCTION

Titanium oxide (TiO<sub>2</sub>) is a material with wide application due to its optical and electronic properties. It is used as an ingredient in sunscreen lotions and food products, as a pigment in paints and as semiconductors in the photocatalytic degradation of organic compounds [1]. In TiO<sub>2</sub>, the crystalline phase, the composition and the surface states strongly affect the electronic structure and the charge properties [2]. The photocatalytic activity of TiO<sub>2</sub> depends on its present phase. There are three crystalline forms of TiO<sub>2</sub>: anatase, rutile and brookite. Anatase phase is metastable and has the greater photocatalytic activity; rutile has a high chemical stability but is less active [3,4]. Besides, some TiO<sub>2</sub> with a large quantity of anatase and a small quantity of rutile exhibits a higher photocatalytic activity than in the pure anatase or rutile phases [2,5]. The absorption spectrum of a semiconductor defines its possible uses. The useful semiconductors for photocatalysis have a bandgap comparable to the energy of the photons of visible or ultraviolet light, having a value of  $E_g < 3.5$  eV. The majority of authors have determined that in TiO<sub>2</sub> the rutile has a direct band gap of 3.06 eV and an indirect one of 3.10 eV and the anatase has only an indirect band gap of 3.23 eV [6,7]. However, Reddy's work [1] shows that a bandgap of anatase phase from the plot for indirect transition are quite low (2.95 – 2.98 eV), which led them, contrary to the other authors, to conclude that the direct transition is more favorable for TiO<sub>2</sub> nanoparticles with anatase phase. There have been reported values in the literature from 2.86 to 3.34 eV for the anatase phase, the differences being attributed to variations in the stoichiometric of the synthesis, the impurities content, the crystalline size and the type of electronic transition [8,9]. In this work the optical properties are evaluated in context of the bandgap of the synthesized TiO<sub>2</sub> samples with the sol-gel

method and the hydrothermal treatment, using a crystallization temperature of 200°C for 2 hours, and TIOT as precursor [8,10-14]. The bandgap was calculated by means of the reflectance diffusion technique, which shows an abrupt increase in the absorbance of the longitude or the wave corresponding to the energy of the prohibited band.

## 2. MATERIALS AND METHODS

### 2.1. Reactives

Tetraisopropyl orthotitanate (TIOT), 2-propanol and hydrochloric acid are from Merck, methyl orange from Carlo Erba, titanium dioxide P-25 Degussa and Milli-q water.

### 2.2. Preparation of the Samples

The titanium precursor TIOT and water were added dropwise into the 2-propanol solvent, continuously stirring for 2 hours, after that 3 drops of HCl 3M was added. For the crystallization under autogenous pressure the solution obtained was put in a steel-teflon reactor and heated to 200°C for 2 hours, after which the sample was filtered and washed with 30 mL of 2-propanol and was dried at 100°C for 1 hour. In order to study the effect of some variables on the synthesis of TiO<sub>2</sub> a 3<sup>2</sup> factorial design was used, with  $R_1$  (water/TIOT) and  $R_2$  (water/TIOT) as factors with the levels 2.85, 3.5, 60 and 10, 15, 20, respectively (Table 1).

### 2.3. Characterization

XRD analysis was performed using an x-ray diffractometer (Rigaku Miniflex) with Cu-K $\alpha$  radiation in 2 $\theta$  range from 10° to 60°; the reflectance diffusion spectrum UV-Vis (UV/DRS) was obtained using a UV-Vis Evolution 600 spectrometer, a thermo Electron Corporation with a reflectance diffuse accessory; the superficial area of Brunauer-Emmett-Teller was determined using a Gemini V Miromerities.

### 2.4. Photocatalytic Activity Measurements

In order to evaluate the photocatalytic activity of each of the synthesized TiO<sub>2</sub>, 37.5 mg of TiO<sub>2</sub> was added in 250 mL

\*Address correspondence to this author at the Applied Physical Chemistry Processes, University of Antioquia, Medellin, Colombia; Tel: 57 4 2196578; Fax: 57 4 2196543; E-mail: gloma@udea.edu.co

of methyl orange solution with initial concentration of 20 ppm for a TiO<sub>2</sub> amount of 0.15 g/L. A test of photolysis for one hour showed no degradation. The photocatalytic experiments were began after the adsorption equilibrium was obtained, in one hour. After that the lamps were turned on for 7 hours, samples were withdrawn each hour and analyzed by UV-Vis spectrometer using a wavelength of 464 nm. A BLB lamp of 25 W/cm<sup>2</sup> with emissions between 300 and 400 nm with a maximum at 360 nm was used as irradiation supply. All experiments were carried out with an aeration system in order to maintain the reaction system saturated with oxygen.


**Table 1.** 3<sup>2</sup> Factorial Designs for the TiO<sub>2</sub> Synthesis by Sol-Gel Method and Hydrothermal Technique at 200°C for 2 Hours, Using TIOT as Precursor

Experiment	R <sub>1</sub> (water/TIOT)	R <sub>2</sub> (2-propanol/TIOT)
M1	2.85	10.0
M2	2.85	15.0
M3	2.85	20.0
M4	3.50	10.0
M5	3.50	15.0
M6	3.50	20.0
M7	6.00	10.0
M8	6.00	15.0
M9	6.00	20.0


### 3. RESULTS AND DISCUSSION

Fig. (1) shows XRD spectrums of the synthesized TiO<sub>2</sub> samples, four characteristic peaks of TiO<sub>2</sub> are detected corresponding to the anatase phase [4,15]. As can be observed in Fig. (1), formation of the anatase phase and its crystallinity indicates a high dependence on the molar ratio water/TIOT; sample M5 with a quantity of water close to the stoichiometric ratio (R<sub>1</sub>(water/TIOT)= 3.5 and R<sub>2</sub>(2-propanol/TIOT)= 15) shows the characteristic peak of the anatase phase with higher intensity and narrower. Upon augmenting the quantity of water above the stoichiometric ratio with R<sub>1</sub>(water/TIOT) = 6 and varying the molar ratio 2-propanol/TIOT with R<sub>2</sub>(2-propanol/TIOT) = 10, 15, 20 materials were obtained with a less intense peak in the anatase phase, see Fig. (1) for M7, M8 and M9; this is due to the strong reactions of hydrolysis. In Fig. (2), a decreasing of the peak intensity of the anatase phase in materials with quantities of water below the stoichiometric ratio (R<sub>1</sub>(water/TIOT)= 0.17 and R<sub>2</sub>(2-propanol/TIOT)= 10) was observed and an amorphous material was obtained due to limited hydrolysis of the TIOT precursor [3,16].

For the study of the optical properties of the synthesized TiO<sub>2</sub> nanoparticles, the bandgap and the type of electronic transition were determined, which were calculated by means of the optic absorption spectrum [17]. When a semiconductor absorbs photons of energy larger than the gap of the semiconductor, an electron is transferred from the valence band to the conduction band where there occurs an abrupt increase in the absorbency of the material to the wavelength corresponding to the band gap energy. The relation of the

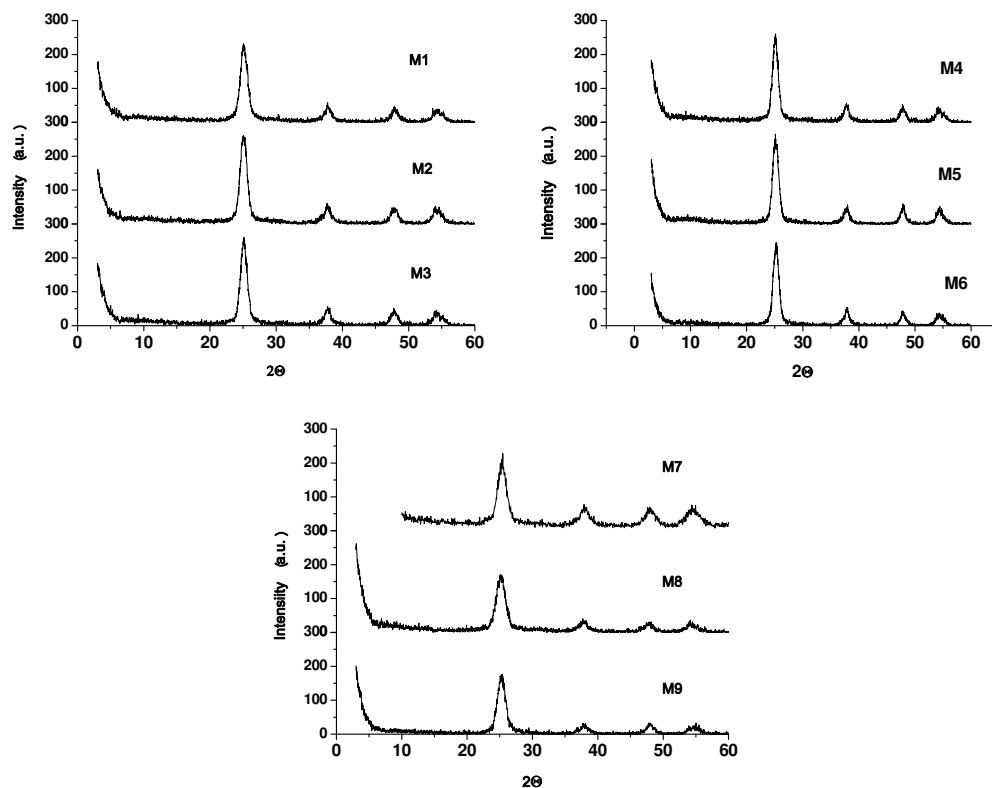

**Fig. (1).** XRD patterns of the TiO<sub>2</sub> dioxides synthesized by sol-gel method and the hydrothermal treatment at different molar ratios of R<sub>1</sub> (water/TIOT) and R<sub>2</sub> (2-propanol/TIOT).

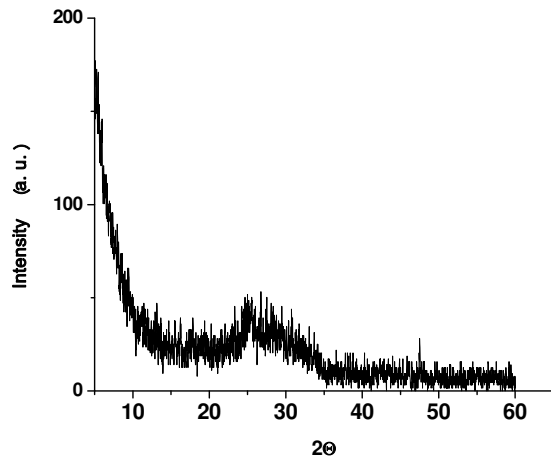

**Fig. (2).** XRD patterns of amorphous TiO<sub>2</sub> at  $R_{1(\text{water}/\text{TIOT})} = 0.17$ , synthesized by sol-gel method and hydrothermal technique at 200°C for 2 hours.

absorption coefficient ( $\alpha$ ) to the incidental photon energy depends on the type of electronic transition. When, in this transition, the electron momentum is conserved, the transition is direct, but if the momentum does not conserve this transition it must be attended by a photon, this is an indirect transition [18,19]. To analyze the electronic properties of the TiO<sub>2</sub> synthesized, the remission function of Kubelka-Munk was used  $F(R'\infty)$  [20-24]:

$$F(R'\infty) = \frac{(1-R'\infty)^2}{2R'\infty} = \frac{\alpha}{S} \quad (2)$$

where:

$$R'\infty = \frac{R\infty(\text{muestra})}{R\infty(\text{estandar})} \quad (3)$$

$R\infty (1/I_0)$  is the diffused reflectance of a given wavelength, of a dense layer of non transparent infinite material,  $\alpha$  is the absorption coefficient ( $\text{cm}^{-1}$ ) and  $S$  is the dispersion factor, which is independent of the wavelength for particles larger than 5  $\mu\text{m}$ .  $\alpha$  is related to the incidental photon energy by means of the following equation [25]:

$$\alpha = A(E - E_g)^\gamma \quad (4)$$

where:  $A$  is a constant that depends on the properties of the material,  $E$  is the photon energy,  $E_g$  is the bandgap and  $\gamma$  is a constant that can take different values depending on the type of electronic transition, for a permitted direct transition  $\gamma = 1/2$ , a prohibited direct transition  $\gamma = 3/2$ , a permitted indirect transition  $\gamma = 2$  and for a prohibited indirect transition  $\gamma = 3$  [26,27]. Therefore:

$$F(R'\infty) = \frac{\alpha}{S} = \frac{A(E - E_g)^\gamma}{S} \quad (5)$$

$$E (\text{eV}) = \frac{hc}{\lambda (\text{nm})} = \frac{1236}{\lambda (\text{nm})} \quad (6)$$


$h$  is the Planck constant and  $C$  is the light velocity. For a direct transition the equation is:

$$F(R'\infty)^2 = \left(\frac{A}{S}\right)^2 (E - E_g) \quad (7)$$

For an indirect transition the equation is:

$$F(R'\infty)^{\frac{1}{2}} = \left(\frac{A}{S}\right)^{\frac{1}{2}} (E - E_g) \quad (8)$$


Figs. (3, 4) shows the  $F(R'\infty)^2$  vs  $E$  (eV) and  $F(R'\infty)^{\frac{1}{2}}$  vs  $E$  (eV) plots for the direct and indirect transitions, respectively, for the synthesized TiO<sub>2</sub> samples, where the value of the band gap ( $E_g$ ) is obtained by extrapolating the linear part of the graphics to the axis of the abscissa. The TiO<sub>2</sub> is activated with photons of energy of a longitude close to 400 nm which involves a band gap of 3.2 eV; the literature reports a 3.23 eV value for anatase phase [28]. For the synthesized TiO<sub>2</sub> samples the direct transition (Fig. 3) shows unrealistic bandgap values above 3.4 eV reaching values of 3.63 eV, which were not expected for anatase phase. The indirect type transition (Fig. 4) showing band gap values of between 3.13 to 3.27 eV, where sample M5 ( $R_{1(\text{water}/\text{TIOT})} = 3.5$  and  $R_{2(2\text{-propanol}/\text{TIOT})} = 15$ ) has a value of 3.24 eV as can be seen in Table 2. Therefore the TiO<sub>2</sub> samples with anatase phase synthesized by the sol-gel method and a hydrothermal treatment follow an indirect type transition [7]. For the amorphous material ( $R_{1(\text{water}/\text{TIOT})} = 0.17$  and  $R_{2(2\text{-propanol}/\text{TIOT})} = 10$ ) the bandgap values obtained were 3.75 eV and 3.4 eV for the direct and indirect transitions, respectively (Fig. 5). These bandgap values for the direct transition as well as for the indirect are quite high compared to the bandgap values for the crystalline phase. These results are in agreement with the work of Welte and co-workers [6] who used the sol-gel method at temperatures of 25°C, 200°C and 500°C to synthesize TiO<sub>2</sub>, obtaining amorphous, amorphous-crystalline and crystalline materials, respectively. For all of the TiO<sub>2</sub> samples, the values of the direct transition were found to be above 3.5 eV. For crystalline material the direct transition showed a bandgap value of 3.23 eV. For amorphous material the indirect transition showed unrealistic bandgap value above 3.5 eV. This behavior suggests that the optical absorption technique is able to determine the type of morphology of the TiO<sub>2</sub> materials [6]. Therefore, optical absorption measurements around 3 eV to 4 eV with plotting the direct transition and the indirect transition perform like an electronic fingerprint and determined if the materials are crystalline or amorphous. For amorphous materials the values of the bandgap are above 3.4eV independent of the transition type, which is in agreement with the XRD. The differences in bandgap values (Table 2), can be attributed to the crystalline size of the catalysts [8] which are in agreement with the diffractograms of the XRD analysis and are influenced by the molar ratio water/TIOT. When the hydrolysis reaction  $\text{Ti}(\text{OR})_4 + 4\text{H}_2\text{O} \rightarrow \text{Ti}(\text{OH})_4 + 4\text{R}(\text{OH})$  is worked with molar ratios lower than those required for the stoichiometric ratio,  $\text{water}/\text{TIOT} < 4$ , the hydrolysis between alkoxide and water is incomplete leaving a large quantity of non hydrolyzed alkoxy anions (OR<sup>-</sup>) that are absorbed onto the surface of the TiO<sub>2</sub>. These OR<sup>-</sup> influence the rate of TiO<sub>2</sub> which favored the formation of a less crystalline anatase phase, the formation of particles with irregular shapes, distribution of large sizes, and low surface areas. An increase of water quantity above the stoichiometric ratio,  $\text{water}/\text{TIOT} > 4$ , involves a strong reaction of nucleophilic replacement between water and the alkoxide molecules and more alkoxy (OR<sup>-</sup>) of the alkoxide precursor, these being substituted by hydroxyl groups of water involved in a reduction of the non hydrolyzed OR<sup>-</sup> diminishing the steric

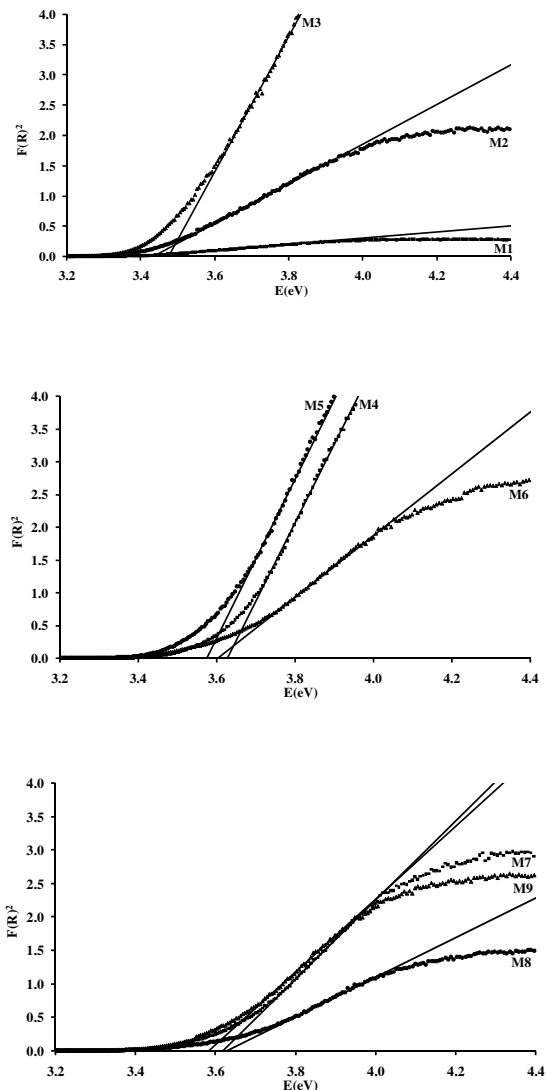

**Fig. (3).** Absorbance spectra for the direct electronic transition,  $F(R)^2$  vs  $E$  (eV) of the synthesized  $\text{TiO}_2$  samples with different molar ratios  $R_1$  (water/TIOT) and  $R_2$  (2-propanol/TIOT).

impediment, which reduces the anatase phase crystallization velocity or the formation of a high crystalline size and an increase of the surface area due to the empty spaces formed in the net structure [3,13,29]. As can be seen in Table 3, the increase in surface area ( $S_{\text{BET}}$ ) observed in the synthesized samples with more than  $159.48$  to  $226.26 \text{ m}^2 \cdot \text{g}^{-1}$  upon augmenting the water/TIOT molar ratio this is in agreement with previous works [30,31]. Fig. (6) shows diffused reflectance spectrums for the synthesized  $\text{TiO}_2$  samples and for Degussa P-25. The synthesized materials present absorption like that of the  $\text{TiO}_2$  Degussa P-25 with similar maximum wavelength. Thus, in this study the  $\text{TiO}_2$  preparation by means of sol-gel method and a hydrothermal treatment does not permit modification of the absorption spectrums toward the visible upon variation of the molar ration water/TIOT in the experiment design. The photocatalytic activity of the synthesized  $\text{TiO}_2$  samples and

$\text{TiO}_2$  Degussa P-25 in the degradation of methyl orange is shown in Table 4. An increase in percentage of methyl orange degradation was observed upon increasing molar ratio water/TIOT up to a molar ratio  $R_1(\text{water/TIOT}) = 3.5$  and  $R_2(2\text{-propanol/TIOT}) = 15$  (sample M5), for molar ratios of water/TIOT lower than  $R_1(\text{water/TIOT}) = 3.5$  there is a decrease in the photocatalytic activity; this agrees with the XRD analysis when sample M5 has a peak with major intensity in the anatase phase, besides having an indirect bandgap of  $3.24 \text{ eV}$ .

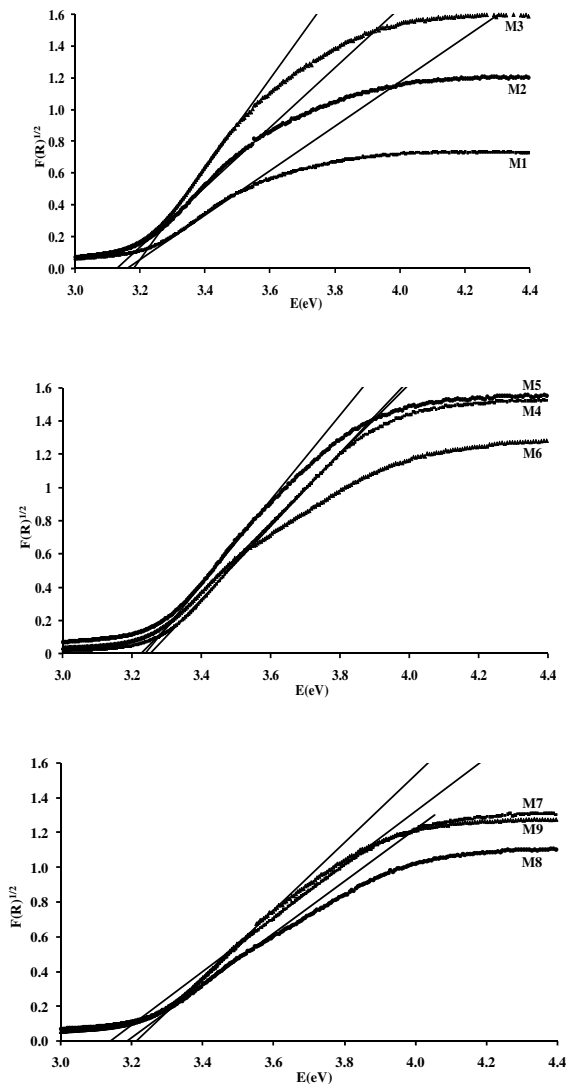

**Fig. (4).** Absorbance spectra for the indirect electronic transition  $F(R)^{1/2}$  vs  $E$  (eV) of the synthesized  $\text{TiO}_2$  samples with different molar ratios  $R_1$  (water/TIOT) and  $R_2$  (2-Propanol/TIOT).

#### 4. CONCLUSIONS

The sol-gel method with a hydrothermal treatment at a temperature of  $200^\circ\text{C}$  for two hours using TIOT as a precursor and 2-propanol as solvent permitted titanium dioxide nanoparticles to be synthesized in the anatase phase, as well as high surface areas, which show a gradual increase

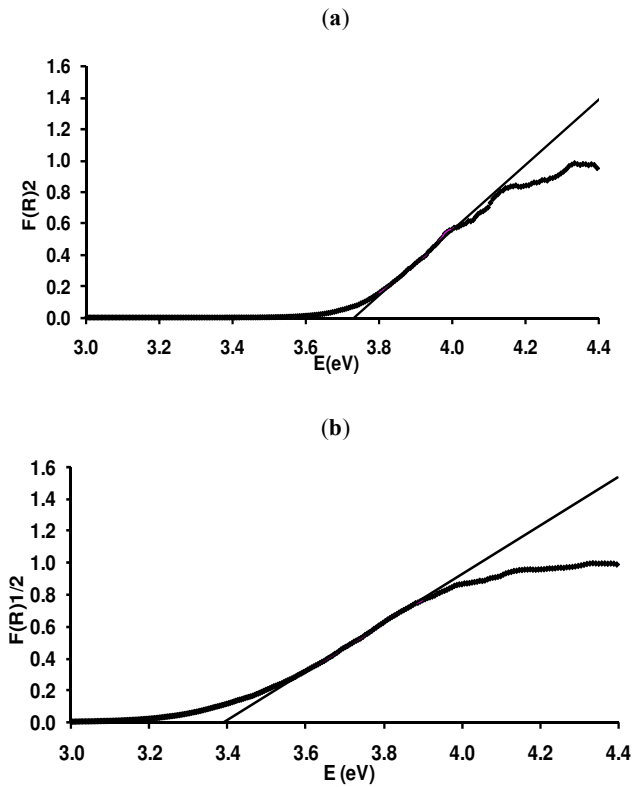


Fig. (5). Absorbance spectra for amorphous TiO<sub>2</sub> samples at R<sub>1(water/TiO<sub>2</sub>)</sub> = 0.17: a) direct electronic transition type and b) Indirect transition type.

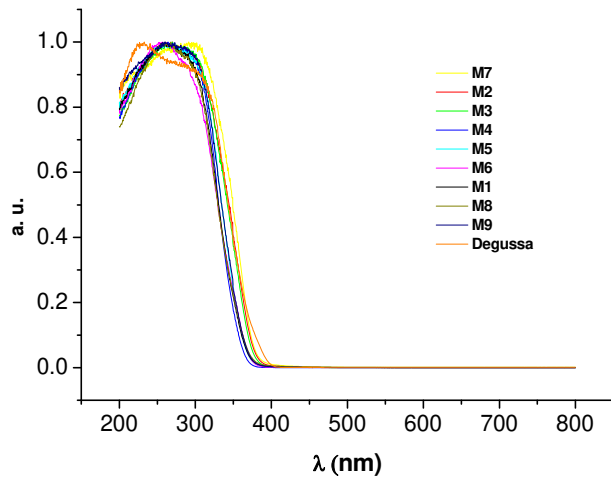


Fig. (6). Diffusion reflectance spectrums of the synthesized TiO<sub>2</sub> samples.

of over 159.48 to 226.26 m<sup>2</sup>g<sup>-1</sup>. These materials show an indirect type band gap close to those reported in the bibliography of 3.23 eV for the anatase phase. Besides, found optical absorption shows that the direct bandgap versus indirect bandgap permits the determination of the crystallinity of a material; for an amorphous material the band gap is greater than 3.4 eV independent of the transition types. All the properties of the synthesized materials

Table 2. Direct and Indirect Bandgap Transitions for Synthesized TiO<sub>2</sub> Samples

Sample	Bandgap (eV)	
	Direct	Indirect
M1	3.40	3.15
M2	3.43	3.13
M3	3.47	3.18
M4	3.63	3.25
M5	3.58	3.24
M6	3.60	3.27
M7	3.62	3.22
M8	3.63	3.19
M9	3.58	3.14

Table 3. Superficial Area of TiO<sub>2</sub> Samples Synthesized the Sol-Gel Method and the Hydrothermal Treatment

Muestra	S <sub>BET</sub> (m <sup>2</sup> ·g <sup>-1</sup> )
M1	159.48
M2	162.30
M3	169.11
M4	175.09
M5	177.65
M6	179.11
M7	203.33
M8	219.86
M9 Degussa	226.26 48.90

Table 4. Photocatalytic Degradation of a Methyl Orange Solution (20ppm) with the Synthesized TiO<sub>2</sub> Samples (150 μm of TiO<sub>2</sub>), Adsorption Time 1 Hour, Degradation 7 Hours

Sample	% Degradation
M1	60.86
M2	62.43
M3	60.69
M4	79.89
M5	100.0
M6	81.11
M7	75.16
M8	61.55
M9 Degussa	58.83 100.0

depended on the  $R_{1(\text{water}/\text{TiOT})}$  molar ratio where the catalyst with the greater photocatalytic activity has the molar ratios:  $R_{1(\text{water}/\text{TiOT})}=3.5$  and  $R_{2(2\text{-propanol}/\text{TiOT})}=15$ .

#### ACKNOWLEDGEMENT

The authors wish to thank the financial support to the University of Antioquia through the “Estrategia de Sostenibilidad de Grupos 2009-2010” program.

#### REFERENCES

- [1] Reddy K, Manorama S, Redd A. Bandgap studies on anatase titanium dioxide nanoparticles. *Mater Chem Phys* 2002; 78: 239-45.
- [2] Jing I, Li S, Song S, Xue L, Fu H. Investigation on the electron transfer between anatase and rutile in nano-sized  $\text{TiO}_2$  by means of surface photovoltage technique and its effects on the photocatalytic activity. *Solar Energy Mater Solar Cells* 2008; 92: 1030-6.
- [3] Wang G. Hydrothermal synthesis and photocatalytic activity of nanocrystalline  $\text{TiO}_2$  powders in ethanol-water mixed solutions. *J Mol Catal A: Chem* 2007; 274: 185-91.
- [4] Sahni S, Reddy B, Murty B. Influence parameters on the synthesis of nano-titania by sol-gel route. *Mater Sci Eng A* 2007; 452-453: 758-62.
- [5] Francisco M. y Mastelero V. Inhibition of the anatase-rutile phase transformation with addition of  $\text{CeO}_2$  to  $\text{CuO-TiO}_2$  system: Raman spectroscopy, X-ray diffraction, and textural studies. *Chem Mater* 2002; 14 (6): 2514-8.
- [6] Welte A, Waldauf C, Brabec C, Wellmann P. Application of optical for the investigation of electronic and structural properties of sol-gel processed  $\text{TiO}_2$  films. *Thin Solid Films* 2008; 516: 7256-9.
- [7] Monllor-Satoca D, Gomez R, González-Hidalgo M, Salvador P. The “Diret-Indirect” model: An Alternative kinetic approach in heterogeneous photocatalysis based on the degree of interaction of dissolved pollutant species with the semiconductor surface. *Catal Today* 2007; 129: 247-55.
- [8] Hidalgo M, Aguilar M, Maicu M, Navio J, Colon G. Hydrothermal preparation of highly photoactive  $\text{TiO}_2$  nanoparticles. *Catal Today* 2007; 129: 50-8.
- [9] Hossain F, Sheppard L, Nowotny J, Murch G. Optical properties of anatase and rutile titanium dioxide: Ab initio calculations for pure and anion-doped material. *J Phys Chem Solids* 2008; 69: 1820-8.
- [10] Marín JM, Restrepo G, Rios LA, Navio JA. Nueva ruta de síntesis para el dióxido de titanio. *Rev Colomb Fis* 2005; 37: 78-81.
- [11] Su C, Tseng C, Chen L, You B, Hsu B, Chen S. Sol hydrothermal and photocatalysis of titanium dioxide. *Thin Solid Films* 2006; 498: 259-65.
- [12] Wen B, Liu C, Liu Y. optimization of the preparation methods synthesis of meso structures  $\text{TiO}_2$  with high photocatalytic activities. *J Photochem Photobiol A: Chem* 2005; 173: 7-12.
- [13] Yu J, Wang G, Cheng B, Zhou M. Effects of hydrothermal temperature and time on the photocatalytic activity and microstructures of bimodal mesoporous  $\text{TiO}_2$  powders. *Appl Catal B: Environ* 2007; 69: 171-80.
- [14] Zhu J, Yang J, Bian Z, *et al.* Nanocrystalline anatase  $\text{TiO}_2$  photocatalysis prepared *via* a facile low temperature nonhydrolytic sol-gel reaction of  $\text{TiCl}_4$  and benzyl alcohol. *Appl Catal B: Environ* 2007; 76: 82-91.
- [15] Liu G, Jin Z, Wang T, Liu Z. Anatase  $\text{TiO}_2$  porous thin films prepared by sol-gel method using CTAB surfactant. *J Sol-Gel Tech* 2007; 41: 49-55.
- [16] Yu H, Wang S. effects of water content and pH on gel-derived  $\text{TiO}_2\text{-SiO}_2$ . *J Non-Crystal Solids* 2000; 261: 260-7.
- [17] Essick J, Mather R. Characterization of a bulk semiconductor's band gap *via* near-absorption edge optical transmission experiment. *Am J Phys* 1993; 61: 646-9.
- [18] Willardson R, Beer A. Optical Properties of III-V Compounds. Academic Press New York 1967; pp. 318-400.
- [19] Dressel M, Gruner G. Electrodynamics of Solids Optical Properties of Electron in Matter. Cambridge University Press 2002; pp. 159-65.
- [20] Kottim G. Reflectance spectroscopy. Springer Verlag. New York 1969.
- [21] Tandon S, Gupta J. Measurement of forbidden energy gap of semiconductors by diffuse reflectance technique. *Phys Stat Sol* 1970; 38: 363-7.
- [22] Wendlandt W, Hecht H. Reflectance Spectroscopy. Wiley Interscience New York 1966.
- [23] Sreen K, Poulouse C, Unni B. Colored cool colorants based on rare earth metal ions. *Solar Energy Mater Solar Cells* 2008; 92: 1462-7.
- [24] Bagheri-Mohagheghi M, Shahtahmasebi N, Alinejad M. The effect of the post-annealing temperature on the nano-structure and energy band gap of  $\text{SnO}_2$  semiconducting oxide nano-particles synthesized by polymerizing-complexing Sol-gel method. *Phys B: Condensed Matter* 2008; 403: 2431-7.
- [25] Ting C, Chen S. Structural evolution and optical properties of  $\text{TiO}_2$  thin films prepared by thermal oxidation of sputtered Ti films. *J Appl Phys* 2000; 88: 4628-33.
- [26] López S, Castillo S, Chávez J, Díaz K. Síntesis y caracterización óptica, eléctrica y estructural de películas delgadas de  $\text{CS}_2$  depositadas por el método PECVD. *Materia* 2003; 8: 341-9.
- [27] Oliva F, Avalle L, Santos E, Camara O. Photoelectrochemical characterization of nanocrystalline  $\text{TiO}_2$  films on titanium substrates. *J Photochem Photobiol A: Chem* 2002; 146: 175-88.
- [28] Litter M. Heterogeneous photocatalysis transition metal ions in photocatalytic systems. *Appl Catal B: Environ* 1999; 23: 89-114.
- [29] Venkatachalam N, Palanichamy M, Murugesan V. Sol-gel preparation and characterization of nanosize  $\text{TiO}_2$ : Its photocatalytic performance. *Mater Chem Phys* 2007; 104: 457-9.
- [30] Kolen'ko Y, Churagulov B, Kunst M, Mazerolles L, Colbeau Justin. Photocatalytic properties of titania powders prepared by hydrothermal method. *Appl Catal B: Environ* 2004; 54: 51-8.
- [31] Kominami G, Kato J, Takada Y, *et al.* Novel synthesis of microcrystalline titanium(IV) oxide having high thermal stability and ultra-high photocatalytic activity: thermal decomposition of titanium(IV) alkoxide in organic solvents. *Catal Lett* 1997; 46: 235-40.

Received: October 14, 2009

Revised: October 16, 2009

Accepted: October 30, 2009

© Valencia *et al.*; Licensee Bentham Open.

This is an open access article licensed under the terms of the Creative Commons Attribution Non-Commercial License (<http://creativecommons.org/licenses/by-nc/3.0/>) which permits unrestricted, non-commercial use, distribution and reproduction in any medium, provided the work is properly cited.