
SUPPRESSION OF SCATTERING FOR SMALL DIELECTRIC PARTICLES:
ANAPOLE MODE AND INVISIBILITY

Boris Luk`yanchuk^{1*}, Ramón Paniagua-Domínguez¹, Arseniy I. Kuznetsov¹,
Andrey E. Miroshnichenko² and Yuri S. Kivshar²

¹Data Storage Institute, A*STAR (Agency for Science, Technology and Research), 2 Fusionopolis Way, #08-01, Innovis 138634, Singapore.

²Nonlinear Physics Centre, Research School of Science and Engineering, The Australian National University, Acton, Australian Capital Territory 2601, Australia.

Keywords: high-index dielectric nanoparticles, Mie resonances, toroidal mode, anapole

We reveal that an isotropic homogeneous subwavelength particle with high refractive index can produce ultra-small total scattering due to vanishing of the electric dipole contribution. This effect can be explained based on the Fano resonance of the scattering efficiency associated with the anapole excitation. The latter is a non-radiative mode emerging from the destructive interference of electric and toroidal dipoles, and it can be useful for the design of highly transparent optical materials.

1. Introduction

The idea of perfect camouflage follows the history of humanity. This idea inspired poets and writers who described the great advantages of invisibility for military, political or even for love affairs. Here the stories from the Arabian “*One Thousand and One Nights*”, the Alexander Pushkin’s poem “*Ruslan and Ludmila*”, and a science fiction novella “*The Invisible Man*” by Herbert G. Wells can be mentioned, as well as the *Harry Potter* of Joanne Rowling and many others. However, for a long time this invisibility was considered to be forbidden by general physics. Since the time of Rayleigh¹, it was recognized that even a very small particle becomes visible due to light scattering. Attempts in Nature, e.g. those of chameleons, to realize invisibility are based on camouflage (i.e. imitating the colour of the background) and, thus, are just a palliative.

P. Ufimtsev suggested another principle in his book published in 1962. His idea was to use a special shape of the aircraft to escape back reflection of radar signal. Such property is demonstrated, for example, with conical mirror directed toward to the light source. Ufimtsev’s book was translated into English² and it gave start for the development of the stealth technology. It is interesting to note that Prof. M. Levin (who was a referee of Ufimtsev’s PhD thesis) wrote in his official review that a zero back scattering could be derived for an azimuthally symmetric material with $\varepsilon = \mu$. Ufimtsev highlighted this story in his book³ but it was never printed in a paper. Meanwhile, the same idea was later independently re-discovered⁴ and published by M. Kerker, after which this condition is named as first Kerker condition. According to Arnold’s Principle “*if a notion bears a personal name, then this name is not the name of the discoverer*”⁵. However, Kerker further developed the idea to reach total scattering suppression. For that, he considered the scattering from multi-layered spheres⁶ and spheroids⁷.

A step further in the development of the invisibility idea led to the next attack based on the concept of cloaking^{8,9} which uses the general principle of optical transformation, i.e. Fermat principle. This

*Author for correspondence (Boris_L@dsi.a-star.edu.sg).

†Present address: ¹Data Storage Institute, A*STAR (Agency for Science, Technology and Research), 2 Fusionopolis Way, #08-01, Innovis 138634, Singapore

idea needs inhomogeneous media, which forces light to go around the cloaking area. Consequently, it is necessary to create some special profiles of permittivity $\varepsilon = \varepsilon(\mathbf{r})$ and permeability $\mu = \mu(\mathbf{r})$, which make their practical realization rather difficult. Other ideas related to multi-shell structures for cloaking were later developed for plasmonic¹⁰, dielectric¹¹ and metamaterial coatings together with scattering cancellation and mantle cloaking¹².

Returning to homogeneous spheres one should mention the idea of directional scattering for plasmonic nanoparticles. This idea is closely related to Fano resonance in plasmonic materials and metamaterials^{13, 14}. However, such Fano resonances and directional suppression of scattering in plasmonic particles is not accompanied by minimization of the total scattering efficiency. Another problem is related to dissipation of real metals, but this can be easily circumvented if dielectric particles are used instead.

2. Rayleigh approximation

The scattering efficiency, Q_{sca} , in the Rayleigh scattering regime is given by well-known formula¹⁵

$$Q_{sca}^{(Ra)} = \frac{8}{3} \left(\frac{\varepsilon - 1}{\varepsilon + 2} \right)^2 q^4, \quad (1)$$

representing the ratio of scattering cross-section to the geometrical one, $\sigma_{geom} = \pi R^2$, where R is particle radius, ε is its permittivity, and $q = 2\pi R/\lambda$ is the so called size parameter, with λ the radiation wavelength. The particle is considered to be a small ideal sphere made of an isotropic, homogeneous and nonmagnetic ($\mu = 1$) material. In addition, the size of this particle should be sufficiently small. If one consider non-dissipative, $\text{Im}\varepsilon = 0$, dielectric materials with positive refractive index $n = \sqrt{\varepsilon} > 1$, then the ratio of scattering efficiency to the fourth power of the size parameter presents a universal function, which monotonously increases with refractive index

$$Q_{sca}^{(Ra)}/q^4 = \frac{8}{3} \left(\frac{n^2 - 1}{n^2 + 2} \right)^2. \quad (2)$$

Formula (1) represents the scattering of electrical dipole. Justification of this formula follows from the Mie theory¹⁵, which is the exact solution of Maxwell's equations for scattering of a plane wave from a spherical particle. Scattering efficiency of the particle according to Mie theory is given by

$$Q_{sca} = \frac{2}{q^2} \sum_{\ell=1}^{\infty} (2\ell + 1) \left[|a_{\ell}|^2 + |b_{\ell}|^2 \right], \quad (3)$$

where the scattering amplitudes a_{ℓ} (electric) and b_{ℓ} (magnetic) are expressed in terms of the Ricatti-Bessel functions¹⁵. With small size parameter, $q \ll 1$, one can find¹⁶ $a_{\ell} \propto q^{2\ell+1}$ and $b_{\ell} \propto q^{2\ell+3}$. Thus, the electrical dipole amplitude a_1 is dominant. For a small plasmonic particle with $\varepsilon < 0$ the scattering efficiency can be very large, $Q_{sca} \gg 1$. The physical reason for this effect can be explained from the Poynting vector field^{16, 17}, which indicates that the cross-section of separatrix tubes for the energy flow into the particle can greatly exceed the geometrical cross-section. Near plasmonic resonances with $\varepsilon = -(1 + \ell^{-1})$, Rayleigh approximation is not valid, e.g. $Q_{sca}^{(Ra)}$ in formula (1) has singularity at $\varepsilon = -2$. However, the Mie theory yields for electrical dipole resonance a limited value $Q_{sca} = 6/q^2$. For weakly dissipative plasmonic materials, one can see an inversion of the hierarchy

of resonances, when the scattering efficiency at the dipole resonance is smaller than that of the quadrupole one, which is, in turn, smaller than for the octupole resonance, etc.¹⁸

A small dielectric particle with $\varepsilon > 1$ produces, according to Rayleigh approximation (1), a very small scattering, which tends to zero at $q \rightarrow 0$. This scattering corresponds to the situation when the electrical dipole amplitude plays the dominant role and all other amplitudes are small. Such situation is typical for small plasmonic particles. A similar situation takes place for small size parameter $q \ll 1$ and refractive index $1 < n < 2$, see e.g.¹⁹. For these cases, Rayleigh formula (1) represents the minimal possible scattering of a small particle.

3. High-index dielectric particles

This situation changes for a particle with high refractive index. For example, silicon particles at the optical range ($n \approx 4$) have scattering efficiencies at the magnetic dipole resonance that are larger than at the electrical dipole resonance even for small particles^{20,21}, as has been experimentally confirmed^{22, 23}. As a result, the scattering near the resonances is not small in spite of fulfilling the condition that the particle size is small. In fact, the true conditions for the applicability of formula (1) are $q \ll 1$ and, additionally, $q < 1/n$. This is easy to see in Fig. 1a, where the total Mie scattering and Rayleigh scattering efficiencies versus refractive index n are presented for a spherical particle with size parameter $q = 0.3$ ($R/\lambda \approx 0.05$). Rayleigh scattering saturates at large n , but formula (1) loses its validity in the vicinity of the magnetic dipole resonance at $n = 10.3$ and also in the vicinity of the subsequent resonances (as shown in the inset of Fig. 1a). Note that some very narrow peaks cannot be seen on the scale of this inset. Also note that, even with large refractive index, the total scattering between resonances is quite close to Rayleigh scattering (blue line).

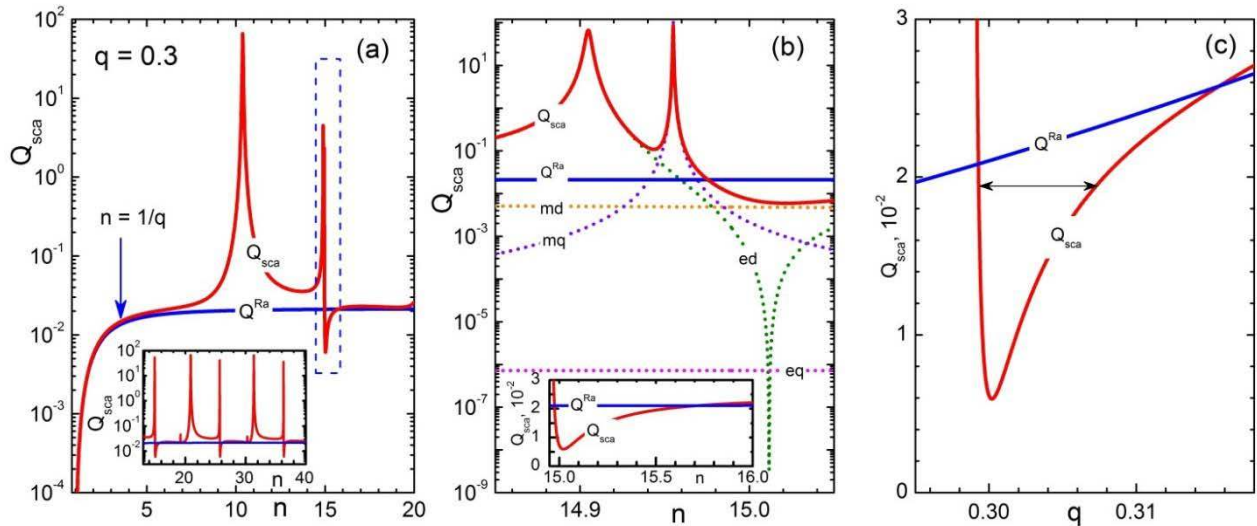


Fig. 1. (a) Scattering efficiencies according to Rayleigh approximation (blue line) and exact Mie theory (red line) for small size parameter $q = 0.3$. The inset in (a) shows resonances at higher values of the refractive index. In the vicinity of $n = 15, 21, 36, \dots$ one can see that the total scattering is less than it follows from formula (1). A zoom of the scattering within the area indicated by the dashed box is shown in (b), where Rayleigh approximation (blue line) and exact Mie theory (red line) are shown together with four partial scattering efficiencies for magnetic dipole (md), electric dipole (ed), magnetic quadrupole (mq) and electric quadrupole (eq). Inset in (b) and Fig. (c) show $Q_{sca} < Q^{Ra}$ region in linear coordinates.

It is not surprising that the particle has a scattering efficiency much larger than Rayleigh scattering near resonances. However, the asymmetric line-shape of the resonance (see Fig. 1a) leads also to a strong suppression of total scattering near the resonance that becomes lower than that given by

Rayleigh formula (1). Such scattering behaviour is achieved e.g. in the region near $n \approx 15$ marked in bracket in Fig. 1a. The zoom into this area is shown in Fig. 1b. There are two closely situated electric dipole and magnetic quadrupole resonances, which cannot be resolved on the scale of Fig. 1a. Although there are many points with local scattering minima, as shown in the inset to Fig. 1a, a more precise examination shows that the global minimum in scattering is reached near $n \approx 15$. Detailed analysis of this resonance reveals that it has a typical Fano shape. Typically, Fano bandwidth is quite narrow, see in Fig. 1c.

Previously, it was shown that such Fano shape arises in the total scattering from single elongated antennas, both in the plasmonic case^{24, 25} and in their dielectric analogues²⁶, within a system of disordered photonic crystals²⁷ as well as in the transmission spectra of two-dimensional square lattices of dielectric circular rods²⁸. In the last case, the Fano resonance is arising due to interplay between the resonant Mie scattering from individual rods and the Bragg scattering from the photonic lattice. One should also mention the Fano profile of the dipole scattering amplitude $|a_1(n)|^2$ at the limit $n \gg 1$ ²⁹. Formally, results of Ref. 29 can be expressed as an interference of two partitions, where one corresponds to the n -independent wave, scattered by a perfectly reflecting particle and plays the role of a background, while the other is associated with the excitation of an n -dependent resonant Mie mode³⁰.

The Fano resonance shape in our case is associated with the destructive interference of an electric dipole with a toroidal dipole mode. Previously it was shown that such type of interference, the so-called anapole mode^{31, 32}, could be observed in Si nanodisks. For nanodisks, this anapole mode can be achieved at a specific wavelength and for some fixed ratio of the disk height to its diameter. It was shown as well that, in the case of a single isolated nonmagnetic isotropic spherical particle, the anapole condition is usually hidden by the rest of multipolar contributions, difficulting its observation. Here, we show that the anapole excitation may be observed even in the simple spherical case, provided the particle is sufficiently small and has a sufficiently high refractive index. In Fig. 2 we present the Poynting vector distribution for the particle with $n = 15.0116$ and $q = 0.3$. The total scattering efficiency, $Q_{sca} \approx 5.99 \cdot 10^{-3}$, for this particle is about 3.5 times less than Rayleigh scattering calculated by formula (1), $Q_{sca}^{(Ra)} \approx 2.11 \cdot 10^{-2}$. One can see in Fig. 2 that the Poynting vector has a toroidal structure. Note that at $q \ll 1$ the magnetic dipole contribution is small, so that inequality $Q_1^{(m)} \ll Q_1^{(e)}$ is satisfied at almost all values of parameters except of regions close to the anapole conditions. Closed singular line in Fig. 2b corresponds to zero energy flow. Near this singular line Poynting vector produces characteristic vortices, see in Fig. 2c, similar to vortices in small plasmonic particle^{16, 33}.

Additionally we can prove the toroidal symmetry by plotting distributions of electric and magnetic vectors inside the particle in mutually perpendicular planes as it is shown in Fig. 3. Here distribution of electric vector \mathbf{E} is shown within the $\{x, z\}$ plane through the diameter of the particle in Fig. 3a. Colour panel in Fig. 3a presents the intensity \mathbf{E}^2 distribution. Within the perpendicular $\{y, z\}$ plane, one can see the distribution of magnetic vector \mathbf{H} , as shown in Fig. 3b. Similar toroidal fields³² recently attract a lot of attention. Dominant contributions of electric and toroidal dipole moments can be clearly seen in Cartesian coordinates³¹. Thus, one can conclude that this Fano resonance is related to constructive and destructive interference of electrical dipole and toroidal dipole moments.

As it follows from Fig. 1b the corresponding Fano resonance arises in the vicinity of the zero of electrical dipole mode, $a_1 = 0$. This condition yields the equation

$$1 - n^2 + q(n^2 - 1 + n^2 q^2) \cot(q) + nq(n^2 - 1 - n^2 q^2) \cot(nq) + nq^2(1 - n^2) \cot(q) \cot(nq) = 0. \quad (4)$$

Within the equation (4) one should consider $\cos(q) \neq 0$ and $\cos(nq) \neq 0$. For each value of refractive index, there are infinite set of solutions with corresponding size parameter q . However just the first root corresponds to the global minimum of Q_{sca} .

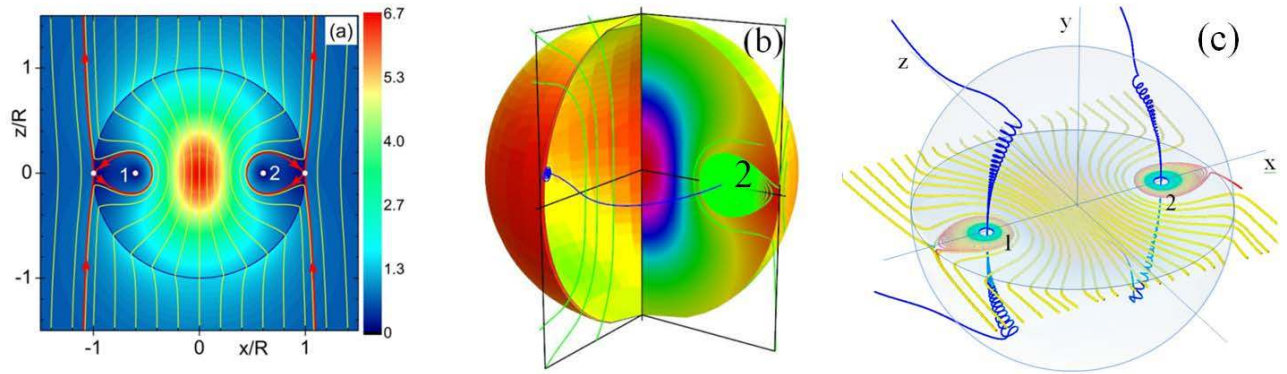


Fig.2. (a) 2D Poynting vector in $\{x, z\}$ plane for $q = 0.3$ and $n = 15.0116$. Colour panel presents the variation of the modulus of the Poynting vector. The full number of modes in the Mie theory is taken into account. There are 2 saddles and 2 focal points. Red lines show the separatrices. Inside the particle, one can see the loops of separatrices representing the cross-sections of the electric toroidal dipole. (b) 3D Poynting vector distribution. The focal points in Fig. 2 are in reality unstable saddle-focal points. Through these points goes the closed singular line, which provides the axis of the toroidal mode. One fourth part of this line is shown by blue line. Green lines show the untwisted spiral of the Poynting vector in $\{x, z\}$ plane. (c) Vortices around the closed singular line, which provides the axis for toroidal mode.

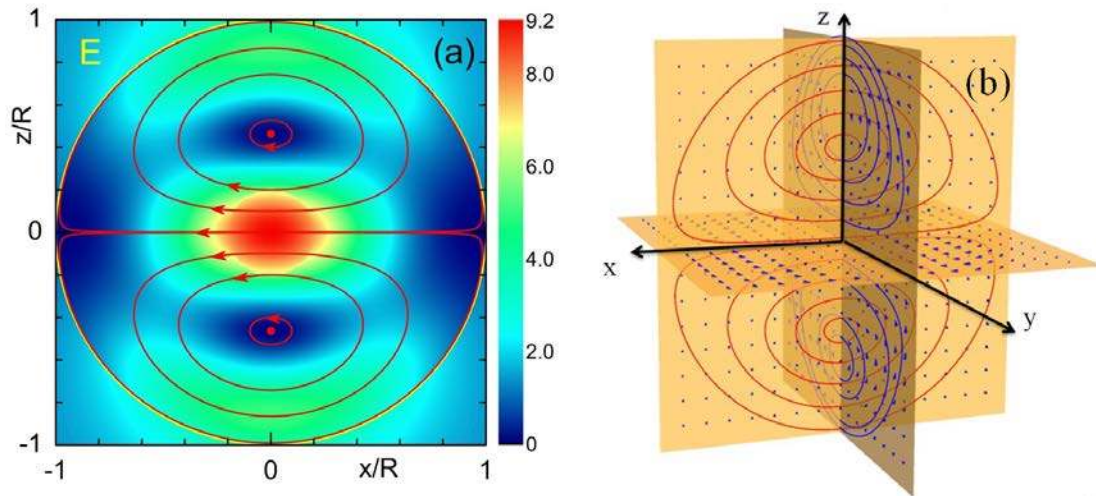


Fig.3. (a) Distribution of electric vector \mathbf{E} within the $\{x, z\}$ plane through the particle diameter. Colour panel indicates the value of electric intensity \mathbf{E}^2 in this plane. (b) 3D distributions of electric \mathbf{E} (red lines) and magnetic \mathbf{H} (blue lines) vectors within the planes through the particle diameter.

It is important to emphasize that anapole mode produces the global minimum in scattering efficiency. Minimization of differential scattering only³⁴⁻³⁷ does not minimize the total scattering. For example, minimization of the forward scattering due to the second Kerker conditions³⁴ is quite close to local minimum in scattering (see in Fig. 4a), but it does not beat the Rayleigh scattering. A better way to visualize this global minimization scattering effect is shown in Fig. 4b, where two curves Q_{sca}/q^4 depend on the refractive index only.

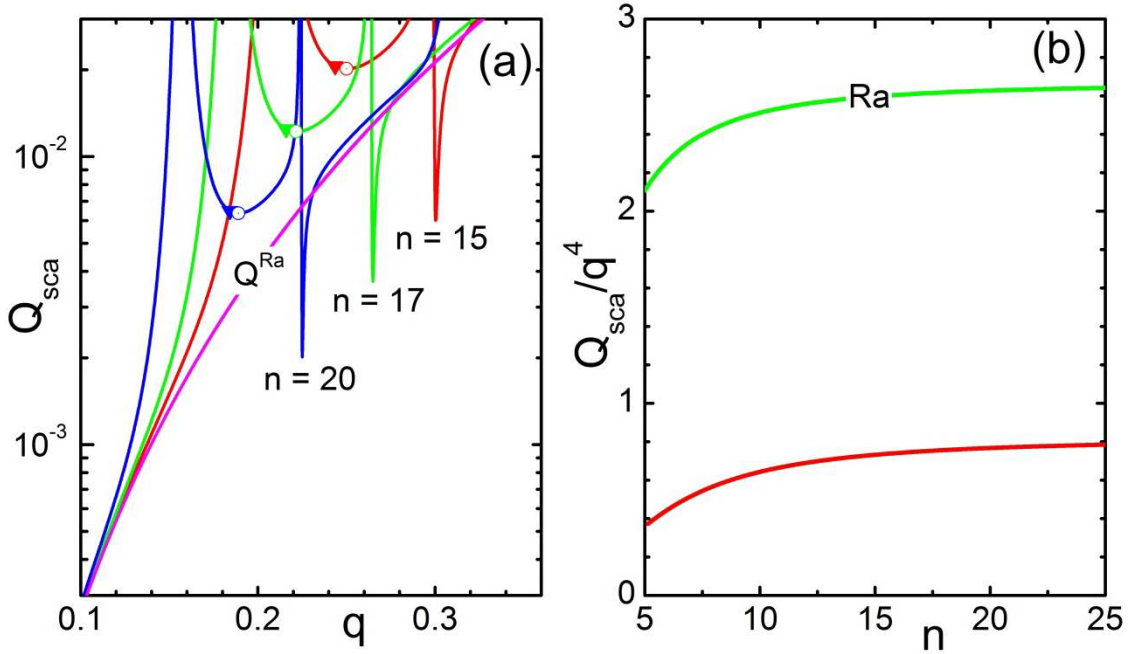


Fig. 4. (a) Scattering efficiencies versus size parameter for three values of refractive index: $n = 15$ (red), $n = 17$ (green) and $n = 20$ (blue). Open circles present positions of the local minima in scattering. Triangular shows the scattering in the points which correspond to minimal forward scattering. (b) Q_{sca}/q^4 along the Rayleigh scattering (green) and anapole mode (red).

It is possible to produce further minimization of scattering using spheroidal particles. In contrast to problem with scattering maximization³⁸ the answer for minimization in fact is quite evident and similar to the stealth effect: the needle directed toward to the light source will produce the minimal scattering. At the same time, behaviour of directional scattering for spherical particle near the magnetic dipole resonance and anapole modes is quite different. The forward, Q_{FS} , and backward, Q_{BS} , scattering efficiencies defined for a spherical particle from Mie theory as:

$$Q_{FS} = \frac{1}{q^2} \left| \sum_{\ell=1}^{\infty} (2\ell+1)(a_{\ell} + b_{\ell}) \right|^2, \quad Q_{BS} = \frac{1}{q^2} \left| \sum_{\ell=1}^{\infty} (2\ell+1)(-1)^{\ell}(a_{\ell} - b_{\ell}) \right|^2. \quad (5)$$

A total suppression of the forward scattering is forbidden by the optical theorem³⁹. The back scattering of small particle can be almost completely suppresses at the condition $a_1 = b_1$ which is referees as the *first Kerker condition*, while minimization of the inverse ratio is often referred to as the *second Kerker condition*³⁴. Calculation with size parameter $q = 0.3$ yields the first Kerker condition for the particle with $n \approx 9.14$ and the second Kerker conditions for the particle with $n \approx 12.08$. It is interesting to note that the second branch of solutions for Kerker conditions at $q = 0.3$ yields the values $n \approx 14.99$ and $n \approx 15.14$ located in the vicinity of the anapole mode. The corresponding polar scattering diagrams¹⁵ are shown in Fig. 5. At conventional Kerker conditions the scattering pattern is independent on incident polarization and is practically the same for linearly polarized and non-polarized light (i.e. it has rotational symmetry). In contrast, the scattering pattern near anapole is not rotationally symmetric, thus yielding polarization-dependent directional scattering (except at backward and forward directions). This behaviour is quite similar to the change of directivity in the vicinity of quadrupole resonance within the weakly dissipated plasmonic particles¹⁴.

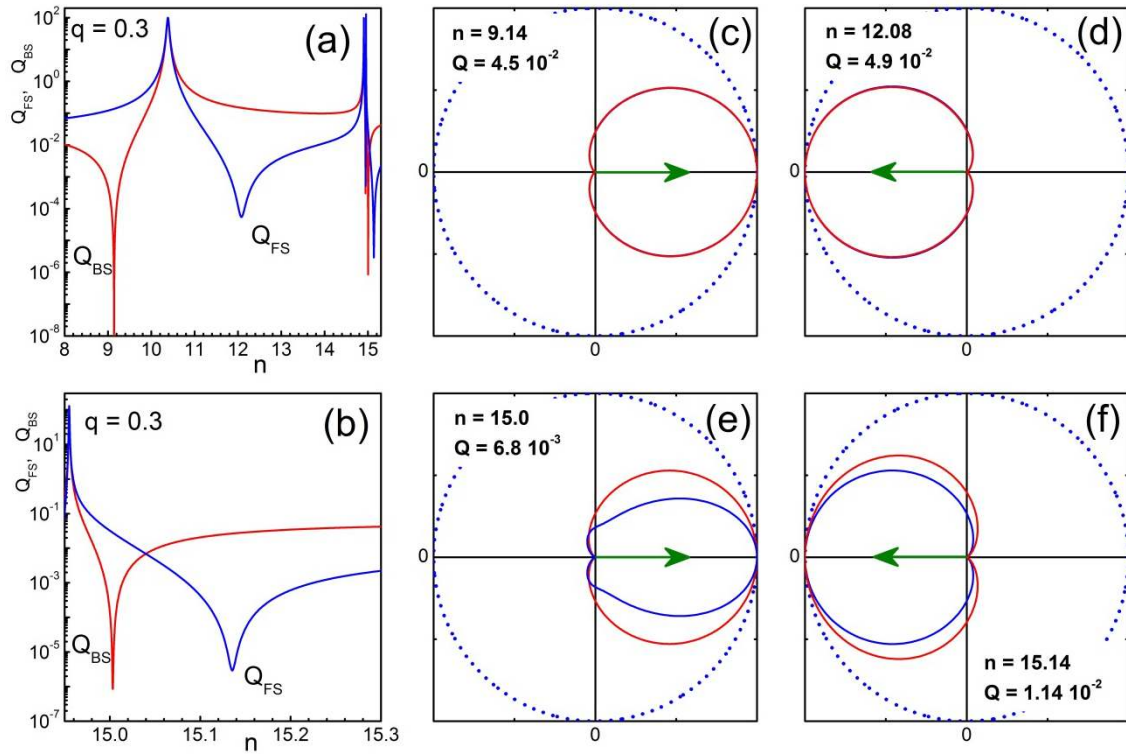


Fig. 5. Left panels (a,b) show forward and backward scattering efficiencies for small particle $q = 0.3$ versus refractive index n . The right panels (c-f) show the polar scattering diagrams in the x - z plane (azimuthal angle $\varphi = 0$ in Mie theory) for different refractive index n . Blue lines shows linearly polarized light and red lines represent non-polarized light. Arrows indicate direction of scattering.

4. Conclusion

We have found conditions when the scattering of a small spherical dielectric particle, $q \ll 1$, is strictly below the value which follows from the Rayleigh formula (1). It is related to the excitation of an anapole scattering mode with an associated Fano line-shape. Similar effects were found previously for a homogeneous dielectric rod³⁰, but the physics behind was explained in a different way. It is important to highlight that our results refer to a homogeneous isotropic small particle. The only conditions for such ultra-small scattering is related to small size parameter, $q \ll 1$, big refractive index, typically $n > 5$, and weak dissipation. There are a number of materials fulfilling these conditions in far-IR and microwave region, e.g. SiC, TiO₂, ceramics, and some other materials⁴⁰. We foresee that cluster assembled materials from such particles may have interesting properties such as high transparency, i.e. the scattering effect in the extinction can be strongly suppressed.

Acknowledgments

BL, RPD and AIK acknowledge support by DSI core funds and A*STAR Science and Engineering Research Council (SERC) Pharos grant #1527000025. AEM and YSK were supported by the Australian Research Council.

Authors' Contributions

B.L. initiated the study of anapole effect by small spherical particle. All authors contributed equally in discussions, writing and editing this paper.

References

1. Lord Rayleigh. (1871). On the light from the sky, its polarization and colour. *Phil. Mag.* Vol. **41**; 107-120; 274-279; On the scattering of light by small particles. *Phil. Mag.* Vol. **41**; 447-454.
2. P. Y. Ufimtsev. (1971). Method of Edge Waves in the Physical Theory of Diffraction. *U.S. Air Force, Foreign Technology Division*.
3. P. Y. Ufimtsev. (2006). Fundamentals of the Physical Theory of Diffraction. *Wiley*.
4. M. Kerker, D. Wang & G. Giles. (1983). Electromagnetic scattering by magnetic spheres. *J. Opt. Soc. Am.* **73**, 765–767.
5. V. I. Arnold. (1998). On teaching mathematics. *Russian Mathematical Surveys* **53**, 229-236.
6. H. Chew & M. Kerker. (1976). Abnormally low electromagnetic scattering cross sections. *J. Opt. Soc. Am.* **66**, 445-449.
7. M. Kerker. (1975). Invisible bodies. *J. Opt. Soc. Am.* **65**, 376-379.
8. U. Leonhardt. (2006). Optical conformal mapping. *Science* **312**, 1777-1780.
9. J. B. Pendry, D. Schurig & D. R. Smith. (2006). *Controlling Electromagnetic Fields*. *Science* **312**, 1780-1782.
10. A. Alù & N. Engheta. (2008). Multifrequency optical invisibility cloak with layered plasmonic shells. *Phys. Rev. Lett.* **100**, 113901.
11. R. Paniagua-Domínguez, D. R. Abujetas, L. S. Froufe-Pérez, J. J. Sáenz & J. A. Sánchez-Gil. (2013). Broadband telecom transparency of semiconductor-coated metal nanowires: more transparent than glass. *Opt. Express* **21**, 22076- 22089.
12. P-Y. Chen , J. Soric & A. Alù. (2012). Invisibility and Cloaking Based on Scattering Cancellation. *Adv. Mater.* **24**, OP281–OP304.
13. A. E. Miroschnichenko, S. Flach & Y. S. Kivshar. (2010). Fano resonances in nanoscale structures. *Rev. Mod. Phys.* **82**, 2257–2298.
14. B. Luk'yanchuk, N. I. Zheludev, S. A. Maier, N. J. Halas, P. Nordlander, H. Giessen & C. T. Chong. (2010). The Fano resonance in plasmonic nanostructures and metamaterials. *Nature Mat.* **9**, 707–715.
15. M. Born & E. Wolf. (1999). Principles of Optics, 7th Ed. *University Press, Cambridge*.
16. Z. B. Wang, B. S. Luk'yanchuk, M. H. Hong, Y. Lin & T. C. Chong. (2004). Energy flow around a small particle investigated by classical Mie theory. *Phys. Rev. B* **70**, 035418.
17. C. F. Bohren. (1983). How can a particle absorb more than the light incident on it? *Am. J. Phys.* **51**, 323-327.
18. M. I. Tribelsky & B. S. Luk'yanchuk. (2006). Anomalous light scattering by small particles. *Phys. Rev. Lett.* **97**, 263902.
19. H. C. van de Hulst. (2005). Light Scattering by Small Particles. *Dover*.
20. A. B. Evlyukhin, C. Reinhardt, A. Seidel, B. Luk'yanchuk & B. N. Chichkov. (2010). *Optical response features of Si-nanoparticle arrays*. *Phys. Rev. B* **82**, 045404.
21. A. Garcia-Etxarri, R. Gomez-Medina, L. S. Froufe-Perez, C. Lopez, L. Chantada, F. Scheffold, J. Aizpurua, M. Nieto-Vesperinas & J. J. Sáenz. (2011). Strong magnetic response of submicron silicon particles in the infrared. *Opt. Express* **19**, 4815–4826.
22. A. I. Kuznetsov, A. E. Miroschnichenko, Y. H. Fu, J. B. Zhang & B. Luk'yanchuk. (2012). Magnetic light, *Nature: Sci. Rep.* **2**, 492.
23. A. B. Evlyukhin, S. M. Novikov, U. Zywiets, R. L. Eriksen, C. Reinhardt, S. I. Bozhevolnyi & B. N. Chichkov. (2012). Demonstration of magnetic dipole resonances of dielectric nanospheres in the visible region. *Nano Lett.* **12**, 3749–3755.
24. F. López-Tejiera, R. Paniagua-Domínguez, R. Rodríguez-Oliveros & J. A. Sánchez-Gil. (2012). Fano-like interference of plasmon resonances at a single rod-shaped nanoantennas. *New. J. Phys.* **14**, 023035.
25. N. Verellen, F. López-Tejiera, R. Paniagua-Domínguez, D. Vercruyssen, D. Denkova, L. Lagae, P. Van Dorpe, V. V. Moshchalkov & J. A. Sánchez-Gil. (2014). Mode parity-controlled Fano-and Lorentz-like line shapes arising in plasmonic nanorods. *Nano Lett.* **14**, 2322-2329.
26. P. Fan, Z. Yu, S. Fan & M. L. Brongersma. (2014). Optical Fano resonance of an individual semiconductor nanostructure. *Nature Mat.* **13**, 471-475.
27. A. N. Poddubny, M. V. Rybin, M. F. Limonov & Y. S. Kivshar. (2012). Fano interference governs wave transport in disordered systems. *Nature Com.* **3**, 914.
28. M. V. Rybin, I. S. Sinev, K. B. Samusev, A. E. Miroschnichenko, Y. S. Kivshar & M. F. Limonov. (2014). Fano resonances in high-index dielectric photonic structures. *Proc. SPIE*, vol. **9127**, 912712.
29. M. I. Tribelsky & A. E. Miroschnichenko. (2016). Giant In-Particle Field Concentration and Fano Resonances at Light Scattering by High-Refractive Index Particles. *Phys. Rev. A* **93**, 053837.
30. M. V. Rybin, D. S. Filonov, P. A. Belov, Y. S. Kivshar & M. P. Limonov. (2015). Switching from visibility to invisibility via Fano resonances. Theory and experiment. *Nature: Sci. Rep.* **5**, 8774.
31. A. E. Miroschnichenko, A. B. Evlyukhin, Y. F. Yu, R. M. Bakker, A. Chipouline, A. I. Kuznetsov, B. Luk'yanchuk, B. N. Chichkov & Y. S. Kivshar. (2015). Nonradiating anapole modes in dielectric nanoparticles. *Nature Com.* **6**, 8069.
32. N. Papasimakis, V. A. Fedotov, V. Savinov, T. A. Raybould & N. I. Zheludev. (2016). Electromagnetic toroidal excitations in matter and free space. *Nature Mat.* **15**, 263.

33. B. S. Luk`yanchuk, A. E. Miroshnichenko, Y. S. Kivshar. (2013). Fano resonances and topological optics: the interplay of far- and near-field interference phenomena. *Journal of Optics* **15**, 073001.
34. B. García-Cámara, J. M. Saiz, F. González & F. Moreno. (2010). Nanoparticles with unconventional scattering properties: size effects. *Opt. Commun.* **283**, 490–496.
35. J. M. Geffrin, B. García-Cámara, R. Gómez-Medina, P. Albella, L. S. Froufe-Pérez, C. Eyraud, A. Litman, R. Vaillon, F. González, M. Nieto-Vesperinas, J. J. Sáenz & F. Moreno. (2012). Magnetic and electric coherence in forward- and back-scattered electromagnetic waves by a single dielectric subwavelength sphere. *Nature Com.* **3**, 1171.
36. Y. H. Fu, A. I. Kuznetsov, A. E. Miroshnichenko, Y. F. Yu & B. Luk`yanchuk. (2013). Directional visible light scattering by silicon nanoparticles. *Nature Comm.* **4**, 1527.
37. S. Person, M. Jain, Z. Lapin, J. J. Sáenz, G. Wicks & L. Novotny. (2013). Demonstration of zero optical backscattering from single nanoparticles. *Nano Lett.* **13**, 1367-1868.
38. B. Luk`yanchuk, N. Voshchinnikov, R. Paniagua-Dominguez & A. Kuznetsov. (2015). Optimum Forward Light Scattering by Spherical and Spheroidal Dielectric Nanoparticles with High Refractive Index. *ACS Photonics* **2**, 993-999.
39. A. Alù & N. Engheta. (2010). How does zero forward scattering in magnetodielectric nanoparticles comply with the optical theorem? *J. Nanophoton.* **4**, 041590.
40. E. D. Palik. (1985). Handbook of Optical Constants of Solids. *New York: Academic.*