

# Synthesis, characterization and guest-host properties of inverted unimolecular dendritic micelles

**Citation for published version (APA):**

Stevelmans, S., Hest, van, J. C. M., Jansen, J. F. G. A., Boxtel, van, D., Berg, van den, E. M. M., & Meijer, E. W. (1996). Synthesis, characterization and guest-host properties of inverted unimolecular dendritic micelles. *Journal of the American Chemical Society*, 118(31), 7398-7399. <https://doi.org/10.1021/ja954207h>

**DOI:**

[10.1021/ja954207h](https://doi.org/10.1021/ja954207h)

**Document status and date:**

Published: 01/01/1996

**Document Version:**

Publisher's PDF, also known as Version of Record (includes final page, issue and volume numbers)

**Please check the document version of this publication:**

- A submitted manuscript is the version of the article upon submission and before peer-review. There can be important differences between the submitted version and the official published version of record. People interested in the research are advised to contact the author for the final version of the publication, or visit the DOI to the publisher's website.
- The final author version and the galley proof are versions of the publication after peer review.
- The final published version features the final layout of the paper including the volume, issue and page numbers.

[Link to publication](#)

**General rights**

Copyright and moral rights for the publications made accessible in the public portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

- Users may download and print one copy of any publication from the public portal for the purpose of private study or research.
- You may not further distribute the material or use it for any profit-making activity or commercial gain
- You may freely distribute the URL identifying the publication in the public portal.

If the publication is distributed under the terms of Article 25fa of the Dutch Copyright Act, indicated by the "Taverne" license above, please follow below link for the End User Agreement:

[www.tue.nl/taverne](http://www.tue.nl/taverne)

**Take down policy**

If you believe that this document breaches copyright please contact us at:

[openaccess@tue.nl](mailto:openaccess@tue.nl)

providing details and we will investigate your claim.

# Communications to the Editor

## Synthesis, Characterization, and Guest–Host Properties of Inverted Unimolecular Dendritic Micelles

S. Stevelmans,<sup>†</sup> J. C. M. van Hest,<sup>†</sup> J. F. G. A. Jansen,<sup>†</sup>  
D. A. F. J. van Boxtel,<sup>‡</sup>  
E. M. M. de Brabander-van den Berg,<sup>‡</sup> and E. W. Meijer<sup>\*†</sup>

Laboratory of Organic Chemistry  
Eindhoven University of Technology  
P.O. Box 513, 5600 MB Eindhoven, The Netherlands  
DSM Research, P.O. Box 18  
6160 MD Geleen, The Netherlands

Received December 15, 1995

Revised Manuscript Received June 4, 1996

Dendrimers, being well-defined and highly-branched macromolecules, have become the subject of extensive studies,<sup>1,2</sup> because their multifunctionality and specific shape have been recognized as powerful tools in the synthesis of new structures. Applications of dendrimers in molecular architectures,<sup>2</sup> and the dendritic box,<sup>3</sup> show the versatility of these materials. In 1985, the use of dendrimers as unimolecular micelles was already proposed by Newkome.<sup>4</sup> Micellar behavior has been demonstrated by dissolving, e.g., organic molecules in dendrimers,<sup>5a–e</sup> whereas some dendrimers have been employed as micellar structures in electrokinetic capillary chromatography.<sup>5f–h</sup> In all of these cases, dendrimers are regarded as regular unimolecular micelles, which consist of an apolar core and a polar shell. In this communication we report on the synthesis of *inverted* unimolecular dendritic micelles, by the modification of the end groups of hydrophilic poly(propylene imine) dendrimers<sup>6</sup> (DAB-dendr-(NH<sub>2</sub>)<sub>4–64</sub>), with hydrophobic alkyl chains.

The modification consists of the conversion (in 60–95% isolated yield) of the 4–64 primary amines of DAB-dendr-(NH<sub>2</sub>)<sub>x</sub> into their amide analogues with a variety of long-chain

alkyl acid chlorides (ClCOC<sub>n</sub> with C<sub>n</sub> = (CH<sub>2</sub>)<sub>n–1</sub>CH<sub>3</sub> with *n* = 5, 9–15) in THF and in the presence of Et<sub>3</sub>N as an external base (Scheme 1). Structural characterization of the dendritic amides (DAB-dendr-(NHCOC<sub>n</sub>)<sub>x</sub>) with <sup>1</sup>H-NMR, <sup>13</sup>C-NMR, IR, and MALDI-TOF spectroscopies showed that all of the dendrimer end groups were amidated.<sup>7</sup> Most remarkably, when the long-chain alkyl acid chlorides were used in the reaction with an excess of DAB-dendr-(NH<sub>2</sub>)<sub>4–64</sub>, two products were always isolated; water-insoluble fully reacted dendrimer (at least 90% of the end groups, as determined by <sup>1</sup>H-NMR) and water-soluble, totally unmodified dendrimers (no fatty acid amide functionality is observed by <sup>1</sup>H-NMR and IR) were obtained in the correct product ratios.<sup>8</sup> This effect proved to be independent with respect to solvent (THF or CH<sub>2</sub>Cl<sub>2</sub>), concentration of the reagents, and the degree of excess dendrimer used. The water (in)solubility of the products makes the separation and characterization very easy. However, this effect is not found for pivaloyl chloride, with which partially converted structures are prepared.<sup>9</sup> A reasonable explanation for the phenomenon observed is lacking at the present time.<sup>10</sup>

Evidence for the development of dendritic character (i.e., high packing of end groups) by increasing generation from DAB-dendr-(NHCOC<sub>n</sub>)<sub>4–64</sub> was obtained by <sup>1</sup>H-NMR spectroscopy. A significant shift for the NHCO proton to lower fields with increasing generation was observed (Figure 1). The low-generations, DAB-dendr-(NHCOC<sub>n</sub>)<sub>4–16</sub>, also showed a concentration dependence of the NHCO position, which was absent for the two higher generations, DAB-dendr-(NHCOC<sub>n</sub>)<sub>32,64</sub>. The shift of the amide proton is a result of the change from predominantly concentration-dependent, but weak, intermolecular H-bonding for the lower generations to concentration-

(7). Typical preparation and characterization of an alkyl-modified dendrimer, DAB-dendr-(palmitoyl)<sub>8</sub>: To a solution of 2.5 g DAB-dendr-(NH<sub>2</sub>)<sub>8</sub> (1 equiv, 3.3 mmol) in 50 mL THF, 5.00 g triethylamine and 8.56 g palmitoyl chloride (1.10 equiv, 28.6 mmol) were added. After the mixture stirred for 20 h at room temperature, the solvent was evaporated. The mixture was heated under reflux in 50 mL of diethyl ether for 30 min and filtered, to remove excess palmitoyl chloride. To the residue, a solution of 2 g Na<sub>2</sub>CO<sub>3</sub> in 50 mL H<sub>2</sub>O was added, and the mixture was heated under reflux for 6 h, in order to remove residual ammonium salts and to deprotonate the dendrimers. The mixture was filtered, the residue was dried *in vacuo* at 40 °C, and the product was obtained as a white/yellow solid material (yield 76%). <sup>1</sup>H-NMR (CDCl<sub>3</sub>): δ 0.90 (t, CH<sub>3</sub>), 1.18–1.75 (m, CH<sub>2</sub>–CH<sub>3</sub> + CH<sub>2</sub>–CH<sub>2</sub>–CH<sub>2</sub>), 2.17 (t, NHCO–CH<sub>2</sub>), 2.40 (m, CH<sub>2</sub>–N–(CH<sub>2</sub>)<sub>2</sub>), 3.28 (q, CH<sub>2</sub>–NHCO), 6.95 (t, NHCO) ppm. <sup>13</sup>C-NMR (CDCl<sub>3</sub>): δ 14.10 (CH<sub>3</sub>), 22.69 (CH<sub>2</sub>–CH<sub>3</sub>), 24.87 (N–CH<sub>2</sub>–CH<sub>2</sub>–CH<sub>2</sub>–CH<sub>2</sub>–N + N–CH<sub>2</sub>–CH<sub>2</sub>–CH<sub>2</sub>–N), 25.96 (NHCO–CH<sub>2</sub>–CH<sub>2</sub>), 27.09 (N–CH<sub>2</sub>–CH<sub>2</sub>–CH<sub>2</sub>–NHCO), 29.37–29.73 (CH<sub>2</sub>–(CH<sub>2</sub>)<sub>n</sub>–CH<sub>2</sub>), 31.93 (CH<sub>2</sub>–CH<sub>2</sub>–CH<sub>3</sub>), 36.75 (NHCO–CH<sub>2</sub>), 37.93 (CH<sub>2</sub>–NHCO), 51.64 (N–CH<sub>2</sub>–CH<sub>2</sub>–CH<sub>2</sub>–NHCO), 52.20 (N–CH<sub>2</sub>–CH<sub>2</sub>–CH<sub>2</sub>–CH<sub>2</sub>–N + N–CH<sub>2</sub>–CH<sub>2</sub>–CH<sub>2</sub>–N), 173.59 (NHCO) ppm. IR: amide N–H stretch 3300.2 cm<sup>–1</sup>, sec. amide N–H stretch 3083.8 cm<sup>–1</sup>, C–H sat. 2918.1 cm<sup>–1</sup>, sec. amide C=O 1638.9 cm<sup>–1</sup>, N–H bend 1560.0 cm<sup>–1</sup>. DSC: phase transition at 74.3 °C. MALDI-TOF: measurement of DAB-dendr-(NHCOC<sub>15</sub>)<sub>8</sub>: 2683 g/mol, calcd 2678 g/mol.

(8) This phenomenon was observed for reactions between a 2-, 3-, and 4-fold excess of DAB-dendr-(NH<sub>2</sub>)<sub>4–64</sub> based on the number of primary amine end groups and palmitoyl and oleyl chloride. The workup procedure with the Na<sub>2</sub>CO<sub>3</sub> solution resulted in separation between water-soluble DAB-dendr-(NH<sub>2</sub>)<sub>4–64</sub> and modified DAB-dendr-(NHCOC<sub>n</sub>)<sub>4–64</sub>. Both products isolated were unambiguously identified with IR and NMR spectroscopies, and the melting points of the amidated products resembled those of the products made by using equimolar amounts of reactants. For experimental details, see the supporting information.

(9) It was found that 13 out of 64 end groups were amidated by using 0.21 equiv of pivaloyl chloride per equivalent end group of DAB-dendr-(NH<sub>2</sub>)<sub>64</sub>. Workup was strongly hampered by the formation of emulsions, and some fractionation during dialysis was found. When equimolar amounts of pivaloyl chloride are used, no emulsions were observed, and the fully amidated structure was easily obtained in pure form (i.e., at least 95% of the end groups have reacted).

(10) For similar effects in calixarenes with 4–6 functional groups in one molecule, see: Shinkai, S.; Araki, K.; Shibata, J.; Manabe, O. *J. Chem. Soc., Perkin Trans. 1* 1989, 195.

<sup>†</sup> Eindhoven University of Technology.

<sup>‡</sup> DSM Research.

(1) (a) Issberner, I.; Moors, R.; Vögtle, F. *Angew. Chem.* 1994, 106, 2507. (c) Tomalia, D. A.; Naylor, A. M.; Goddard, W. A., III. *Angew. Chem.* 1990, 102, 119. (c) Hawker, C. J.; Fréchet, J. M. J. *J. Am. Chem. Soc.* 1990, 112, 7638.

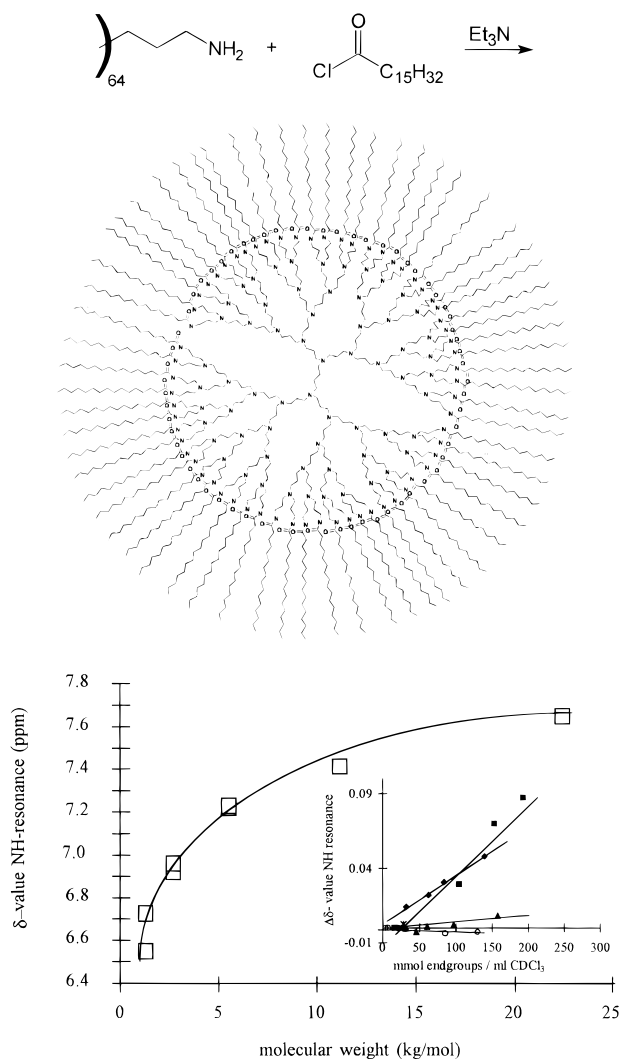
(2) (a) Newkome, G. R.; Nayak, A.; Behera, R. K.; Moorefield, C. N.; Baker, G. R. *J. Org. Chem.* 1992, 57, 358. (b) Percec, V.; Chu, P.; Kawasumi, M. *Macromolecules* 1994, 27, 4441. (c) Watanabe S.; Regen, S. L. *J. Am. Chem. Soc.* 1994, 116, 8855. (d) Gitsov, I.; Fréchet, J. M. J. *Macromolecules* 1994, 27, 7309. (e) Chapman, T. M.; Hillyer, G. L.; Mahan, E. J.; Shaffer, K. A. *J. Am. Chem. Soc.* 1994, 116, 11195. (f) van Hest, J. C. M.; Baars, M. W. P. L.; Delnoye, D. A. P.; van Genderen, M. H. P.; Meijer, E. W. *Science* 1995, 268, 1592.

(3) (a) Jansen, J. F. G. A.; de Brabander-van den Berg, E. M. M.; Meijer, E. W. *Science* 1994, 266, 1226. (b) Jansen, J. F. G. A.; Meijer, E. W.; de Brabander-van den Berg, E. M. M. *J. Am. Chem. Soc.* 1995, 117, 4417.

(4) Newkome, G. R.; Yao, Z.-q.; Baker, G. R.; Gupta, V. K. *J. Org. Chem.* 1985, 50, 2003.

(5) (a) Tomalia, D. A.; Berry, V.; Hall, M.; Hedstrand, D. *Macromolecules* 1987, 20, 1164. (b) Newkome, G. R.; Moorefield, C. N.; Baker, G. R.; Saunders, M. J.; Grossman, S. H. *Angew. Chem.* 1991, 103, 1207. (c) Wooley, K. L.; Hawker, G. J.; Fréchet, J. M. J. *J. Am. Chem. Soc.* 1993, 115, 11496. (d) Newkome, G. R.; Young, J. K.; Baker, G. R.; Potter, R. L.; Audoly, L.; Cooper, D.; Weiss, C. D. *Macromolecules* 1993, 26, 2394. (e) Hawker, C. J.; Wooley, K. L.; Fréchet, J. M. J. *J. Chem. Soc., Perkin Trans. 1* 1993, 1287. (f) Tanaka, N.; Tanigawa, T.; Hosoya, K.; Kimata, K.; Araki, T.; Teraba, S. *Chem. Lett.* 1992, 959. (g) Kuzdzal, S. A.; Monning, C. A.; Newkome, G. R.; Moorefield, C. N. *J. Chem. Soc., Chem. Commun.* 1994, 2139. (h) Muijselaar, P. G. H. M.; Claessens, H. A.; Cramers, C. A.; Jansen, J. F. G. A.; Meijer, E. W.; de Brabander-van den Berg, E. M. M.; van der Wal, S. J. *High Resolut. Chromatogr.* 1995, 18, 121.

(6) de Brabander-van den Berg, E. M. M.; Meijer, E. W. *Angew. Chem.* 1993, 105, 1370.

**Scheme 1.** Modification of DAB-dendr-(NH<sub>2</sub>)<sub>64</sub> with Palmitoyl Chloride**Figure 1.** Generation dependence of the NHCO NMR resonance of DAB-dendr-(NHCOC<sub>15</sub>)<sub>x</sub> series, measured in CDCl<sub>3</sub>. Inset: Concentration dependence of the NHCO NMR resonance of the series, measured in CDCl<sub>3</sub> (moles of alkyl amide end groups per liter): ■, *x* = 4; ◆, *x* = 8; ▲, *x* = 16; ○, *x* = 32; \*, *x* = 64.

independent strong intramolecular H-bonding for the higher generations. Dynamic light scattering (DLS) also confirms the absence of clustering between DAB-dendr-(NHCOC<sub>15</sub>)<sub>64</sub> molecules: single particle behavior was observed with a hydrodynamic diameter of 2–3 nm in dichloromethane.

The first-generation dendrimers showed melting points (measured by DSC) that resemble those of the corresponding alkylamides, indicating that the first generation is a regular

organic compound. Phase transitions observed for the higher generation dendrimers were independent of the number of end groups and fully determined by the alkyl chain length. The phase transition temperature increased continuously with increasing chain length (mp of DAB-dendr-(NHCOC<sub>*n*</sub>)<sub>8–64</sub> varies from –1 °C for *n* = 5 to 75 °C for *n* = 15), and no odd–even behavior could be detected.<sup>11,12</sup>

Evidence for an inverted micellar structure of the alkyl amide-modified dendrimers was obtained by their capability to act as guest–host systems. DAB-dendr-(NHCOC<sub>5, 9, 15</sub>)<sub>8,64</sub> were used as dynamic hosts for guest molecules like Bengal Rose. The hydrophilic dye was trapped into the inverted unimolecular micelles by first dissolving micelle and dye in ethanol, allowing the dye to enter the dendritic core. Precipitation of the complex in acetonitrile, followed by an extensive washing procedure with acetonitrile until no coloration of solvent occurred, resulted in the removal of untrapped and adhered dye. The *x* = 64 compounds were further purified by dialysis with water. The number of dye molecules trapped (varying from an average of 1 for *x* = 8 to 7 for *x* = 64) was determined with UV spectroscopy.<sup>13</sup> It was possible to strongly improve the compatibility between Bengal Rose and an apolar solvent such as *n*-hexane by first encapsulating the dye into the inverted micelle. It was impossible to release the dye from the solution by washing with water; however, the addition of toluene to Bengal Rose@DAB-dendr-(NHCOC<sub>*n*</sub>)<sub>64</sub> in *n*-hexane released the dye from the micelle. These guest–host systems also open routes toward compatibilization of apolar and polar materials using nanoscopic phase separation, as a result of the unique properties of dendritic macromolecules.<sup>14</sup>

**Supporting Information Available:** Synthetic procedures and spectroscopic properties of the palmitoyl-modified dendrimers and the yields after workup of all the fully modified structures (14 pages). See any current masthead page for ordering and Internet access instructions.

JA954207H

(11) (a) Percec, V.; Tsuda, Y. *Macromolecules* **1990**, *23*, 3509. (b) Percec, V.; Tomazos, D. *Comprehensive Polymer Science*; Allen, G., Ed.; Pergamon Press: Oxford, 1992, Suppl. Vol. I, pp 300–383.

(12) The phase transition is probably due to the melting of small ordered domains of alkyl chains, as proposed for alkanethiol-stabilized gold clusters and poly(L-glutamates) with long alkyl chains; see e.g.: (a) Watanabe, J.; Ono, H.; Uematsu, I.; Abe, A. *Macromolecules* **1985**, *18*, 2141. (b) Terrill, R. H.; Postlewaite, T. A.; Chen, C.-h.; Poon, C.-D.; Terzis, A.; Chen, A.; Hutchison, J. E.; Clark, M. R.; Wignall, G.; Londono, J. D.; Superfine, R.; Falvo, M.; Johnson, C. S., Jr.; Samulski, E. T.; Murray, R. W. *J. Am. Chem. Soc.* **1995**, *117*, 12537. (c) Badia, A.; Singh, S.; Demers, L.; Cuccia, L.; Brown, G. R.; Lennox, R. B. *Chem. Eur. J.* **1996**, *2*, 359.

(13) It is assumed that the absorption coefficients  $\epsilon$  of “free” and encapsulated Rose Bengal, both measured in ethanol, are identical. The load of the dye is strongly dependent on both generation and fatty acid chain length. The highest number (seven) of molecules entrapped is found for DAB-dendr-(NHCOC<sub>9</sub>)<sub>64</sub>. The chain-length dependent barrier effect seems to have its optimum at C<sub>9</sub>, in which case the hydrophobic shell favors trapping of the dye into the micelle instead of release or exclusion.

(14) Independently, Tomalia et al. prepared guest–host systems based on inverted unimolecular micelles from PAMAM dendrimers modified with fatty acids: D. A. Tomalia, personal communication.