

AD-A275 378



2

OFFICE OF NAVAL RESEARCH

Contract N00014-82K-0612

R&T CODE: 4133032

TECHNICAL REPORT NO. 91

Template Synthesized Nanoscopic Gold Particles: Optical Spectra and the Effects of Particle Size and Shape

by

Colby A. Foss, Jr., Gabor L. Hornyak, Jon A. Stockert and C. R. Martin

Prepared for publication

in

Journal of Physical Chemistry

**Department of Chemistry
Colorado State University
Ft. Collins, CO 80523**

**DTIC
ELECTE
FEB 04 1994
S B D**

January 25, 1994

**Reproduction in whole or part is permitted for
any purpose of the United States Government**

**This document has been approved for public release
and sale; its distribution is unlimited**

94-03548



94 2 02 057

**Best
Available
Copy**

REPORT DOCUMENTATION PAGE

OMB No. 0704-0188

Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302, and to the Office of Management and Budget, Paperwork Reduction Project (0704-0188), Washington, DC 20503.

1. AGENCY USE ONLY (Leave blank)	2. REPORT DATE Jan. 24, 1994	3. REPORT TYPE AND DATES COVERED Interim
4. TITLE AND SUBTITLE Template Synthesized Nanoscopic Gold Particles: Optical Spectra and the Effects of Particle Size and Shape		5. FUNDING NUMBERS Contract # N00014-82K-0612
6. AUTHOR(S) Colby A. Foss, Jr., Gabor L. Hornyak, Jon A. Stockert and C. R. Martin		8. PERFORMING ORGANIZATION REPORT NUMBER ONR TECHNICAL REPORT #91
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) Dr. Charles R. Martin Department of Chemistry Colorado State University Fort Collins, CO 80523		
9. SPONSORING / MONITORING AGENCY NAME(S) AND ADDRESS(ES) Office of Naval Research 800 North Quincy Street Arlington, VA 22217		10. SPONSORING / MONITORING AGENCY REPORT NUMBER
11. SUPPLEMENTARY NOTES		
12a. DISTRIBUTION / AVAILABILITY STATEMENT Reproduction in whole or part is permitted for any purpose of the United States Government. This document has been approved for public release and sale; its distribution is unlimited.		12b. DISTRIBUTION CODE
13. ABSTRACT (Maximum 200 words) We have prepared nanoscopic gold cylinders of controlled radius and aspect ratio via electrodeposition of the metal within the pores of anodically-grown porous aluminum oxide membranes. The nanocylinder radii are determined by the pore dimensions of the host alumina which, in turn, depend on anodization conditions. The particle aspect ratios were controlled by varying the amount of Au deposited within the pores. The optical spectra of the gold nanocylinder/alumina composites exhibit strong absorption bands in the visible spectrum. The extinction maxima (λ_{max}) values for gold particles approaching sphere-like geometry agree well with Mie Theory calculations. The blue shift of λ_{max} as the particle aspect ratio is increased is in qualitative agreement with Maxwell-Garnett Theory. We propose a simple modification of Maxwell-Garnett Theory that addresses both size and shape effects.		
14. SUBJECT TERMS Nanometals, nanomaterials, Maxwell-Garnett Theory		15. NUMBER OF PAGES 41
		16. PRICE CODE
17. SECURITY CLASSIFICATION OF REPORT	18. SECURITY CLASSIFICATION OF THIS PAGE	19. SECURITY CLASSIFICATION OF ABSTRACT UNCLASSIFIED
20. LIMITATION OF ABSTRACT		

Template Synthesized Nanoscopic Gold Particles: Optical Spectra and the Effects of Particle Size and Shape

Colby A. Foss, Jr.*, Gabor L. Hornyak, Jon A. Stockert
and Charles R. Martin#

Department of Chemistry
Colorado State University
Fort Collins, CO 80523

DTIC QUALITY INSPECTED 6

Corresponding Author

* **Current Address:** Department of Chemistry
Georgetown University
Washington, D.C. 20057

Accession For	
NTIS GRA&I	<input checked="" type="checkbox"/>
DTIC TAB	<input type="checkbox"/>
Unannounced	<input type="checkbox"/>
Justification	
By _____	
Distribution/	
Availability Codes	
Dist	Avail and/or Special
A-1	

Abstract

We have prepared nanoscopic gold cylinders of controlled radius and aspect ratio via electrodeposition of the metal within the pores of anodically-grown porous aluminum oxide membranes. The nanocylinder radii are determined by the pore dimensions of the host alumina which, in turn, depend on anodization conditions. The particle aspect ratios were controlled by varying the amount of Au deposited within the pores. The optical spectra of the gold nanocylinder/alumina composites exhibit strong absorption bands in the visible spectrum. The extinction maxima (λ_{max}) values for gold particles approaching sphere-like geometry agree well with Mie Theory calculations. The blue shift of λ_{max} as the particle aspect ratio is increased is in qualitative agreement with Maxwell-Garnett Theory. We propose a simple modification of Maxwell-Garnett Theory that addresses both size and shape effects.

I. Introduction

The optical properties of nanoscopic metal particles have attracted a great deal of interest for many decades. Indeed, it has been almost a century since Gustav Mie demonstrated how particle size gives rise to the various colors of colloidal gold solutions [1,2]. In more recent times attention has focused on the application of such small metal particles in surface enhanced spectroscopy [3], photocatalysis [4,5] and selective solar absorbers [6].

Most work to date on the optical properties of nanoscopic metal particles has involved methods that preclude control of particles shape

and orientation with respect to the electric field of the incident light. Exceptions to this include the work of Liao and coworkers who prepared ordered arrays of ellipsoidal silver particles with aspect ratios as high as 3:1 using photolithography [7]. In our laboratories we have developed methods based on the template synthesis strategy in which various materials are deposited within the pores of host membranes such as track-etched polycarbonate [8] and anodic aluminum oxide [9]. The microstructure of the host material and other conditions of deposition thus define particle geometry and orientation.

In our efforts to understand the optical properties of submicron metallic particles, we have found that anodic aluminum oxides are ideal host templates: they are optically transparent over a wide range ($0.3 \mu\text{m} \leq \lambda \leq 6 \mu\text{m}$) and the parallel alignment of the cylindrical pores means that the template-synthesized metal particles are also aligned in one direction. Hence, the particles can be studied without removing the host template, and there is no ambiguity in particle orientation.

In our early work we relied upon commercially available anodic aluminas [9], which contain pores *ca.* $0.25 \mu\text{m}$ in diameter. In these membranes we prepared cylindrical gold particles with aspect ratios (defined as the particle length, **A**, divided by its diameter, **B**) as high as 10:1. The resulting Au/Al₂O₃ composites showed significant transparency in the infrared spectrum but not at shorter wavelengths where $0.25 \mu\text{m}$ diameter particles scattered appreciably.

In a recent note, we presented preliminary results of our optical characterization of gold cylinders template-synthesized in anodic alumina membranes prepared in our laboratory [10]. The membranes

prepared in that study had much smaller pores (ca. 50 nm in diameter), and the resulting particles showed extinction maxima in the visible spectrum reminiscent of aqueous gold colloids of similar size. In that work, we demonstrated how the template synthesis approach allows for simple control of gold nanocylinder aspect ratio and that varying the particle aspect ratio gives rise to systematic shifts in the extinction maximum [10]. We also showed that the observed effects of particle shape are qualitatively consistent with the predictions of Maxwell-Garnett Theory (M-G), which is a simple treatment for composite materials that addresses particle shape and orientation but not size [11].

In this paper we present the results of a study in which we have systematically varied both nanocylinder aspect ratio and diameter. We show how the template synthesis method is a convenient means by which one can control these parameters and hence, the composite's optical properties. Because there is no ambiguity in nanocylinder orientation with respect to the incident field, the analysis of size and shape effects on optical spectra should be greatly simplified. We compare the spectra of the gold nanocylinder/alumina composites with the predictions of M-G Theory and Mie Scattering Theory [2]. We also propose an approximation within the M-G framework that addresses both the size and shape of the nanoscopic particles.

II. Theory: Mie Scattering and Maxwell-Garnett Treatments for Nanoscopic Particles

In this section we review two approaches that we use to model the optical spectra of composites containing nanoscopic particles. Mie Scattering Theory is a rigorous formulation for particles of any size but is limited to spherical geometry and interparticle separation distances which are much larger than the wavelength of the incident light [1,2]. Maxwell-Garnett (M-G) Theory is strictly valid only in the limit where particle dimensions and separation distances are infinitely small relative to the wavelength but can be easily generalized to particles of various shapes [11]. In our experiments, because we vary both size and shape of the gold particles, each of these approaches has something to offer in the interpretation of the optical spectra.

In the Mie approach, the total transmittance through a film containing spherical metal particles is given by [2a]

$$T_{\text{tot}} = \exp (- N \pi a^2 Q_{\text{ext}} d) \quad (1)$$

where N is the number concentration of spheres per unit volume, a is the sphere radius, and d is the film thickness. The extinction coefficient Q_{ext} is related to the Mie scattering coefficients a_n and b_n through [2a]

$$Q_{\text{ext}} = \left(\frac{2}{x^2} \right) \sum_{n=1}^{\infty} (2n+1) \text{Re} (a_n + b_n) \quad (2)$$

where $x = 2\pi n_0/\lambda$ (n_0 is the refractive index of the host medium and λ is the wavelength of the incident light *in vacuo*). The term Re in Equation 2 signifies the real part of the complex function in parentheses. The scattering coefficients a_n and b_n describe the amplitudes of the scattered electric and magnetic fields, respectively [10], and are given by

$$a_n = \frac{\Psi'_n(y) \Psi_n(x) - m \Psi_n(y) \Psi'_n(x)}{\Psi'_n(y) \zeta_n(x) - m \Psi_n(y) \zeta'_n(x)} \quad (3a)$$

$$b_n = \frac{m \Psi'_n(y) \Psi_n(x) - \Psi_n(y) \Psi'_n(x)}{m \Psi'_n(y) \zeta_n(x) - \Psi_n(y) \zeta'_n(x)} \quad (3b)$$

where m is related to the complex refractive index of the metal, \tilde{n}_m , and to the host medium refractive index, n_0 , via

$$m = \tilde{n}_m / n_0 \quad (4a)$$

and

$$\tilde{n}_m = n_m + i k_m \quad (4b)$$

where n_m is the real refractive index of the metal and k_m is the absorption coefficient. The quantity y in Equations 3a and 3b is equal to $2\pi\tilde{n}_m/\lambda$. The primes in Equations 3a and 3b signify first derivatives with respect to the argument.

The functions Ψ_n and ζ_n are related to the Bessel (J_n) and second order Hankel (H_n^2) functions via [2,12].

$$\Psi_n(z) = (z \pi / 2)^{1/2} J_{n+1/2}(z) \quad (5a)$$

and

$$\zeta_n(z) = (z \pi / 2)^{1/2} H_{n+1/2}^{(2)}(z) \quad (5b)$$

where z is equal to x or y .

For metal particles less than ca. 100 nm in diameter, the Mie scattering treatment for visible wavelengths requires only the first two or three expansion terms in Equation 2. Nonetheless, the computation is still quite tedious. A quite different approach which is valid when the metal particle dimensions are much smaller than the wavelength of light was developed by J.C. Maxwell-Garnett [9a]. M-G Theory assumes that it is reasonable to define an effective complex dielectric constant $\tilde{\epsilon}_c$ for a composite containing metal particles (with complex dielectric constant $\tilde{\epsilon}_m$) imbedded in a host matrix (with complex dielectric constant $\tilde{\epsilon}_0$) through

$$\left(\frac{\tilde{\epsilon}_c - \tilde{\epsilon}_0}{\tilde{\epsilon}_c + 2\tilde{\epsilon}_0} \right) = f_m \left(\frac{\tilde{\epsilon}_m - \tilde{\epsilon}_0}{\tilde{\epsilon}_m + 2\tilde{\epsilon}_0} \right) \quad (6)$$

where f_m is the volume fraction of metal in the composite. The complex dielectric constant is related to the optical refractive index n and absorption coefficient k via

$$\tilde{\epsilon} = \tilde{n}^2 = \epsilon' + i \epsilon'' \quad (7a)$$

$$\epsilon' = n^2 - k^2 \quad (7b)$$

$$\epsilon'' = 2 n k \quad (7c)$$

where ϵ' is the real part of the dielectric constant and ϵ'' is the imaginary component (the refractive index n is not to be confused with the summation index in Equations 2 and 3).

Maxwell-Garnett's original work addressed spherical inclusions, and it is for this specific geometry that the factor 2 appears in the denominators of Equation 6. This factor is also called the screening parameter [11b] and is in general denoted κ . Hence, while $\kappa = 2$ for spheres, long needle-like particles oriented with their axes of revolution parallel to the direction of light incidence have a κ value that approaches unity. On the other hand, κ approaches infinity for thin flat discs oriented with their axes of revolution perpendicular to the light incidence.

From a knowledge of $\tilde{\epsilon}_m$, $\tilde{\epsilon}_o$, f_m and κ , one can derive the effective dielectric constant $\tilde{\epsilon}_c$ for the composite, and then, via Equations 7a-c, the effective composite optical constants n_c and k_c can be calculated. The total transmittance is then given by [13]

$$T_{tot} = \left[1 - \frac{(n_c - 1)^2 + k_c^2}{(n_c + 1)^2 + k_c^2} \right]^2 \exp(-4 \pi k_c d / \lambda) \quad (8)$$

where d is the film thickness and λ is the incident wavelength. The term preceding the exponential accounts for reflective losses at the film/air interface [14].

III. Experimental Section

A. Porous Alumina Membrane Preparation

Nanoporous alumina template membranes were prepared by anodization of aluminum (Aldrich 2mm plate 99.999% purity) in aqueous oxalic acid media. Anodization of aluminum to yield porous oxides is a well established technique and has been discussed extensively in the literature [15]. For details on how the porous oxide is removed from the aluminum substrate, consult Reference 16.

Our two electrode anodization cell consisted of an insulated thermostat-controlled plastic bucket (ca. 19 L), a 6 cm x 10 cm stainless steel cathode and a 10 cm x 10 cm Al plate anode. Voltage control was provided by a Sorensen DCR-9B power supply.

Pore diameters in anodic aluminas are roughly proportional to the applied voltage in potential-controlled anodization [16]. In this study, we prepared membranes with pores of four different diameters. Anodization at 40 V and 50 V in 4% (w/v) oxalic acid yielded membranes with pore diameters of approximately 60 nm and 75 nm respectively. Anodization at 70 V and 90 V in 2% (w/v) oxalic acid produced pores with diameters of approximately 86 nm and 120 nm respectively. The electrolyte temperatures was maintained between 0° C and 7° C. Membranes were grown from 30 μm to 40 μm in thickness before removal. Figure 1 shows transmission electron micrographs (TEMs) of facial sections of alumina composite membranes prepared under the above conditions. The porosity of these membranes is in the range of 25% to 30%.

B. Gold Nanoparticle Preparation

Gold nanoparticles were prepared by electrodeposition of Au(I) (*Technic Inc., Orotemp 24™* gold plating solution) within the pores of the alumina membranes. The details of this procedure are given in Reference 9b. Four amounts of gold (0.20 C, 0.40 C, 0.70 C and 1.00 C), in terms of coulombs, were deposited in each of the four different pore diameter membranes over a 3.3 - 3.5 cm² area, depending on the measured porosity. The potentiostat employed was an *EG&G Princeton Applied Research Model 173* equipped with a *Model 179* digital coulometer.

C. Anodic Alumina and Gold Nanoparticle/Alumina Composite Characterization

Alumina pore radii and gold nanoparticle dimensions were determined by means of transmission electron microscopy (JEOL 2000 TEM). The thin sample sections required for these analyses were obtained by diamond-knife microtome. UV/Visible/Near-IR spectra were obtained using a *Hitachi U-3501* spectrometer. Figure 2 shows a schematic of the experimental optical configuration used to examine the gold nanocylinder/alumina composites.

IV. Results

The template synthesis method allows for straightforward control of nanocylinder size, shape and orientation. Figure 3 shows TEM images of cross sections of alumina membranes (prepared at 40 V in 4% oxalic acid) after the deposition of Au into the pores. At low deposition levels like 0.020 C (0.06 C Au/cm²), the particles are short and sphere-like. At

higher deposition levels such as 1.00 C (0.30 C Au/cm²), the particles become longer and needle-like within the cylindrical radius held constant by the pore walls. Table I summarizes the results of measurements of particle dimensions for the various pore radius/gold deposition combinations as obtained from TEM images.

The TEM images of the gold/alumina composites also show that the gold particles do not lie at a uniform distance from the membrane face but rather through a layer *ca.* 1 μm in thickness. We discussed the reasons for this in a previous paper, and also how this non-uniform particle placement affects the optical path length, d , and metal volume fraction, f_m [9b]. We will discuss this point further in the next section.

Figure 4 shows UV/Vis/NIR extinction spectra [17] for three composites of different pore radii in which the gold nanoparticles are short and nearly spherical (Curves 1,2 and 3). In each case the composite exhibits a significant transparency in the NIR region of the spectrum and a strong extinction band in the visible. The wavelength of maximum extinction increases with increasing particle radius giving rise to color variations in the different gold particle radius composites. The transmitted light for the 30 nm radius particles appears red-purple while 60 nm radius particles appear blue-green. This trend is consistent with the colors exhibited by colloidal gold particles of different sizes in aqueous solutions [2]. The 60 nm particle composite also shows a weak shoulder (at *ca.* 550 nm) on the broad band centered at 655 nm.

The dependence of the optical spectra on particle shape is shown in Figure 5. As the aspect ratio increases, the extinction intensity increases and λ_{max} shifts to shorter wavelengths. This trend is seen for

all composite systems considered in this study and is summarized in Figure 6, where λ_{max} is plotted against the natural logarithm of the aspect ratio, $\ln(A/B)$. The two smallest pore radius systems (30 nm and 38 nm) show λ_{max} values that converge at high aspect ratios. The larger pore systems exhibit similar trends with respect to shape, but the λ_{max} values are red-shifted relative to the small particle radius composites.

Thus there are two trends immediately apparent for gold nanocylinder particles aligned with their principal axes parallel to the direction of light incidence. First of all, λ_{max} red-shifts with increasing cylinder radius for particles of all aspect ratios (Figure 6). Secondly, for constant cylinder radius, λ_{max} blue-shifts as the particle aspect ratio is increased (Figure 6).

V. Discussion

A. Comparison of Spectra of Sphere-Like Gold Particles with Mie Calculations

As it was mentioned in the previous section, deposition of small amounts of gold gives rise to particles whose aspect ratios are nearly unity. It is of interest then to compare the experimental spectra for these spherical particle composites with spectra calculated using Mie Theory. The calculation requires a knowledge of the particle radii (which we obtain from the TEM measurements), the values of the optical constants for the metal particles and host membrane for the spectral range of interest, and finally the particle density N and optical path length d . The values of n_m and k_m for gold were taken from Reference 18. For the host medium, we assumed $n_o = 1.6$ [19]. While the anodic alumina used in

this study are slightly absorbing in the visible spectrum ($k_0 < 10^{-3}$), we assumed $k_0 = 0$ to avoid complex arguments in the parameter x of equations 3a and 3b and thus simplify the calculation.

We computed Q_{ext} using Equations 2-4 with $n = 1$ through 3. We have found that the third term in Equation 2 is negligible for all particle sizes considered in this study. The total transmittance was then calculated from Equation 1, with particle density N and composite path length d chosen so as to yield extinction intensities comparable to experiment (*vide infra*).

The Mie-calculated spectra shown in Figure 7 are in good qualitative agreement with the experimental spectra. As the sphere radius increases, the extinction maximum shifts to longer wavelengths and decreases in intensity. The calculated spectra also exhibit increased band broadening with particle size, though not to the extent seen in experiment (see Figure 4).

As shown in Figure 6, the lowest aspect ratio particles are still somewhat prolate (i.e., their aspect ratios are greater than unity). Hence, in order to compare the experimental and Mie Theory λ_{max} values, we extrapolated the experimental λ_{max} values shown in Figure 6 to unit aspect ratio using a quadratic fit of λ_{max} versus $\ln(A/B)$. Table II summarizes these λ_{max} values extrapolated from experiment as well as those calculated from Mie Theory. It is evident that the quantitative agreement is quite satisfactory.

The Mie-calculated spectrum for the 60 nm radius particles exhibits a shoulder at 530 nm which compares favorably with the weak shoulder seen in the experimental spectrum at ca. 550 nm. In the Mie

treatment, this band is due to the gold sphere quadrupole mode and arises from the $n = 2$ index term in Equations 2 and 3 [20]. This mode is negligible in all but the 60 nm radius calculation. For the particle radius range considered in this study, the leading dipole term ($n = 1$) predominates.

In principle, it should be possible to determine the particular concentration N using

$$N = 3 f_m / 4 \pi a^3 \quad (9)$$

As we discussed in a previous paper, because of the geometry of the oxide pores and the manner in which the particles are created in the pores, the metal volume fraction should be related to the intrinsic porosity P of the host membrane and the optical path length d via [9b]

$$f_m = P (2 a / d) \quad (10)$$

In fact, when we attempted spectral calculations using N based on Equations 9 and 10, with estimates of P and d from TEM images, the extinction intensities were much higher than those seen experimentally (the λ_{\max} results are not affected by N in the Mie treatment). Although the reasons for this apparent discrepancy are not explicitly known, the values of the experimental and simulated spectra converge if lower porosities are input into the Mie calculations.

B. Particle Shape Effects in the Maxwell-Garnett Limit

If a composite contains particles whose dimensions are much smaller than the wavelength of the incident light, then the Maxwell-Garnett formulation of Equation 6 is applicable. Because Equation 6 does not address particle size, it cannot be used to model size effects on extinction maxima as in the case of Mie Theory. On the other hand, particle shape determines the screening parameter κ , and hence, will be manifest in the composite optical properties n_c and k_c .

In our attempts to model shape effects in the experimental spectra, we treat the gold nanocylinders as ellipsoids of revolution. The long axis, A , of the particle is thus identified with twice the semimajor axis a of an ellipsoid. The semiminor axis b is then the particle's cylindrical radius where $2b = B$, the short axis or diameter of the particle.

The M-G screening parameter κ is related to the Lorentz depolarization factor q through [11b]

$$\kappa = \frac{1}{q} - 1 \quad (11)$$

The factor q depends on the shape of the particle. For an electric field incident along the long axis A of a prolate ellipsoid, the depolarization factor q_a is given by [2]

$$q_a = \frac{1 - \zeta^2}{\zeta^2} \left[\frac{1}{2\zeta} \ln \left(\frac{1 + \zeta}{1 - \zeta} \right) - 1 \right] \quad (12a)$$

where

$$\zeta = 1 - \left(\frac{b}{a}\right)^2 \quad (12b)$$

In our study, the gold particles are aligned with their principal axes parallel to the direction of light incidence. The electric field is thus incident along the short axes of the particles. For the special case of an ellipsoid of revolution, we can relate the depolarization factor along the long axis (q_a) to q_b , the depolarization factor along the short axis via [21]

$$q_b = \frac{1 - q_a}{2} \quad (13)$$

In our experiments, low amounts of deposited gold leads to particles that are nearly spherical. In the spherical limit (as $A/B \rightarrow 1$), the depolarization factor q_b is equal to $1/3$ and κ is equal to 2. However, as we increase the amount of gold deposited, the aspect ratio increases, and as it approaches infinity ($A/B \rightarrow \infty$), Equations 11-13 lead to $q_b = 1/2$ and $\kappa=1$. It is thus relevant to examine the M-G-calculated spectra for $1 < \kappa \leq 2$.

Figure 8 shows absorption spectra calculated using M-G Theory for composites containing gold ellipsoids of varying aspect ratios such that $1 < \kappa \leq 2$. As in the case of the Mie calculations, the optical properties of gold were taken from Reference 18. For the host oxide, we used complex \tilde{n}_o values obtained in this laboratory [22]. We modeled the experimental membranes as three-layer systems in which the gold/alumina composite layer is sandwiched between two layers of alumina which contain no gold

(see inset of Figure 8). Thus there are four interfaces where reflective losses occur in addition to the absorption losses in the composite and alumina layers. [9b].

The M-G-calculated spectra shown in Figure 8 agree qualitatively with experimental data (see Figures 5a and 5b). As the gold particle aspect ratio increases, the absorption intensity increases (due to the attendant increase in path length and metal volume fraction). However, the increase in aspect ratio also engenders a decrease in κ and λ_{\max} shifts to shorter wavelengths. This effect is seen in the experimental spectra for all pore diameter systems, as summarized in Figure 6. The lowest curve in Figure 6 describes the shape effect on λ_{\max} in the M-G limit. All experimental λ_{\max} values are shifted red relative to the M-G limit.

In the M-G limit, the dependence of λ_{\max} on particle shape can be understood in terms of the particle dipole resonance condition often discussed in the surface enhanced Raman spectroscopy (SERS) literature [3]. The wavelength of highest absorption in the metal particle composite corresponds to the condition where the induced field in the metal is maximal. This occurs when the real component of the metal dielectric constant ϵ'_m is equal to $-\kappa\epsilon'_o$. Hence, the right hand side of Equation 6 becomes very large (assuming the imaginary component of the metal and host dielectric functions are very small and the composite dielectric function is maximized). The real dielectric constant ϵ'_m for gold (and most metals) is negative in sign and monotonically decreases at wavelengths above the plasma edge [23]. Hence, if κ decreases, the dipole resonance condition occurs at a shorter wavelength.

C. An Approximate Dynamical Maxwell-Garnett Model for Addressing Size and Shape Effects

Mie Theory successfully describes size effects but is limited to spheres. In contrast, M-G Theory predicts qualitative trends in λ_{\max} with shape, but cannot deal with size. While there have been numerous scattering treatments for ellipsoidal [24] and cylindrical particles [25], they are, unfortunately, even more tedious than the Mie treatment for spheres. It is desirable to have a simple, if very approximate, model which deals with size and shape effects simultaneously, and is also appropriate for systems in which interparticle separations cannot be considered infinite, as is formally required in single particle scattering treatments such as Mie Theory. In this section we propose such a model. The basic strategy is to incorporate a size-dependent depolarization factor into the M-G treatment and then calculate an effective composite dielectric function from which we can simulate spectra.

In 1983, Meier and Wokaun, in an effort to predict metal particle size effects in SERS, derived an alternate expression for the depolarization factor. Specific for spheres, their model defines an effective depolarization factor q_{eff} , which is related to sphere radius a via [26]

$$q_{\text{eff}} = \frac{1}{3} - \left(\frac{1}{3}\right) k^2 a^2 - \left(\frac{2}{9}\right) i k^3 a^3 \quad (14)$$

where the first term on the *r.h.s.* of Equation 14 is the Lorentz depolarizing factor ($q = 1/3$) for spheres. The second term involves *dynamic depolarization* and accounts for the fact that a particle that is

not small relative to the incident wavelength will experience different phases of the incident field [27]. The term k is equal to $2\pi\tilde{n}_0/\lambda$ (and should not be confused with the absorption coefficient of Equations 4, 7 and 8). The third term accounts for damping of the induced dipole due to radiation emission [27].

The expression for spheres in Equation 14 was generalized to ellipsoids of revolution by Zeman and Schatz [27,28]. The dimension of relevance in the size dependent terms is the ellipsoid axis parallel to the electric field [26-28]. Therefore, we can calculate an effective screening factor κ_{eff} using

$$q_{\text{eff}} = q_b - \left(\frac{1}{3}\right)k^2 b^2 - \left(\frac{2}{9}\right)i k^3 b^3 \quad (15a)$$

$$\kappa_{\text{eff}} = \frac{1}{q_{\text{eff}}} - 1 \quad (15b)$$

where q_b is the depolarization factor for infinitely small particles, and b is the semiminor axis of the particles. The choice of b follows from the orientation of our particles in the optical experiments (see Figure 2).

Using the same approach as in Section VB but with κ_{eff} replacing κ in Equation 6, we calculated spectra for different nanoparticle radii and aspect ratios. Figures 9A and 9B show these calculated spectra for the 30 nm and 60 nm particle radius cases respectively. In each case, as the particle aspect ratio increases, λ_{max} shifts to shorter wavelengths. Also, as seen clearly in the experimental results, the extinction bands for the 60 nm set is red-shifted relative to the 30 nm radius case, and the bands

are significantly broadened (again, in accord with experiment). Figure 10 summarizes the calculated λ_{\max} values as a function of aspect ratio. The general similarity to Figure 6 is quite apparent, particularly with regard to the degree to which the different pore radius systems are sensitive to shape. For example, the experimental λ_{\max} values for the smallest particle systems (30 nm radius) shift about 20 nm going from spherical ($A/B = 1$) to needle-like ($A/B \rightarrow \infty$) geometry. On the other hand, the largest systems (60 nm radius) blue-shift *ca.* 70 nm going from spherical to needle-like shapes. The analogous shifts based on the dynamical M-G calculation are 48 nm for the 30 nm radius set and 132 nm for the 60 nm systems.

The dynamical M-G approach *overestimates* λ_{\max} in all cases and most seriously at the largest particle radius (for the spherical case, see Table II). This is not terribly surprising, since we know from the Mie calculations that 60 nm radius spheres scatter considerably. Indeed, what we are attempting to do in the dynamical M-G model is to fold scattering losses into the composite absorption coefficient, k_c . For three of the particle size regimes examined in this study, this approach is certainly not quantitatively correct. However, it does offer simplicity and a reasonable description of trends in λ_{\max} , band shape and band intensity.

VI. Conclusions

We have used aluminum anodization and the template synthesis method to prepare nanoscopic gold particles of various radii and aspect ratios. Optical spectra for the gold/alumina composites containing

spherical gold particles are quantitatively amenable to Mie Theory. The spectra of the higher aspect ratio particle composites show both a size and shape dependence, the latter following qualitatively the predictions of Maxwell-Garnett Theory. We propose a simple modification of the M-G treatment using dynamical models for the depolarization factor q developed for SERS theory [26-28] to deal with size and shape effects in a unified calculation. While this dynamical M-G approach overestimates λ_{\max} , it does capture qualitative trends in λ_{\max} , as well as band shape and intensity as the size and shape of the metal particles is varied.

References

1. Mie, G. *Ann Physik*, **1908**, 25, 377.
2. van de Hulst, H.C. *Light Scattering by Small Particles*; Dover: New York, 1981.
3. Chang, R.K.; Furtak, T.E.; Eds. *Surface Enhanced Raman Scattering*; Plenum Press: New York, 1981.
4. Heller, A.; Aspnes, D.E.; Porter, J.D.; Sheng, T.T.; Vadimsky, R.G.; *J. Phys. Chem.* **1985**, 89, 4444.
5. Franzke, D.; Wokaun, A. *J. Phys. Chem.* **1992**, 96, 6377.
- 6a. Andersson, A.; Hunderi, O.; Granqvist, C.G. *J. Appl. Phys.* **1980**, 51, 754.
- 6b. Niklasson, G.A. *Solar Energy Materials* **1988**, 17, 217.
7. Liao, P.F.; in Ref. 3.
8. Cai, Z.; Lei, W.; Liang, W.; Menon, V.; Martin, C.R. *Chemistry of Materials* **1991**, 3, 960.
- 9a. Tierney, M.J.; Martin, C.R.; *J. Phys. Chem.* **1989**, 93, 2878.
- 9b. Foss, C.A., Jr.; Tierney, M.J.; Martin, C.R. *J. Phys. Chem.* **1992**, 96, 9001.
10. Foss, C.A., Jr.; Hornyak, G.L.; Stockert, J.A.; Martin, C.R. *J. Phys. Chem.* **1992**, 96, 7497.
- 11a. Maxwell-Garnett, J.C. *Philo. Trans. R. Soc. London* **1904**, 302, 385.

- 11b. Aspnes, D.E. *Thin Solid Films* **1982**, 89, 249.
12. Lide, D.R. Ed.; *Handbook of Chemistry and Physics*, 71st Edition, Chemical Rubber Company: Boca Raton, 1990.
13. Abeles, F. in *Advanced Optical Techniques*; Van Heel, A.C.S., Ed.; North Holland: Amsterdam, 1967.
14. Equation 8 does not address multiple reflections and thus cannot model interference fringes. Since we do not observe fringes except at the longest wavelengths in the near-IR, Equation 8 is appropriate for the present discussion.
- 15a. Despic, A.; Parkhutik, V.P. in Bockris, J. O'M. Ed. *Modern Aspects of Electrochemistry*; Plenum Press: New York 1989 Vol.20 (Chapter 6).
- 15b. Thompson, G.E.; Xu, Y.; Sheldon, P.; Shimizu, K.; Han, S.H.; Wood, G.C. *Philos. Mag. B* **1987**, 55, 651.
- 15c. Diggle, J.W.; Downie, T.C.; Goulding, C.W. *Chem. Rev.* **1969**, 69, 365.
16. Furneaux, R.C.; Rigby, W.R.; Davidson, A.P. *U.S. Patent No. 4,687,551* August 18, 1987.
17. While the y-axis is labeled "Absorbance" it should be clear that we are dealing with total extinction which is the sum of particle scattering and absorption losses.
18. Johnson, P.B.; Christy, R.W. *Phys. Rev. B* **1972**, 6, 4370.
19. Harns, L. *J. Opt. Soc. Amer.* **1955**, 45, 27.

20. For a visual description of the induced moments in spherical particles corresponding to $n=1,2,3$ and 4, see Born, M.; Wolf, E. *Principles of Optics*, Pergamon Press: Oxford, 1965, Third Edition.
21. See Ref. 2 and Aspnes, et al. *J. Appl. Phys.* **1986**, 60, 3028.
22. We determined n_o by plotting $\ln(T_{tot})$ versus d for four anodic aluminum oxide films grown to different thicknesses. From Equation 8, we obtain k_o from the slope and n_o from the y-intercept. Since these films are porous, a back-calculation using the M-G equation applied to an alumina/air composite yielded the optical constants for the pure oxide. The refractive index for the pure oxide was found to be ca. 1.5-1.6 for most of the visible and near-IR spectrum.
23. Kittel, C. *Solid State Physics*; John Wiley and Sons: New York, 1986; Sixth Edition.
- 24a. Molt, A.R.; Uzunoglu, N.K.; Evans, B.G. *IEEE Trans. Antennas Propagat.* **1978**, AP-6, 706.
- 24b. Asano, S.; Yamamoto, G. *Applied Optics* **1975**, 14, 29.
- 24c. Stevenson, A.F. *J. Appl. Phys.* **1953**, 24, 1143.
- 25a. Ruppin, R. *J. Phys. D: Appl. Phys.* **1990**, 23, 757.
- 25b. Swathi, P.S.; Tong, T.W. *J. Quant. Spectrosc. Radiat. Transfer* **1988**, 40, 525.
26. Meier, M.; Wokaun, A. *Optics Letters* **1983**, 8, 581.

27. Zeman, E.J.; Schatz, G.C. In *Proceedings of the 17th Jerusalem Symposium*; Pullman, B.; Hortner, J.; Nitzan, A.; Gerber, B. Eds.; Reidel: Dordrecht, Holland, 1984; p413.
28. Zeman, E.J.; Schatz, G.C. *J. Phys. Chem.* **1987**, *91*, 634.
29. Carron, K. manuscript in preparation.

Acknowledgments

- **Dr. John Chandler and Dr. Robert E. Lee, Colorado State University Electron Microscopy Center.**
- **Dr. Keith Carron, University of Wyoming.**
- **Office of Naval Research**
- **Paula J. Davidson, electron microscopy support.**

Table I.
Experimental Results: Gold Nanoparticle Dimensions

Anodic Voltage (Volts)	No. C Au(I)^a (Coulombs)	Particle Radius^b (nm)	Particle Length^b (nm)	Aspect Ratio^c (A/B)	κ^d
40	0.20	30 ± 3	92 ± 12	1.53	1.65
40	0.40	"	132 ± 6	2.20	1.46
40	0.70	"	268 ± 16	4.47	1.22
40	1.00	"	434 ± 22	7.23	1.14
50	0.20	38 ± 2	98 ± 8	1.29	1.78
50	0.40	"	160 ± 6	2.11	1.48
50	0.70	"	256 ± 7	3.37	1.30
50	1.00	"	406 ± 7	5.34	1.19
70	0.20	43 ± 2	130 ± 20	1.51	1.67
70	0.40	"	192 ± 20	2.23	1.45
70	0.70	"	360 ± 40	4.14	1.24
70	1.00	"	390 ± 70	4.51	1.22
90	0.20	60 ± 5	120 ± 50	1.02	1.98
90	0.40	"	410 ± 30	3.38	1.29
90	0.70	"	640 ± 100	5.28	1.18
90	1.00	"	800 ± 200	6.31	1.16

a. Number of coulombs of Au(I) reduced over a 3.3-3.5^{cm²} electrode area.

b. Determined from transmission electron microscopy.

c. Defined as the particle length, A, divided by the particle diameter, B. In the text, A = 2a and B = 2b.

d. M-G screening parameter (see text).

Table II.

Comparison of λ_{\max} Values from Experiment, Mie Theory and the Dynamical M-G Model (λ_{\max} in nm) for Spherical Particles

Particle Radius (nm)^a	Experimental Values^b	Mie Theory Calculation	Dynamical M-G Model Calculation
30	556	556	568
38	559	576	608
43	604	592	636
60	656	658	756

a. Determined from transmission electron microscopy.

b. Extrapolated values from experimental data shown in Figure 6 (see text).

Figures

Figure 1. Transmission electron micrographs of facial microtome sections of gold plated anodic alumina membranes grown under the conditions: **(A)** 40 V in 4% oxalic acid; **(B)** 50 V in 4% oxalic acid; **(C)** 70 V in 2% oxalic acid; **(D)** 90 V in 2% oxalic acid. Scale bar in each case is 20 nm. Note: gold nanoparticles are not visible in these sections.

Figure 2. Schematic of optical transmission experiment for gold/alumina composites. The cylindrical particles are aligned with their principal axes parallel to the direction of light incidence.

Figure 3. Transmission electron micrographs of gold particles prepared by electrodeposition of gold into oxalic acid membranes prepared under 40 V anodizing conditions. The amount of gold in terms of the number of coulombs of Au(I) reduced per unit area of pores in the membrane is given with each image. Scale bar in each case is 20 nm.

Figure 4. UV/Vis/NIR spectra for blank anodic alumina membranes and gold particle/alumina composites in which the particles are nearly spherical. **Curve 1:** particle radius 60 nm; **Curve 2:** particle radius 43 nm; **Curve 3:** particle radius 30 nm; **Curve 4:** blank 30 nm pore radius alumina; **Curve 5:** blank 43 nm pore radius alumina; **Curve 6:** blank 60 nm pore radius alumina.

Figure 5. UV/Vis/NIR spectra for gold particle/alumina composites containing particles of various aspect ratios. Particle length in all cases equals $2a$. **(A)** 30 nm pore radius systems: **Curve 1.** Blank membrane (ca. 30 μm in thickness) prepared at 40 V in 4% oxalic acid; **Curve 2.** $2a = 92$ nm; **Curve 3.** $2a = 132$ nm; **Curve 4.** $2a = 268$ nm. **(B)** 60 nm pore radius membranes prepared at 90 V in 2% oxalic acid: **Curve 1.** Blank alumina membrane; **Curve 2.** $2a = 120$ nm; **Curve 3.** $2a = 410$ nm; **Curve 4.** $2a = 800$ nm.

Figure 6. Summary of λ_{max} dependence on particle shape. The cylindrical radii are given next to the curves. The values for the aspect ratio (A/B) are taken from Table I. The M-G calculation yields the λ_{max} values shown in the curve labeled M-G.

Figure 7. Spectra calculated from Mie Theory (Equations 1-3). Input parameters as follows: **Curve 1:** radius $a = 30$ nm, particle density $N = 57.5 \mu\text{m}^{-1}$. **Curve 2:** $a = 43$ nm, $N = 19.5 \mu\text{m}^{-1}$. **Curve 3:** $a = 60$ nm, $N = 9.95 \mu\text{m}^{-1}$. The optical path length is 1 μm in all cases. Host medium $n_0 = 1.6$.

Figure 8. Absorption spectra calculated from simple M-G Theory using Equations 6-8 (Inset: The three layer model assumed for calculations). The input parameters are as follows: **Curve 1.** $\kappa = 2$, $f_m = 0.0065$, $d_2 = 1$ mm, $d_1 = 28 \mu\text{m}$; **Curve 2.** $\kappa = 1.4$, $f_m = 0.025$, $d_2 = 1.07 \mu\text{m}$,

$d_1 = 27.93$; **Curve 3.** $\kappa = 1.22$, $f_m = 0.034$, $d_2 = 1.21 \mu\text{m}$, $d_1 = 27.79 \mu\text{m}$.
The d_3 layer equals $1 \mu\text{m}$ in all cases.

Figure 9. Absorption spectra calculated using M-G Theory with size-adjusted depolarization factor q_{adj} . **(A)** 30 nm radius system input parameters: **Curve 1.** $a = 46 \text{ nm}$, $f_m = 0.0065$, $d_2 = 1 \mu\text{m}$, $d_1 = 28 \text{ nm}$; **Curve 2.** $a = 66 \text{ nm}$, $f_m = 0.0133$, $d_2 = 1.070 \mu\text{m}$, $d_1 = 27.93 \mu\text{m}$; **Curve 3.** $a = 0.130$, $f_m = 0.217$, $d_2 = 1.208 \mu\text{m}$, $d_1 = 27.79 \mu\text{m}$. **(B)** 60 nm radius system input parameters: **Curve 1.** $a = 62 \text{ nm}$, $f_m = 0.0093$, $d_2 = 1.0 \mu\text{m}$, $d_1 = 28 \mu\text{m}$; **Curve 2.** $a = 206 \text{ nm}$, $f_m = 0.024$, $d_2 = 1.288 \mu\text{m}$, $d_1 = 26.71 \mu\text{m}$; **Curve 3.** $a = 385 \text{ nm}$, $f_m = 0.0314$, $d_2 = 1.520 \mu\text{m}$, $d_1 = 26.48 \mu\text{m}$. The d_3 layer equals $1 \mu\text{m}$ in all cases.

Figure 10. Extinction maxima calculated using M-G Theory with size-adjusted depolarization factor q_{adj} plotted against the natural logarithm of the particle aspect ratio (A/B).

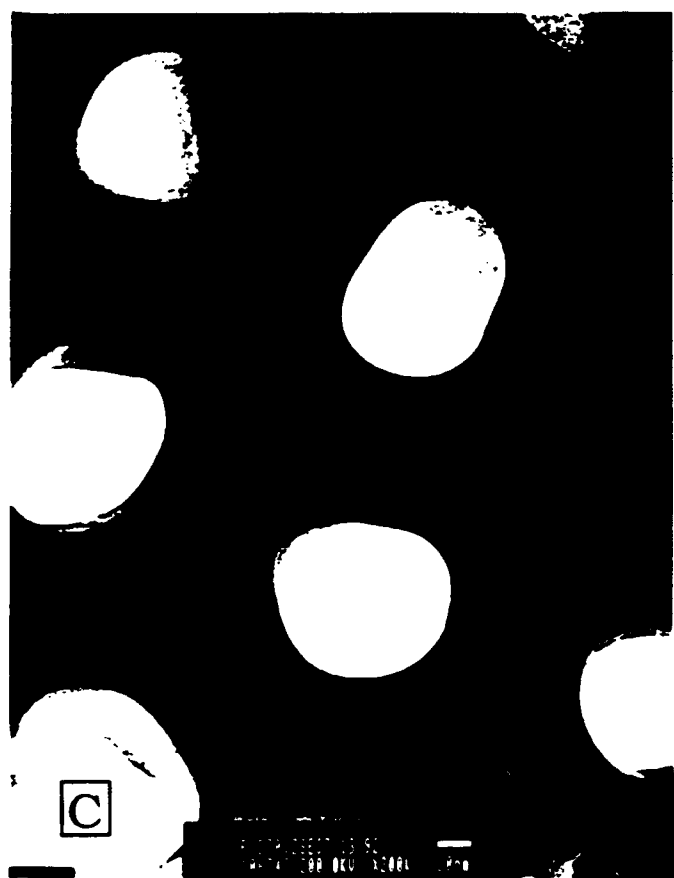
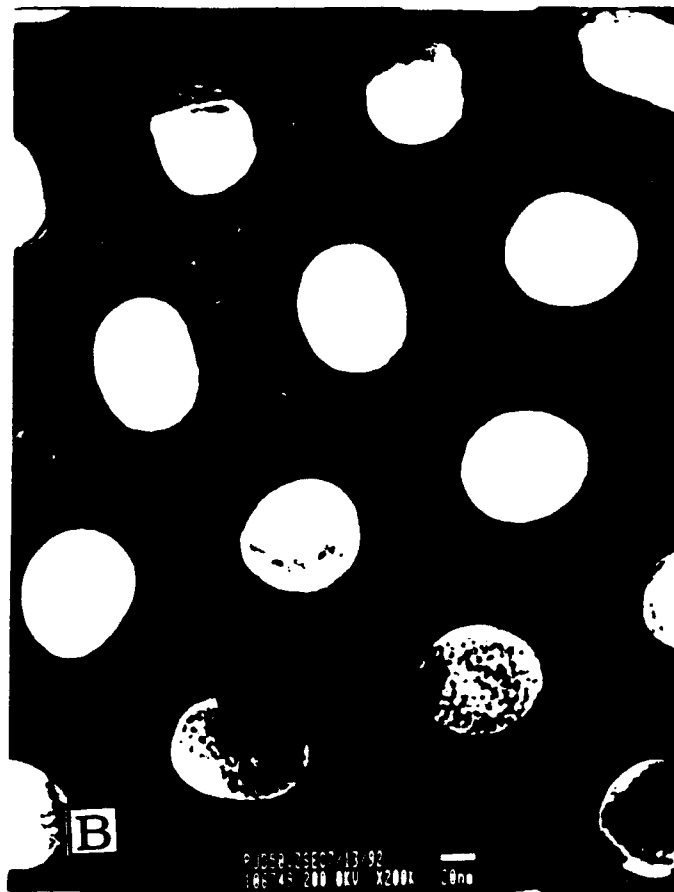
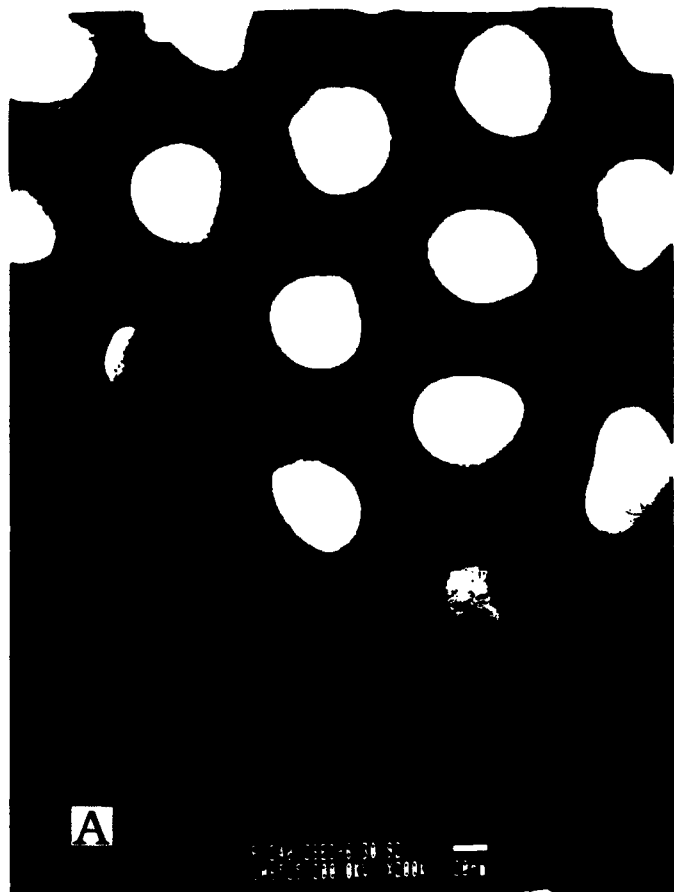


Figure 1.


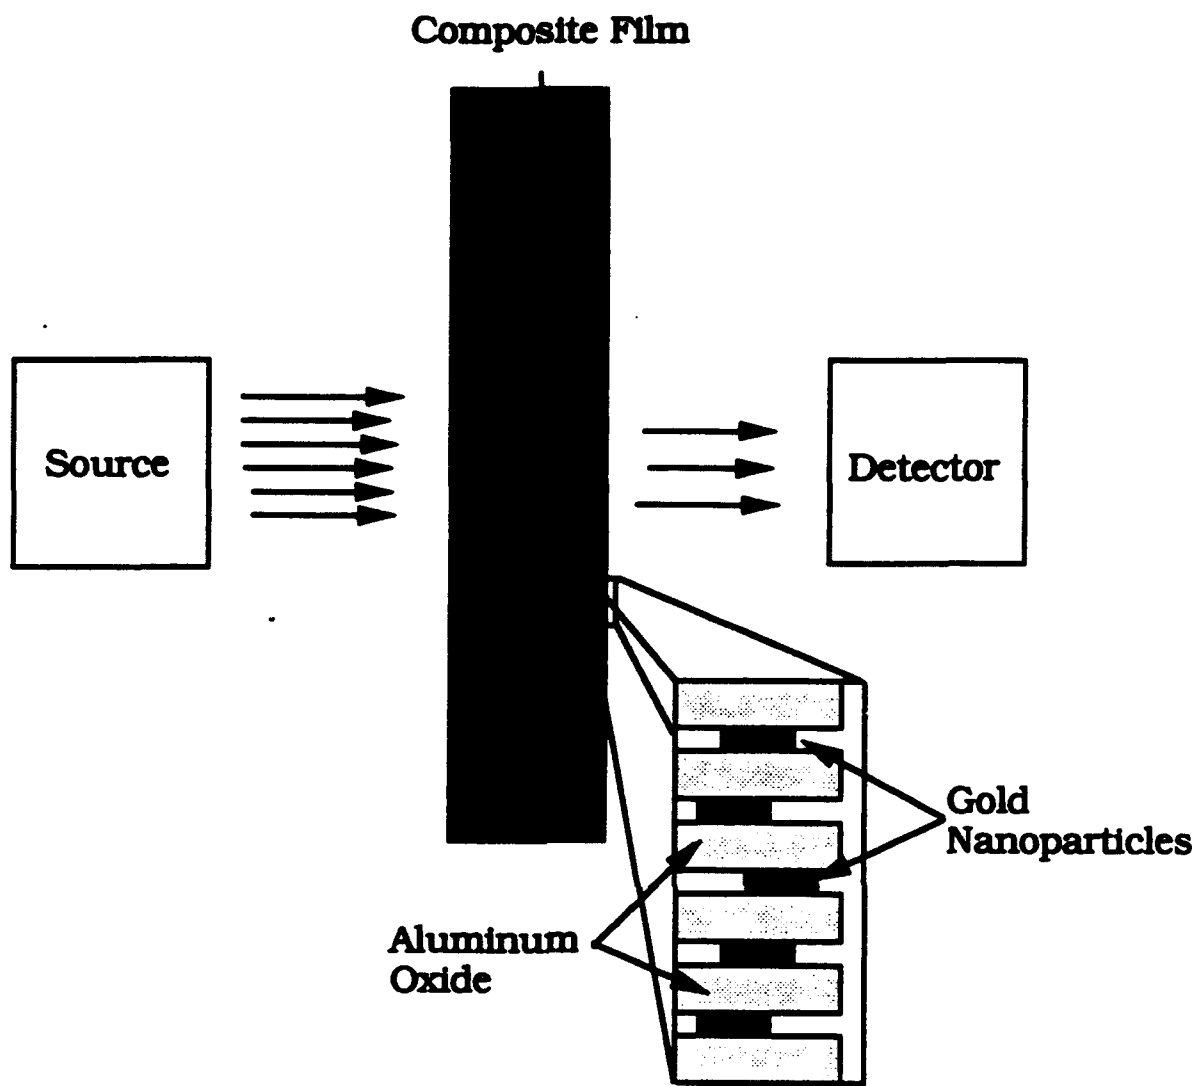


Figure 2.

0.20C (0.06C Au/cm²)



0.40C (0.12C Au/cm²)

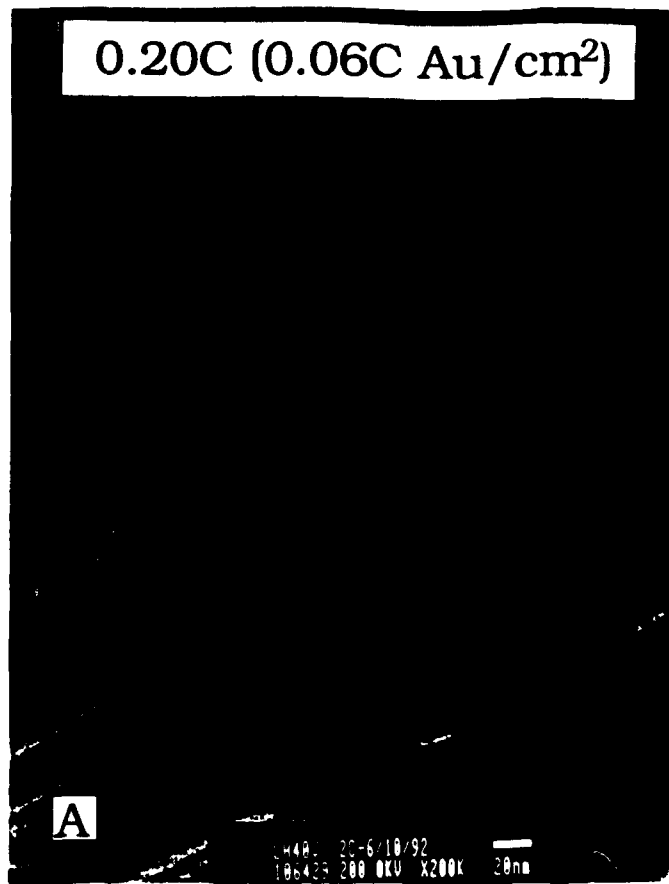

0.70C (0.20C Au/cm²)



1.00C (0.30C Au/cm²)



Figure 3.

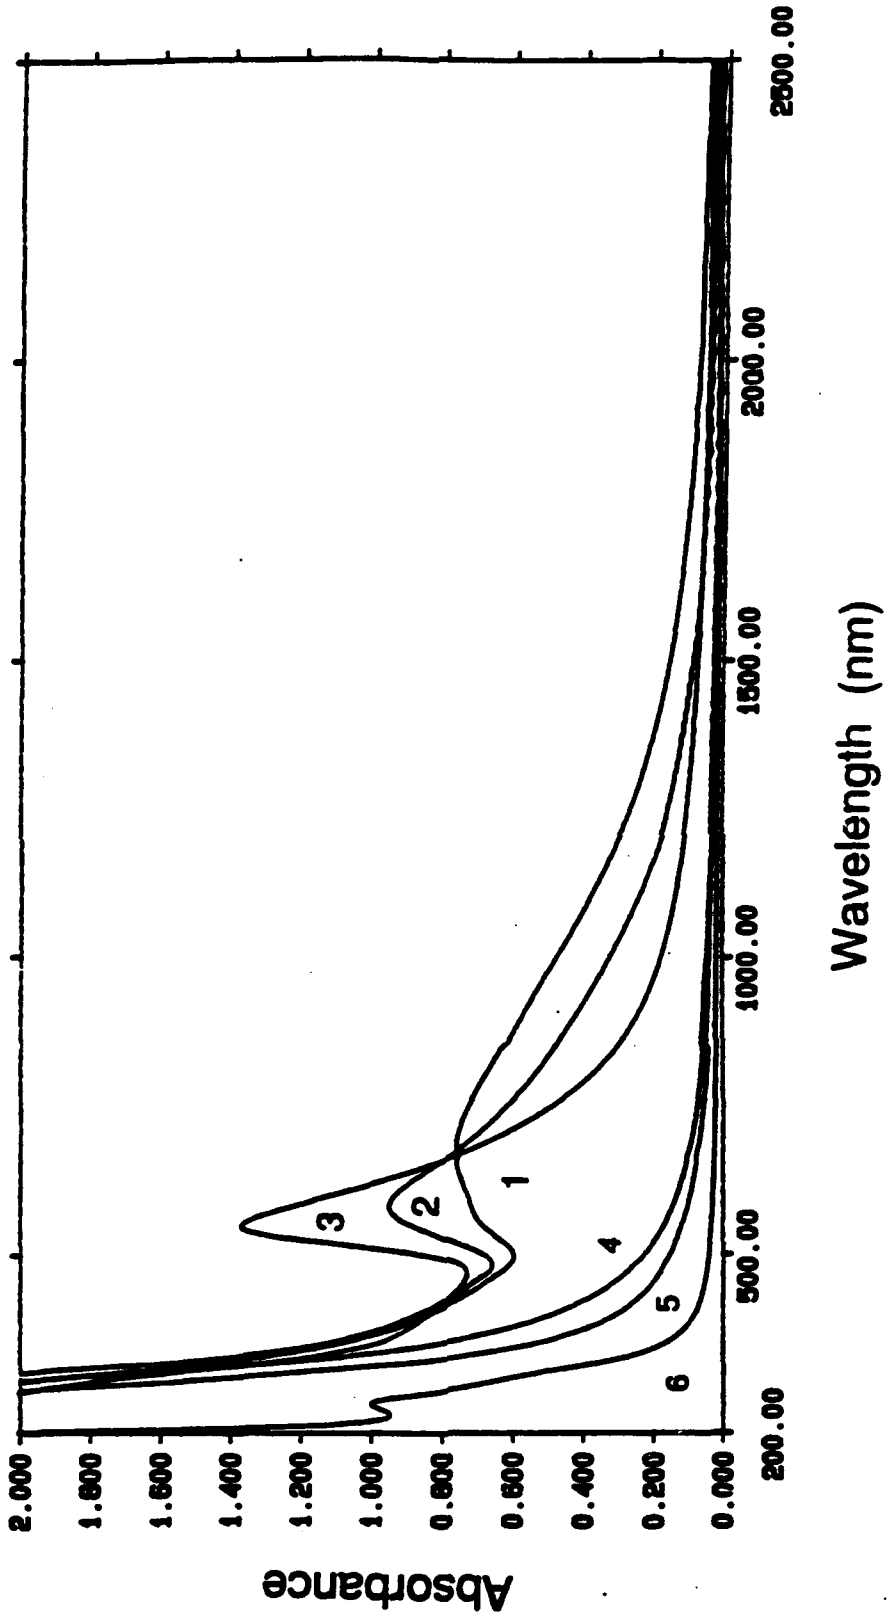


Figure 4.

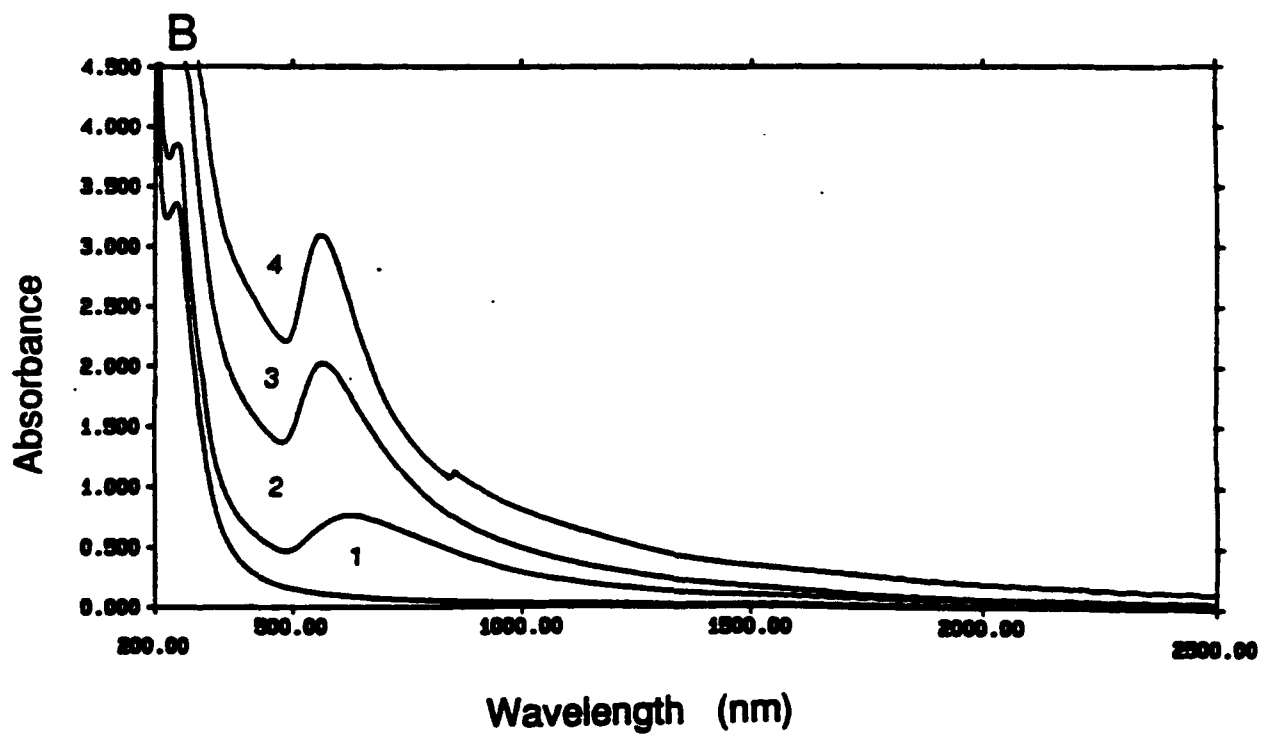
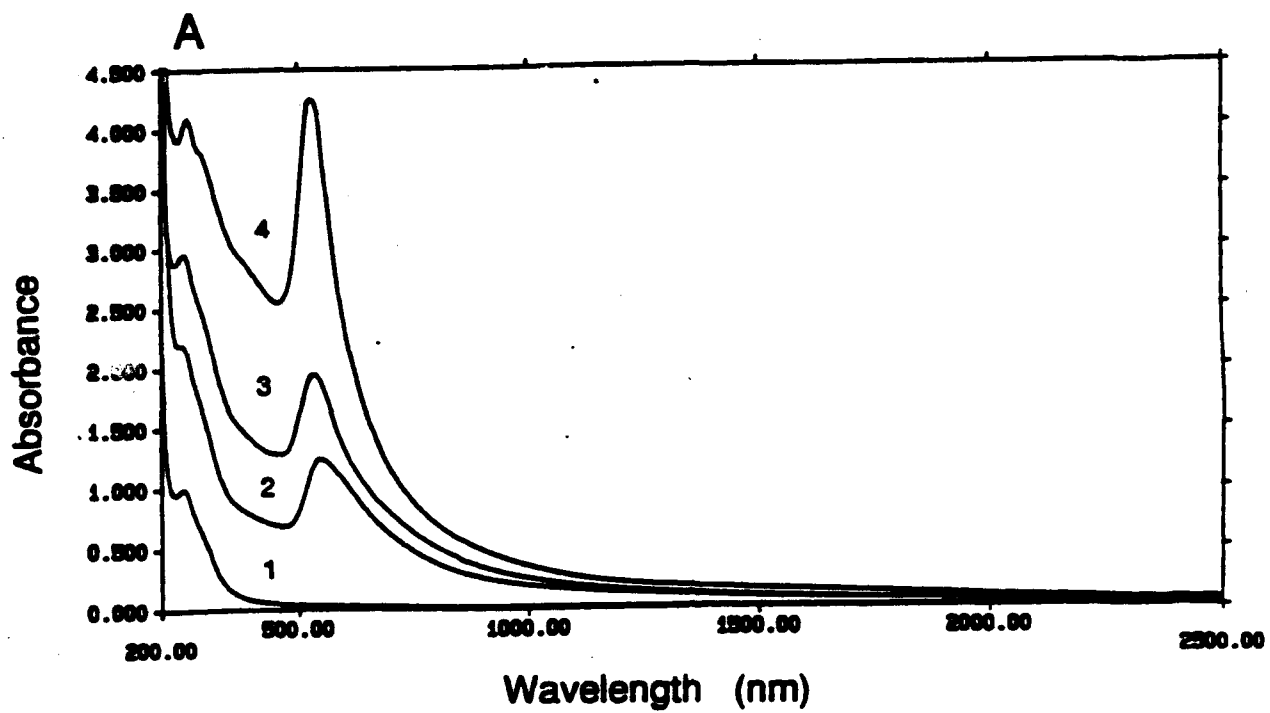


Figure 5.

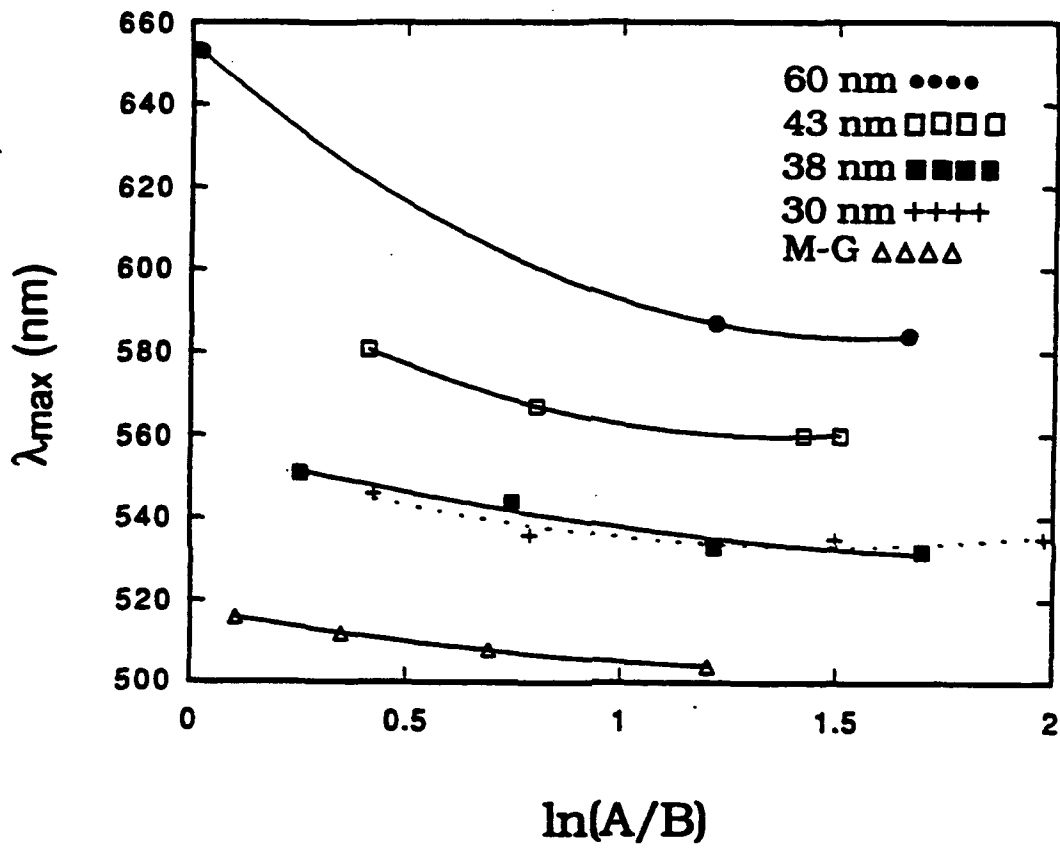


Figure 6.

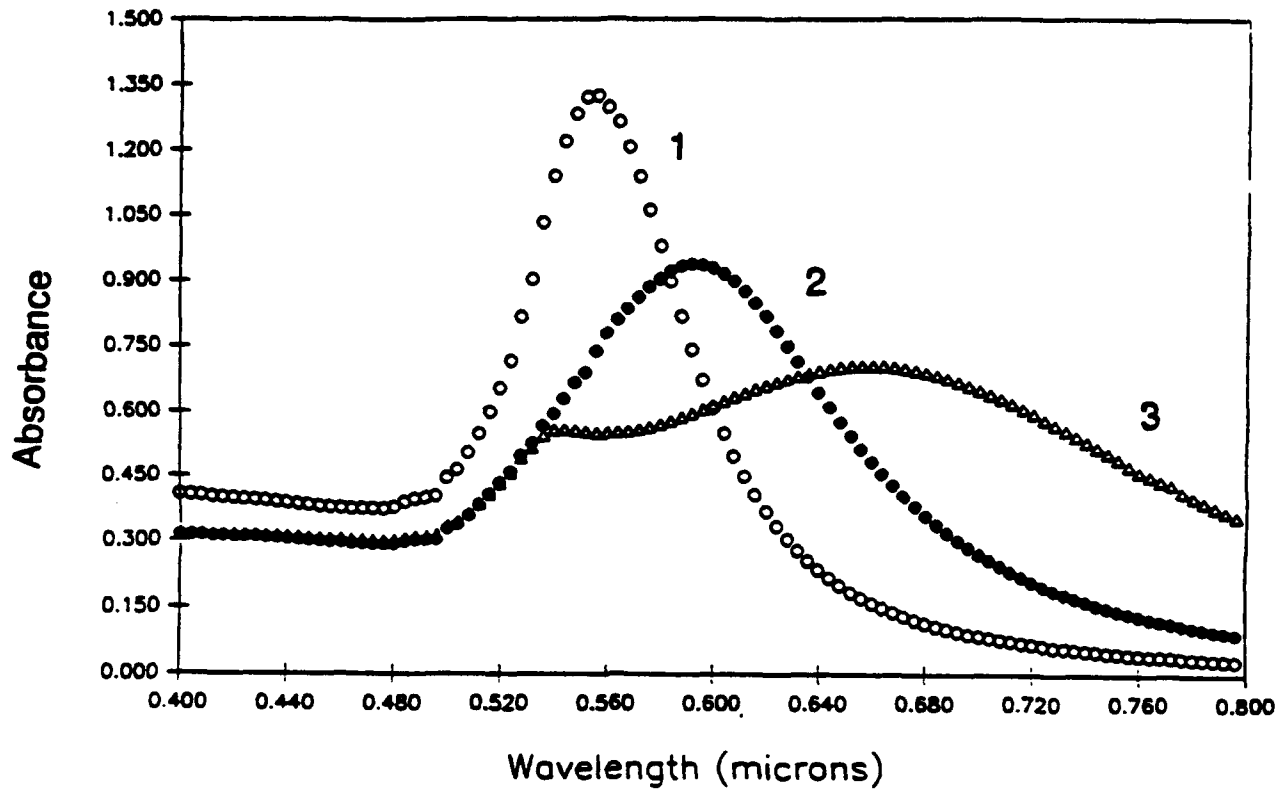


Figure 7.

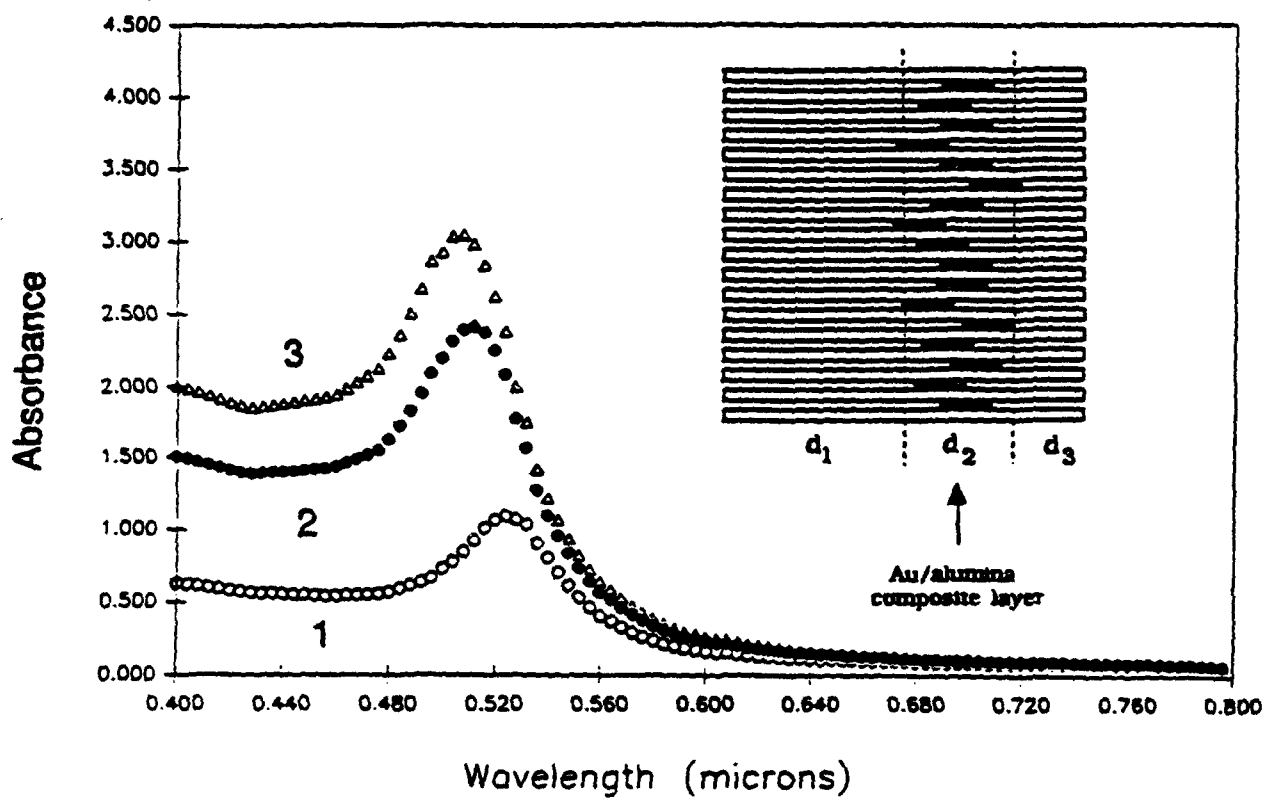


Figure 8.

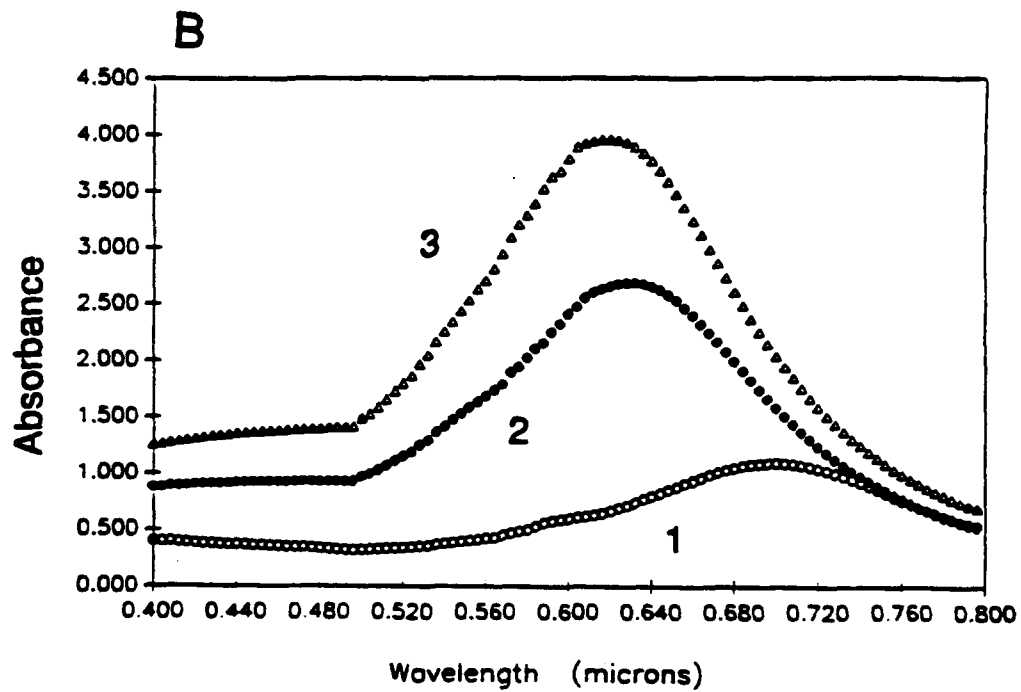
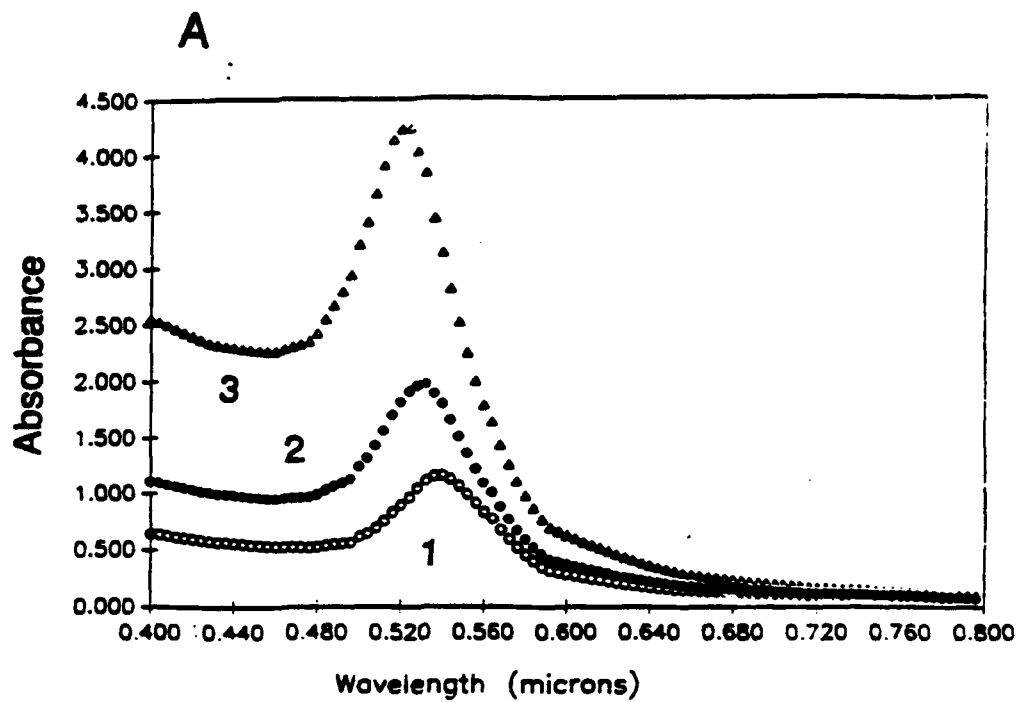


Figure 9.

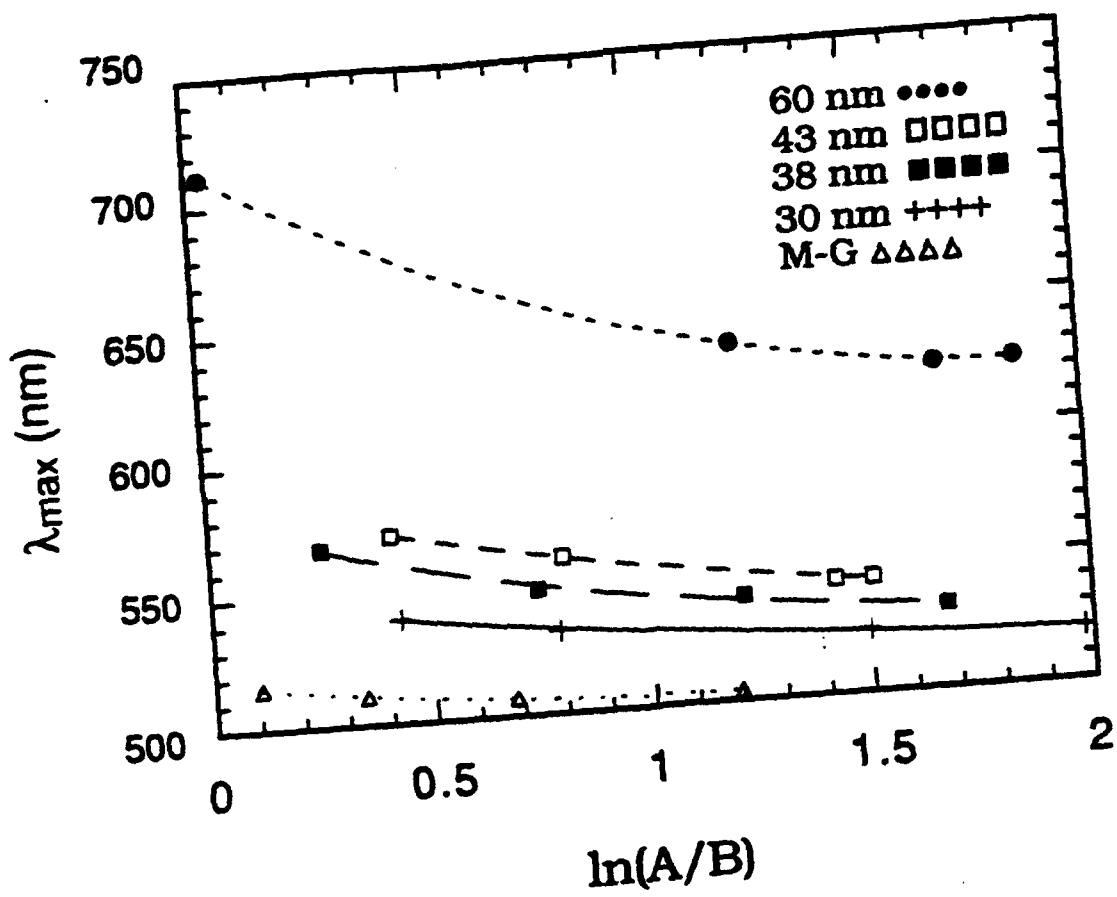


Figure 10.