

# Lawrence Berkeley National Laboratory

## Recent Work

### Title

THE CHEMISOPTION OF ACETYLENE AND ETHYLENE ON Rh(111): A. LOW ENERGY ELECTRON DIFFRACTION (LEED), HIGH RESOLUTION ELECTRON ENERGY LOSS (ELS) AND THERMAL DESORPTION MASS SPECTRO-METRY (TDS) STUDY

### Permalink

<https://escholarship.org/uc/item/73c2q7n8>

### Author

Dubois, L.H.

### Publication Date

1979-08-01



# Lawrence Berkeley Laboratory

UNIVERSITY OF CALIFORNIA

## Materials & Molecular Research Division

Submitted to The Journal of Chemical Physics

THE CHEMISORPTION OF ACETYLENE AND ETHYLENE ON  
Rh(111): A LOW ENERGY ELECTRON DIFFRACTION (LEED),  
HIGH RESOLUTION ELECTRON ENERGY LOSS (ELS) AND  
THERMAL DESORPTION MASS SPECTROMETRY (TDS) STUDY

L. H. Dubois, D. G. Castner and G. A. Somorjai

August 1979


RECEIVED  
LAWRENCE  
BERKELEY LABORATORY

DEC 18 1979

LIBRARY AND  
DOCUMENTS SECTION

### TWO-WEEK LOAN COPY

*This is a Library Circulating Copy  
which may be borrowed for two weeks.  
For a personal retention copy, call  
Tech. Info. Division, Ext. 6782.*

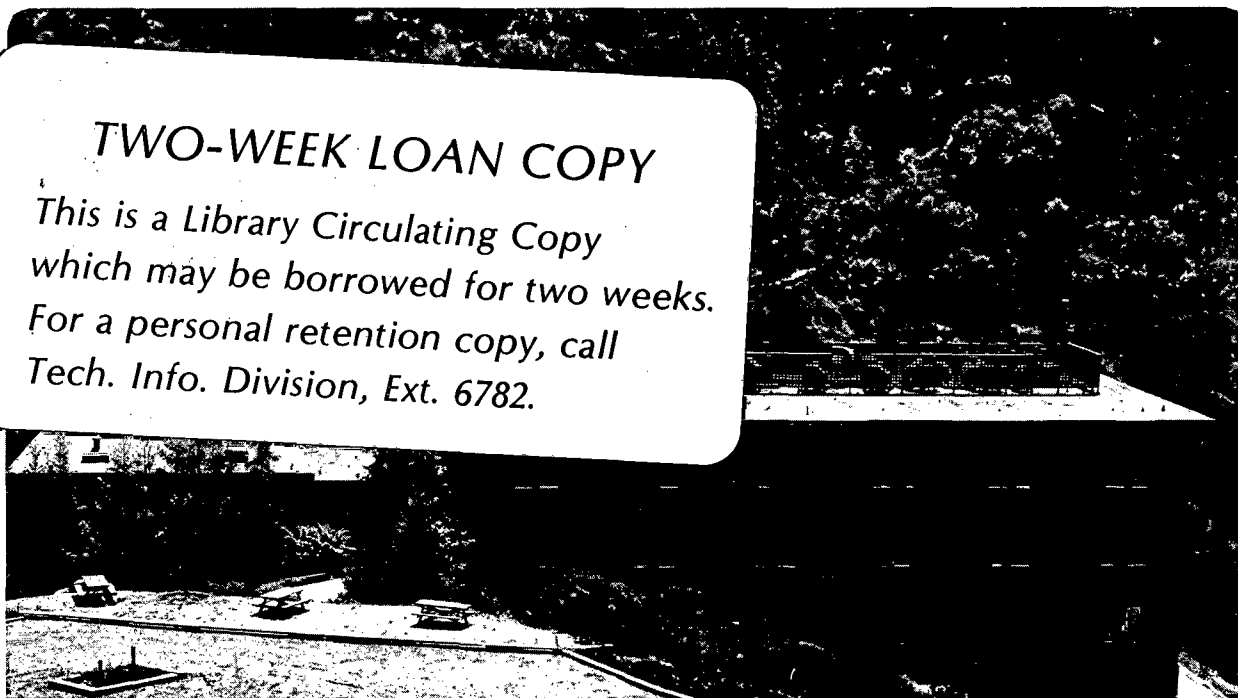

LBL-9946 c. 2

## DISCLAIMER

This document was prepared as an account of work sponsored by the United States Government. While this document is believed to contain correct information, neither the United States Government nor any agency thereof, nor the Regents of the University of California, nor any of their employees, makes any warranty, express or implied, or assumes any legal responsibility for the accuracy, completeness, or usefulness of any information, apparatus, product, or process disclosed, or represents that its use would not infringe privately owned rights. Reference herein to any specific commercial product, process, or service by its trade name, trademark, manufacturer, or otherwise, does not necessarily constitute or imply its endorsement, recommendation, or favoring by the United States Government or any agency thereof, or the Regents of the University of California. The views and opinions of authors expressed herein do not necessarily state or reflect those of the United States Government or any agency thereof or the Regents of the University of California.

THE CHEMISORPTION OF ACETYLENE AND ETHYLENE ON Rh(111): A LOW ENERGY  
ELECTRON DIFFRACTION (LEED), HIGH RESOLUTION ELECTRON ENERGY LOSS (ELS)  
AND THERMAL DESORPTION MASS SPECTROMETRY (TDS) STUDY

L.H. Dubois, D.G. Castner\* and G.A. Somorjai

Materials and Molecular Research Division, Lawrence Berkeley  
Laboratory, and Department of Chemistry, University of  
California, Berkeley, California 94720

Abstract

We report the results of a detailed investigation of the chemisorption and reactivity of acetylene ( $C_2H_2$ ) and ethylene ( $C_2H_4$ ) on the Rh(111) single crystal surface. Below 270K ELS measurements indicate that acetylene chemisorbs on Rh(111) with its C-C bond oriented parallel to the surface forming an approximately  $sp^2$  hybridized species. LEED investigations show that both  $C_2H_2$  and  $C_2H_4$  form metastable (2x2) surface structures on Rh(111) below 270K. An irreversible order-order transformation occurs between 270 and 300K to a stable c(4x2) hydrocarbon overlayer. The stable species formed from both molecules are identical. Hydrogen addition to chemisorbed acetylene is necessary to complete this conversion. The geometry of the adsorbed ethylene species does not change during this transformation although the overlayer structure does. This <sup>stable</sup> hydrocarbon fragment is identical to the hydrocarbon species formed from the chemisorption of either  $C_2H_4$  or  $C_2H_2$  and hydrogen on Pt(111) <sup>above 300 K.</sup> The addition of  $H_2$  to chemisorbed  $C_2D_2$  or  $C_2D_4$  results in H-D exchange, but no change in the adsorbate geometry is detected by ELS. Decomposition of these molecules occurs on the Rh(111) surface above  $\sim 420K$ .

\*Present Address: Chevron Research Company, P.O. Box 1627, Richmond, CA 94802

## Introduction

Determination of the molecular structure of adsorbed monolayers on metal surfaces is now possible by a variety of complementary techniques. Recently a combination of low energy electron diffraction (LEED) intensity analysis and high resolution electron energy loss spectroscopy (ELS) has been used to determine the structure of ethylene ( $C_2H_4$ ) chemisorbed on Pt(111) at 300 K.<sup>1</sup> ELS is a particularly valuable technique for probing hydrocarbon interactions with metal surfaces since the observed inelastic losses correspond to the vibrational modes of the adsorbed species. Thus the orientation and geometry of chemisorbed molecules can be determined and monitored as a function of both surface coverage and substrate temperature. Hydrogen can also be detected through its vibration against either the substrate or other adsorbed atoms. Finally, ordered adsorbate overlayers are not needed to obtain intense ELS spectra. A dynamical LEED structure analysis provides bond lengths, bond angles and the position of the adsorbate on the surface if the overlayer is ordered. It is not very effective, however, in determining the location of hydrogen atoms—an important question in hydrocarbon surface chemistry. Changes in bonding with coverage and temperature can only be studied by LEED if the adsorbate layer remains well ordered.

We report here the results of a detailed investigation of the chemisorption and reactivity of  $C_2H_2$  and  $C_2H_4$  on the Rh(111) single crystal surface. In the present study we have extended previous LEED and thermal desorption mass spectrometry (TDS)<sup>2</sup> investigations to lower temperatures ( $T \sim 210$  K) and have complemented these results with data obtained by high resolution ELS and Auger electron spectroscopy (AES). This combination of techniques allows us to determine the structure of these hydrocarbons on the surface and follow their molecular rearrangements as a function of temperature

between 210 and 420 K. We have also studied the vibrational spectra of chemisorbed  $C_2D_2$  and  $C_2D_4$ , and the reactions of these molecules with hydrogen. Finally, the bonding of acetylene and ethylene on Rh(111) is compared to data previously obtained on the (111) single crystal faces of platinum and nickel.

### Experimental

Experiments were carried out in two ion pumped ultrahigh vacuum chambers both having LEED, retarding field AES and TDS capabilities. One system was also equipped with a high resolution ELS spectrometer. The procedures for sample preparation, mounting and cleaning have been described previously.<sup>2</sup> Briefly, the Rh(111) crystal, oriented to  $\pm \frac{1}{2}^\circ$ , was cleaned by a combination of argon ion bombardment (500-2000 eV) followed by annealing (800-1000 K) in vacuum and  $O_2$  to remove carbon, sulfur and boron.

Acetylene and ethylene adsorption was studied at pressures between  $5 \times 10^{-9}$  and  $1 \times 10^{-6}$  torr and at temperatures between 210 and 420 K. Surface structures were observed both with increasing exposure and after the gas was pumped away. Gas exposures were not corrected for ion gauge sensitivity and differed slightly between the two chambers. TDS spectra were recorded at a heating rate of 40 K/sec. Blank desorption experiments were performed by replacing the crystal with tantalum foil to insure that all observed desorption peaks were from the rhodium surface.

The high resolution ELS spectrometer has been described elsewhere.<sup>3</sup> In the present series of experiments the angle of incidence was fixed at  $65^\circ$  to the surface normal and electrons were collected in the specular direction. The beam energy varied from 4.8 to 5.8 eV. The elastic scattering peak had a full width at half maximum between 70 and 90  $cm^{-1}$  and maximum intensity of  $1 \times 10^5$  counts per second.

## Results and Discussion

### A. LEED studies of ethylene and acetylene adsorption on Rh(111).

Exposing the clean Rh(111) surface (Fig.1a) between 230 and 250 K to  $C_2H_4$  results in the appearance of sharp half order diffraction spots in the LEED pattern (Fig.1b) from a (2x2) surface structure. If the crystal temperature is below  $\sim 230$  K, ethylene adsorption is disordered and the only change observed in the LEED pattern is an increased background intensity. This disordered hydrocarbon layer can be transformed into an ordered (2x2) surface structure by heating the crystal to between 230 and 250 K. Acetylene adsorption on the Rh(111) surface between 210 and 250 K also produces a (2x2) surface structure. The new diffraction spots from the ordered (2x2) hydrocarbon structures are sensitive to surface coverage. Although the spots are visible after a 1 L (1L = 1 Langmuir =  $1 \times 10^{-6}$  torr\*sec) gas exposure, they do not become sharp and intense until 1.5 L and then immediately begin disordering above 1.5 L. A 15 sec exposure of  $1 \times 10^{-7}$  torr  $C_2H_4$  or a 150 sec exposure of  $1 \times 10^{-8}$  torr  $C_2H_2$  produce optimum (2x2) surface structures.

A diffraction pattern corresponding to a c(4x2) surface structure (Fig.1c) can be generated from the (2x2) surface structure without additional hydrocarbon exposure. For adsorbed  $C_2H_4$ , the transformation occurs in vacuum by slowly warming the crystal to 300 K over the course of several hours. Rapid heating results in the formation of a disordered c(4x2) structure (broad, diffuse diffraction features and some streaking). For adsorbed  $C_2H_2$  even this slow warm-up results in a disordered overlayer. To form a well ordered c(4x2) structure from adsorbed acetylene the crystal must be annealed for  $\sim 4$  minutes at 273 K in  $1 \times 10^{-8}$  torr of  $H_2$  with the mass spectrometer filaments on. These filaments are located approximately 5 cm. from the crystal and provide the surface with a good

source of atomic hydrogen.<sup>4</sup> Castner *et al*<sup>2</sup> previously observed the c(4x2) surface structures from the chemisorption of either acetylene or ethylene on Rh(111) near room temperature. The reported diffraction patterns were neither as sharp nor as intense as that shown in Fig.1c, however. The (2x2) hydrocarbon surface structures have not been seen previously.

In the transformation from the (2x2) to the c(4x2) structures the orientation and shape of the unit cell change,<sup>5</sup> but the areas of the primitive unit cells of these two structures are the same ( $25 \text{ \AA}^2$  on Rh(111)). Thus, no variation in the surface coverage occurs. Furthermore, AES shows that the carbon coverage from the (2x2) structures produced during  $\text{C}_2\text{H}_2$  and  $\text{C}_2\text{H}_4$  chemisorption are the same and remain constant during the conversion to the c(4x2) structures. Thus, changes in binding site and adsorbate geometry are probably taking place without any change in the adsorbate coverage. Determination of the overlayer structure by LEED requires the analysis of the intensity vs. incident energy (I-V) beam profiles. We have not undertaken such calculations in the present study. The transformation from the (2x2) to the c(4x2) surface structures is irreversible; once the c(4x2) structure forms, the crystal can be cooled to 210 K with no visible changes in the diffraction pattern. The c(4x2) structures can only be altered by heating the crystal above 420 K which causes the surface to irreversibly disorder.

#### B. ELS studies of acetylene and ethylene adsorption on Rh(111)

The vibrational spectrum of the (2x2) hydrocarbon surface structure formed from the chemisorption of  $\text{C}_2\text{H}_2$  on Rh(111) between 210 and 270 K is shown in Fig.2a. The peak positions and their relative intensities<sup>6</sup> are listed in Table I.



Analysis of the low frequency region in this spectrum is hampered by a spurious background peak near  $800\text{ cm}^{-1}$ . This apparent loss, first observed by Froitzheim *et al*, may be caused by electron reflection from the outer half of the analyzer.<sup>8</sup> The dashed lines in Figs. 2 and 3 indicate the approximate location and magnitude of this peak. As a result of this experimental artifact, both the position and intensity of all loss features between  $650$  and  $900\text{ cm}^{-1}$  are rather uncertain. Isotopic substitution is of some help in assigning the observed vibrational frequencies to normal modes of the adsorbed species. The ELS spectrum of the  $(2\times 2)$   $\text{C}_2\text{D}_2$  surface structure is shown in Fig. 2b.

The vibrational spectra of the  $(2\times 2)$  acetylene overlayer in Figs. 2a and 2b do not change up to  $270\text{ K}$  in vacuum. Furthermore, the positions and relative intensities of the observed energy loss peaks are independent of the acetylene exposure (from  $>0.2\text{ L}$  to  $<50\text{ L}$ ) and, more importantly, are independent of surface order (as determined by observation of the LEED pattern). Thus, using high resolution ELS we conclude that the bonding of the adsorbed molecules do not change upon disordering.

The frequencies of the carbon-hydrogen (carbon-deuterium) stretching vibrations can be used to characterize the state of hybridization of the adsorbed species. Acetylene,  $\text{C}_2\text{H}_2$  ( $\text{C}_2\text{D}_2$ ), is  $\text{sp}$  hybridized in the gas phase and has C-H (C-D) stretching vibrations between  $3289$  and  $3374$  ( $2439$  and  $2701$ )  $\text{cm}^{-1}$ ;<sup>9</sup> ethylene,  $\text{C}_2\text{H}_4$  ( $\text{C}_2\text{D}_4$ ), is  $\text{sp}^2$  hybridized and has C-H (C-D) stretching vibrations between  $2989$  and  $3106$  ( $2200$  and  $2345$ )  $\text{cm}^{-1}$ ;<sup>9</sup> while ethane,  $\text{C}_2\text{H}_6$  ( $\text{C}_2\text{D}_6$ ), is  $\text{sp}^3$  hybridized and has C-H (C-D) stretching vibrations between  $2896$  and  $2985$  ( $2083$  and  $2235$ )  $\text{cm}^{-1}$ .<sup>9</sup> Thus, the losses at  $2980$  ( $2230$ ) and  $3085$  ( $\sim 2320$ )  $\text{cm}^{-1}$  in Figs. 2a and 2b and Table I correspond to the C-H (C-D) stretching vibrations of a molecule near  $\text{sp}^2$  hybridization. This indicates that the C-C-H (C-C-D) bond

in adsorbed acetylene is no longer linear. Thus, the adsorbed  $C_2H_2$  molecule is more "ethylene-like" in its C-H bonding and one might conclude that the C-C-H (C-C-D) bond angle is near  $120^\circ$  (as found in gas phase ethylene). The low frequency mode at  $323\text{ cm}^{-1}$  does not shift significantly upon deuteration ( $\sim 20\text{ cm}^{-1}$ ) and most likely corresponds to the entire molecule vibrating against the surface. The two largest peaks in the spectrum at  $706$  and  $887\text{ cm}^{-1}$  shift by almost  $200\text{ cm}^{-1}$  (to  $565$  and  $686\text{ cm}^{-1}$ , respectively) when  $C_2D_2$  is chemisorbed and can be assigned to C-H (C-D) bending modes. The adsorbate must be oriented with its carbon-carbon axis approximately parallel to the surface since only small, broad peaks ( $1300 - 1400\text{ cm}^{-1}$ ) are seen in the C-C stretching region. Observation of such a mode is prohibited by the normal dipole selection rule<sup>10</sup> if the C-C bond is parallel to the surface. The vibrational mode assignments are summarized in Table I.

Bond lengths, bond angles and the position of adsorbed  $C_2H_2$  on the surface cannot be accurately determined without a complete dynamical LEED intensity analysis. Nevertheless, the high resolution ELS results indicate that acetylene chemisorbs on Rh(111) below 270 K with its C-C axis oriented approximately parallel to the surface. The molecule is near  $sp^2$  hybridization and therefore the C-C-H bond angle is no longer linear. A similar  $C_2H_2$  geometry is seen in numerous organometallic cluster compounds.<sup>11,12</sup>

Both LEED and ELS indicate that the (2x2) acetylene overlayer is stable on the surface in vacuum between 210 and 270 K. The addition of  $H_2$  to adsorbed  $C_2H_2$  below  $\sim 260$  K causes no changes in the observed ELS spectra, although this surface species is still quite reactive. The addition of  $H_2$  to chemisorbed  $C_2D_2$  below 260 K results in a complex vibrational spectrum with peaks in both the C-H (C-D) stretching and bending regions. Although the deuterium and

hydrogen readily exchange, no change in the adsorbate geometry is detected by high resolution ELS. The vibrational spectra of adsorbed acetylene only begin to change when the crystal is heated above 270 K in vacuum. The (2x2) C<sub>2</sub>H<sub>2</sub> surface structure also disorders at this temperature.

The vibrational spectrum from the c(4x2) acetylene overlayer is shown in Fig.2c. This spectrum can either be obtained by warming the (2x2) acetylene overlayer to ~270 K in the presence of  $1 \times 10^{-8}$  torr of hydrogen or by chemisorbing C<sub>2</sub>H<sub>2</sub> on Rh(111) above 300 K. Hydrogen addition to the surface species above 270 K is necessary to obtain good quality, intense ELS spectra, however. Hydrogen addition was also required to complete this conversion in the LEED studies. This species <sup>is</sup> stable on the surface up to ~420 K. The structure of this hydrocarbon overlayer will be discussed in the next section.

The vibrational spectra from the (2x2) and c(4x2) ethylene surface structures are shown in Figs. 3a and 3b. The ELS spectrum in Fig.3a is obtained by chemisorbing C<sub>2</sub>H<sub>4</sub> on the crystal below 270 K. Spectrum 3b can either be observed by slowly warming the (2x2) overlayer structure (3a) to room temperature or by simply adsorbing ethylene on the Rh(111) surface above 290 K. The measured peak positions are listed in Table II. Once again the observed vibrational frequencies are independent of surface order and hydrocarbon exposure (>0.2 to <50 L). Note that these ELS spectra are almost identical to the vibrational spectrum from the stable c(4x2) acetylene overlayer shown in Fig.2c. The hydrocarbon species derived from ethylene chemisorption is also stable on the surface up to ~420 K. Degradation of both the c(4x2) LEED pattern and of the vibrational spectrum occur at this temperature. The ELS spectrum resulting from the chemisorption of either C<sub>2</sub>H<sub>4</sub> or C<sub>2</sub>H<sub>2</sub> and H<sub>2</sub> on Pt(111)<sup>4,13</sup> above room temperature are

quite similar and their stretching frequencies are also listed in Table II. The vibrational spectrum from the chemisorption of  $C_2D_4$  on either Rh(111) (Fig. 3c and Table II) or Pt(111)<sup>4</sup> (Table II) are also quite similar. Although the chemisorption of ethylene on Pt(111) has been studied by numerous techniques,<sup>1,4,13,14</sup> there is still debate over the precise geometry of the stable surface species. We simply point out that the stable hydrocarbon overlayer formed from the chemisorption of either ethylene or acetylene/on both Pt(111) and Rh(111) yield identical vibrational spectra. A more complete discussion of the similarities between the chemisorption of ethylene on Rh(111) and Pt(111) will be presented in the next section.

It is interesting to note that the geometry of the adsorbed ethylene species on Rh(111) remains the same (as indicated by the ELS spectra) while the overlayer structure changes from a (2x2) to a c(4x2). This chemisorbed hydrocarbon should be an excellent candidate for a LEED structural analysis since the I-V beam profiles should change while the molecular geometry does not. The order-order transformation observed by LEED is irreversible at the low pressures employed in our experiments, and again no intermediate species are observed. Although this conversion is not affected by the presence of hydrogen, H-D exchange will occur in the hydrocarbon overlayer when  $H_2$  is added to chemisorbed  $C_2D_4$ . No change in the adsorbate geometry is detected by high resolution ELS. The stable ethylene or acetylene plus hydrogen overlayer on Rh(111) can be decomposed to surface CH and  $CH_2$  species above  $\sim 420$  K. The LEED pattern disorders at this temperature as well. These decomposition products will be discussed in a subsequent publication.<sup>15</sup>

C. TDS studies of ethylene and acetylene adsorption on Rh(111)

Castner et al<sup>2,15</sup> have previously shown that both  $C_2H_2$  and  $C_2H_4$  decompose

on the Rh(111) single crystal surface upon heating to yield gas phase molecular hydrogen and surface carbon. The  $H_2$  thermal desorption traces from the room temperature adsorption of these hydrocarbons have one major peak near 500 K followed by continuous hydrogen evolution up to approximately 825 K. The position of this desorption maximum was found to be independent of gas exposure.

Hydrogen desorption spectra from the ordered hydrocarbon overlayers chemisorbed on Rh(111) are shown in Fig.4. Traces 4a and 4d are from the (2x2) structures formed at 240 K from the adsorption of 1.5 L of acetylene and ethylene, respectively. Spectra 4b and 4c are from the c(4x2) surface structures formed from the metastable (2x2)  $C_2H_2$  and  $C_2H_4$  structures, respectively. After forming the c(4x2) structures, the crystal is cooled to 240 K before initiating the desorption experiments. Molecular  $C_2H_2$  and  $C_2H_4$  desorption near 375 K is also observed.<sup>16</sup> The amount of hydrocarbon that is detected desorbing is less than 1% of the amount of hydrogen desorbed indicating that most of the adsorbed hydrocarbons decompose on the surface upon heating. → The hydrogen desorption spectrum from the c(4x2) ethylene species (Fig.4c) has a single desorption peak at 440 K followed by continuous hydrogen evolution until 750 K. This suggests that the desorption peak at 440 K in Fig.4d is from the stable hydrocarbon species which can be formed as the crystal is heated during the TDS experiments. The desorption peak at 350 K in Fig.4d is due to chemisorbed hydrogen on the Rh(111) surface. This desorption peak has been observed from hydrogen adsorption on clean Rh(111)<sup>2,16,17</sup> and after annealing the Rh(111)-(2x2)- $C_2H_2$  structure in hydrogen (Fig.4b). A similar peak is seen in  $H_2$  TDS spectra from ethylene chemisorbed on Pt(111) at 320 K.<sup>14</sup> The origin of the desorption peak at 395 K in Fig.4d remains in question. Possible assignments include an

unstable low temperature ethylene species or a transient intermediate hydrocarbon fragment present during the conversion of the metastable adsorbate to the stable surface phase.

Desorption traces b and c in Fig.4 from the c(4x2) hydrocarbon surface structures are identical above  $\sim 400$  K. The low temperature peak in 4b is from the hydrogen added in order to form a well ordered c(4x2) overlayer structure. This is in agreement with both the LEED and ELS results. ELS spectra taken before and after heating the crystal to 350 K show no major differences. Finally, the amount of  $H_2$  desorbed from the surface in 4c is significantly less than the amount desorbed in 4d, indicating that the stable ethylene phase on Rh(111) is partially dehydrogenated.

#### Correlations with $C_2H_4$ Chemisorption on Pt(111) and Ni(111)

Below room temperature  $C_2H_2$  and  $C_2H_4$  associatively adsorb on Pt(111) with their C-C bond oriented approximately parallel to the surface.<sup>4,13,18</sup> Both molecules form (2x2) surface structures<sup>19</sup> and are significantly rehybridized.<sup>4,13,18</sup> These species are only metastable and can be transformed into a single stable phase by gently heating the crystal.<sup>4,13,18,19</sup> Addition of hydrogen and heating to  $\sim 350$  K are necessary for acetylene to complete this conversion.<sup>4</sup> Although the stable species remains in a (2x2) surface structure, the LEED intensity vs. incident energy beam profiles change significantly.<sup>18,19</sup> This transformation has been detected by LEED,<sup>18,19</sup> ultraviolet photoelectron spectroscopy (UPS)<sup>14</sup> and high resolution ELS,<sup>4,13</sup> but there is still disagreement as to the geometry of the stable surface state. Proposed structures include ethylidyne ( $\rightarrow C-CH_3$ )<sup>1</sup>, ethylidene ( $>CH-CH_3$ )<sup>4,13</sup> and a vinyl species ( $>CH-CH_2$ ).<sup>14</sup> Finally, the partial dehydrogenation of the surface ethylene species during the metastable to stable transition was observed by a combination of TDS and UPS.<sup>14</sup>



The chemisorption behavior of these two simple hydrocarbons on Rh(111) and Pt(111) are summarized in Table III. The similarities are quite striking. The rhodium substrate appears to be more reactive, however, since the conversion to the stable state occurs at a lower temperature. This can be correlated with the relative positions of these two metals in the periodic table; in general the bonding of small molecules to transition metal surfaces becomes stronger as one moves to the left in the periodic table.<sup>20</sup> By analogy with Pt(111) one might expect a weakly parallel bonded ethylene phase to form on Rh(111) at low temperatures. Such a species is not detected under our experimental conditions.

By comparison, the chemisorption of acetylene and ethylene on Ni(111) is quite different from that on either Rh(111) or Pt(111). Both molecules are associatively adsorbed at low temperatures,<sup>7,21-25</sup> but upon heating, the C-C bond of chemisorbed  $C_2H_2$  is broken.<sup>21</sup> The remaining CH fragments undergo either carbon-hydrogen bond cleavage to leave carbon atoms on the surface or self-hydrogenation to form  $CH_2$  species.<sup>21</sup> Alternatively, at high gas exposures acetylene can cyclotrimerize on the Ni(111) surface to form chemisorbed benzene.<sup>22</sup> Upon heating, chemisorbed ethylene first dehydrogenates to adsorbed acetylene<sup>7,22,25</sup> and then can undergo a similar C-C and C-H bond breaking sequence. The formation of CH and  $CH_2$  species on Rh(111) at elevated temperatures is also observed.<sup>15</sup> High temperature studies have not been performed on Pt(111) as yet. We conclude that the species formed from the chemisorption of acetylene and ethylene on the Rh(111) and Pt(111) are quite similar and that analogous hydrocarbon fragments are not formed on Ni(111). Extension of these studies to Pd(111) would be most interesting.

### Conclusions

These investigations lead to the following conclusions:

1. The chemisorption of acetylene and ethylene on Rh(111) yields a series of ordered structures:



where  $\text{C}_2\text{H}_n$  stands for the stable hydrocarbon species with undetermined hydrogen content. These order-order transformations are irreversible.

2. Below 270 K acetylene chemisorbs on Rh(111) with its C-C bond oriented parallel to the surface forming an approximately  $\text{sp}^2$  hybridized species.

3. The chemisorption of  $\text{C}_2\text{H}_4$  or  $\text{C}_2\text{H}_2$  and hydrogen on Rh(111) and Pt(111) produce an identical stable surface species. This species has a stoichiometry of  $\text{C}_2\text{H}_n$  where n is less than 4.

4. The geometry of the adsorbed ethylene species on Rh(111), as determined by ELS, does not change during the conversion from the metastable to the stable species although the overlayer structure changes from a (2x2) to a c(4x2).

5. The addition of  $\text{H}_2$  to chemisorbed  $\text{C}_2\text{D}_2$  or  $\text{C}_2\text{D}_4$  results in H-D exchange, but no change in the adsorbate geometry is detected by ELS.

#### Acknowledgements

We thank Professor P.K. Hansma for many enlightening discussions and for valuable technical assistance. DGC acknowledges an NSF Energy Fellowship.

This work is supported by the Division of Materials Sciences, Office of Basic Energy Sciences, United States Department of Energy.



References

1. L.L. Kesmodel, L.H. Dubois and G.A. Somorjai, Chem. Phys. Lett 56, 267 (1978); J. Chem. Phys. 70, 2180 (1979).
2. D.G. Castner, B.A. Sexton and G.A. Somorjai, Surface Sci. 71, 519 (1978).
3. L.H. Dubois and G.A. Somorjai, Surface Sci., in press.
4. H. Ibach and S. Lehwald, J. Vac. Sci. Technol. 15, 407 (1978).
5. On the (111) crystal face of an fcc metal the (2x2) unit cell is a rhombohedron while the c(4x2) primitive unit cell is a rectangle.
6. The loss intensities are a strong function of the incident electron energy and only average values are reported here. This could be due to resonance or short-range scattering as discussed by Lehwald and Ibach for the case of acetylene chemisorption on Ni(111).<sup>7</sup>
7. S. Lehwald and H. Ibach, to be published.
8. H. Fröitzheim, H. Ibach and S. Lehwald, Rev. Sci. Instrum. 46, 1325 (1975).
9. See for example, T. Shimanouchi, Tables of Molecular Vibrational Frequencies, Consolidated Vol. 1, U.S. Dept. of Commerce publication NSRDS-NBS 39.
10. E. Evans and D.L. Mills, Phys. Rev. B5, 4126 (1972).
11. E.L. Meutterties, Bull. Soc. Chim. Belg. 85, 451 (1977).
12. E.L. Meutterties, T.N. Rhodin, Elliot Band, C.F. Brucker and W.R. Pretzer, Chem. Rev. 79, 91 (1979).
13. H. Ibach, H. Hopster and B. Sexton, Appl. Surface Sci. 1, 1 (1977).
14. J.E. Demuth, Surface Sci. 80, 367 (1979).
15. L.H. Dubois, P.K. Hansma and G.A. Somorjai, to be published.
16. D.G. Castner, Ph.D. Thesis, University of California, Berkeley, 1979.
17. J.T. Yates, Jr., P.A. Thiel and W.H. Weinberg, Surface Sci. 84, 427 (1979).
18. L.L. Kesmodel, R.C. Baetzold and G.A. Somorjai, Surface Sci. 66, 299 (1977).
19. P.C. Stair and G.A. Somorjai, Chem. Phys. Lett. 41, 391 (1976); Surface Sci. 66, 299 (1977).
20. I. Toyoshima and G.A. Somorjai, Catal. Rev.,-Sci. Eng. 19, 105 (1979).
21. J.E. Demuth and H. Ibach, Surface Sci. 78, L238 (1978).
22. J.C. Bertolini, J. Massardier and G. Dalmai-Imelik, J. Chem. Soc. Faraday I 74, 1920 (1978).
23. J.E. Demuth and H. Ibach, Surface Sci. 85, 365 (1979).

24. J.E. Demuth, H. Ibach and S. Lehwald, Phys. Rev. Lett. 40, 1044 (1978).
25. J.C. Bertolini and J. Rousseau, Surface Sci. 83, 531 (1979).

TABLE I: Vibrational modes for the metastable (2x2) -  
 $C_2H_2$  ( $C_2D_2$ ) species observed on Rh(111) at  $T < 270K$   
 (all frequencies in  $cm^{-1}$ )

$C_2H_2(C_2D_2)/Rh(111)$	Assignments
3085 ( $\sim 2320$ ) w	} C-H(C-D) stretch
2984 (2230) m	
a	C-C stretch
887 (686) m	} C-H (C-D) bend
706 (565) m	
323 ( $\sim 300$ ) w	M-C stretch

Intensity: s=strong m=medium w=weak

- a. Small broad peak in the  $1300-1400\text{ cm}^{-1}$  region is observed in several spectra

TABLE II: VIBRATIONAL MODES FOR THE STABLE SPECIES OBSERVED ON  
 Rh(111) AND Pt(111) UPON ADSORPTION OF EITHER  
 $C_2H_4$  OR  $C_2H_2$  AND H ABOVE 300 K.  
 (all frequencies in  $cm^{-1}$ )

Chemisorption of $C_2H_4$ or $C_2H_2+H$		Chemisorption of $C_2D_4$	
Rh(111)	Pt(111)	Rh(111)	Pt(111)
$\sim 3000$ w	3025 - 3105 w	2180 w	broad unresolved band
$\sim 2900$ w	2900 - 2940 m	2080 m	
shoulder	1420 m	1150 s	1150 s
1350 s	1350 - 1360 s	990	1010 w
1130 s	1130 s	860 m	850 w
880 m	900 m	403 w	430 m
450 w	435 m		

Intensity: s=strong

m=medium

w=weak

TABLE III: Summary of LEED, ELS and TDS data for the chemisorption of  $C_2H_2$  and  $C_2H_4$  on Rh(111) and Pt(111).


	Rh(111)		Pt(111)	
	$C_2H_2$	$C_2H_4$	$C_2H_2$	$C_2H_4$
Metastable species:				
LEED	(2x2)	(2x2)	(2x2)	(2x2)
ELS	parallel bonded ( $\sim sp^2$ )	$C_2H_n^a$	parallel bonded ( $\sim sp^2$ )	parallel bonded ( $\sim sp^3$ )
Conversion to stable species: <sup>b</sup>				
Temperature	$\sim 270K$	$\sim 270K$	$\sim 350K$	$\sim 300K$
Addition of hydrogen?	yes	no	yes	no
Stable species:				
LEED	c(4x2)	c(4x2)	(2x2)	(2x2)
ELS	$C_2H_n$	$C_2H_n$	$C_2H_n$	$C_2H_n$
Partial dehydrogenation (TDS)	no	yes	no	yes
Decomposition temperature	420K	420K	450K	450K

a. Vibrational spectrum previously assigned as ethylidyne ( $\equiv C-CH_3$ ), ethylidene ( $>CH-CH_3$ ) and a vinyl species ( $>CH-CH_2$ ), see text.


b. Conditions for complete conversion.

Figure Captions

1. LEED patterns from surface structures produced by either  $C_2H_2$  or  $C_2H_4$  adsorption on Rh(111). (a) clean Rh(111) at 92.5 eV, (b) Rh(111)-(2x2) from  $C_2H_4$  chemisorption at 74 eV, and (c) Rh(111)-c(4x2)- $C_2H_2+H$  at 67.5 eV.
2. High resolution ELS spectra of chemisorbed acetylene on Rh(111). (a) (2x2)- $C_2H_2$ , (b) (2x2)- $C_2D_2$ , and (c) c(4x2)- $C_2H_2+H$ . The vibrational frequencies are listed in Tables I (spectra a and b) and II (spectrum c). The broad peak (dotted line) centered near  $800\text{ cm}^{-1}$  may be caused by a reflection inside the spectrometer (see text).<sup>8</sup>
3. High resolution ELS spectra of chemisorbed ethylene on Rh(111). (a) (2x2) from  $C_2H_4$  chemisorption, (b) c(4x2) from  $C_2H_4$  chemisorption and (c) (2x2) from  $C_2D_4$  chemisorption. The vibrational frequencies are listed in Table II.
4. Hydrogen desorption from the (a) (2x2) and (b) c(4x2) overlayer structures formed during  $C_2H_2$  adsorption on Rh(111) and from the (c) c(4x2) and (d) (2x2) structures from  $C_2H_4$  adsorption on Rh(111). After forming the c(4x2) surface structures, the crystal is cooled to 240K before initiating the desorption experiments. The heating rate is 40K/sec.

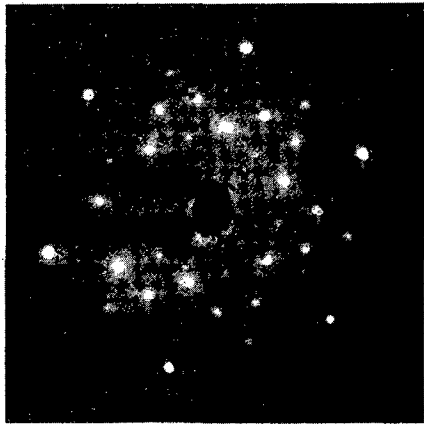

**c**  
XBB788 10161

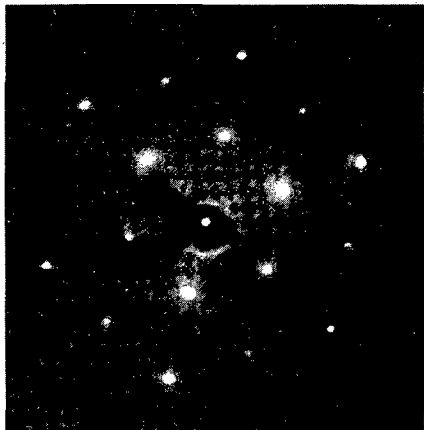


**b**



**a**


Fig. 1

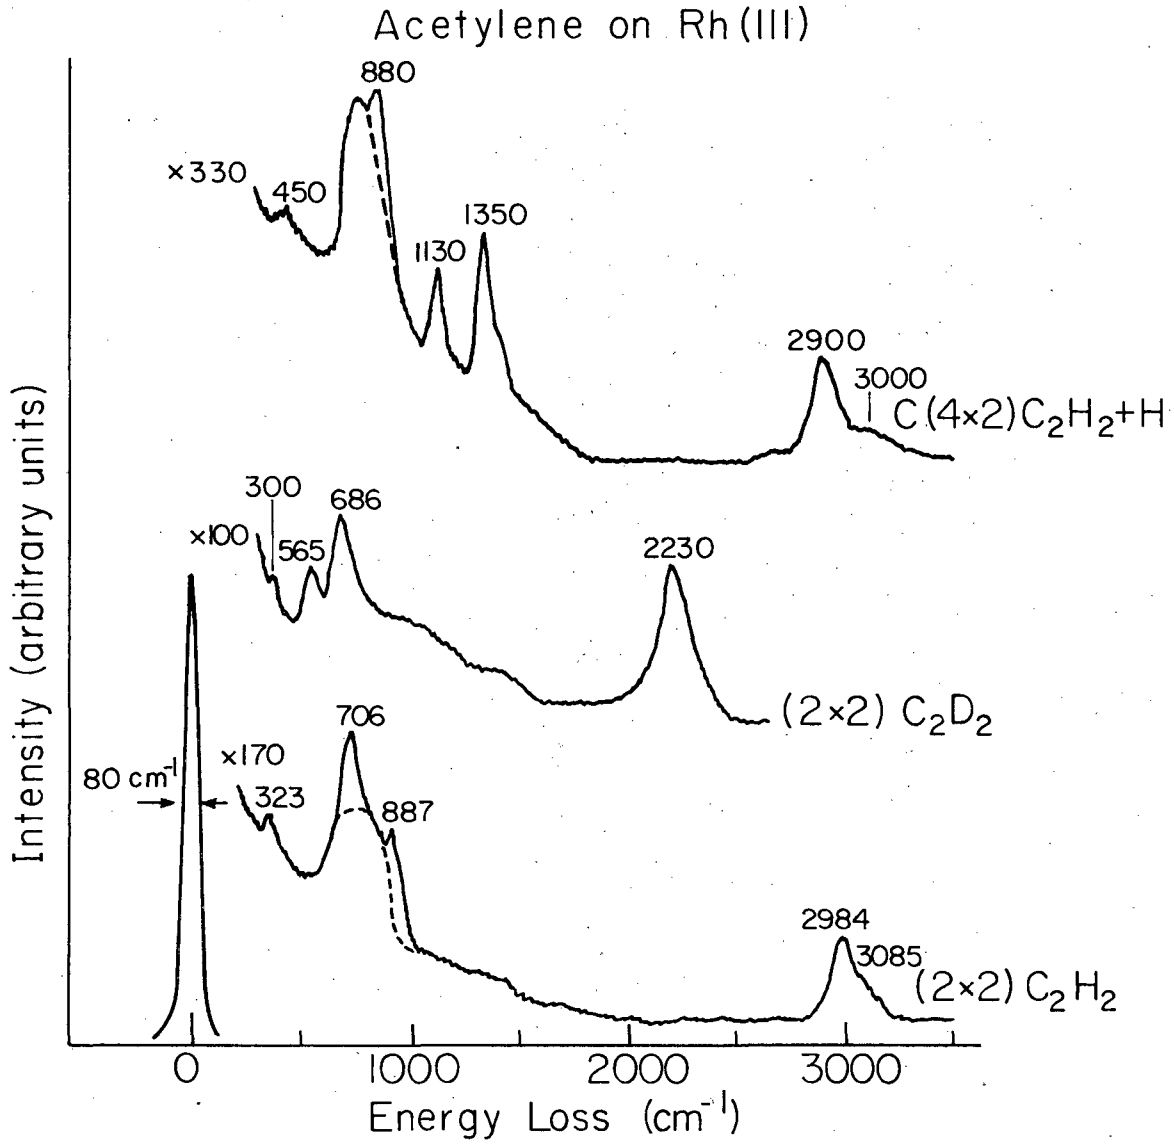

XBL798-6968


Fig.2



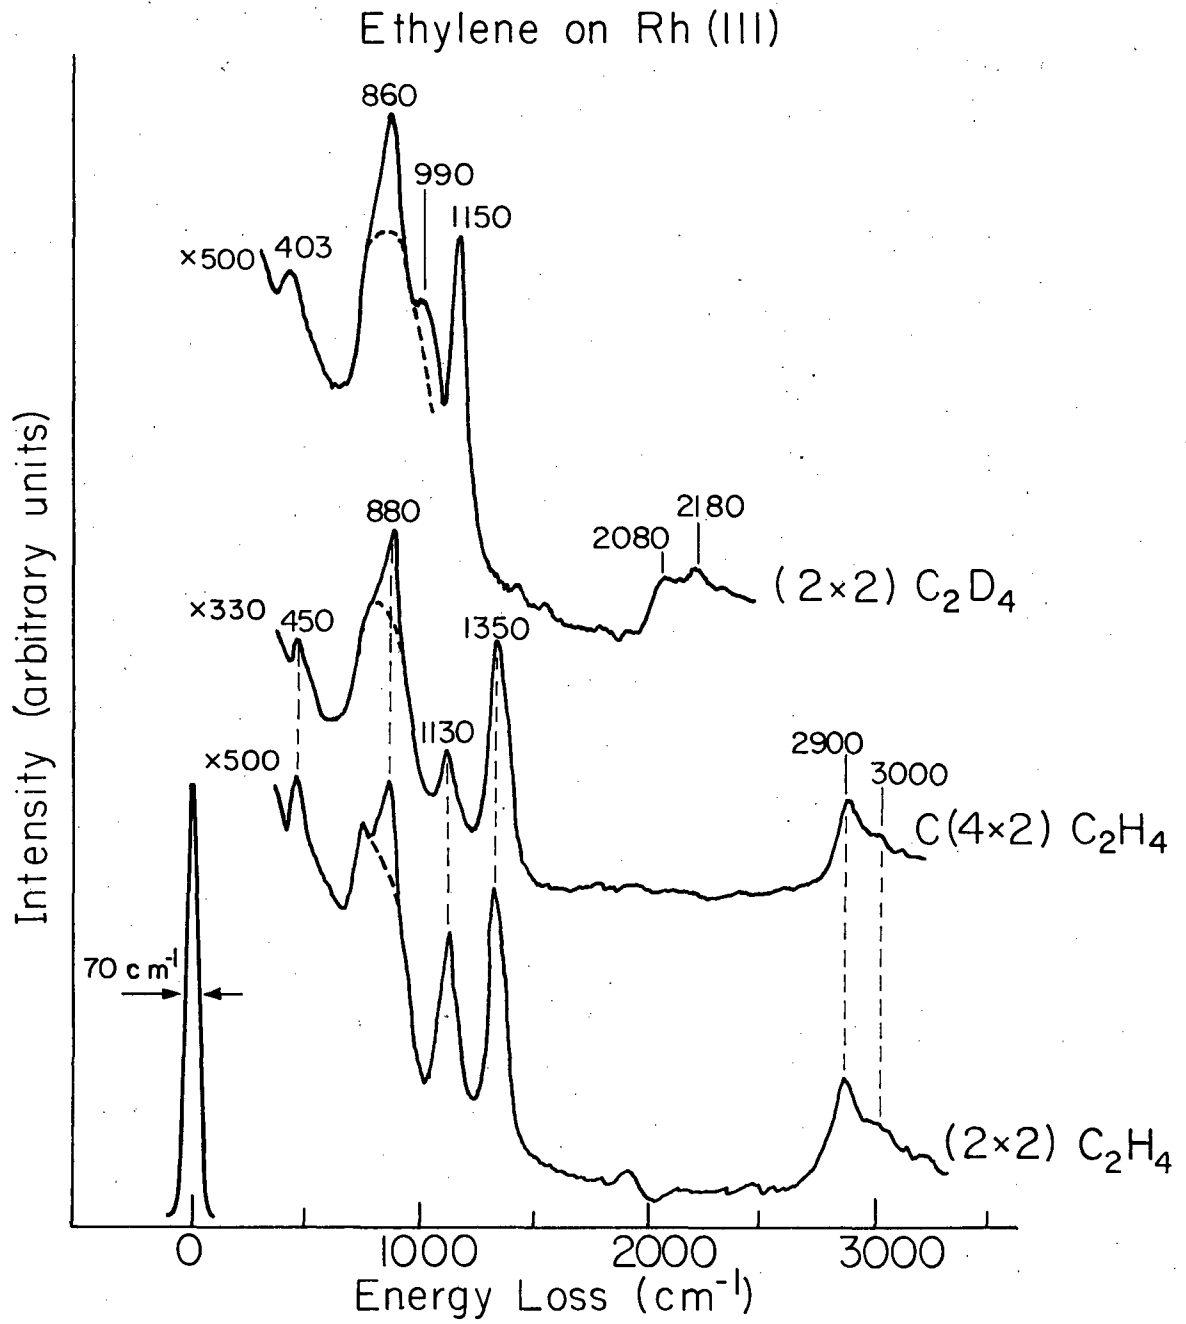

XBL798-6969

Fig.3

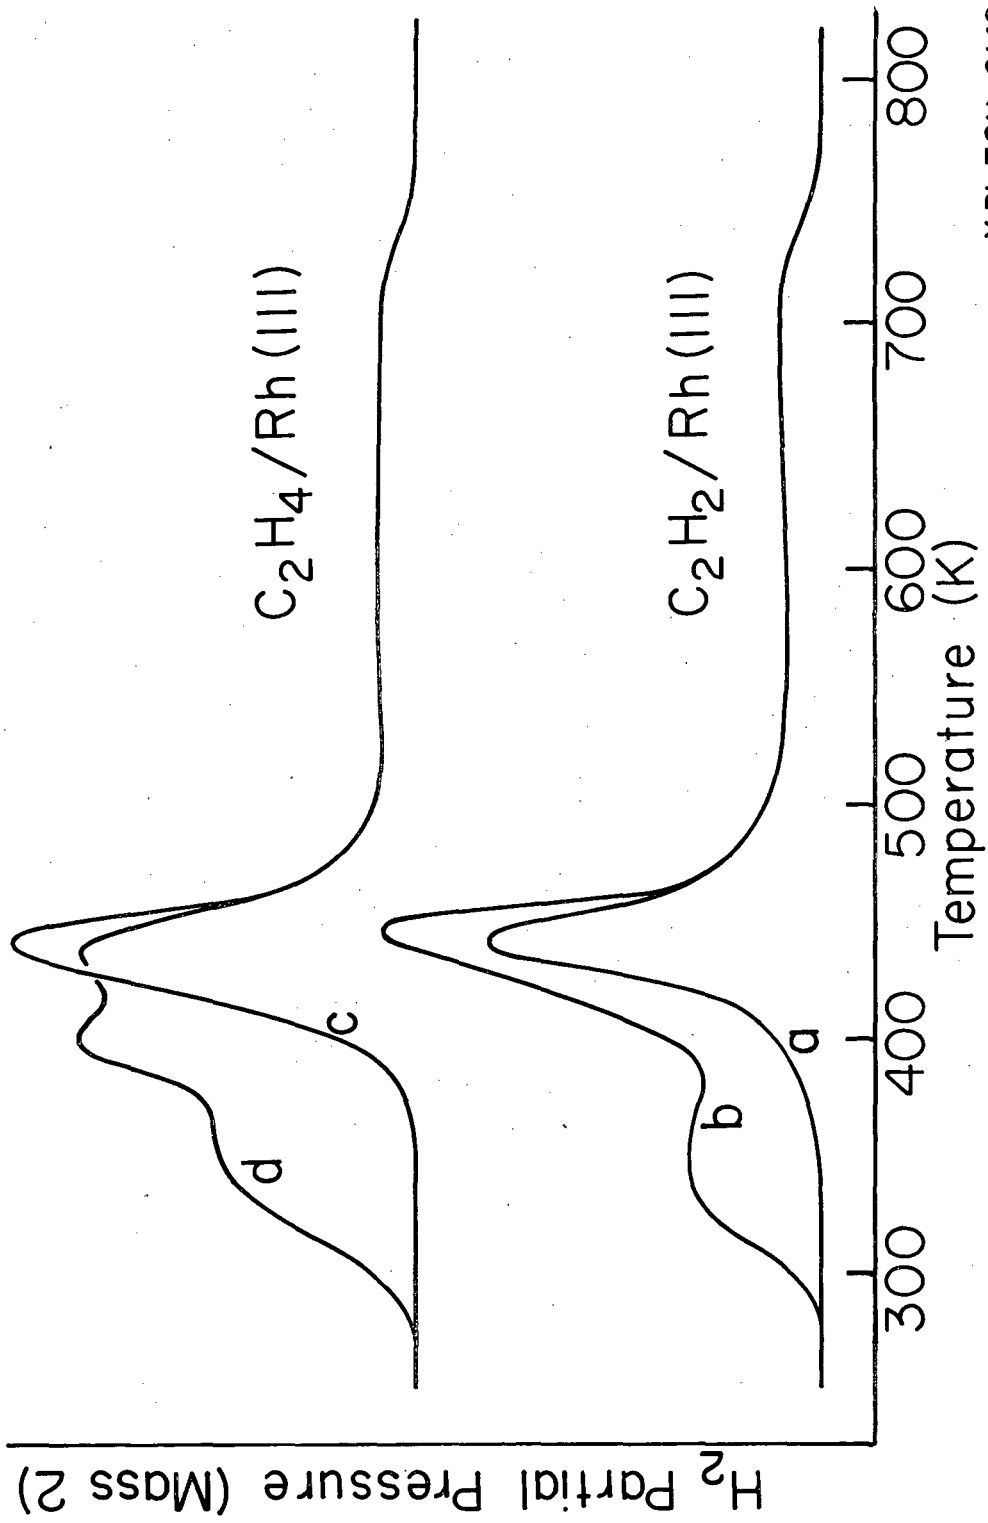

XBL 7811-6149A

Fig. 4

52

50

This report was done with support from the Department of Energy. Any conclusions or opinions expressed in this report represent solely those of the author(s) and not necessarily those of The Regents of the University of California, the Lawrence Berkeley Laboratory or the Department of Energy.

Reference to a company or product name does not imply approval or recommendation of the product by the University of California or the U.S. Department of Energy to the exclusion of others that may be suitable.

TECHNICAL INFORMATION DEPARTMENT  
LAWRENCE BERKELEY LABORATORY  
UNIVERSITY OF CALIFORNIA  
BERKELEY, CALIFORNIA 94720