

Tissue engineering in cardiovascular surgery: new approach to develop completely human autologous tissue[☆]

Qing Ye^a, Gregor Zünd^{b,*}, Stefan Jockenhoevel^a, Simon P. Hoerstrup^b, Andreina Schoeberlein^b, Jurg Grunenfelder^b, Marko Turina^b

^aDepartment of Surgical Research, University Hospital, Rämistrasse 1000, CH-8091, Zurich, Switzerland

^bClinic for Cardiovascular Surgery, University Hospital, Rämistrasse 100, CH-8091 Zurich, Switzerland

Received 7 September 1999; received in revised form 19 January 2000; accepted 26 January 2000

Abstract

Objective: In cardiovascular tissue engineering, three-dimensional scaffolds serve as physical supports and templates for cell attachment and tissue development. Currently used scaffolds are still far from ideal, they are potentially immunogenic and they show toxic degradation and inflammatory reactions. The aim of this study is to develop a new method for a three-dimensional completely autologous human tissue without using any scaffold materials. **Methods:** Human aortic tissue is harvested from the ascending aorta in the operation room and worked up to pure human myofibroblasts cultures. These human aortic myofibroblasts cultures (1.5×10^6 cells, passage 3) were seeded into 15-cm culture dishes. Cells were cultured with Dulbecco's modified Eagle's medium supplemented with 1 mM L-ascorbic acid 2-phosphate for 4 weeks to form myofibroblast sheets. The harvested cell sheets were folded to form four-layer sheets. The folded sheets were then framed up and cultured for another 4 weeks. Tissue development was evaluated by biochemical assay and light and electron microscopy. **Results:** After 4 weeks of culture in ascorbic acid supplemented medium, myofibroblasts formed thin cell sheets in culture dishes. The cell sheets presented in a multi-layered pattern surrounded by extracellular matrices. Cultured for additional 4 weeks on the frames, the folded sheets further developed into more solid and flexible tissues. Light microscopy documented a structure resembling to a native tissue with confluent extracellular matrix. Under transmission electron microscope, viable cells and confluent bundles of striated mature collagen fibers were observed. Hydroxyproline assays showed significant increase of collagen content after culturing on the frames and were 80.5% of that of natural human pericardium. **Conclusions:** Improved cell culture technique may render human aortic myofibroblasts to a native tissue-like structure. A three-dimensional completely autologous human tissue may be further developed on the base of this structure with no show toxic degradation or inflammatory reactions. © 2000 Elsevier Science B.V. All rights reserved.

Keywords: Tissue engineering; Autologous human tissue; Cardiovascular; Scaffolds

1. Introduction

Tissue engineering may provide an alternative to organ and tissue transplantation, because of the limited supply of donor organs [1]. Most common mode of engineering new tissue is based on seeding isolated cells on a three-dimensional scaffold followed by in vitro culture. The scaffolds serve as physical supports and templates for cell attachment and tissue development. With the principles of tissue engineering, researchers are trying to create new tissue in cardiovascular surgery, such as heart valves, cardiac muscle, pericardium and vessels [2–6].

The currently used materials for maintaining three-

dimensional structures in tissue engineering are either polymers composed of chemical substances like polyglycolic acid, polyhydroxybutyrate and gels out of extracellular matrix proteins such as collagen [7,8]. Unfortunately, these materials are still far from ideal. They are expensive, potentially immunogenic and further more they show toxic degradation and inflammatory reactions. In addition they might be of poor resorbability [8–11].

Collagen is a major component of various tissue in cardiovascular system, such as heart valve and pericardium [12,13]. Considered to be the main stress bearing component, it has been the focus of most studies about heart valve or pericardial tissue engineering. The collagen is produced by fibroblast cells. In long-term postconfluent fibroblasts cultures, connective tissue matrix is produced with many in vivo-like properties including supermolecular organization of collagen. Collagen is not only processed essentially complete, but is also cross-linked efficiently and the

[☆] Presented at the 13th Annual Meeting of the European Association for Cardio-thoracic Surgery, Glasgow, Scotland, UK, September 5–8, 1999.

* Corresponding author. Tel.: +41-1-255-3801; fax: +41-1-255-4369.

E-mail address: gregor.zund@chi.usz.ch (G. Zünd)

collagen fibrils are assembled into bundles [14]. The long-term culture forms a three-dimensional structure with the fibroblasts settle in the self-produced extracellular matrix [15]. The formed three-dimensional structure might serve as a template for further tissue development.

The aim of this study is to develop a new method for a three-dimensional completely autologous human tissue without using any scaffold materials.

2. Material and methods

2.1. Human aortic myofibroblast cell expansion

Human ascending aortic tissue was collected in the operation room. After harvesting, the explants were rinsed with phosphate-buffered saline (PBS) and stripped off adventitia. The tissue was then cut into small pieces of 2×2 mm for primary culture in Dulbecco's modified Eagle's medium supplemented with 10% fetal bovine serum and 1% streptomycin (Gibco BRL-Life Technologies, Grand Island, NY). After 3–4 weeks, human aortic myofibroblasts grew into confluent monolayers and were serially passaged by trypsinization (trypsin/EDTA solution, 0.05%/0.02%, Gibco BRL-Life Technologies, 3–5 min) and subcultured to obtain sufficient cell numbers for cell seeding (passage 3–4).

2.2. Cell sheets culture and tissue development

The myofibroblasts were cultured in 15-cm culture dishes for 4 weeks with Dulbecco's modified Eagle's medium, supplemented with 10% fetal bovine serum and 1% streptomycin (Gibco BRL-Life Technologies, Grand Island, NY), 1.0 mmol/l L-ascorbic acid 2-phosphate (Asc 2-P, Sigma Chemical Co, St. Louis, MO). Cell sheets formed after 4 weeks of culture and were detached from the culture dish. These cell sheets were folded into four-layer sheets (Fig. 1) and mounted on culture frames (diameter = 1.5 cm). The framed cell sheets were cultured for another 4 weeks in the same medium.

2.3. Structure assessment

2.3.1. Collagen content

Collagen content was estimated with hydroxyproline (Hyp) assay according to Reddy et al. [16]. Briefly, samples

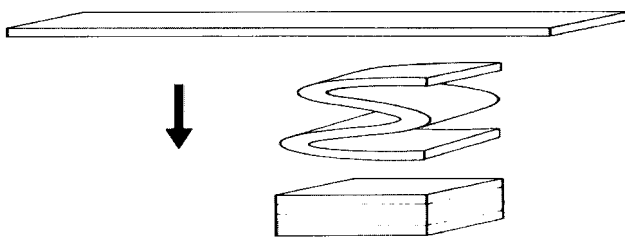


Fig. 1. Illustration of cell sheets folding. A piece of cell sheet harvested from the 15-cm culture dish was folded to form a four-layer sheet.

were lyophilized and hydrolyzed with 2 M NaOH. Hydrolyzed free hydroxyproline was oxidized with chloramine-T and the addition of Ehrlich's reagent resulted in the formation of a chromophore. It's absorbance measured at 550 nm. The hydroxyproline content of the cell sheets and framed sheets were compared human pericardium.

2.3.2. Histological evaluation

Specimens for light microscope examination were fixed in 4% formalin, embedded in paraffin and sectioned. The sections were stained by hematoxylin and eosin (HE) or Masson's trichrome. Transmission electron microscopy specimens were fixed with Na-Cacodylat-buffered glutaraldehyde (2.5%) and paraformaldehyde (0.8%), and were post-fixed with 1% osmium tetroxide, dehydrated in a series of alcohol, and embedded. Ultra-thin sections were stained with uranyl acetate and lead citrate. The specimens were observed under light microscopy and transmission electron microscopy.

2.3.3. Statistics

Results data were expressed as mean \pm 1 SD. Comparisons between groups were performed by ANOVA test. Statistical significance was set at $P < 0.05$.

3. Results

After 4 weeks of culture in Asc 2-P supplemented medium, human ascending aortic myofibroblasts formed thin cell sheets in the culture dishes and were detached from the culture dish. The cell sheets measured about 20 μ m in thickness under microscope, and were presented in a multilayer pattern surrounded by extracellular matrix (Fig. 2). In contrast, myofibroblasts cultured in medium without Asc 2-P remained as a cell monolayers and could hardly be detached from the culture dish. The harvested cell sheets were folded to form four-layer cell sheets and were cultured for additional 4 weeks on the frames, the folded sheets further developed into more solid and flexible tissues (Fig. 3). With regard to the mechanical properties, the tissue is flexible and elastic. An excursion of the framed tissue to 10 mm without rupture was possible. Light microscopy documented an integral structure resembling to a native tissue structure with confluent extracellular matrix, measuring about 150 μ m in thickness (Fig. 4A,B). Under transmission electron microscope, active viable cells and confluent bundles of striated mature collagen fibers were observed (Fig. 5A,B).

Hydroxyproline content (Hyp/tissue dry weight) of folded cell sheets was significantly higher than that of the cell sheets before folding (6.012 ± 0.197 vs. 4.387 ± 0.349 μ g/mg, $P < 0.01$) (Fig. 6). Folded cell sheets had a hydroxyproline content of 80.5% of human pericardium, while the cell sheets before folding has only 58.7%. These assay results showed, that the folded cell sheets on the frames were further growing and producing more collagen and a continuous tissue development was achieved.

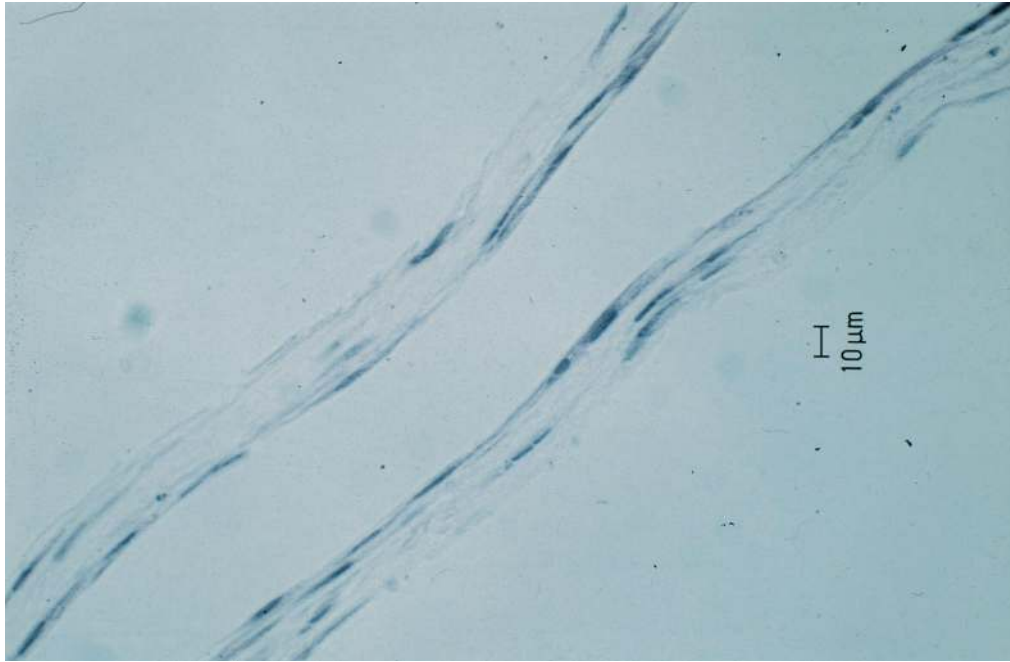


Fig. 2. After 4 weeks of culture in Asc 2-P supplemented medium, human ascending aortic myofibroblasts a multilayer cell sheet with cells surrounded by extracellular matrix (hematoxylin and eosin staining).

4. Discussion

The currently used materials for maintaining three-dimensional structures in tissue engineering are either polymers composed of chemical substances like polyglycolic

acid, polyhydroxybutyrate and gels out of extracellular matrix proteins such as collagen. Unfortunately, these materials are still far from ideal, they are expensive, potentially immunogenic and furthermore they show toxic degradation and inflammatory reactions, in addition they might be of

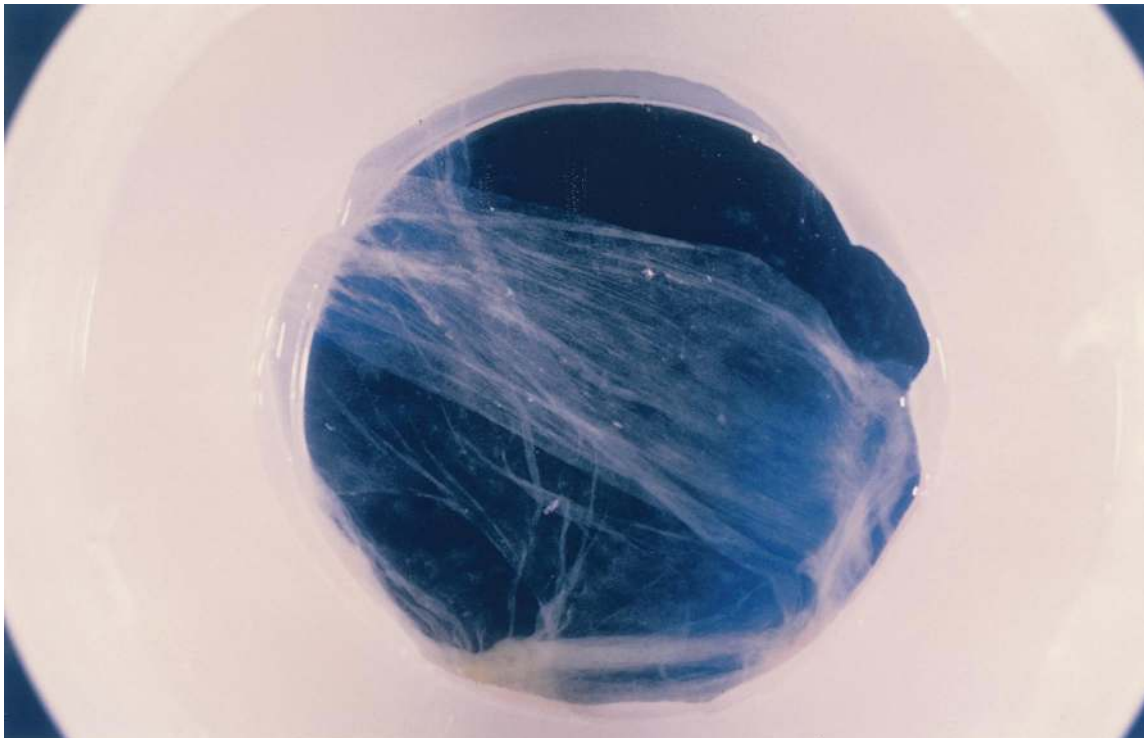


Fig. 3. Folded cell sheets developed into a solid and flexible tissues on the frame.

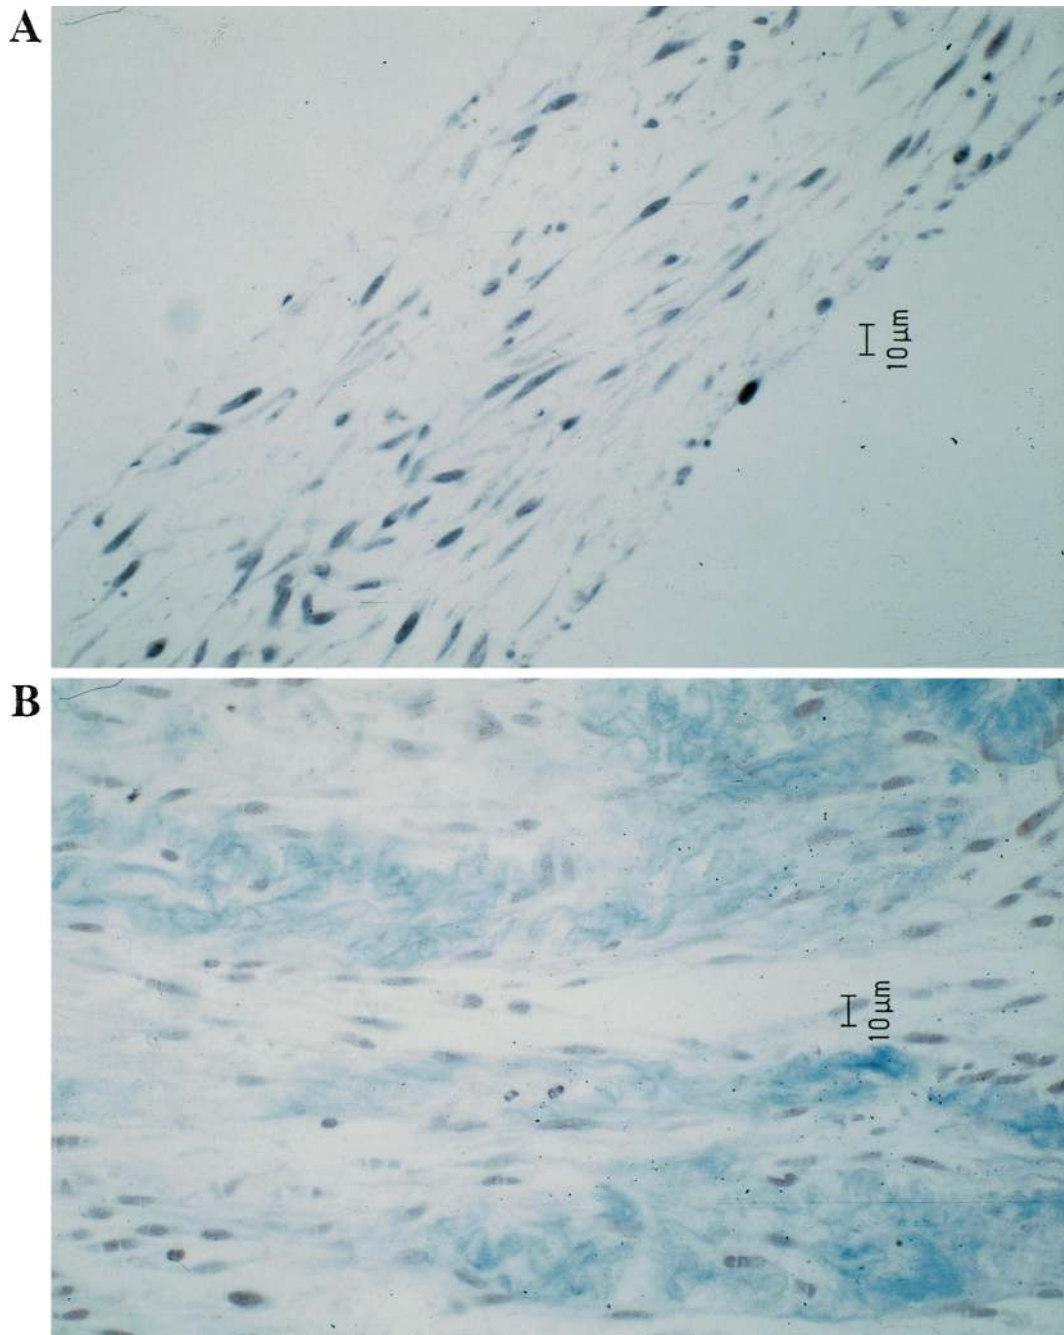


Fig. 4. Light microscopy documented folded cell sheets developed into an integral structure resembling to a native tissue with viable cells and confluent extracellular matrix. (A) Hematoxylin and eosin staining, (B) Masson's trichrome staining.

poor resorbability. Thus, the final goal of the presented study is to demonstrate a new method, which allows the creation of a three-dimensional new tissue without any disadvantages of the common used scaffolds. Furthermore we demonstrate a core structure which might be used for further application in the cardiovascular tissue engineered field.

Hata et al. [17] first demonstrated that supplementation of fibroblast cell cultures with Asc 2-P stimulates the accumulation of intact collagen which leads to the formation of

mature ECM. Ascorbic acid is an essential cofactor for the hydroxylation of proline and lysine residues in collagens synthesized by human fibroblasts. Ascorbic acid is also known to increase the transcriptional rate of procollagen genes and the stability of procollagen mRNA [18,19] as well as to modulate growth properties of cells [20]. Grinnel et al. [14] found accelerated collagen assembly in extracellular matrix by fibroblasts in long-term cultures supplemented with ascorbic acid. The matrix was highly differentiated as shown by complete processing of procollagen to collagen

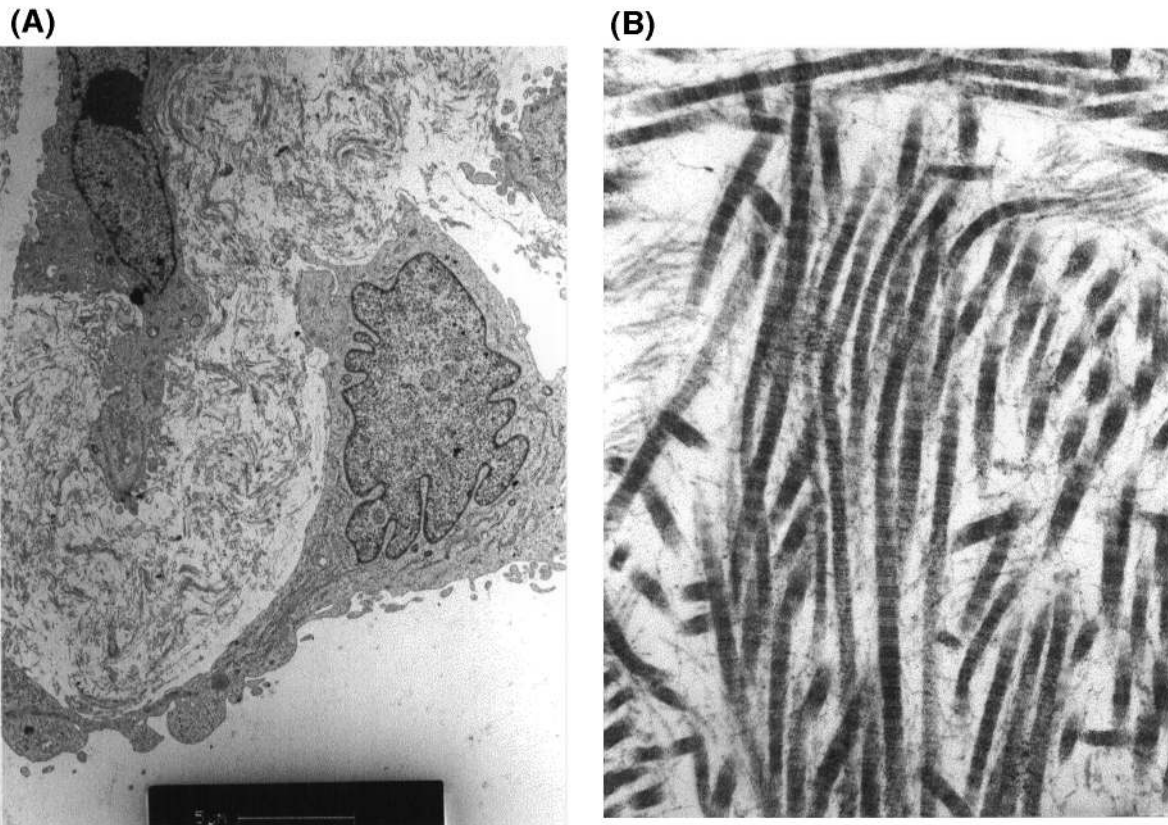


Fig. 5. (A) Active viable cells and confluent bundles collagen were observed by transmission electron microscope, (B) the collagen fibers are highly striated at high magnification.

and the assembly of collagen fibrils into bundles. We have similar results in this study, after 8 weeks culture in Asc 2-P supplemented medium, extracellular matrix accumulated around the cells, and bundles of collagen with mature striated appearance were observed by transmission electron microscopy.

Mechanical stress enhances synthesis and secretion of proteins and mechanical stiffness, and effects on the level of gene expression. Tension as a specific form of mechanical stress affects the cell function and behavior [21]. Connective tissue morphogenesis was induced by isometrically strained fibroblast cultures. In our previous study, when seeded PGA meshes were cultured under certain tension on the culture frame, production of collagen by the myofibroblasts was significantly increased. Hydroxyproline content was more than six times higher in the framed cultures compared with the unframed, and even ten times higher compared with the unframed cultures with ascorbic [22]. In this study, we modified our framework and mounted the folded four-layer cell sheets on the frames so as to perform tension on the sheets to stimulate extracellular matrix generation.

When the cell sheets are framed up, not only mechanical tension is achieved, but in addition, the framed cell sheets are in good contact with medium on both surfaces, this will greatly facilitating the nutrition supply to the inner part of

the structure. Histological study shows low necrosis even in the core part of the structure. The thickness of the tissue we have developed was about 150 μm , which is much thicker than the simple addition of four cell layers before culturing. Moreover, the folded cell sheets had a significantly higher hydroxyproline contents compared to the cell sheets before folding. These results suggest the harvested tissue is viable and has the ability of further growing under in vitro culture

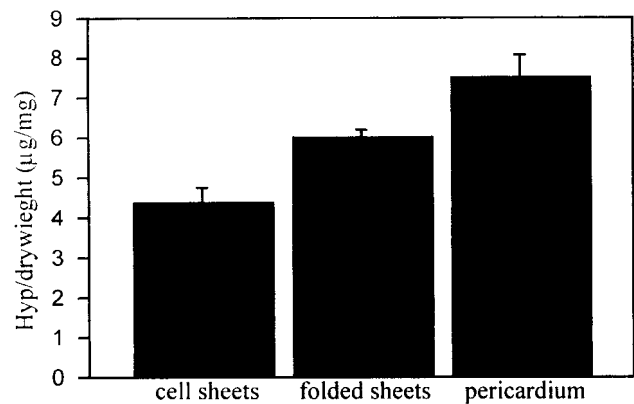


Fig. 6. Hydroxyproline content (Hyp/tissue dry weight) of folded cell sheets was significantly higher than that of the cell sheets before folding ($P < 0.01$). They contain 80.5 and 58.7% Hyp content in comparison with human pericardium.

conditions. In addition, the presented new method is potentially not immunogenic and showed no toxic degradation or even inflammatory reactions.

An improvement of the mechanical properties might be possible by higher folding cycles. More investigations are necessary to characterize the mechanical properties subject to the number and time intervals of folding cycles. Nevertheless at that moment the tissue is strong enough to be implanted as a artificial pericardium. By the production of a thicker and stiffer tissue sheet the construction of cardiac valves will be possible in a surgical technique like the manufacture of pericardium valves.

In conclusion, improved cell culture technique may render human aortic myofibroblasts to a native tissue-like structure. A autologous tissue in the cardiovascular field might be of further development based on the presented core structure.

References

- [1] Kim BS, Mooney DJ. Development of biocompatible synthetic extracellular matrices for tissue engineering. *Trends Biotechnol* 1998;16:224–230.
- [2] Shinoka T, Breuer CK, Tanel RE, Zünd G, Miura T, Ma PX, Langer R, Vacanti JP, Mayer JE. Tissue engineering heart valves: valve leaflet replacement study in a lamb model. *Ann Thorac Surg* 1995;60:S513–S516.
- [3] Shinoka T, Ma PX, Shum Tim D, Breuer CK, Cusick RA, Zünd G, Langer R. Tissue engineering heart valves: autologous valve leaflet replacement in a lamb model. *Circulation* 1996;94(Suppl II):II164–II168.
- [4] Shinoka T, Shum Tim D, Ma PX, Tanel RE, Isogai N, Langer R, Vacanti JP, Mayer Jr JE. Creation of viable pulmonary artery autografts through tissue engineering. *J Thorac Cardiovasc Surg* 1998;115:536–545.
- [5] Zund G, Breuer CK, Shinoka T, Ma PX, Langer R, Mayer JE, Vacanti JP. The in vitro construction of a tissue engineered bioprosthetic heart valve. *Eur J Cardio-thorac Surg* 1997;11:493–497.
- [6] Zund G, Hoerstrup SP, Schoeberlein A, Lachat M, Uhlschmid G, Vogt PR, Turina M. Tissue engineering: a new approach in cardiovascular surgery; seeding of human fibroblasts followed by human endothelial cells on resorbable mesh. *Eur J Cardio-thorac Surg* 1998;13:160–164.
- [7] Freed LE, Vunjak Novakovic G, Biron RJ, Eagles DB, Lesnoy DC, Barlow SK, Langer R. Biodegradable polymer scaffolds for tissue engineering. *Biotechnol NY* 1994;12:689–693.
- [8] Grande DA, Halberstadt C, Naughton G, Schwartz R, Manji R. Evaluation of matrix scaffolds for tissue engineering of articular cartilage grafts. *J Biomed Mater Res* 1997;34:211–220.
- [9] Sims CD, Butler PE, Cao YL, Casanova R, Randolph MA, Black A, Vacanti CA, Yaremchuk MJ. Tissue engineered neocartilage using plasma derived polymer substrates and chondrocytes. *Plast Reconstr Surg* 1998;101:1580–1585.
- [10] Zibaitis A, Greentree D, Ma F, Marelli D, Duong M, Chiu RC. Myocardial regeneration with satellite cell implantation. *Transplant Proc* 1994;26:3294.
- [11] Greentree D, Marelli D, Ma F, Chiu RC. Satellite cell transplantation for myocardial repair: labeling techniques. *Transplant Proc* 1994;26:3357.
- [12] Scott M, Vesely I. Aortic valve cusp microstructure: the role of elastin. *Ann Thorac Surg* 1995;60:S391–S394.
- [13] Ishihara T, Ferrans VJ, Jones M, Boyce SW, Kawanami O, Roberts WC. Histologic and ultrastructural features of normal human parietal pericardium. *Am J Cardiol* 1980;46:744–753.
- [14] Grinnell F, Fukamizu H, Pawelek P, Nakagawa S. Collagen processing, crosslinking, and fibril bundle assembly in matrix produced by fibroblasts in long-term cultures supplemented with ascorbic acid. *Exp Cell Res* 1989;181:483–491.
- [15] Ishikawa O, Kondo A, Okada K, Miyachi Y, Furumura M. Morphological and biochemical analyses on fibroblasts and self-produced collagens in a novel three-dimensional culture. *Br J Dermatol* 1997;136:6–11.
- [16] Reddy GK, Enwemeka CS. A simplified method for the analysis of hydroxyproline in biological tissues. *Clin Biochem* 1996;29:225–229.
- [17] Hata R, Senoo H. L-ascorbic acid 2-phosphate stimulates collagen accumulation, cell proliferation, and formation of a three-dimensional tissue-like substance by skin fibroblasts. *J Cell Physiol* 1989;138:8–16.
- [18] Lyons BL, Schwarz RI. Ascorbate stimulation of PAT cells causes an increase in transcription rates and a decrease in degradation rates of procollagen mRNA. *Nucleic Acids Res* 1984;12:2569–2579.
- [19] Tajima S, Pinnell SR. Regulation of collagen synthesis by ascorbic acid. Ascorbic acid increases type I procollagen mRNA. *Biochem Biophys Res Commun* 1982;106:632–637.
- [20] Hata R, Sunada H, Arai K, Sato T, Ninomiya Y, Nagai Y, Senoo H. Regulation of collagen metabolism and cell growth by epidermal growth factor and ascorbate in cultured human skin fibroblasts [published erratum appears in *Eur J Biochem* 1988 Aug 15;175(3):679]. *Eur J Biochem* 1988;173:261–267.
- [21] Kanda K, Matsuda T, Oka T. Mechanical stress induced cellular orientation and phenotypic modulation of 3-D cultured smooth muscle cells. *ASAIO J* 1993;39:M686–M690.
- [22] Hoerstrup SP, Zund G, Ye Q, Schoeberlein A, Schmid AC, Turina M. Tissue engineering of a bioprosthetic heart valve: stimulation of extracellular matrix assessed by hydroxyproline assay. *ASAIO J* 1999;45(5):397–402.