

 Open access • Journal Article • DOI:10.1002/ANIE.202015703

Ultra-Low Molecular Weight Photoswitchable Hydrogelators — [Source link](#)





Fayaz Ali Larik, Lucy L. Fillbrook, Sandra S. Nurttila, Adam D. Martin ...+5 more authors

Institutions: University of New South Wales, Macquarie University

Published on: 15 Mar 2021 - Angewandte Chemie (John Wiley & Sons, Ltd)

Related papers:

- [A visible light responsive azobenzene-functionalized polymer: Synthesis, self-assembly, and photoresponsive properties](#)
- [Controlled Sol-Gel Transitions of a Thermoresponsive Polymer in a Photoswitchable Azobenzene Ionic Liquid as a Molecular Trigger.](#)
- [Stimuli-Responsive Copolymer and Uniform Polymeric Nanoparticles with Photochromism and Switchable Emission](#)
- [A Diarylethene-Based Photoswitch and its Photomodulation of the Fluorescence of Conjugated Polymers](#)
- [Visible light photoswitching of conjugated polymer nanoparticle fluorescence.](#)

Share this paper:    

View more about this paper here: <https://typeset.io/papers/ultra-low-molecular-weight-photoswitchable-hydrogelators-2j9sh2b7j>

Ultra-low molecular weight photoswitchable hydrogelators

Fayaz Ali Larik, Lucy L. Fillbrook, Sandra S. Nurttala, Adam D. Martin, Rhiannon P. Kuchel, Karrar Al Taief, Mohan Bhadbhade, Jonathon E. Beves* and Pall Thordarson*

KEYWORDS: Low molecular weight gelator, light responsive hydrogelator; arylazopyrazole, photoswitch

ABSTRACT: Photoswitchable arylazopyrazoles **2** and **3** form hydrogels at a concentration of 1.2% (w/v). With a molecular weight of 258.11 g/mol, these are the lowest known molecular weight hydrogelators that respond reversibly to light. Single-crystal X-ray structures show anisotropic aggregation of **2** and **3** is driven by in-plane hydrogen bonding interactions and π - π stacking. Photoswitching of **2** and **3** from the *E*- to the *Z*-form by 365 nm light results in a macroscopic gel→sol transition; nearly an order of magnitude reduction in the measured elastic and loss moduli. Cryogenic transmission electron microscopy suggests that the 29 ± 7 nm wide sheets in the *E*-**2** gel state narrow to 13 ± 2 nm upon photoswitching to the predominantly *Z*-**2** solution state. In the case of **2**, photoswitching is reversible through cycles of 365 nm and 520 nm excitation with little fatigue. The release of a Rhodamine B dye encapsulated in gels formed from **2** and **3** can be accelerated more than 20-fold upon photoswitching with 365 nm light, demonstrating these materials are suitable for light-controlled cargo release.

The formation of cytoskeletal filaments¹ and flagellar filaments of bacteria², rely on the self-assembly of smaller components. Similarly, synthetic small molecules have shown to self-assemble in water to form structures ranging from the nanometer scale to micrometer scale,³ with hydrogelators⁴ being one example. Controlling the self-assembly of hydrogels using external stimuli has been challenging⁵ but can be achieved by introducing the appropriate responsive units within the molecular components of these systems.

Hydrogel research⁴ has evolved from static materials to dynamic smart materials. Controlling the mechanical, physical and chemical properties of hydrogels with external stimuli is important for both medical and industrial uses such as controlled drug delivery,⁶ sensing,⁷ robotics⁸ and 3D cell cultures.⁹ Light has a clear advantage due to its ability to operate in a highly precise manner without contaminating samples.¹⁰ Hydrogels have been made light responsive by the inclusion of a light responsive photoswitchable unit in the gelator molecule.^{10c,10d} All previous examples have relied on the inclusion of peptides or other additional groups to enable hydrogel formation. Peptide^{11,10c,10d} or polymer¹² hydrogels have been rendered photoresponsive by introducing molecular photoswitches such as diarylethene,¹³ spiropyran,^{11,14a,10d,14b} azobenzene,^{15a-1,10e,15m,15n} stilbene,¹⁶ *ortho*-fluoroazobenzenes,¹⁷ and arylazopyrazoles.^{18,12c}

Arylazopyrazoles (AAP) are a recently introduced class of azoheteroarene photoswitches. Azoheteroarenes⁵³ are related to azobenzenes but differ as one of the phenyl rings of conventional azobenzene is replaced with heteroarene ring. The Fuchter group has extensively studied these compounds showing almost complete photoisomerization in both directions with the thermal half-life of the metastable *Z*-isomer being tunable from hours to 10 days.¹⁹ Ravoo and co-workers²⁰ have used photoswitches to form light responsive gels where a central linker is connected to three photoswitching groups (MW=1193.50 g/mol). Tetrapeptides gelators (Fmoc-RGDS) (MW=1193.50 g/mol). Tetrapeptides gelators (Fmoc-RGDS)

were combined with an arylazopyrazole photoswitching unit attached via a linker chain (Fmoc-RGDS-AAP).²⁰

Most gelators, including all photoswitchable gelators, reported in literature have a MW > 300 g/mol. The bulk of light-responsive gelators contain long alkyl chains, peptides, or polymers and hence the photoswitchable unit plays a secondary role in the self-assembly of these systems. Herein we introduce the first gelators with a molecular weight below 300 (MW= 258.11 g/mol) that form stable hydrogels at physiological pH and respond to light in a bidirectional way (Figure 1).

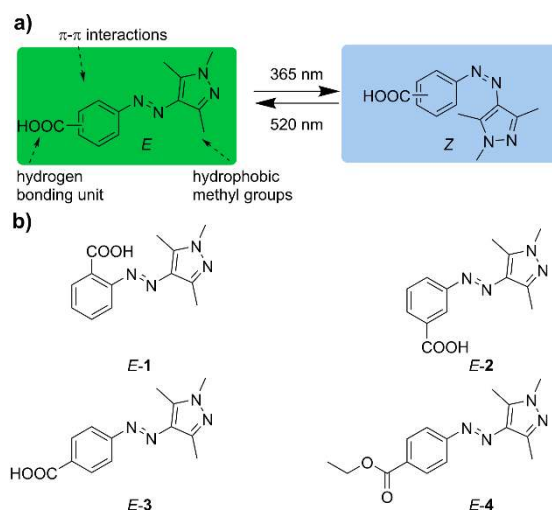


Figure 1. a) Design of low molecular weight photoswitchable gelators. b) Photoswitching compounds **1-4** (in their *E*-form) reported in this work. Compounds **2-3** (MW 258.11 g/mol) form gel in water at 1.0% (w/v), while **1** and control compound **4** do not form gels.

The photoswitches **2** and **3** form hydrogels as a result of intermolecular hydrogen bonding and hydrophobic effects, and represent the minimal non-covalent interactions usually re-

quired to trigger gelation. Arylazopyrazole photoswitches **1–3** (Figure 1) are isomers that differ only in the substitution of the carboxylic acid group on the aromatic ring. The carboxylic acid group can act as a hydrogen bond donor and acceptor, and the pyrazole ring and the diazo nitrogens can act as hydrogen bond acceptors to aid the gelation process. The arylazopyrazole photoswitch **4** bears an ester group at the *para* position and is used as a control compound not capable of intermolecular hydrogen bonding and hence does not form a gel.

Synthesis of photoswitches 1-4

Compounds **1–4** were synthesized using modified literature procedures of related compounds.^{19b} The *ortho*-, *meta*- or *para*-aminobenzoic acid and ethylaminobenzoate were reacted with hydrochloric acid and sodium nitrite to form the diazonium salt, which was reacted with acetylacetone to obtain pentane-2,4-diones (**S1–S4**) intermediates (see full characterization in SI-2, SI-12, SI-13, analytical methods described in SI-3). The intermediates (**S1–S4**) were refluxed for 3 h with *N*-methylamine and then concentrated under reduced pressure to obtain **1–4** as yellow solids in quantitative yield.

The photoswitching behavior of **1–4** was evaluated by UV-vis absorption (SI-4) and NMR spectroscopy (SI-12). Photoswitching using UV-vis absorption was recorded in a range of solvents (DMSO, DCM, methanol, THF, ethyl acetate, chloroform, toluene and acetonitrile) and the spectra in water are shown in Figure 2a. No significant solvatochromism was observed between the eight solvents that were studied (Table S2-S5). The samples were irradiated with 365 nm and 520 nm LED light sources for ~2 min to generate photostationary states (PSS) enriched in the *Z*- or *E*-isomer, labelled PSS_Z and PSS_E respectively. The data is in agreement with that observed for related arylazopyrazole compounds.^{19b}

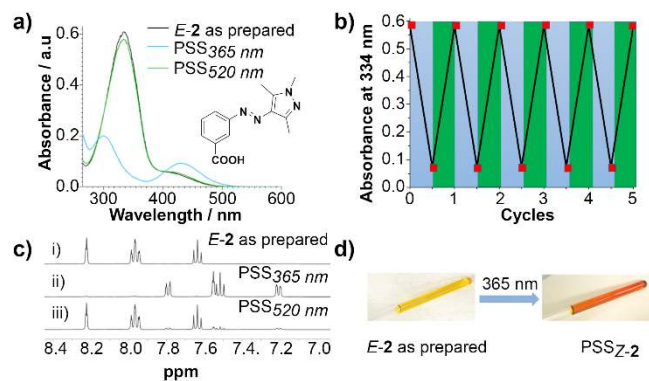


Figure 2. Photoswitching of **2** monitored by a) UV-vis absorption spectra in water of *E*-**2** as prepared (black line) and at photostationary states upon irradiation with 365 nm (blue line) and 520 nm (green line) light. b) Reversible switching of absorption in water monitored at 334 nm upon alternating irradiation with UV (365 nm, indicated with blue) and green (520 nm) light. c) ¹H NMR (400 MHz, DMSO-*d*₆) of i) as prepared *E*-**2**, ii) after irradiation with UV (365 nm) or iii) green (520 nm) light. d) NMR tube of *E*-**2** in DMSO-*d*₆ as prepared and PSS_Z obtained after irradiation with 365 nm light. See Figure SI-4, SI-12 for similar data on **1**, **3** and **4**.

The PSS compositions were quantified by ¹H NMR spectroscopy. The ¹H NMR spectra in DMSO-*d*₆ of samples equilibrated in the dark showed a single isomer in each case, the expected thermodynamically stable *E*-isomer (see SI-12.9, SI-12.16, SI-12.23 and SI-12.27). The samples were irradiated

with 365 nm light for 60 min and ¹H NMR spectra were recorded to obtain the PSS distribution (PSS_Z ≈ 90% *Z* for each of **1–4**, see SI-12.11, SI-12.18, SI-12.25, SI-12.29). Each sample was then irradiated with 520 nm light to produce a new photostationary state (PSS_E ≈ 92% *E*; Figure 2c). The PSS_Z is thermally stable at 25 °C in water over the time scale relevant to all the studies in this work with an apparent half-life measured by UV-vis absorption of 29-34 h for compound **1–4** (Figures S7, S12, S17, S22). All the compounds showed excellent photoswitching behavior in water and DMSO-*d*₆.

Solid state interactions

Crystals suitable for single crystal X-ray diffraction were grown of **1–4** from saturated solutions in DMF/diethyl ether, DMSO and ethanol (SI-6 for details). The structure of **1** showed an intramolecular hydrogen bond between the carboxylic acid group and the adjacent diazo nitrogen (O···N = 2.595(7) Å). Compound **2** is slightly twisted, with an angle of 20.1° between the least-squares planes of the phenyl- and the pyrazole rings. By comparison compound **3** is almost completely flat, with the same angle between the two rings being just 5.39°. The structures of both **2** and **3** show intermolecular hydrogen bonds between the carboxylic acid group and the free pyrazole nitrogen of an adjacent molecule, with short and similar N···O distances (2.712(4) and 2.689(2) Å, respectively). In both **2** and **3** the O-H···N angles is 160°, suggesting the hydrogen bonding interactions in these structures are essentially identical (Figure 3a, c, Table 1). In each case the hydrogen bonds result in 1D chains that are self-assembled by π-π interactions (centroid-to-plane distances of 3.34 Å and 3.30 Å for **2** and **3** respectively, see Figure 3b, d and Table 1). Details for the structures of **1** and **4** are given in SI-6.

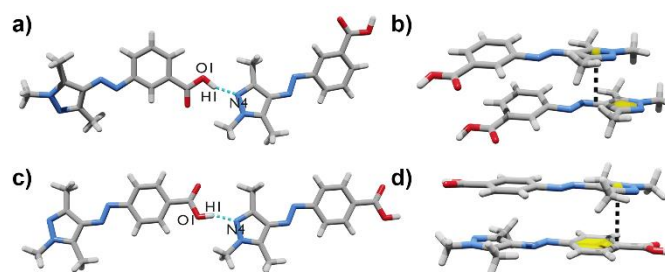


Figure 3. Single crystal X-ray structures of a-b) **2** and c-d) **3**. The *ortho* derivative **1** has an intramolecular hydrogen bond and does not form extended chains (SI-6.5). Both the *meta*-**2** and *para*-derivatives **3** form 1D hydrogen bonded chains as shown. Centroid-to-plane distances are shown with black dotted lines.

Table 1. Comparison of the key parameters of hydrogen bonding of isomers **1–3**, obtained from the single crystal X-ray diffraction data.

	1	2	3
Inter/Intra	Intra-	Inter-	Inter-
O-H / Å	0.840	0.98(4)	0.94(2)
H···N / Å	1.822	1.774	1.793
O···N / Å	2.595(7)	2.712(4)	2.689(2)
O-H···N / °	152.3	160(4)	160(2)

Hirshfeld surface analysis²¹ is a powerful tool for visualizing short and long contacts within crystal structures. The so-called “fingerprint” plots of **2–3** (SI-7) are superficially very similar, highlighting the importance of the two intermolecular shorts contacts show in Figures 3a and 3c. However, the Hirshfeld fingerprint of **3** highlights a significant pairwise intermolecular H···O interaction between the carbonyl oxygen and an aromatic *meta*-hydrogen on a neighboring molecule. This suggests why gelator **3** packs in an antiparallel fashion in the single crystal structure, in contrast to gelator **2**. Previous studies have shown similar pair-wise interaction drive the formation of antiparallel stacked aromatic molecules.²² No significant intermolecular short contacts were observed in the Hirshfeld fingerprint plot of **1** (Figure S70) due to the intramolecular hydrogen bond between the carboxylic acid and the diazo nitrogen.

Hydrogel formation

Gelation was investigated using the pH switch method with glucono- δ -lactone (g δ L).²³ All the starting materials were in the pure *E*-form and these experiments were carried out in the absence of light. Compounds **2** and **3** were dissolved at pH 11, followed by the addition of g δ L. After standing at room temperature overnight, hydrogels were formed as determined by the inverted vial test (see SI-9). The minimum gelation concentration for both gelators was determined to be 1.0% (w/v), however, to ensure better consistency in gel properties, all subsequent studies were carried out at 1.2% (w/v) concentration of **2** and **3**. The kinetics of gelation of compounds **2** and **3** was monitored by ¹H NMR spectroscopy (see SI-11). The disappearance of the ¹H NMR signals of the monomeric gelator over ~80 min for **2** or **3** was consistent with aggregation. Compound **1**, which does not form any intermolecular hydrogen bonds in the solid state, does not form a gel in water (SI-8.1). Compound **4**, which also does not display any solid-state intermolecular hydrogen bonding interactions (SI-6.8), does not form a gel. The pK_a values of compound **1–3** are practically indistinguishable (determined by pH titrations, see SI-10) with pK_a values of 6.4, 6.4 and 6.7 for **1**, **2** and **3**, respectively.

The viscoelastic properties of gels formed by **2** and **3** were studied using a rheometer (Table 2, SI-8). In the dark, the gel formed by **2** was stiffer (elastic modulus G' ~10 kPa) than that of **3** (G' ~1.2 kPa); both were prepared by the pH switch method using g δ L (1.2% (w/v); dissolved in 0.1 M sodium hydroxide, followed by the addition of g δ L, see SI-8). The frequency sweeps (SI-8.2) showed that the storage modulus is independent of the applied frequency. The strain sweep (SI-8.2) for both **2** and **3** showed that both hydrogels possess malleable-like characteristics, with the linear viscoelastic region lasting until about 10% strain for both gelators. Further increases in strain result in gel collapse at about 60% and 80% strain for **2** and **3**, respectively.

We postulate here that the approximately one order of magnitude ($\times 10$) difference in the elastic modulus of gels formed by **2** and **3** in the dark can be explained with reference to the observed parallel versus anti-parallel packing in the single crystal structures of **2** and **3**, respectively. Powder X-ray diffraction of xerogels formed from **2** and **3** yielded patterns similar to those predicted from the single crystal X-ray structures (SI-6.11, SI-6.12). The single crystal X-ray structure data and Hirshfeld surface analysis in turn indicate that pairwise intermolecular H···O interactions drive the slightly less compact packing of **3** in an antiparallel orientation.

Table 2. Key properties of gels formed by **2** and **3** in the dark.

Gelator	mgc ^a	G' ^b	LVR ^c	Fiber diameter ^d
2	1%	10 kPa	10%	12.2±0.5 nm
3	1%	1.2 kPa	9.5%	13.4 ±0.6 nm

^aMinimum gelation concentration (mgc, w/v). ^bElastic modulus (G') at strain = 1%, frequency = 1 Hz and 1.2% (w/v) concentration. ^cElasticity (strain) or linear viscoelastic region (LVR) at frequency = 1 Hz. ^dHistograms of the fiber heights obtained from AFM microscopy and measured for **2** and **3** before irradiation with light. The histograms represent 25 measurements in four different areas for each sample (bin size = 100).

Gel→Sol Photoswitching

Immediately after the addition of g δ L, 1.2% (w/v) solutions of **2** and **3** were cast onto a rheometer fitted with a glass plate and allowed to form hydrogel in dark over ~85 min. Dynamic *in situ* time sweep rheological measurements were conducted on **2** and **3** upon exposure to alternating 365 nm and 520 nm light. As the illuminated area is significantly smaller than the diameter (25 mm) of the rheometer measurement plate, the ~500 μ L gap was only filled with ca 20% (110 μ L) of the gel solution. The absolute elastic (G') and loss (G'') module obtained are therefore not directly comparable to the rheological data obtained under standard conditions in the dark discussed above (see SI-3.8 for further information).

Upon the first irradiation with 365 nm UV light, G' for **2** decreased from about 200 Pa to about 50 Pa over a period of 1 h (Figure 8.4). Subsequent irradiation of **2** with 520 nm green light restored the initial elasticity of **2** (see Figure 4a). Both green and UV light-irradiated states retained stable G' values for at least 15 min after the light was switched off. Multiple photoswitching cycles were performed on **2** by alternating between UV and green light irradiation and minimal fatigue was observed.

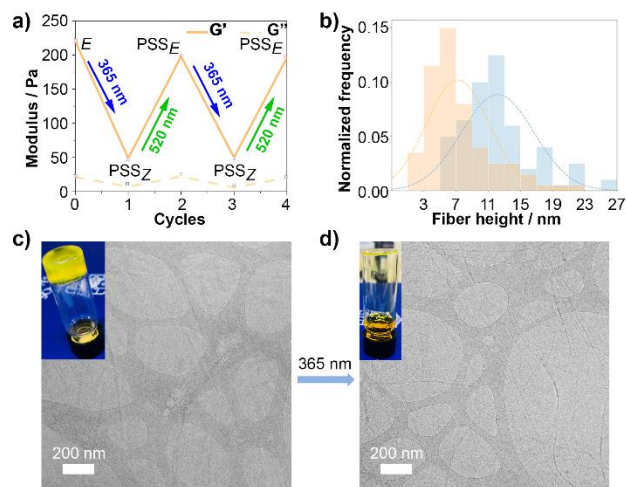


Figure 4. Photoswitching of **2** by alternating irradiation with 365 nm and 520 nm light. Changes in a) rheology with *in situ* irradiation and b) Size of fibers obtained from AFM microscopy before (blue) and after irradiation (orange) after drop casting dilute (0.0006%, w/v) solution of **2** on to a mica surface. Morphology of fibers obtained from cryo-TEM microscopy of gels formed from **2** in water (1.2% (w/v)) c) before light and d) after irradiation with 365 nm light, scale bar is 200 nm. For the analogous data for compound **3**, see SI-5.3.6 and SI-8.4.

While a gel→sol transition appears to have occurred using a conventional inversion test on **2** (Figure 4) and **3** (Figure S76), the $\tan \delta$; the G''/G' ratio, remains well below 1—the conventional rheological definition of a gel—during the entire course of the light-switching experiments (Figure S75). Strong arguments have been made in the literature that a $\tan \delta < 1$ is a more reliable indicator of gelation than the inversion test, albeit that argument is usually in the situation whereby the materials appears to pass the inversion test while $\tan \delta > 1$.^{24,4b} Here, the opposite situation was observed, but further work is required to explain why irradiation of **2** and **3** leads to an apparent gel transition despite the fact that $\tan \delta < 1$.

Microscopy studies of gel morphology

Atomic force microscopy (AFM) measurements were conducted starting with 1.2% (w/v) solutions of **1–4** that were then rapidly diluted (to 0.0006% w/v) and drop casted on a mica substrate to investigate the size and topography of any self-assembled fibers formed under such conditions (SI-5.1). We have previously shown that AFM measurements on fibers formed from dilute drop-cast solutions yield comparable information to more experimentally challenging cryogenic transmission electron microscopy (cryo-TEM) and *in situ* small angle neutron scattering (SANS) methods.²⁵ No fibers were found for compounds **1** and **4**, which is in line with the observation that they did not self-assemble into gels. Compound **2** formed fibers with a diameter of 12.2 ± 0.5 nm (in the dark) and when irradiated with 365 nm light the diameter of the fibers reduced to 7.2 ± 0.4 nm, as measured by AFM (Figure 4b). Similarly, compound **3** formed fibers with a diameter of 13.4 ± 0.5 nm (in the dark) and 4.7 ± 0.3 nm (after irradiation with 365 nm). Scanning electron microscopy (SEM) was used to image the structures formed from **1–4** when more concentrated 1.2% (w/v) solutions (in the dark) were drop-cast onto silica (SI-5.2). The desiccated gels from **2** and **3** showed fiber-like surfaces, while the precipitates from compounds **1** and **4** were found to have crystal-like surfaces (SI-5.2.1, SI-5.2.4). If the solutions were irradiated with 365 nm light prior to being drop-cast, the morphology observed for **2** and **3** changed from fibrous to crystalline, consistent with disassembly (see SI-5.2.2, SI-5.2.3).

The combination of TEM and cryo-TEM techniques were applied to investigate in more detail the structural changes in the self-assembly of **2** and **3** before and after illumination with 365 nm light (SI-5.3). When comparing the cryo-TEM micrographs of the fibers from gels formed by **2** at 1.2% (w/v) in water before (Figure 4c) and after irradiation with 365 nm light (Figure 4d), a clear “thinning” of the fibers is observed, as the 29 ± 7 nm wide sheets narrow down to 13 ± 2 nm. These results are qualitatively consistent with the AFM analysis above, given that the latter are presumably dried out. This data is supported by conventional TEM analysis on 1.2% (w/v) solutions of **2** (SI-5.3.2). Compounds **1** and **4** did not show any fiber-like aggregates under these conditions. TEM analysis of **3** was less conclusive; conventional TEM did not show fibers but rather spherical, perhaps micellar-like objects prior to illumination that disintegrated upon illumination with 365 nm light (SI-5.3.3). The cryo-TEM micrographs of **3** before illumination showed very wide (≈ 400 nm) thin sheet like structures that do also become thinner (≈ 200 nm) after irradiation with 365 nm light (SI-5.3.6).

Photocontrolled dye release from gels

Hydrogels formed with compounds **2** or **3** can be used for controlled cargo release.²⁰ The fluorescent dye Rhodamine B was encapsulated during the hydrogel formation. The hydrogels were formed at the bottom of a quartz cuvette and allowed to gel overnight (see SI-3.15 for details). Water was carefully layered over the gels and the dye release was monitored by fluorescence emission spectroscopy (Figure 5). In the dark, gels of **2** and **3** released 15–25% of the dye load over 4 h (most of this due to the initial burst release of Rhodamine B). Upon continuous irradiation with 365 nm light, the gels readily released the dye, reaching approximately 80–90% dye release over 4 h.

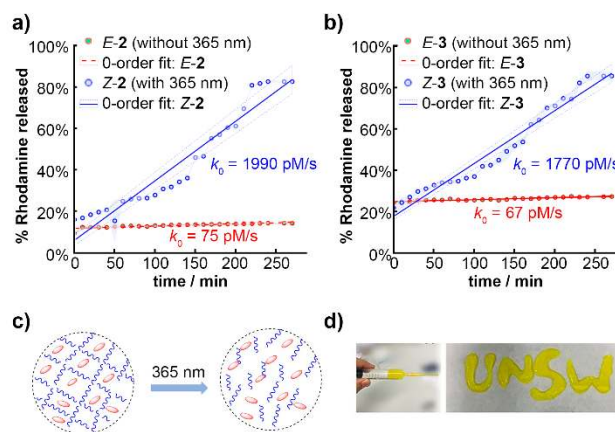


Figure 5. a) Release of Rhodamine B dye from hydrogels formed by a) **2** or b) **3** prepared by dissolving 1.2% (w/v) of **2** or **3** and 0.01% (w/v) of the dye in a solution of sodium hydroxide (98 mmol/L), followed by the addition of 0.16% (w/v) g δ L. The samples were continually irradiated with UV light (365 nm) from above for the duration of the experiment. Release was monitored by fluorescence emission spectroscopy ($\lambda_{\text{ex}} = 540$ nm, $\lambda_{\text{em}} = 576$ nm), relative to complete release of the dye following heating of the sample. Solid lines: Fitted release according to a zero-order kinetic model based on the zero-order rate constant (k_0) shown. Dotted lines indicate ± 1 standard deviations (std) of the fitted zero-order kinetics. Circles: Averages of $n = 3$ repeat measurements of Rhodamine B releases. Shaded bands around the circles: ± 1 std of the $n = 3$ repeat measurements. c) Cartoon representation of dye release from hydrogels upon irradiation with 365 nm light. d) Injectability: a gel formed by **3** can be pushed through a syringe to form a pattern.

The release of Rhodamine B from the hydrogel formed by **2** and **3** follow zero-order kinetics (k_0), which is usually considered desirable in second generation drug delivery systems.²⁶ More importantly, the rate of Rhodamine B release from gels formed by *E-2* and *E-3* increased more than 20-fold upon irradiation with a 365 nm light source, or from $k_0 = 75 \pm 11$ pM/s for *E-2* to 1990 ± 110 pM/s for *Z-2* and $k_0 = 67 \pm 8$ pM/s for *E-3* to 1770 ± 80 pM/s for *Z-3*. This can be readily explained by the fact that the 365 nm excitation triggers a gel→sol transition for these hydrogels over a period of ≈ 200 min (Figure 5). Hydrogels formed by **2** and **3** also show good thixotropic properties at 37 °C (SI-8.3), indicating that they can be readily injected with syringe (Figure 5d) – an advantageous property for application of these gels in light-controlled release systems.

Conclusion

Four photoswitchable arylazopyrazoles derivatives were synthesized, of which two form hydrogels at 1.2% w/v. The *m*- and *p*-arylazopyrazoles **2** and **3**, respectively, are the lowest molecular weight photoswitchable hydrogelators reported to date. Using a 365 nm light source, photoswitching of gels formed from the as synthesized *E*-**2** and *E*-**3**, to the corresponding photostationary state predominantly forms (>90%) *Z*-**2** and *Z*-**3**. This results in nearly an order of magnitude reduction in the elastic (G') and loss (G'') modulus. Detailed microscopy studies, including cryo-TEM imaging, suggests that this transition is associated with significant thinning of the gel fibers. The light induced gel→sol transition for gels formed from **2** and **3** can be used to accelerate more than 20-fold the release of an encapsulated dye in these gels, suggesting that these low-molecular hydrogelator could be used for light-controlled release systems in water at physiologically relevant pH. The insight that the structural simple and photoswitchable hydrogelators **2** and **3** have given here into the mechanism of hydrogel assembly and disassembly, is likely to aid the design of other related light-controlled materials and systems in the future.

ASSOCIATED CONTENT

Experimental procedures and characterization data are included in the Supporting Information. This material is available free of charge via the Internet at <http://pubs.acs.org>. CCDC 1977099–1977105, 2006840 contains the supplementary crystallographic data for this paper. These data can be obtained free of charge from The Cambridge Crystallographic Data Centre via www.ccdc.cam.ac.uk/structures.

AUTHOR INFORMATION

Corresponding Authors

Jonathon E. Beves – School of Chemistry, UNSW Sydney, NSW 2052, Australia; orcid.org/0000-0002-5997-6580; E-mail: j.beves@unsw.edu.au

Pall Thordarson – School of Chemistry, UNSW Sydney, NSW 2052, Australia; Australian Centre for Nanomedicine and the ARC Centre of Excellence in Convergent Bio-Nano Science and Technology, UNSW Sydney, NSW 2052, Australia; orcid.org/0000-0002-1200-8814; E-mail: p.thordarson@unsw.edu.au

Authors

Fayaz Ali Larik – School of Chemistry, UNSW Sydney, NSW 2052, Australia; Australian Centre for Nanomedicine and the ARC Centre of Excellence in Convergent Bio-Nano Science and Technology, UNSW Sydney, NSW 2052, Australia. orcid.org/0000-0002-8491-5229

Lucy L. Fillbrook – School of Chemistry, UNSW Sydney, NSW 2052, Australia; orcid.org/0000-0001-9443-0834

Sandra S. Nurtila – School of Chemistry, UNSW Sydney, NSW 2052, Australia; Australian Centre for Nanomedicine and the ARC Centre of Excellence in Convergent Bio-Nano Science and Technology, UNSW Sydney, NSW 2052, Australia; orcid.org/0000-0003-2565-2673

Adam D. Martin – Dementia Research Centre, Department of Biomedical Science, Faculty of Medicine and Health Sciences, Macquarie University, Sydney, NSW 2109, Australia.

Rhiannon P. Kuchel – Mark Wainwright Analytical Centre, Electron Microscope Unit, UNSW Sydney, NSW 2052, Australia.

Karrar Al Taief – School of Chemistry, UNSW Sydney, NSW 2052, Australia; Australian Centre for Nanomedicine and the ARC Centre of Excellence in Convergent Bio-Nano Science and Technology, UNSW Sydney, NSW 2052, Australia.

Mohan Bhadbhade – Mark Wainwright Analytical Centre, Solid State & Elemental Analysis Unit, UNSW Sydney, NSW 2052, Australia; orcid.org/0000-0003-3693-9063

Complete contact information is available at:
<https://pubs.acs.org/10.1021/jacs.XXXXXX>

ACKNOWLEDGMENT

This work was supported by the Australian Research Council (FT170100094 to JEB and CE140100036 & DP190101892 to PT) and UNSW Sydney through a PhD TFS award to FAL. We acknowledge access and support from the facilities of the Mark Wainwright Analytical Centre at UNSW Sydney. We like to thank Dr Shyamal Prasad at UNSW Sydney for LED power measurements and Mr. Ashish Kumar at Anton Paar Australia for advice on photorheological measurements.

REFERENCES

- (1) Yonekura, K.; Maki, S.; Morgan, D. G.; DeRosier, D. J.; Vondervis, F.; Imada, K.; Namba, K. The bacterial flagellar cap as the rotary promoter of flagellin self-assembly. *Science* **2000**, *290*, 2148-2152.
- (2) Cohen, E. J.; Ferreira, J. L.; Ladinsky, M. S.; Beeby, M.; Hughes, K. T. Nanoscale-length control of the flagellar driveshaft requires hitting the tethered outer membrane. *Science* **2017**, *356*, 197-200.
- (3) Dattler, D.; Fuks, G.; Heiser, J.; Moulin, E.; Perrot, A.; Yao, X.; Giuseppone, N. Design of collective motions from synthetic molecular switches, rotors, and motors. *Chem. Rev.* **2019**, *120*, 310-433.
- (4) (a) Du, X.; Zhou, J.; Shi, J.; Xu, B. Supramolecular hydrogelators and hydrogels: from soft matter to molecular biomaterials. *Chem. Rev.* **2015**, *115*, 13165-13307; (b) Draper, E. R.; Adams, D. J. Low-molecular-weight gels: the state of the art. *Chem.* **2017**, *3*, 390-410; (c) Mondal, S.; Das, S.; Nandi, A. K. A review on recent advances in polymer and peptide hydrogels. *Soft. Matter.* **2020**, *16*, 1404-1454.
- (5) (a) Segarra-Maset, M. D.; Nebot, V. J.; Miravet, J. F.; Escuder, B. Control of molecular gelation by chemical stimuli. *Chem. Soc. Rev.* **2013**, *42*, 7086-7098; (b) Hoque, J.; Sangaj, N.; Varghese, S. Stimuli-Responsive Supramolecular Hydrogels and Their Applications in Regenerative Medicine. *Macromol. Biosci.* **2019**, *19*, 1800259.
- (6) Hu, J.; Liu, S. Engineering responsive polymer building blocks with host-guest molecular recognition for functional applications. *Acc. Chem. Res.* **2014**, *47*, 2084-2095.
- (7) Ikeda, M.; Tanida, T.; Yoshii, T.; Kurotani, K.; Onogi, S.; Urayama, K.; Hamachi, I. Installing logic-gate responses to a variety of biological substances in supramolecular hydrogel-enzyme hybrids. *Nat. Chem.* **2014**, *6*, 511-518.
- (8) Wei, S.; Lu, W.; Le, X.; Ma, C.; Lin, H.; Wu, B.; Zhang, J.; Theato, P.; Chen, T. Bioinspired Synergistic Fluorescence-Color-Switchable Polymeric Hydrogel Actuators. *Angew. Chem. Int. Ed.* **2019**, *58*, 16243-16251.
- (9) Dou, X. Q.; Feng, C. L. Amino acids and peptide-based supramolecular hydrogels for three-dimensional cell culture. *Adv. Mat.* **2017**, *29*, 1604062.
- (10) (a) Balzani, V.; Credi, A.; Venturi, M. Light powered molecular machines. *Chem. Soc. Rev.* **2009**, *38*, 1542-1550; (b) Habault, D.; Zhang, H.; Zhao, Y. Light-triggered self-healing and shape-memory polymers. *Chem. Soc. Rev.* **2013**, *42*, 7244-7256; (c) Draper, E. R.; Adams, D. J. Photoresponsive gelators. *Chem. Commun.* **2016**, *52*, 8196-8206; (d) Li, X.; Fei, J.; Xu, Y.; Li, D.; Yuan, T.; Li, G.; Wang, C.; Li, J. A photoinduced reversible phase transition in a dipeptide supramolecular assembly. *Angew. Chem. Int. Ed.* **2018**, *57*, 1903-1907; (e) Pianowski, Z. L. Recent Implementations of Molecular Photoswitches into Smart Materials and Biological Systems. *Chem.–Eur. J.* **2019**, *25*, 5128-5144.
- (11) Qiu, Z.; Yu, H.; Li, J.; Wang, Y.; Zhang, Y. Spiropyran-linked dipeptide forms supramolecular hydrogel with dual responses to light and to ligand-receptor interaction. *Chem. Commun.* **2009**, 3342-3344.

- (12) (a) Zhao, Y.-L.; Stoddart, J. F. Azobenzene-based light-responsive hydrogel system. *Langmuir* **2009**, *25*, 8442-8446; (b) Tamesue, S.; Takashima, Y.; Yamaguchi, H.; Shinkai, S.; Harada, A. Photoswitchable supramolecular hydrogels formed by cyclodextrins and azobenzene polymers. *Angew. Chem. Int. Ed.* **2010**, *49*, 7461-7464; (c) Davidson-Rozenfeld, G.; Stricker, L.; Simke, J.; Fadeev, M.; Vázquez-González, M.; Ravoo, B. J.; Willner, I. Light-responsive arylazopyrazole-based hydrogels: their applications as shape-memory materials, self-healing matrices and controlled drug release systems. *Polymer Chem.* **2019**, *10*, 4106-4115; (d) Tabet, A.; Forster, R. A.; Parkins, C. C.; Wu, G.; Scherman, O. A. Modulating stiffness with photo-switchable supramolecular hydrogels. *Polym. Chem.* **2019**, *10*, 467-472.
- (13) van Herpt, J. T.; Stuart, M. C.; Browne, W. R.; Feringa, B. L. A dithienylethene-based rewritable hydrogelator. *Chem.-Eur. J.* **2014**, *20*, 3077-3083.
- (14) (a) Stumpel, J. E.; Ziolkowski, B.; Florea, L.; Diamond, D.; Broer, D. J.; Schenning, A. P. Photoswitchable ratchet surface topographies based on self-protonating spiropyran-NIPAAM hydrogels. *ACS Appl. Mater. Inter.* **2014**, *6*, 7268-7274; (b) Li, C.; Iscen, A.; Palmer, L. C.; Schatz, G. C.; Stupp, S. I. Light-Driven Expansion of Spiropyran Hydrogels. *J. Am. Chem. Soc.* **2020**, *142*, 8447-8453.
- (15) (a) Peng, K.; Tomatsu, I.; Kros, A. Light controlled protein release from a supramolecular hydrogel. *Chem. Commun.* **2010**, *46*, 4094-4096; (b) Beharry, A. A.; Woolley, G. A. Azobenzene photoswitches for biomolecules. *Chem. Soc. Rev.* **2011**, *40*, 4422-4437; (c) Huang, Y.; Qiu, Z.; Xu, Y.; Shi, J.; Lin, H.; Zhang, Y. Supramolecular hydrogels based on short peptides linked with conformational switch. *Org. Bio. Chem.* **2011**, *9*, 2149-2155; (d) Doran, T. M.; Ryan, D. M.; Nilsson, B. L. Reversible photocontrol of self-assembled peptide hydrogel viscoelasticity. *Polym. Chem.* **2014**, *5*, 241-248; (e) Rosales, A. M.; Mabry, K. M.; Nehls, E. M.; Anseth, K. S. Photoresponsive elastic properties of azobenzene-containing poly (ethylene-glycol)-based hydrogels. *Biomacromol.* **2015**, *16*, 798-806; (f) Pianowski, Z. L.; Karcher, J.; Schneider, K. Photoresponsive self-healing supramolecular hydrogels for light-induced release of DNA and doxorubicin. *Chem. Commun.* **2016**, *52*, 3143-3146; (g) Xie, F.; Qin, L.; Liu, M. A dual thermal and photo-switchable shrinking–swelling supramolecular peptide dendron gel. *Chem. Commun.* **2016**, *52*, 930-933; (h) Lee, I.-N.; Dobre, O.; Richards, D.; Ballestrom, C.; Curran, J. M.; Hunt, J. A.; Richardson, S. M.; Swift, J.; Wong, L. S. Photoresponsive hydrogels with photoswitchable mechanical properties allow time-resolved analysis of cellular responses to matrix stiffening. *ACS Appl. Mater. Inter.* **2018**, *10*, 7765-7776; (i) Rosales, A. M.; Rodell, C. B.; Chen, M. H.; Morrow, M. G.; Anseth, K. S.; Burdick, J. A. Reversible control of network properties in azobenzene-containing hyaluronic acid-based hydrogels. *Bioconjugate Chem.* **2018**, *29*, 905-913; (j) Roth-Konforti, M. E.; Comune, M.; Halperin-Sternfeld, M.; Grigoriants, I.; Shabat, D.; Adler-Abramovich, L. UV Light-Responsive Peptide-Based Supramolecular Hydrogel for Controlled Drug Delivery. *Macromol. Rapid. Commun.* **2018**, *39*, 1800588; (k) Wang, C.; Hashimoto, K.; Tamate, R.; Kokubo, H.; Watanabe, M. Controlled Sol–Gel Transitions of a Thermoresponsive Polymer in a Photoswitchable Azobenzene Ionic Liquid as a Molecular Trigger. *Angew. Chem. Int. Ed.* **2018**, *57*, 227-230; (l) Li, L.; Scheiger, J. M.; Levkin, P. A. Design and applications of photoresponsive hydrogels. *Adv. Mater.* **2019**, *31*, 1807333; (m) de Luna, M. S.; Marturano, V.; Manganelli, M.; Santillo, C.; Ambrogio, V.; Filippone, G.; Cerruti, P. Light-responsive and self-healing behavior of azobenzene-based supramolecular hydrogels. *J. Colloid. Interf. Sci.* **2020**, *568*, 16-24; (n) Higashi, N.; Yoshikawa, R.; Koga, T. Photo-responsive azobenzene interactions promote hierarchical self-assembly of collagen triple-helical peptides to various higher-order structures. *RSC Adv.* **2020**, *10*, 15947-15954.
- (16) Tong, F.; Chen, S.; Li, Z.; Liu, M.; Al-Kaysi, R. O.; Mohideen, U.; Yin, Y.; Bardeen, C. J. Crystal-to-Gel Transformation Stimulated by a Solid-State E→Z Photoisomerization. *Angew. Chem. Int. Ed.* **2019**, *58*, 15429-15434.
- (17) (a) Accardo, J. V.; Kalow, J. A. Reversibly tuning hydrogel stiffness through photocontrolled dynamic covalent crosslinks. *Chem. Sci.* **2018**, *9*, 5987-5993; (b) Karcher, J.; Pianowski, Z. L. Photocontrol of Drug Release from Supramolecular Hydrogels with Green Light. *Chem.-Eur. J.* **2018**, *24*, 11605-11610; (c) Zhao, F.; Bonasera, A.; Nöchel, U.; Behl, M.; Bléger, D. Reversible Modulation of Elasticity in Fluoroazobenzene-Containing Hydrogels Using Green and Blue Light. *Macromol. Rapid. Commun.* **2018**, *39*, 1700527; (d) Tong, X.; Qiu, Y.; Zhao, X.; Xiong, B.; Liao, R.; Peng, H.; Liao, Y.; Xie, X. Visible light-triggered gel-to-sol transition in halogen-bond-based supramolecules. *Soft. Matter.* **2019**, *15*, 6411-6417.
- (18) Chu, C. W.; Stricker, L.; Kirse, T. M.; Hayduk, M.; Ravoo, B. J. Light-Responsive Arylazopyrazole Gelators: From Organic to Aqueous Media and from Supramolecular to Dynamic Covalent Chemistry. *Chem.-Eur. J.* **2019**, *25*, 6131-6140.
- (19) (a) Weston, C. E.; Richardson, R. D.; Haycock, P. R.; White, A. J. P.; Fuchter, M. J. Arylazopyrazoles: azoheteroarene photoswitches offering quantitative isomerization and long thermal half-lives. *J. Am. Chem. Soc.* **2014**, *136*, 11878-11881; (b) Calbo, J.; Weston, C. E.; White, A. J. P.; Rzepa, H. S.; Contreras-García, J.; Fuchter, M. J. Tuning azoheteroarene photoswitch performance through heteroaryl design. *J. Am. Chem. Soc.* **2017**, *139*, 1261-1274; (c) Crespi, S.; Simeth, N. A.; König, B. Heteroaryl azo dyes as molecular photoswitches. *Nat. Rev. Chem.* **2019**, *3*, 133-146; (d) Gibson, R. S.; Calbo, J.; Fuchter, M. J. Chemical Z–E Isomer Switching of Arylazopyrazoles Using Acid. *Chem. Photo. Chem.* **2019**, *3*, 372-377; (e) Gerkmann, M. A.; Gibson, R. S.; Calbo, J.; Shi, Y.; Fuchter, M. J.; Han, G. G. Arylazopyrazoles for Long-Term Thermal Energy Storage and Optically Triggered Heat Release below 0° C. *J. Am. Chem. Soc.* **2020**, *142*, 8688-8695.
- (20) Chu, C.-W.; Ravoo, B. J. Hierarchical supramolecular hydrogels: self-assembly by peptides and photo-controlled release via host–guest interaction. *Chem. Commun.* **2017**, *53*, 12450-12453.
- (21) Spackman, M. A.; Jayatilaka, D. Hirshfeld surface analysis. *CrystEngComm* **2009**, *11*, 19-32.
- (22) Martin, A. D.; Britton, J.; Easun, T. L.; Blake, A. J.; Lewis, W.; Schröder, M. Hirshfeld surface investigation of structure-directing interactions within dipicolinic acid derivatives. *Cryst. Grow. Des.* **2015**, *15*, 1697-1706.
- (23) Adams, D. J.; Butler, M. F.; Frith, W. J.; Kirkland, M.; Mullen, L.; Sanderson, P. A new method for maintaining homogeneity during liquid–hydrogel transitions using low molecular weight hydrogelators. *Soft Matter* **2009**, *5*, 1856-1862.
- (24) Raghavan, S. R.; Cipriano, B. H. Gel Formation: Phase Diagrams Using Tabletop Rheology and Calorimetry. In *Molecular gels*; Weiss, R., G., Terech, P., Eds.; Springer: Dordrecht, 2006; pp. 241-252.
- (25) Martin, A. D.; Wojciechowski, J. P.; Robinson, A. B.; Heu, C.; Garvey, C. J.; Ratcliffe, J.; Waddington, L. J.; Gardiner, J.; Thordarson, P. Controlling self-assembly of diphenylalanine peptides at high pH using heterocyclic capping groups. *Sci. Rep.* **2017**, *7*, 43947.
- (26) Park, K. Controlled drug delivery systems: past forward and future back. *J. Controlled Release* **2014**, *190*, 3-8.

