

10-23-2019

## Upcycling Single-Use Polyethylene into High-Quality Liquid Products

Gokhan Celik

Robert M. Kennedy

Ryan A. Hackler

Magali Ferrandon

Akalanka Tennakoon

*See next page for additional authors*

Follow this and additional works at: [https://scholarcommons.sc.edu/eche\\_facpub](https://scholarcommons.sc.edu/eche_facpub)

 Part of the [Chemical Engineering Commons](#)

---

### Publication Info

Published in *ACS Central Science*, Volume 5, 2019, pages 1795-1803.

© 2019 American Chemical Society

This is an open access article published under an ACS AuthorChoice License, which permits copying and redistribution of the article or any adaptations for non-commercial purposes.

This Article is brought to you by the Chemical Engineering, Department of at Scholar Commons. It has been accepted for inclusion in Faculty Publications by an authorized administrator of Scholar Commons. For more information, please contact [digres@mailbox.sc.edu](mailto:digres@mailbox.sc.edu).

---

**Author(s)**

Gokhan Celik, Robert M. Kennedy, Ryan A. Hackler, Magali Ferrandon, Akalanka Tennakoon, Smita Patnaik, Anne M. LaPointe, Salai Ammal, Andreas Heyden, Frédéric A. Perras, Marek Pruski, Susannah L. Scott, Kenneth R. Poepelmeier, Aaron D. Sadow, and Massimiliano Delferro

# Upcycling Single-Use Polyethylene into High-Quality Liquid Products

Gokhan Celik,<sup>†</sup> Robert M. Kennedy,<sup>†</sup> Ryan A. Hackler,<sup>†</sup> Magali Ferrandon,<sup>†</sup> Akalanka Tennakoon,<sup>‡,§</sup> Smita Patnaik,<sup>‡,§</sup> Anne M. LaPointe,<sup>||</sup> Salai C. Ammal,<sup>⊥</sup> Andreas Heyden,<sup>⊥</sup> Frédéric A. Perras,<sup>‡</sup> Marek Pruski,<sup>‡,§</sup> Susannah L. Scott,<sup>#</sup> Kenneth R. Poeppelmeier,<sup>\*,○</sup> Aaron D. Sadow,<sup>\*,‡,§</sup> and Massimiliano Delferro<sup>\*,†</sup>

<sup>†</sup>Chemical Sciences and Engineering Division, Argonne National Laboratory, Lemont, Illinois 60439, United States

<sup>‡</sup>U.S. DOE Ames Laboratory, Ames, Iowa 50011, United States

<sup>§</sup>Department of Chemistry, Iowa State University, Ames, Iowa 50011, United States

<sup>||</sup>Department of Chemistry and Chemical Biology, Cornell University, Ithaca, New York 14853, United States


<sup>⊥</sup>Department of Chemical Engineering, University of South Carolina, Columbia, South Carolina 29208, United States

<sup>#</sup>Department of Chemical Engineering, University of California, Santa Barbara, California 93106, United States

<sup>○</sup>Department of Chemistry, Northwestern University, Evanston, Illinois 60208, United States

## Supporting Information

**ABSTRACT:** Our civilization relies on synthetic polymers for all aspects of modern life; yet, inefficient recycling and extremely slow environmental degradation of plastics are causing increasing concern about their widespread use. After a single use, many of these materials are currently treated as waste, underutilizing their inherent chemical and energy value. In this study, energy-rich polyethylene (PE) macromolecules are catalytically transformed into value-added products by hydrogenolysis using well-dispersed Pt nanoparticles (NPs) supported on SrTiO<sub>3</sub> perovskite nanocuboids by atomic layer deposition. Pt/SrTiO<sub>3</sub> completely converts PE ( $M_n = 8000$ – $158,000$  Da) or a single-use plastic bag ( $M_n = 31,000$  Da) into high-quality liquid products, such as lubricants and waxes, characterized by a narrow distribution of oligomeric chains, at 170 psi H<sub>2</sub> and 300 °C under solvent-free conditions for reaction durations up to 96 h. The binding of PE onto the catalyst surface contributes to the number averaged molecular weight ( $M_n$ ) and the narrow polydispersity ( $\mathcal{D}$ ) of the final liquid product. Solid-state nuclear magnetic resonance of <sup>13</sup>C-enriched PE adsorption studies and density functional theory computations suggest that PE adsorption is more favorable on Pt sites than that on the SrTiO<sub>3</sub> support. Smaller Pt NPs with higher concentrations of undercoordinated Pt sites over-hydrogenolyzed PE to undesired light hydrocarbons.

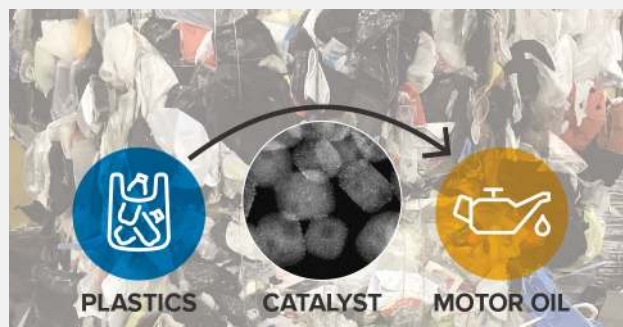

## INTRODUCTION

Polyolefins are ubiquitous in single-use and short-term applications because their starting materials are abundant and inexpensive. In addition, researchers have learned to vary the chemical structure of the polymer chains (such as branching, molecular weight, and dispersity) through catalysis, and in such alter their physical properties. The single-use nature of plastics is essential in sterile packaging for foods, strong-but-inexpensive materials for transportation and storage, and safe and disposable components in medical devices, leading to their manufacture in tremendous quantities. Three hundred and eighty million tons (380 Mt) of plastics are created worldwide each year, which corresponds to roughly 7% of crude oil and natural gas produced. Moreover, the plastic market is currently increasing, and some analysts predict quadrupled production by 2050 (~1100 to 1500 Mt per year).<sup>1–3</sup> The downside,

however, is the massive quantity of waste, pollution, and lost-value associated with single-use plastics. Over 75% of materials produced each year, 300 Mt, are discarded after a single use. Currently, most of this waste is either lost to landfills and the environment, or inefficiently incinerated in power plants to produce electricity, generating greenhouse gases (e.g., CO<sub>2</sub>) and toxic byproducts in the process. Glass and aluminum recycling are effective, whereas processing of plastic waste is limited by technical challenges, which include contamination from mixtures of polymers and additives as well as oxidative degradation during melt reprocessing. Thus, recycling provides lower-value materials with downgraded properties (down-cycling).<sup>1–3</sup> Polyolefin waste represents a vast and as-yet

Received: July 18, 2019

Published: October 23, 2019

untapped resource for the production of chemicals and new materials. Efficient technologies for extracting this value from discarded polymers would be equivalent to recovering about 3.5 billion barrels of oil (\$175B at \$50/barrel) each year and could create entirely new industries. Consequently, selective catalytic processes that transform abundant plastic waste into value-added products (upcycling) could provide both scientific and technical advances. Today, existing conversions of waste polymers include catalytic pyrolysis, tandem alkane metathesis/transfer hydrogenation catalysis,<sup>4</sup> and unselective hydrocracking, which converts raw materials into a lower value, broad distribution of smaller molecular fragments including light hydrocarbons and aromatics at temperatures higher than 500 °C.<sup>5–7</sup>

To date, there have been few reports of catalytic hydrogenolysis of PE.<sup>8–10</sup> In particular, Dufaud and Basset showed that highly electrophilic Zr–H species synthesized by surface organometallic chemistry transformed short-chain (C<sub>20</sub>–C<sub>50</sub>) and high molecular weight (*M<sub>w</sub>* = 125,000 Da) PE into fuels and short-chain hydrocarbons.<sup>8</sup> Excessive hydrogenolysis, however, resulted in further transformations, producing light hydrocarbons such as methane, ethane, propane, and butane. Nakagawa, Tomishige, and co-workers deconstructed squalane (C<sub>30</sub>) by regioselective hydrogenolysis of internal C–C bonds into lighter hydrocarbons over Ru/CeO<sub>2</sub> at 240 °C and 60 bar.<sup>9,10</sup> While it was shown that the choice of support and particle size of Ru affected the hydrogenolysis of internal C–C bonds as compared to terminal C–C bonds of methyl branching, the catalytic features responsible for steering the pathways for hydrogenolysis were not clear.

Owing to the chemical resemblance of the feedstocks, some aspects of catalytic hydrogenolysis of polyolefins may be guided by the principles governing hydrogenolysis of *n*-alkanes. Catalytic hydrogenolysis of C<sub>2</sub>–C<sub>10</sub> alkanes has been studied extensively by Iglesia and co-workers over supported Pt, Ir, Ru, and Rh NPs.<sup>11–15</sup> The catalytic performance depends on a number of factors including operating conditions (temperature and H<sub>2</sub> pressure), characteristics of supported metal particles (size and metal type), and degree of substitution at each carbon atom of *n*-alkanes.<sup>11–17</sup> The kinetically relevant step in the hydrogenolysis reaction network is the cleavage of C–C bonds, after sequential quasi-equilibrated dehydrogenation steps that progressively weaken the C–C bonds and facilitate hydrogenolysis. The hydrogenolysis of *n*-alkanes is, however, prone to inhibition due to adsorbed hydrogen that limits the availability of active sites.<sup>11–17</sup>

Our approach for the transformation of high molecular weight PE requires the C–C bonds to undergo selective hydrogenolysis to produce a narrow molecular weight distribution of high-quality liquid hydrocarbons (Scheme 1). Such liquids, with a molecular weight ranging from 200 to 1000 Da, would be perfectly linear or have branching defined by the polyolefin feedstock and have advanced applications as lubricating oil<sup>18–21</sup> or as intermediates (e.g., waxes) that can be

further processed to produce ingredients for everyday necessities such as detergents and cosmetics.<sup>22,23</sup> Waxes, for example, are intensively employed in coatings to enhance electrical insulation, thermal stability, surface nature, friction stability, and heat and chemical resistance, with an expected revenue of more than USD 370 million by the end of 2024.<sup>24</sup> New catalytic hydrogenolysis that could affect the mean molecular weight and provide a narrow molecular distribution of products would allow access to such materials from polyolefin wastes, allowing this feedstock to be part of the circular economy.

Benchmarks for activity and selectivity for hydrogenolysis of PE are not available prior to the work described below. On the basis of the earlier hydrogenolysis of *n*-alkanes studies mentioned above, this catalytic transformation is expected to take place at high temperatures and pressures. Thus, we speculate that harsh, condensed-phase conditions require exceptionally stable nanoparticle–support interactions that resist sintering/deactivation under reaction conditions.

Strontium titanate (SrTiO<sub>3</sub>) is an excellent support because its crystalline, highly ordered, and well-characterized surfaces assist the assembly of ordered NP arrays.<sup>25</sup> SrTiO<sub>3</sub> is an archetypical cubic perovskite (*Pm* $\bar{3}$ *m*) that is optically transparent and possesses a high band gap.<sup>26,27</sup> The SrTiO<sub>3</sub> used in the present study features single crystal nanocuboids having a sub-100 nm average size, with {100} facets and rounded stepped edges. It is synthesized under hydrothermal conditions,<sup>28,29</sup> and the majority {100} surface termination has been determined to be the ( $\sqrt{13} \times \sqrt{13}$ )R33.7° TiO<sub>2</sub> double-layer surface reconstruction.<sup>25,28–33</sup> The SrTiO<sub>3</sub> nanocuboids are used as a support for deposition of Pt NPs to form a Pt/SrTiO<sub>3</sub> hydrogenolysis catalyst. Atomic layer deposition (ALD) is chosen for this process because it allows programmed control over key catalyst features that are potentially important to hydrogenolysis. ALD affords Pt NPs rather than films,<sup>34</sup> and the size of the Pt NP depends on the ALD conditions and the interaction between the metal and the support.<sup>35,36</sup> The close lattice-match between the cubic SrTiO<sub>3</sub> and FCC Pt results in a cube-on-cube epitaxy for Pt NPs on the {100} facets of SrTiO<sub>3</sub>. The cube-on-cube epitaxy contributes to a large interfacial energy term for the Pt/SrTiO<sub>3</sub> interface, which in turn stabilizes the Pt NPs.<sup>37–39</sup>


Here, we investigate (1) Pt/SrTiO<sub>3</sub> as a hydrogenolysis catalyst for the upcycling of linear PE chains with negligible branching, (2) the adsorption of PE onto the catalyst surface by kinetics, solid-state nuclear magnetic resonance (ssNMR) spectroscopy and computational modeling, (3) the structure sensitivity of Pt NPs by varying the facet to edges/corners ratio and by DFT models, and (4) the catalytic competence of Pt/SrTiO<sub>3</sub> compared to commercially available Pt/Al<sub>2</sub>O<sub>3</sub> catalyst. It will be seen that the catalytic performance of Pt/SrTiO<sub>3</sub> balances on preferential binding of longer hydrocarbon chains onto the Pt surface and the rate of hydrogenolysis at different catalytic sites (facet versus edge/corner). Thus, controlling the Pt edge to facet ratio is essential for suppressing overhydrogenolysis.

## RESULTS AND DISCUSSION


### Catalytic Hydrogenolysis of Polyethylene Using Pt/SrTiO<sub>3</sub>.

The catalyst support, SrTiO<sub>3</sub> nanocuboids with an average size of 65 ± 19 nm, was synthesized via hydrothermal methods (Figure S1).<sup>31,34</sup> Five ALD cycles (5c) of Pt deposition using trimethyl(methylcyclopentadienyl)platinum-

**Scheme 1. Hydrogenolysis of PE into High-Quality Liquid Products**

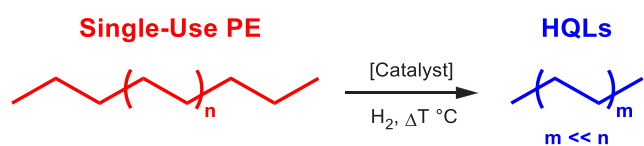

(IV) precursor and ozone on SrTiO<sub>3</sub> afforded highly dispersed Pt NPs with an average size of 2.0 ± 0.5 nm (Figure 1). A

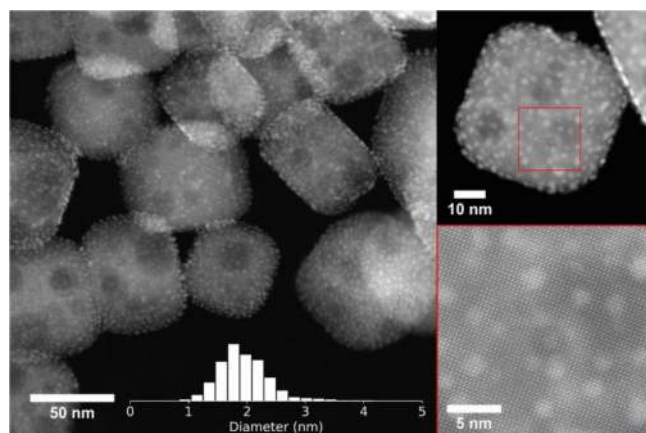

**Figure 1.** Electron micrographs of Pt NPs with an average size of 2.0 ± 0.5 nm, deposited by ALD on SrTiO<sub>3</sub> nanocuboid supports via 5 ALD cycles. Inset: histogram for Pt particle size distribution on 5c-Pt/SrTiO<sub>3</sub>.

growth rate of 1.9 ± 0.2 wt %/cycle was established on the SrTiO<sub>3</sub> surface as measured by inductively coupled plasma–optical emission spectroscopy (ICP–OES). The catalytic performance of 5c-Pt/SrTiO<sub>3</sub> was first investigated using a PE with  $M_n = 8150$  Da,  $M_w = 22,150$  Da, and dispersity ( $\mathcal{D}$ ) of 2.7, employing a high-throughput batch reactor (see the Supporting Information for experimental details). Reaction parameters that were varied (Figure S2) include catalyst loading (from 1 mg to 50 mg), reaction temperature (100, 300, and 350 °C), hydrogen pressure (100, 170, 400, and 600 psi), and reaction duration (up to 96 h). Optimized experimental conditions based on conversion of PE into high-quality liquid products are 170 psi H<sub>2</sub> at 300 °C under solvent-free conditions for 96 h, 10 mg of catalyst per 50 mg of PE. Solvent-free conditions have been chosen to eliminate competing adsorption and reaction of the hydrocarbon solvent with PE. Under these reaction conditions, 5c-Pt/SrTiO<sub>3</sub> converts the starting PE into a high-quality lubricant-like product ( $M_n = 590$  Da,  $M_w = 625$  Da, and  $\mathcal{D} = 1.1$ ) at a yield of 42% (yield = mass of liquid hydrocarbons vs initial mass of PE; Table 1). <sup>13</sup>C and <sup>1</sup>H NMR analysis (Figures S3 and S4, respectively) of the liquid product (10 methyl branch/1000C) indicates the formation of linear products with a negligible amount of olefinic groups.

The control experiment performed under thermal hydrogenolysis (no catalyst) in the presence of H<sub>2</sub> shows a significant reduction in  $M_n$  (from 8150 to 5700 Da), whereas  $M_w$  exhibits a slight decrease (from 22,150 Da to 18,200 Da), resulting in a broadened distribution of polymeric material ( $\mathcal{D} = 3.2$ ). Note also that another control experiment of hydrogenolysis of PE using Pt-free SrTiO<sub>3</sub> displays negligible changes in the molecular weight distribution compared to thermal hydrogenolysis, (Figure S5), indicating that the Pt is responsible for catalytic hydrogenolysis. The catalytic performance of 5c-Pt/SrTiO<sub>3</sub> was further examined using PE with different molecular weights ( $M_n = 8000$ –160,000 Da and  $M_w = 18,000$ –420,000 Da). The 5c-Pt/SrTiO<sub>3</sub> catalyst again completely converts PE into the same low-molecular weight product in high yield and narrow molecular weight distribution independently of the chain length of the starting PE (Table 1).

**Table 1. Properties of PE Feedstocks and Hydrogenolyzed Products over Thermal Hydrogenolysis or Catalytic Hydrogenolysis Using 5c-Pt/SrTiO<sub>3</sub><sup>a</sup>**


entry	$M_n$ , Da	$M_w$ , Da	$\mathcal{D}$	yield, <sup>b</sup> %
PE	8150	22,150	2.7	n/a
thermal	5700	18,200	3.2	n/a
5c-Pt/SrTiO <sub>3</sub>	590	625	1.1	42
PE	15,400	17,200	1.1	n/a
thermal	17,300	19,550	1.1	n/a
5c-Pt/SrTiO <sub>3</sub>	660	700	1.1	68
PE	64,300	70,400	1.1	n/a
thermal <sup>c</sup>	30,050	54,900	1.8	n/a
5c-Pt/SrTiO <sub>3</sub>	800	920	1.2	91
PE	158,000	420,000	2.7	n/a
thermal <sup>c</sup>	16,800	136,250	8.1	n/a
5c-Pt/SrTiO <sub>3</sub>	820	960	1.2	>99
plastic bag	33,000	115,150	3.5	n/a
thermal	38,800	114,800	3.0	n/a
5c-Pt/SrTiO <sub>3</sub>	990	1130	1.3	97

<sup>a</sup>Reaction conditions: 170 psi H<sub>2</sub>, 300 °C, 96 h, and 50 mg PE, and 1.1 mg of Pt as 5c-Pt/SrTiO<sub>3</sub> (11.1 wt % Pt loading). <sup>b</sup>Yield is defined as the mass of the weight of hydrocarbons recovered relative to the initial mass of PE. Owing to the high viscosity of the melt polymer, mass transfer effects cannot be ruled out completely. <sup>c</sup>Bimodal distribution.

Remarkably, the catalytic hydrogenolysis of PE is also effective starting with a single-use, commercial-grade plastic bag as a feedstock ( $M_n = 33,000$  Da,  $M_w = 115,150$  Da, and  $\mathcal{D} = 3.5$ ) to afford similar high-quality liquid products ( $M_n = 990$  Da,  $M_w = 1130$  Da, and  $\mathcal{D} = 1.3$ ) as obtained from research-grade HDPE (Table 1). These results suggest that the additives present in the plastic bag may not affect the catalyst.<sup>40</sup>

**Polyethylene–Catalyst Interaction.** Several sets of experiments were performed in order to gain insight into a possible relationship between selective conversion and the interactions between polymer and the catalyst surface, including (i) monitoring the change in molecular weight and distribution versus time, to (ii) measuring the conformation of adsorbed PE, and (iii) determining the strength of adsorption of alkanes on relevant crystalline facets.


Hydrogenolysis of PE in a Parr batch reactor at 170 psi H<sub>2</sub> and 300 °C affords hydrogenolyzed products with progressively shifted  $M_n$  to lower molecular weights over a series of reaction times (Figure 2). This progressive shift indicates that all of the molecules in the sample are hydrogenolyzed to some extent. Conversion of the starting polymer  $M_n$  of 8,150 to 625 Da corresponds to an average of 12 C–C bond cleavage steps per chain by the end of the reaction. Importantly, the decreasing  $\mathcal{D}$  also suggests that the PE chains with the highest molecular weights are more susceptible to hydrogenolysis than molecules with lower molecular weights. Carr et al. have shown that the highest molecular weight fraction of PE and other polymers preferentially adsorb to alkali halide crystals and that this adsorption could be used to preferentially extract the highest molecular weight fraction of a given sample.<sup>41</sup> A similar preferential adsorption of longer chains onto 5c-Pt/SrTiO<sub>3</sub> is consistent with the low dispersity of hydrocarbon chains,

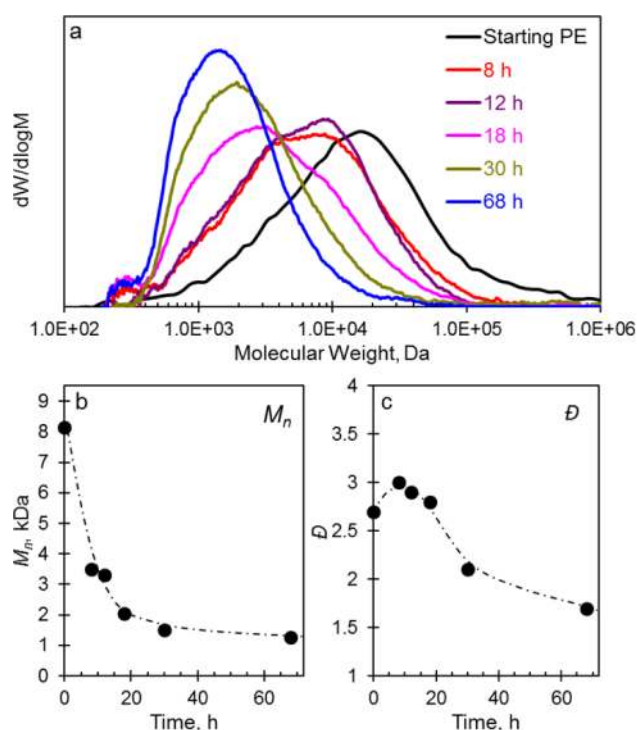

**Figure 2.** (a) Weight distribution, (b)  $M_n$ , and (c)  $D$  plots of the hydrogenolyzed products with respect to time over 5c-Pt/SrTiO<sub>3</sub>. Reaction conditions: 170 psi H<sub>2</sub>, 300 °C, 3 g of PE, and 8 mg of Pt as 5c-Pt/SrTiO<sub>3</sub>.

whereas preferential adsorption of lighter molecules to the catalyst would result in increased  $D$  with time as lighter species are hydrogenolyzed into even shorter chains (see Figure S6). Given that sequential hydrogenolysis takes place and leads to the selective formation of narrower high-quality liquid products, it is reasonable to assume that PE adsorption on the catalyst surface plays a key role in the overall performance. Examination of the interactions between the hydrocarbon chain and the surface was then carried out by <sup>13</sup>C magic-angle-spinning (MAS) ssNMR spectroscopy.

A monolayer of <sup>13</sup>C-enriched PE (see Supporting Information) was loaded onto the 5c-Pt/SrTiO<sub>3</sub> catalyst and the Pt-free SrTiO<sub>3</sub> support. As shown by Ando et al.,<sup>42,43</sup> <sup>13</sup>C MAS ssNMR spectroscopy is able to distinguish mobile ( $\delta = 30$  ppm), anti ( $\delta = 32.9$  ppm), and gauche ( $\delta = 27.5$  ppm) PE adsorbed on surfaces, and thus both the rigidity and linearity of PE onto the catalyst surface can be established. The <sup>13</sup>C MAS spectra are quantitative, while the <sup>1</sup>H → <sup>13</sup>C cross-polarization (CP) MAS spectra highlight the signals from the most rigid polymer molecules, presumably those that are closest to the surface. As can be seen in Figure 3a, no signal from gauche conformations can be detected for polymer adsorbed on the SrTiO<sub>3</sub> nanocuboid materials, despite the presence of a strong resonance belonging to the antipolymer conformer, indicative of a rigid conformation. This is in stark contrast with polymers adsorbed on silica gel for which clear evidence of nonlinearity is present.<sup>43</sup> On the other hand, the polymer mobility is dramatically enhanced when the surface contains Pt NPs (Figure 3a). This suggests that interactions with the metal NPs prevent the polymer from interacting as strongly with the SrTiO<sub>3</sub> surface. Thus, the observed catalytic behavior arises from the adsorption of the long chain hydrocarbon onto the active cleavage metal NP sites.

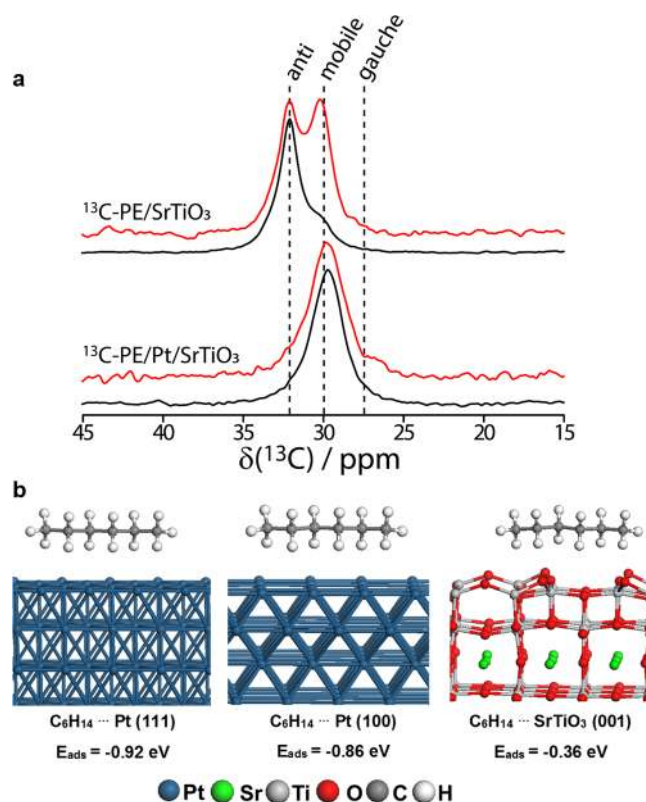

**Figure 3.** (a) <sup>13</sup>C MAS (red) and CPMAS (black) spectra of <sup>13</sup>C-enriched PE adsorbed on the SrTiO<sub>3</sub> support (top), and Pt/SrTiO<sub>3</sub> catalyst (bottom). (b) Side view of the optimized structures of *n*-hexane on Pt (111), Pt (100), and TiO<sub>2</sub> double-layer terminated SrTiO<sub>3</sub> (001) surface models.

Theoretical models support the idea that hydrocarbon molecules interact more strongly with the Pt NPs than with the SrTiO<sub>3</sub>. DFT calculations were performed using the VASP code<sup>44–47</sup> based on the SCAN-*r*VV10 functional and the projector augmented-wave method (see Supporting Information). The adsorption energies were calculated for the interaction of model *n*-alkanes (C<sub>*n*</sub>H<sub>2*n*+2</sub>, *n* = 4, 6, 8) onto Pt(111) and Pt(100) surface models as representations of the Pt NPs, as well as the TiO<sub>2</sub> double-layer terminated SrTiO<sub>3</sub>(001)<sup>48,49</sup> model as a representation of SrTiO<sub>3</sub> support. The *n*-alkanes prefer to adsorb on Pt surfaces, aligning their C–C bonds with all-anti conformation parallel to the metal surface (Figure 3b and Figure S7) as suggested by previous reflection-adsorption infrared spectroscopic studies<sup>50–52</sup> and ssNMR (vide supra). Despite the fact that adsorption onto Pt NPs is favored, the particles introduce irregularities onto the surface, which disfavor all-anti conformers (Figure 1), particularly in the space between the particles where interactions with the SrTiO<sub>3</sub> are limited and the polymer must bridge between particles. Such an interaction is responsible for the increased mobility of the surface-bound polymer. In addition, the total adsorption energy of *n*-alkanes increases with the number of carbon atoms (Figure S8). The adsorption of *n*-alkanes on the Pt(111) surface (−0.15 eV per CH<sub>2</sub> group) is slightly more favorable compared to the Pt(100) surface (−0.14 eV per CH<sub>2</sub>). The adsorption of *n*-alkanes on the SrTiO<sub>3</sub> support is found to occur through the oxygen on the TiO<sub>2</sub> double-layer terminated SrTiO<sub>3</sub> surface, with a lower average binding energy of only about −0.06 eV

**Table 2.** Catalytic Activity Comparison of 1c, 5c, and 10c-Pt/SrTiO<sub>3</sub> under Equal Surface Area (2000 cm<sup>2</sup>) or Mass (1 mg) of Pt in the Reactor<sup>a</sup>

catalyst	Pt weight loading <sup>g</sup> , %	average Pt diameter <sup>e</sup> , nm	Pt edge/facet ratio <sup>d</sup> , nm/nm <sup>2</sup>	amount of Pt, mg	surface area of Pt <sup>e</sup> , cm <sup>2</sup>	time, h	M <sub>n</sub> , Da <sup>f</sup>	Đ <sup>f</sup>	yield <sup>g</sup> , %
thermal	–	–	–	–	–	24	5600	4.2	<sup>h</sup>
						96	5700	3.2	>99
Equal Surface Area of Pt (2000 cm <sup>2</sup> )									
1c-Pt/SrTiO <sub>3</sub>	1.7	1.2	0.27	0.6		96	over-hydrogenolysis		
5c-Pt/SrTiO <sub>3</sub>	11.1	2.3	0.14	1.1	2000	96	600	1.1	42
10c-Pt/SrTiO <sub>3</sub>	18.8	2.9	0.11	1.4		96	750	1.1	95
Equal Weight of Pt (1 mg)									
1c-Pt/SrTiO <sub>3</sub>	1.7	1.2	0.27		3270	24	1250	4.7	91
						96	over-hydrogenolysis		
5c-Pt/SrTiO <sub>3</sub>	11.1	2.3	0.14	1.0	2000	24	2150	4.7	97
						96	600	1.1	42
10c-Pt/SrTiO <sub>3</sub>	18.8	2.9	0.11		1480	24	3400	3.4	>99
						96	800	1.2	>99

<sup>a</sup>Reaction conditions: 170 psi H<sub>2</sub>, 300 °C, 24 or 96 h, and 50 mg PE (M<sub>n</sub> = 8150 Da, Đ = 2.7). <sup>b</sup>Determined by ICP-OES. <sup>c</sup>Determined by TEM particle size analysis. <sup>d</sup>Pt NPs approximated as Winterbottom constructions, with  $\gamma_{\text{Pt}(111)}:\gamma_{\text{Pt}(100)} = 0.84$ , Pt(100)∥SrTiO<sub>3</sub>(100) at 61% truncation. <sup>e</sup>Surface area calculated from Pt loading and average particle size, assuming the minimum energy Winterbottom construction. <sup>f</sup>Determined by GPC. <sup>g</sup>Yield is defined as the mass of the weight of liquid hydrocarbons recovered relative to the initial mass of PE. <sup>h</sup>Not measured.

per carbon atom (Figure S9). The predicted linearity in the binding energy of the *n*-alkanes with respect to the number of carbon atoms (Figure S8) suggests that the trends observed here can be extended to larger alkanes. Furthermore, these results support the earlier hypothesis that the stronger binding of higher molecular weight polymer molecules helps in directing the decrease of the Đ index.

**Catalyst Structure Sensitivity of Polyethylene Hydrogenolysis.** The structure sensitivity of hydrogenolysis of short-chain *n*-alkanes has been well established;<sup>15,33</sup> however, to the best of our knowledge, no catalytic studies have been conducted on the effect of structure sensitivity on polyolefin hydrogenolysis. Here, Pt NPs of different metal loading, size, and edge to facet ratio were synthesized by varying the number of ALD cycles.<sup>54–56</sup> For 1 cycle (1c-), 5 cycles (5c-), and 10 cycles (10c-) Pt/SrTiO<sub>3</sub>, the loading of Pt and the volume of the Pt NPs increase linearly with the number of ALD cycles (Figure S10 and Table S2). Average particle sizes of Pt NPs on 1c-Pt/SrTiO<sub>3</sub>, 5c-Pt/SrTiO<sub>3</sub>, and 10c-Pt/SrTiO<sub>3</sub> are found to be 1.2 ± 0.2 nm, 2.3 ± 0.7 nm, and 2.9 ± 1.1 nm, respectively (Figure S11). The majority of Pt particles on the SrTiO<sub>3</sub>(100) facet have a cube-on-cube epitaxy with a truncation of 61% relative to the free Wulff shape of a Pt NPs.<sup>54</sup> The proportion of undercoordinated edge sites to the total Pt surface area increases as the diameter of the Pt NPs decreases (Table S2). Similarly to previous observations, the spacing of the Pt NPs, measured as the center-to-center distance, increased with the number of ALD cycles.<sup>34</sup>

Hydrogenolysis of PE performed at 300 °C and 170 psi over 1c-, 5c-, and 10c-Pt/SrTiO<sub>3</sub> catalysts shows that the Pt particle size and coordination of surface atoms affect the molecular weight and dispersity of products. Catalytic experiments were performed under an equal basis of Pt surface area in the reactor (2000 cm<sup>2</sup> Pt) (Table 2) for 96 h. Catalyst 1c-Pt/SrTiO<sub>3</sub> completely transforms PE into gaseous hydrocarbons (C<sub>1</sub>–C<sub>8</sub>), while 5c-Pt/SrTiO<sub>3</sub> and 10c-Pt/SrTiO<sub>3</sub> convert PE into a similar high-quality liquid product (M<sub>n</sub> ≈ 675 Da and Đ = 1.1) at yields of 42% and 95%, respectively. In addition,

experiments performed for 24 h under an equal basis of the Pt amount in the reactor (1.0 mg Pt) show that the lowest molecular weight of hydrogenolyzed products is achieved with 1c-Pt/SrTiO<sub>3</sub>. 1c-Pt/SrTiO<sub>3</sub> reduced the M<sub>n</sub> from 8150 Da to 1250 Da in 24 h, while 5c and 10c reduced the M<sub>n</sub> to 2150 Da and 3400 Da, respectively. It should be noted that the molecular weight of the hydrogenolyzed products at 24 h (M<sub>n</sub> = 1250 Da, ~C<sub>90</sub>) is not low enough for mass losses into the headspace to be a significant contributor to yield. Furthermore, for extended time (96 h), 1c-Pt/SrTiO<sub>3</sub> completely converts the starting PE into gaseous products while lubricant-like hydrocarbons (M<sub>n</sub> ≈ 800 Da and Đ = 1.1) are obtained over 5c-Pt/SrTiO<sub>3</sub> and 10c-Pt/SrTiO<sub>3</sub>. The results show that smaller Pt NPs with higher concentrations of undercoordinated Pt sites promote over-hydrogenolysis of PE to undesired light hydrocarbons. This, however, can be prevented by controlling the Pt properties such as size and edge to facet ratio while obtaining a high-quality liquid product with relatively narrow polydispersity at high yields.

Under the experimental reaction conditions (T = 300 °C; P<sub>H<sub>2</sub></sub> = 170–300 psi), the presence of excess H<sub>2</sub> could inhibit the adsorption of PE and limit the availability of active sites for C–C bond hydrogenolysis. The dissociative adsorption of H<sub>2</sub> to form surface –OH moieties on the SrTiO<sub>3</sub> surface is endergonic (SrTiO<sub>3</sub> + H<sub>2</sub>(gas) → 2H···SrTiO<sub>3</sub>, ΔE = –0.09 eV; ΔG = 0.48 eV at T = 300 °C and P<sub>H<sub>2</sub></sub> = 300 psi) suggesting that the SrTiO<sub>3</sub> surface is free of adsorbed H atoms under experimental conditions. On the other hand, the adsorption of H atoms on Pt surface sites was found to be exergonic under our experimental reaction conditions (Figure S12). The calculations predicted that the average binding energy for a monolayer (ML) coverage of H calculated with reference to the energy of gas phase H<sub>2</sub> is –0.79 eV (ΔG (300 °C) = –0.50 eV) and –0.38 eV (ΔG (300 °C) = –0.10 eV) for the Pt(100) and Pt(111) surfaces, respectively. Removing a single H atom from the 1 ML H-covered surface was found to be endergonic by 0.51 eV on the Pt(100) surface and is slightly exergonic by –0.02 eV on the Pt(111) surface. These results suggest that

the (100) surface facets are fully covered by H under reaction conditions, whereas some sites are available for the adsorption and cleavage of C–C bonds of the hydrocarbon on the close-packed Pt(111) sites. On the fully hydrogenated Pt(100) and Pt(111) surface facets, the hydrocarbon adsorption strength per site (and carbon atom) is found to be only slightly larger (−0.09 and −0.10 eV, respectively, Figure S12) than on the SrTiO<sub>3</sub> support. However, calculations suggested that a large fraction of the surface hydrogen atoms can be displaced from the Pt(111) facet under reaction conditions and the hydrocarbon chain is able to strongly interact with this facet ( $E^{\text{ads}} = -0.22$  eV per CH<sub>2</sub>, Figure S12c–d) and can facilitate dehydrogenation and C–C cleavage reactions at nearby sites. This finding is in agreement with a recent literature report that H\* saturates Pt at lower coverages, both on edge and terrace sites, and only a few H vacancies are necessary to activate the \*HC–CH\* bond on Pt compared to other metals such as Ru, Rh, and Ir.<sup>16</sup>

**Comparison of Pt/SrTiO<sub>3</sub> versus Pt/Al<sub>2</sub>O<sub>3</sub>.** Commercially available Pt/Al<sub>2</sub>O<sub>3</sub> (1 wt %, Sigma-Aldrich) provides remarkable contrast to the behavior of 5c-Pt/SrTiO<sub>3</sub>. The comparison of catalytic activity between 5c-Pt/SrTiO<sub>3</sub> and Pt/Al<sub>2</sub>O<sub>3</sub> at the equal basis of Pt amount in the reactor (Table S3) shows that the  $M_n$  of the hydrogenolyzed products is similar over both samples (~1950 Da) after 18 h. Both  $M_w$  and  $\bar{D}$ , however, highlight the effect of Pt/SrTiO<sub>3</sub> on catalytic performance.  $M_w$  of the hydrogenolyzed product over 5c-Pt/SrTiO<sub>3</sub> (5800 Da) is significantly lower than that over Pt/Al<sub>2</sub>O<sub>3</sub> (10,750 Da). Negligible variation of  $\bar{D}$  of the hydrogenolyzed products from 5c-Pt/SrTiO<sub>3</sub> is detected with respect to the starting PE. In contrast, the  $\bar{D}$  of the products over Pt/Al<sub>2</sub>O<sub>3</sub> increases to ~6. The broadening of the hydrogenolyzed product distribution from the Pt/Al<sub>2</sub>O<sub>3</sub> catalyst is also observed by pyrolysis gas chromatography–mass (GC-MS) spectrometry analysis (Figures S13–S15). In addition, the quantification of the gases in the headspace of the reactor by GC (Figure S16) revealed that the formation of light hydrocarbons (saturated C<sub>1</sub>–C<sub>8</sub> and cyclic C<sub>5</sub>–C<sub>6</sub> alkanes) is significantly suppressed over 5c-Pt/SrTiO<sub>3</sub>, when compared to Pt/Al<sub>2</sub>O<sub>3</sub>. Note that thermal degradation leads to the formation of C<sub>1</sub>–C<sub>8</sub> gases, even in the absence of any catalyst (Table S3), due to the thermal degradation of the PE. After the amount of light hydrocarbons formed from the thermal degradation (0.65 mmol, 3 g of PE at 300 °C, 170 psi H<sub>2</sub> for 18 h) was accounted for, the total number of light hydrocarbons produced over Pt/Al<sub>2</sub>O<sub>3</sub> (1.69 mmol) is more than 3× that produced over 5c-Pt/SrTiO<sub>3</sub> (0.52 mmol). This difference constitutes an important advantage since relatively narrow dispersity, high-quality liquid products are obtained at high yields without producing any substantial amounts of light hydrocarbons.

Comparison of hydrogenolysis performance under equal area × time (defined as surface area of Pt multiplied by reaction time) for 1c-Pt/SrTiO<sub>3</sub> and Pt/Al<sub>2</sub>O<sub>3</sub> (1.2 nm, Figures S11 and S17, respectively) reveals unique aspects of the SrTiO<sub>3</sub> support. While the  $M_n$  of the hydrogenolyzed products is similar ( $M_n \approx 1500$  Da) (Figure S18), the  $\bar{D}$  index of the product from 1c-Pt/SrTiO<sub>3</sub> ( $\bar{D} = 2.4$ ) is significantly lower than for Pt/Al<sub>2</sub>O<sub>3</sub> ( $\bar{D} = 6.6$ ), indicating for the latter that part of the starting material is not converted to HQL (Figure S18). In addition, the extent of over-hydrogenolysis for Pt/Al<sub>2</sub>O<sub>3</sub> is greater compared to the entire Pt/SrTiO<sub>3</sub> series

(Figure S19), suggesting that Al<sub>2</sub>O<sub>3</sub> catalyst promotes the formation of light hydrocarbons.

TEM images of Pt NPs on  $\gamma$ -Al<sub>2</sub>O<sub>3</sub> (Figure S17 and Table S4) reveal that the average particle size is  $1.2 \pm 0.4$  nm and after 18 h of PE hydrogenolysis is  $1.6 \pm 0.4$  nm. The average Pt particle diameter for 5c-Pt/SrTiO<sub>3</sub> increased from  $2.0 \pm 0.5$  nm to  $2.1 \pm 0.5$  nm after 18 h (Figure 1 and Figure S20). The negligible change in particle size of Pt in 5c-Pt/SrTiO<sub>3</sub> suggests that the stabilization of Pt by SrTiO<sub>3</sub> relative to  $\gamma$ -Al<sub>2</sub>O<sub>3</sub> is effective in minimizing the effect of sintering under reaction conditions. Note that platinum has a weaker interfacial interaction with  $\gamma$ -Al<sub>2</sub>O<sub>3</sub> than with SrTiO<sub>3</sub> and the minimum energy Winterbottom shape of Pt on  $\gamma$ -Al<sub>2</sub>O<sub>3</sub> is closer to that of a free Wulff particle, facilitating the sintering.<sup>39</sup>

5c-Pt/SrTiO<sub>3</sub> is shown to be recyclable for hydrogenolysis of PE, albeit with reduced catalytic performance (Table S5). Although no changes in average particle size of Pt NPs were noted (vide supra), the reduced catalytic performance is attributed to oxidation of Pt NPs during physical recovery of the catalyst from the reaction medium.

## CONCLUSIONS

Catalytic processes that convert waste PE into value-added products are key to mitigating adverse impacts of the plastic pollution and developing a circular economy. An effective catalyst for chemical upcycling of PE must be able to break carbon–carbon bonds of longer chains in preference to shorter chains. In this work, Pt NPs supported on SrTiO<sub>3</sub> nanocuboids by ALD completely converted PE samples, ranging from  $M_n$  of 8000–158,000 Da and  $M_w$  of 17,200–420,000 Da, into narrowly distributed high-quality liquid products, such as motor oil and waxes. The hydrogenolysis occurred at 300 °C and 170 psi of H<sub>2</sub> under solvent-free conditions, yielding negligible amounts of light hydrocarbons, in marked contrast to the benchmark hydrogenolysis catalyst Pt/Al<sub>2</sub>O<sub>3</sub>.

Several features of Pt/SrTiO<sub>3</sub> contribute to its performance in selective PE hydrogenolysis. First, the selective hydrogenolysis is attributed to more favorable adsorption of PE on Pt sites than on the SrTiO<sub>3</sub> support as evidenced by ssNMR and DFT and preferential binding of high molecular weight PE on the Pt NPs surface. Second, the electronic and geometric properties of Pt NPs on SrTiO<sub>3</sub> play a key role in producing high-quality liquid products from a single-use PE stream and suppressing the undesired over-hydrogenolysis to light hydrocarbons. Specifically, Pt edge sites are found to be highly reactive for hydrogenolysis of PE compared to Pt facets. Cube-on-cube epitaxy for Pt NPs on the {100} facets of SrTiO<sub>3</sub> provides significant nanoparticle–support interactions that minimized sintering under the solvent-free, harsh reaction conditions.

The substantially superior performance of 5c-Pt/SrTiO<sub>3</sub> compared to commercial Pt/Al<sub>2</sub>O<sub>3</sub> in selective PE hydrogenolysis suggests that there may be some special features of the former material that could guide future catalyst development. In particular, evenly dispersed and similarly sized Pt NPs on Pt/SrTiO<sub>3</sub> should be noted. These features would also affect the distances between sites where carbon–carbon bond cleavage occurs. Because the macromolecules are long and could adsorb to multiple NPs on a face of the SrTiO<sub>3</sub> nanocuboid support, the ordering and distances may also exert an influence over selective formation of specific chain lengths. While the organization of Pt particles in 5c-Pt/SrTiO<sub>3</sub> is insufficient to test this idea, the next phase of this project is



focused on synthesis of ordered and organized catalytic materials. Such materials, with well-characterized distances between sites, may ultimately provide the fundamental design principles needed for effective upcycling catalysis.

## MATERIALS AND METHODS

SrTiO<sub>3</sub> nanocuboids were synthesized hydrothermally according to literature procedures.<sup>31</sup> Platinum NPs were deposited onto the SrTiO<sub>3</sub> using ALD in a viscous flow reactor.<sup>34</sup> ALD precursor (MeCp)PtMe<sub>3</sub> (Strem Chemicals, 99%) and 70% output O<sub>3</sub> (Pacific Ozone L11 Ozone Generator, ultrahigh purity 20 Torr O<sub>2</sub> source) were used. The ALD deposition temperature was set to 200 °C. A pretreatment of O<sub>3</sub> exposure at 200 °C for 2 h was used for all ALD-prepared Pt samples. The resulting samples were characterized by TEM and ICP-OES. ssNMR experiments were performed using <sup>13</sup>C-labeled PE adsorbed onto the surface of the samples. DFT calculations were performed using the Vienna ab initio simulation package (VASP). A Parr reactor and a high-throughput screening pressure reactor (SPR; Unchained Labs) at the Argonne National Laboratory's High-Throughput Research Laboratory were used for catalytic activity experiments. Activity experiments were performed under solvent-free conditions at 170 psi and 300 °C, unless otherwise noted. Samples were analyzed by high temperature GPC to obtain molecular weight after hydrogenolysis. The accuracy of the GPC measurements was verified by calibration at low-molecular weights (Table S1; 400–1000 Da). For detailed experimental information, see the Supporting Information.

## ASSOCIATED CONTENT

### Supporting Information

The Supporting Information is available free of charge on the ACS Publications website at DOI: 10.1021/acscentsci.9b00722.

General procedures regarding synthesis, characterization, and activity experiments and supplemental data (PDF)  
Additional data (ZIP)

XYZ coordinates of optimized structures (PDF)

## AUTHOR INFORMATION

### Corresponding Authors

\*(M.D.) E-mail: [delferro@anl.gov](mailto:delferro@anl.gov).

\*(A.D.S.) E-mail: [sadow@iastate.edu](mailto:sadow@iastate.edu).

\*(K.R.P.) E-mail: [krp@northwestern.edu](mailto:krp@northwestern.edu).

### ORCID

Gokhan Celik: 0000-0001-8070-5219

Robert M. Kennedy: 0000-0001-6836-7923

Anne M. LaPointe: 0000-0002-7830-0922

Andreas Heyden: 0000-0002-4939-7489

Frédéric A. Perras: 0000-0002-2662-5119

Marek Pruski: 0000-0001-7800-5336

Susannah L. Scott: 0000-0003-1161-0499

Kenneth R. Poepelmeier: 0000-0003-1655-9127

Aaron D. Sadow: 0000-0002-9517-1704

Massimiliano Delferro: 0000-0002-4443-165X

### Funding

This work was supported as part of Catalysis for Polymer Upcycling (CPU) by the U.S. Department of Energy (DOE), Office of Basic Energy Sciences, Division of Chemical Sciences, Geosciences, and Biosciences, under Contract DE-AC-02-

06CH11357 (Argonne National Laboratory) and DE-AC-02-07CH11358 (Ames Laboratory).

### Notes

The authors declare the following competing financial interest(s): Two patent applications partially based on this work have been filed (US Patent Applications 62/796,482 and 62/892,347).

## ACKNOWLEDGMENTS

The authors acknowledge Dr. D. M. Kaphan and Dr. J. Wen for helpful discussions. This work made use of the Center for Nanoscale Materials, an Office of Science user facility, supported by the U.S. Department of Energy, Office of Science, Office of Basic Energy Sciences, under Contract No. DE-AC02-06CH11357. This work also made use of (i) the EPIC and BioCryo facilities of Northwestern University's NUANCE Center, which has received support from the Soft and Hybrid Nanotechnology Experimental (SHyNE) Resource (NSF ECCS-1542205); the MRSEC program (NSF DMR-1720139) at the Materials Research Center; the International Institute for Nanotechnology (IIN); the Keck Foundation; and the State of Illinois, through the IIN, (ii) CryoCluster equipment, which has received support from the MRI program (NSF DMR-1229693), and (iii) Jerome B. Cohen X-ray Diffraction Facility supported by the MRSEC program of the National Science Foundation (DMR-1720139) at the Materials Research Center of Northwestern University and the Soft and Hybrid Nanotechnology Experimental (SHyNE) Resource (NSF ECCS-1542205). Finally, computational resources provided by XSEDE resources located at San Diego Supercomputer Center and Texas Advanced Computing Center (Grant No. TG-CTS090100) as well as Pacific Northwest National Laboratory (Ringgold ID 130367, Grant Proposal 50576) are gratefully acknowledged.

## REFERENCES

- (1) *Advancing Sustainable Materials Management*, 2014 fact sheet, EPA530-R-17-01; United States Environmental Protection Agency (EPA) - Office of Land and Emergency Management (5306P), 2016.
- (2) Hopewell, J.; Dvorak, R.; Kosior, E. Plastics recycling: challenges and opportunities. *Philos. Trans. R. Soc., B* **2009**, *364*, 2115–2126.
- (3) Rahimi, A.; García, J. M. Chemical recycling of waste plastics for new materials production. *Nat. Rev. Chem.* **2017**, *1*, 0046.
- (4) Jia, X.; Qin, C.; Friedberger, T.; Guan, Z.; Huang, Z. Efficient and selective degradation of polyethylenes into liquid fuels and waxes under mild conditions. *Sci. Adv.* **2016**, *2*, No. e1501591.
- (5) Burange, A. S.; Gawande, M. B.; Lam, F. L. Y.; Jayaram, R. V.; Luque, R. Heterogeneously catalyzed strategies for the deconstruction of high density polyethylene: plastic waste valorisation to fuels. *Green Chem.* **2015**, *17*, 146–156.
- (6) Wong, S.; Ngadi, N.; Tuan Abdullah, T. A.; Inuwa, I. M. Catalytic cracking of LDPE dissolved in benzene using nickel-impregnated zeolites. *Ind. Eng. Chem. Res.* **2016**, *55*, 2543–2555.
- (7) Mastral, J. F.; Berruoco, C.; Gea, M.; Ceamanos, J. Catalytic degradation of high density polyethylene over nanocrystalline HZSM-5 zeolite. *Polym. Degrad. Stab.* **2006**, *91*, 3330–3338.
- (8) Dufaud, V.; Basset, J.-M. Catalytic hydrogenolysis at low temperature and pressure of polyethylene and polypropylene to diesels or lower alkanes by a zirconium hydride supported on silica-alumina: A step toward polyolefin degradation by the microscopic reverse of Ziegler–Natta polymerization. *Angew. Chem., Int. Ed.* **1998**, *37*, 806–810.
- (9) Oya, S.-i.; Kanno, D.; Watanabe, H.; Tamura, M.; Nakagawa, Y.; Tomishige, K. Catalytic production of branched small alkanes from biohydrocarbons. *ChemSusChem* **2015**, *8*, 2472–2475.

- (10) Nakaji, Y.; Nakagawa, Y.; Tamura, M.; Tomishige, K. Regioselective hydrogenolysis of alga-derived squalane over silica-supported ruthenium-vanadium catalyst. *Fuel Process. Technol.* **2018**, *176*, 249–257.
- (11) Hibbitts, D. D.; Flaherty, D. W.; Iglesia, E. Effects of chain length on the mechanism and rates of metal-catalyzed hydrogenolysis of *n*-alkanes. *J. Phys. Chem. C* **2016**, *120*, 8125–8138.
- (12) Flaherty, D. W.; Uzun, A.; Iglesia, E. Catalytic ring opening of cycloalkanes on Ir clusters: Alkyl substitution effects on the structure and stability of C–C bond cleavage transition states. *J. Phys. Chem. C* **2015**, *119*, 2597–2613.
- (13) Flaherty, D. W.; Hibbitts, D. D.; Iglesia, E. Metal-Catalyzed C–C Bond Cleavage in Alkanes: Effects of Methyl Substitution on Transition-State Structures and Stability. *J. Am. Chem. Soc.* **2014**, *136*, 9664–9676.
- (14) Flaherty, D. W.; Hibbitts, D. D.; Gürbüz, E. I.; Iglesia, E. Theoretical and kinetic assessment of the mechanism of ethane hydrogenolysis on metal surfaces saturated with chemisorbed hydrogen. *J. Catal.* **2014**, *311*, 350–356.
- (15) Flaherty, D. W.; Iglesia, E. Transition-state enthalpy and entropy effects on reactivity and selectivity in hydrogenolysis of *n*-alkanes. *J. Am. Chem. Soc.* **2013**, *135*, 18586–18599.
- (16) Almithn, A.; Hibbitts, D. Comparing rate and mechanism of ethane hydrogenolysis on transition-metal catalysts. *J. Phys. Chem. C* **2019**, *123*, 5421–5432.
- (17) Almithn, A.; Hibbitts, D. Effects of catalyst model and high adsorbate coverages in ab initio studies of alkane hydrogenolysis. *ACS Catal.* **2018**, *8*, 6375–6387.
- (18) Holmberg, K.; Andersson, P.; Erdemir, A. Global energy consumption due to friction in passenger cars. *Tribol. Int.* **2012**, *47*, 221–234.
- (19) Holmberg, K.; Erdemir, A. Influence of tribology on global energy consumption, costs and emissions. *Friction* **2017**, *5*, 263–284.
- (20) Holmberg, K.; Erdemir, A. The impact of tribology on energy use and CO<sub>2</sub> emission globally and in combustion engine and electric cars. *Tribol. Int.* **2019**, *135*, 389–396.
- (21) Hamad, A.; Al-Zubaidy, E.; Fayed, M. E. Used lubricating oil recycling using hydrocarbon solvents. *J. Environ. Manage.* **2005**, *74*, 153–159.
- (22) Liang, Z.; Chen, L.; Alam, M. S.; Zeraati Rezaei, S.; Stark, C.; Xu, H.; Harrison, R. M. Comprehensive chemical characterization of lubricating oils used in modern vehicular engines utilizing GC × GC-TOFMS. *Fuel* **2018**, *220*, 792–799.
- (23) Stubington, J. F.; Sergeant, G. D.; Barrett, D.; Do, P. T. D. H.; Raval, K. A. Molecular weight determination in the study of the lubricating oil potential of shale oils. *Fuel* **1995**, *74* (1), 79–82.
- (24) Pulidindi, K.; Pandey, H. *Polyethylene Wax Market Size By Form (Pellets, Powders, Flakes), By Application (Candles, Packaging, Wood & Firelogs, Plastic Additives & Lubricants, Rubber, Adhesive & Coatings, Cosmetics), Industry Analysis Report, Regional Outlook (U.S., Canada, Germany, UK, France, Spain, Italy, China, India, Japan, Australia, Indonesia, Malaysia, Brazil, Mexico, South Africa, GCC), Growth Potential, Price Trends, Competitive Market Share & Forecast, 2016–2024; Global Market Insights*, 2018.
- (25) Andersen, T. K.; Fong, D. D.; Marks, L. D. Pauling's rules for oxide surfaces. *Surf. Sci. Rep.* **2018**, *73*, 213–232.
- (26) Deak, D. S. Strontium titanate surfaces. *Mater. Sci. Technol.* **2007**, *23*, 127–136.
- (27) Goodenough, J. B. Electronic and ionic transport properties and other physical aspects of perovskites. *Rep. Prog. Phys.* **2004**, *67*, 1915–1993.
- (28) Crosby, L. A.; Chen, B.-R.; Kennedy, R. M.; Wen, J.; Poeppelmeier, K. R.; Bedzyk, M. J.; Marks, L. D. All roads lead to TiO<sub>2</sub>: TiO<sub>2</sub>-rich surfaces of barium and strontium titanate prepared by hydrothermal synthesis. *Chem. Mater.* **2018**, *30*, 841–846.
- (29) Lin, Y.; Wen, J.; Hu, L.; Kennedy, R. M.; Stair, P. C.; Poeppelmeier, K. R.; Marks, L. D. Synthesis-dependent atomic surface structures of oxide nanoparticles. *Phys. Rev. Lett.* **2013**, *111*, 156101.
- (30) Kienzle, D. M.; Marks, L. D. Surface transmission electron diffraction for SrTiO<sub>3</sub> surfaces. *CrystEngComm* **2012**, *14*, 7833–7839.
- (31) Rabuffetti, F. A.; Kim, H.-S.; Enterkin, J. A.; Wang, Y.; Lanier, C. H.; Marks, L. D.; Poeppelmeier, K. R.; Stair, P. C. Synthesis-Dependent First-Order Raman Scattering in SrTiO<sub>3</sub> Nanocubes at Room Temperature. *Chem. Mater.* **2008**, *20*, 5628–5635.
- (32) Marks, L. D.; Peng, L. Nanoparticle shape, thermodynamics and kinetics. *J. Phys.: Condens. Matter* **2016**, *28*, 053001.
- (33) Crosby, L.; Enterkin, J.; Rabuffetti, F.; Poeppelmeier, K.; Marks, L. Wulff shape of strontium titanate nanocuboids. *Surf. Sci.* **2015**, *632*, L22–L25.
- (34) Christensen, S. T.; Elam, J. W.; Rabuffetti, F. A.; Ma, Q.; Weigand, S. J.; Lee, B.; Seifert, S.; Stair, P. C.; Poeppelmeier, K. R.; Hersam, M. C.; Bedzyk, M. J. Controlled Growth of Platinum Nanoparticles on Strontium Titanate Nanocubes by Atomic Layer Deposition. *Small* **2009**, *5*, 750–757.
- (35) Dendooven, J.; Ramachandran, R. K.; Solano, E.; Kurttepel, M.; Geerts, L.; Heremans, G.; Rongé, J.; Minjauw, M. M.; Dobbelaere, T.; Devloo-Casier, K.; Martens, J. A.; Vantomme, A.; Bals, S.; Portale, G.; Coati, A.; Detavernier, C. Independent tuning of size and coverage of supported Pt nanoparticles using atomic layer deposition. *Nat. Commun.* **2017**, *8*, 1074.
- (36) Grillo, F.; Van Bui, H.; La Zara, D.; Aarnink, A. A. I.; Kovalgin, A. Y.; Kooyman, P.; Kreutzer, M. T.; van Ommen, J. R. From single atoms to nanoparticles: Autocatalysis and metal aggregation in atomic layer deposition of Pt on TiO<sub>2</sub> nanopowder. *Small* **2018**, *14*, 1800765.
- (37) Enterkin, J. A.; Poeppelmeier, K. R.; Marks, L. D. Oriented Catalytic Platinum Nanoparticles on High Surface Area Strontium Titanate Nanocuboids. *Nano Lett.* **2011**, *11*, 993–997.
- (38) Enterkin, J. A.; Setthapun, W.; Elam, J. W.; Christensen, S. T.; Rabuffetti, F. A.; Marks, L. D.; Stair, P. C.; Poeppelmeier, K. R.; Marshall, C. L. Propane oxidation over Pt/SrTiO<sub>3</sub> nanocuboids. *ACS Catal.* **2011**, *1*, 629–635.
- (39) Zhang, Z.; Li, L.; Yang, J. C. Adhesion of Pt Nanoparticles Supported on  $\gamma$ -Al<sub>2</sub>O<sub>3</sub> Single Crystal. *J. Phys. Chem. C* **2013**, *117*, 21407–21412.
- (40) Hahladakis, J. N.; Velis, C. A.; Weber, R.; Iacovidou, E.; Purnell, P. An overview of chemical additives present in plastics: Migration, release, fate and environmental impact during their use, disposal and recycling. *J. Hazard. Mater.* **2018**, *344*, 179–199.
- (41) Carr, S. H.; Keller, A.; Baer, E. Relationship between self-seeded and epitaxial crystallization from polymer solutions: A potentially new method for molecular weight separation and a new decoration method for alkali halides. *J. Polym. Sci., Part A-2* **1970**, *8*, 1467–1490.
- (42) Kurosu, H.; Takahashi, K.; Inoue, D.; Ando, I. Structural characterization of <sup>13</sup>C-labeled *n*-tetracosane adsorbed on the surface of silica gel by high-resolution solid-state <sup>13</sup>C NMR spectroscopy. *J. Mol. Struct.* **2000**, *516*, 177–184.
- (43) Inoue, D.; Kurosu, H.; Chen, Q.; Ando, I. Structural and dynamical studies of <sup>13</sup>C-labeled polyethylene adsorbed on the surface of silica gel by high-resolution solid-state <sup>13</sup>C NMR spectroscopy. *Acta Polym.* **1995**, *46*, 420–423.
- (44) Kresse, G.; Furthmüller, J. Efficient iterative schemes for ab initio total-energy calculations using a plane-wave basis set. *Phys. Rev. B: Condens. Matter Mater. Phys.* **1996**, *54*, 11169–11186.
- (45) Kresse, G.; Furthmüller, J. Efficiency of ab-initio total energy calculations for metals and semiconductors using a plane-wave basis set. *Comput. Mater. Sci.* **1996**, *6*, 15–50.
- (46) Kresse, G.; Hafner, J. Ab initio molecular-dynamics simulation of the liquid-metal-amorphous-semiconductor transition in germanium. *Phys. Rev. B: Condens. Matter Mater. Phys.* **1994**, *49*, 14251–14269.
- (47) Kresse, G.; Hafner, J. Ab initio molecular dynamics for liquid metals. *Phys. Rev. B: Condens. Matter Mater. Phys.* **1993**, *47*, 558–561.
- (48) Kienzle, D. M.; Becerra-Toledo, A. E.; Marks, L. D. Vacant-site octahedral tilings on SrTiO<sub>3</sub> (001), the ( $\sqrt{13} \times \sqrt{13}$ )R33.7° surface, and related structures. *Phys. Rev. Lett.* **2011**, *106*, 176102.

(49) Erdman, N.; Warschkow, O.; Asta, M.; Poepelmeier, K. R.; Ellis, D. E.; Marks, L. D. Surface Structures of SrTiO<sub>3</sub> (001): A TiO<sub>2</sub>-rich Reconstruction with a c(4 × 2) Unit Cell. *J. Am. Chem. Soc.* **2003**, *125*, 10050–10056.

(50) Manner, W. L.; Bishop, A. R.; Girolami, G. S.; Nuzzo, R. G. Melting of rodlike molecules on Pt(111). Infrared spectroscopic studies of isotopically labeled *n*-Alkanes. *J. Phys. Chem. B* **1998**, *102*, 8816–8824.

(51) Chesters, M. A.; Gardner, P.; McCash, E. M. The reflection-absorption infrared spectra of *n*-alkanes adsorbed on Pt(111). *Surf. Sci.* **1989**, *209*, 89–99.

(52) Yang, M.; Somorjai, G. A. Adsorption and reactions of C<sub>6</sub> hydrocarbons at high pressures on Pt(111) single-crystal surfaces studied by sum frequency generation vibrational spectroscopy: Mechanisms of isomerization and dehydrocyclization of *n*-hexane. *J. Am. Chem. Soc.* **2004**, *126*, 7698–7708.

(53) Che, M.; Bennett, C. O. The Influence of Particle Size on the Catalytic Properties of Supported Metals. In *Adv. Catal.*; Eley, D. D.; Pines, H.; Weisz, P. B., Eds.; Academic Press, 1989; Vol. 36, pp 55–172.

(54) Enterkin, J. A.; Kennedy, R. M.; Lu, J.; Elam, J. W.; Cook, R. E.; Marks, L. D.; Stair, P. C.; Marshall, C. L.; Poepelmeier, K. R. Epitaxial stabilization of face selective catalysts. *Top. Catal.* **2013**, *56*, 1829–1834.

(55) Kennedy, R. M.; Crosby, L. A.; Ding, K.; Canlas, C. P.; Gulec, A.; Marks, L. D.; Elam, J. W.; Marshall, C. L.; Poepelmeier, K. R.; Stair, P. C. Replication of SMSI via ALD: TiO<sub>2</sub> overcoats increase Pt-catalyzed acrolein hydrogenation selectivity. *Catal. Lett.* **2018**, *148*, 2223–2232.

(56) Engelhardt, C. M.; Kennedy, R. M.; Enterkin, J. A.; Poepelmeier, K. R.; Ellis, D. E.; Marshall, C. L.; Stair, P. C. Structure Sensitivity of Acrolein Hydrogenation by Platinum Nanoparticles on Ba<sub>x</sub>Sr<sub>1-x</sub>TiO<sub>3</sub> Nanocuboids. *ChemCatChem* **2018**, *10*, 632–641.