

VALIDATION OF CRACK INTERACTION LIMIT MODEL FOR PARALLEL EDGE CRACKS USING TWO-DIMENSIONAL FINITE ELEMENT ANALYSIS

R. Daud, A.K. Ariffin and S. Abdullah

Department of Mechanical and Materials Engineering, Faculty of Engineering and Built Environment, Universiti Kebangsaan Malaysia, 43600, Bangi, Selangor, Malaysia

Email: ruslizam@unimap.edu.my

Phone: +6049885323; Fax: +6049885167

ABSTRACT

Shielding interaction effects of two parallel edge cracks in finite thickness plates subjected to remote tension load is analyzed using a developed finite element analysis program. In the present study, the crack interaction limit is evaluated based on the fitness of service (FFS) code, and focus is given to the weak crack interaction region as the crack interval exceeds the length of cracks ($b > a$). Crack interaction factors are evaluated based on stress intensity factors (SIFs) for Mode I SIFs using a displacement extrapolation technique. Parametric studies involved a wide range of crack-to-width ($0.05 \leq a/W \leq 0.5$) and crack interval ratios ($b/a > 1$). For validation, crack interaction factors are compared with single edge crack SIFs as a state of zero interaction. Within the considered range of parameters, the proposed numerical evaluation used to predict the crack interaction factor reduces the error of existing analytical solution from 1.92% to 0.97% at higher a/W . In reference to FFS codes, the small discrepancy in the prediction of the crack interaction factor validates the reliability of the numerical model to predict crack interaction limits under shielding interaction effects. In conclusion, the numerical model gave a successful prediction in estimating the crack interaction limit, which can be used as a reference for the shielding orientation of other cracks.

Keywords: Crack interaction limit; interacting cracks; shielding effects; fitness for service.

INTRODUCTION

The presence of an edge cracking strip in aging critical engineering structures, e.g., aerospace structures and pressure vessel components, always places the structural integrity at risk of failure. In structural safety assessments, the presence of isolated single edge cracks may be easier to conduct. For multiple surface cracks, the damage tolerance of a single crack is no longer applicable owing to the existence of crack interaction behavior between the cracks (i.e., shielding and amplification). The pattern of evolution of multiple crack interaction is different and becomes increasingly complex when two or more cracks are present in close proximity. Table 1 shows the past and most recent solution models for evaluating stress-shielding parameters in parallel cracks. The list of analytical models and approaches in Table 1 that are used to develop the model, can be categorized into energy release rate criterion, stress intensity criterion, stress field traction, and the combination of many approaches. These models have contributed to the advancement of stress shielding assessment.

Table 1. Analytical elastic shielding interaction models.

Parallel multiple cracks	Models and approaches used	References
Parallel and collinear cracks	Simultaneous Singular Integral based on Disturbance Stress	(Ratwani and Gupta, 1974)
Parallel-Collinear cracks	Coefficient of Interaction	(Yokobori et al., 1979)
Parallel cracks	Asymptotic Approximation	(Chang, 1982)
Row of periodic cracks	Fredholm Integral Equations	(Chen, 1987)
Parallel and collinear cracks	Kachanov Method by Superposition-Average Traction	(Kachanov, 1987, 1993, 2003; Kachanov and Laures, 1988; Kachanov and Montagut, 1986; Kachanov et al., 1990)
Offset parallel cracks	Edge function methods	(Dwyer, 1997)
Periodic array cracks	Hypersingular Integral Equation	(Choi, 1997)
Shedding arrays of edge cracks	Energy release rate	(Parker, 1999)
Micro-cracks	Actual Displacement Discontinuity	(Gorbatikh and Kachanov, 2000)
Collinear and parallel interface cracks	Mushkelishvili and Burger's vector	(Han et al., 2002)
Distributed parallel cracks	Rotated Staggered Grid	(Orlowsky et al., 2003)
Parallel cracks and collinear cracks	Modified Kachanov Method	(Gorbatikh et al., 2007; Li et al., 2008)
Inclined and offset parallel and collinear cracks	Integral Equation Method	(Chen, 2007; Saha and Ganguly, 2005)
Offset parallel cracks	Complex Stress Function Method	(Sankar and Lesser, 2006)
Parallel cracks	Muskhelishvili and Laurent's series	(Li et al., 2008)
Parallel symmetric cracks	Schmidt Method	(Yang, 2009)
Parallel surface cracks	Singular Integral Method	(Feng and Jin, 2009)
Periodic edge cracks	Fourier Integral	(Yildirim et al., 2011)
Parallel edge cracks	Fourier and Cauchy Integral	(Chen and Wang, 2012)

Safety assessment of the presence of multiple cracks is commonly referred to recommended FFS codes. However, the theoretical and practical examination of the recommended FFS codes, such as ASME Boiler and Pressure Vessel Code Section XI (ASME, 1998, 2004), API 579 (ASME, 2007), British Standard PD6495 (BSI, 1991) and BS7910 (BSI, 1997, 2005), Nuclear Electric CEGB R6 (R6, 2006), and JSME Fitness-for-Service Code (JSME, 2000), have found that the exception of crack interaction in FFS combination rules has resulted in over-estimated and unrealistic

fracture and failure predictions, particularly for closely spaced cracks. Burdekin (1982) presented elastic and plastic crack interaction solutions based on crack open displacement and the J -integral.

The formulation by Iida (1983) established a new single coalesced crack, but crack interaction is excluded. Moreover, based on the Iida solution, Leek and Howard (1994a) proposed an estimation of a single coalesced crack and a function of crack interaction factor (Leek and Howard, 1994b, 1996) corresponding to stress intensity factors (SIFs) at crack tips obtained by finite element (FE) analysis. An FE alternating method has been developed by O'donoghue et al. (1984) to solve the problem of interacting multiple cracks in a finite solid. Moussa et al. (1999) used the finite element method (FEM) to calculate the J -integral and used it to analyze the interaction of two identical parallel non-coplanar surface cracks subjected to remote tension and pure bending loads in a 3D finite body. The application of the body force method (BFM) by Kamaya (2003) justified the direction of coalesced cracks with a proposed new formulation. Owing to the limitations of BFM, FEM and the virtual crack extension method is employed by Kamaya (2008a, 2008b) to investigate the formation of a single coalesced crack as a result of crack growth under fatigue loading. In creep loading conditions, Xuan et al. (2009) introduced a creep interaction factor to address the interaction between cracks as a reaction to the stress field under loading. Kamaya et al. (2010) used an S-version FEM to analyze the crack growth of surface cracks. In relation to the FFS code limitations, crack interaction problems are more concentrated on elastic crack interaction with crack propagation, rather than on elastic crack interaction without crack propagation. In the past, many techniques have focused on the strong interaction region, particularly on the combination rule of parallel to coplanar (shielding effect), and the assumption of two cracks as a single crack for coplanar cracks (amplification effect). Most proposed solutions have considered mainly the strong interaction region and none of them question how crack interaction will behave within the weak interaction region, especially when the interaction approaches the crack interaction limit (CIL) (Zulkifli et al., 2011). To date, there are few investigations with emphasis on investigating the shielding effects in the weak interaction region as the interaction approaches CIL.

This paper presents a numerical approach for modeling multiple edge strip cracks that experience weak elastic crack interaction in a finite plate (Kamal et al., 2012; Domínguez Almaraz et al., 2010). The crack interaction is limited to crack interaction without crack propagation, where the shielding effect is dominated in promoting fracture and failure. The aim of this paper is to study the effect of the relative position of two parallel edge cracks, subjected to a variation of crack interval b/a and crack-to-width ratio a/W . The numerical analysis was performed using 2D linear FE analysis using developed APDL codes in ANSYS. The obtained value of the SIFs and elastic crack interaction factor are compared with corresponding FFS rules and numerical data from literature.

For the present investigation of elastic CIL, the BSI codes (1991, 1997, 2005) statements and the works of Jiang et al. (1990, 1991, 1992), and Leek and Howard (1994a, 1994b, 1996) are taken as the interaction limit reference. It is used for determining the onset of weak interaction and where the weak interaction is diminished, focusing specifically on the effect of shielding for parallel edge cracks in a finite body. For reference, the elastic crack interaction (ECI) of all parallel cracks may be redefined to diminish approximately at $b \geq 3a$ with the assumption that the crack lengths

$a_i (i = 1, 2, \dots, n)$ are equal length. The new analytical ECI factor γ_{ECI} to address the CIL problem is proposed and it written as Eq. (1)

$$\gamma_{ECI} = \gamma_{ECI \rightarrow CIL}(a_i / W, b / a_i) \quad , (i = 0, 1, 2, \dots, n) \quad (1)$$

and needs to comply with FFS codes in the condition of

$$\begin{aligned} \gamma_{ECI}(a_i / W, b / a_i) &\propto FFS \text{ (ASME, BSI, JSME)} \\ \gamma_{ECI}(a_i / W, b / a_i) &\propto FFS \text{ (} b \geq 12.7 \text{ mm, } b \geq (a_1 + a_2) / 2, b > 10 \text{ mm)} \end{aligned} \quad (2)$$

CRACK INTERACTION LIMIT DETERMINATION

The new model of CIL is based on the formulation of the state of no interaction or a single cracked body to the state of having weak interaction, until the interaction becomes stronger as the crack interval decreases. The elastic CIL is based on the analytical works of Jiang et al. (1990, 1991, 1992), and Leek and Howard (1994a, 1994b, 1996) as reference. The SIF calculation is limited to a linear elastic problem with a homogeneous, isotropic material near the crack region. The SIF determination is based on the creation of a singular element at the crack tip based on a quadratic isoparametric finite element. A quarter-point singular element or 8-node collapsed quadrilateral element developed by Henshell and Shaw (1975) is used; this has distinct advantages in terms of time, meshing, and re-meshing over the other quarter-point element (Banks Sills, 2010). The singularity is obtained by shifting the mid-side node $1/4$ points close to the crack tip. To calculate the SIF, we assumed the elements to be in rigid body motion and constant strain modes. The accuracy of this special element has been addressed by Murakami (1976), where the crack tip nodal point is enclosed by a number of special elements and in analysis, the size, number, and compatibility of special elements really affect the accuracy.

By assuming the crack interaction will be diminished at $b \geq 3a_i$ and therefore, it is about equivalent to the SIF of a single crack in the state of zero crack interaction factor, the analytical single crack Mode I SIF proposed by Brown and Strawley (1966) is used as the SIF reference K_{Iref} , expressed as Eq. (3).

$$K_{Iref} = \sigma \sqrt{\pi a} \left(1.12 - 0.23 \left(\frac{a}{W} \right) + 10.6 \left(\frac{a}{W} \right)^2 - 21.7 \left(\frac{a}{W} \right)^3 + 30.4 \left(\frac{a}{W} \right)^4 \right) \quad (3)$$

Theoretically, to validate the model, the Mode I SIF of the CIL model $K_{I \rightarrow CIL}$ must be close to the value of K_{Iref} or $K_{I \rightarrow CIL} \approx K_{Iref}$, but it cannot be equal, i.e., $K_{I \rightarrow CIL} \neq K_{Iref}$. Therefore, based on Tada et al. (2001), the new $K_{I \rightarrow CIL}$ function is written as:

$$K_{I \rightarrow CIL} = \sigma^\infty \sqrt{\pi a_i} \left(C_1 - C_2 \left(\frac{a}{W} \right) + C_3 \left(\frac{a}{W} \right)^2 - C_4 \left(\frac{a}{W} \right)^3 + C_5 \left(\frac{a}{W} \right)^4 - C_n \left(\frac{a}{W} \right)^{n-1} \right) \quad (4)$$

where the constants C_1, \dots, C_n are assumed to be constant over the crack surface. Shown in Figure 1(a) are two straight parallel edge cracks in a finite plate and the two cracks

are under uniform far-field tension $P(\sigma^\infty)$ normal to crack faces, and where the cracks are of equal lengths: a_1 and a_2 . In this analysis, the ratios of (a/W) and (b/a) are used to evaluate the γ_I in the weak interaction region, which is assumed to be in the range of $1 \leq b/a \leq 3$. Therefore, the following cases are considered, where $(b/a) = 1.5, 2.0, 2.5, 3.0$ and $(a/W) = 0.05, 0.1, 0.15, 0.20, 0.25, 0.30, 0.35, 0.40, 0.45, 0.50$. Figure 1(a)–(c) also shows the two-dimensional configuration of the singular element. Based on Arakere et al. (2008), the meshing scheme is generated using ANSYS, as shown in Figure 1(d). The mesh encompassing the interacting cracks is divided into two zones: a global mesh, and the local mesh zone. Both zones are meshed with the 8-node isoparametric quadrilateral element that is used to build up the entire element for the two-dimensional plate, as illustrated in Figure 1(b). The SIF calculation is limited to the linear elastic problem with a homogeneous, isotropic material near the crack region. The studies are conducted in a pure Mode I loading condition with the specified material, Aluminium Alloy 7475 T7351 solid plate with constant thickness, homogenous isotropic continuum material, linear elastic behavior, small strain and displacements, and crack surfaces are smooth with the crack surfaces are almost contacting each other ($c_1 = c_2 = 0$).

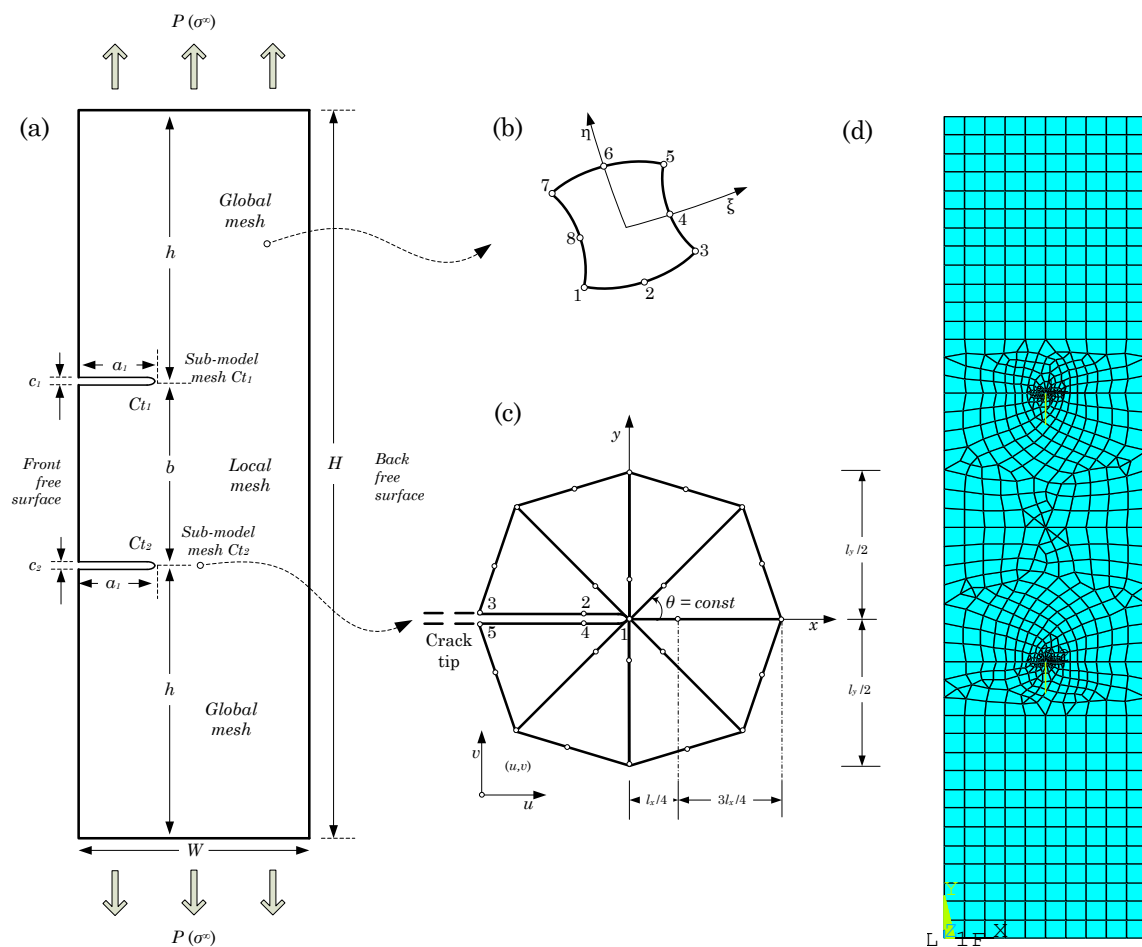


Figure 1. (a) Two parallel edge cracks in finite body, (b) 8-node quadrilateral element, (c) Barsoum singular element, and (d) complete meshing.

The SIF for CIL $K_{I \rightarrow CIL}$, is evaluated at the both crack tips of the edge strip cracks, as shown in Figure 1(a). The reduction of $K_{I \rightarrow CIL}$ comparative to K_{Iref} is denoted as $\Delta K_{I \rightarrow CIL}$ and is expressed as $\Delta K_{I \rightarrow CIL} = K_{Iref} - K_{I \rightarrow CIL}$. The SIF for Mode I K_I , is determined using the displacement extrapolation method using written APDL macro code in ANSYS, and is expressed as Eq. (5).

$$K_{I \rightarrow CIL} = (E / 3(1 + \nu)(1 + \kappa)) * (2\pi / l_y)^{1/2} * (4(\nu_2 - \nu_4) - ((\nu_3 - \nu_5) / 2)) \quad (5)$$

where E =Young's Modulus, $\kappa = 3 - 4\nu$ for plane stress, $\kappa = 3 - 4\nu / 1 - \nu$ for plane strain, l_y is the length of element, ν and u are displacements in a local Cartesian coordinate system, and ν is Poisson's ratio.

The elastic crack interaction factor for Mode I SIF is expressed as Eq. (6).


$$\gamma_I = K_{I \rightarrow CIL} / K_0 \quad (6)$$

where γ_I denotes the elastic interaction factor for Mode I and K_0 is the SIF for the plain specimen.


RESULTS AND DISCUSSION

Figure 2 shows the relationship between elastic crack interaction factor γ_I and the crack-to-width ratio a/W for the crack interval ratios ($b/a = 3$) and ($b/a = 2.5$). The elastic crack interaction factor γ_I is based on the SIF at the crack tips $K_{I \rightarrow CIL}$ and is normalized by K_0 , which is the SIF for the plain specimen. In the weak interaction range, ($1 < b/a \geq 3$) for ($b/a = 3$), strong interaction γ_I appears at $a/W = 0.5$ and it rapidly decreases when a/W approaches $a/W = 0.05$. Therefore, the intensity of γ_I depends on the variation of a/W ; it becomes larger as a/W increases. Figure 2 also shows a very small discrepancy (0.035%) between the intensity of γ_I for crack tips Ct_1 and Ct_2 . This indicates that under the assumption of a homogenous material with equal length cracks, the intensity of γ_I can be assumed equal.

According to FFS codes by ASME (2004, 2007), BSI (1997, 2005), and JSME (2000, 2008), parallel cracks can be assumed a single coplanar crack under certain conditions of crack interval. In reduction of the a/W ratio from 0.5 to 0.05, the present numerical model supports the FFS code by the indication of the intersection point at 0.1 and 0.07 (see Figure 2) and 0.05 (see Figure 3) as the crack interval decreases from $b/a = 3$ to $b/a = 1.5$. The prediction by Jiang et al. (1990) of $F_n(K_I)$ shows no intersection point for a single crack of $f_I(K_{Iref})$ (Brown and Strawley, 1966), and shows no possible sign for single coplanar crack agreement, as outlined by the FFS codes. Again, the present $\gamma_{I \rightarrow CIL}(C_1)$ and $\gamma_{I \rightarrow CIL}(C_2)$ show a good trend line prediction of elastic crack interaction intensity and comply with the recommended FFS codes.

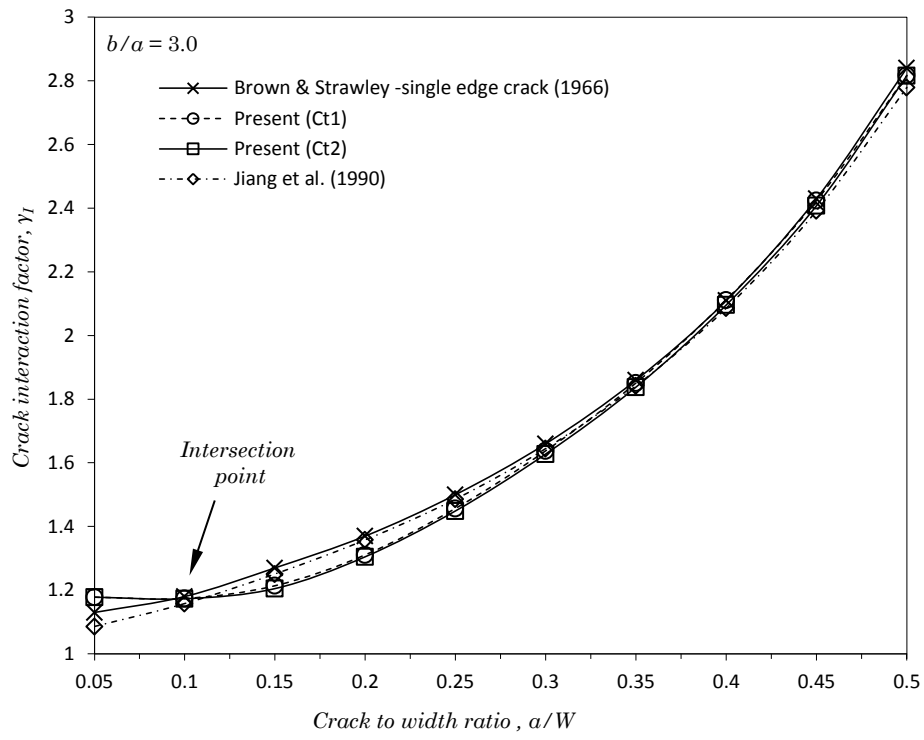


(a)

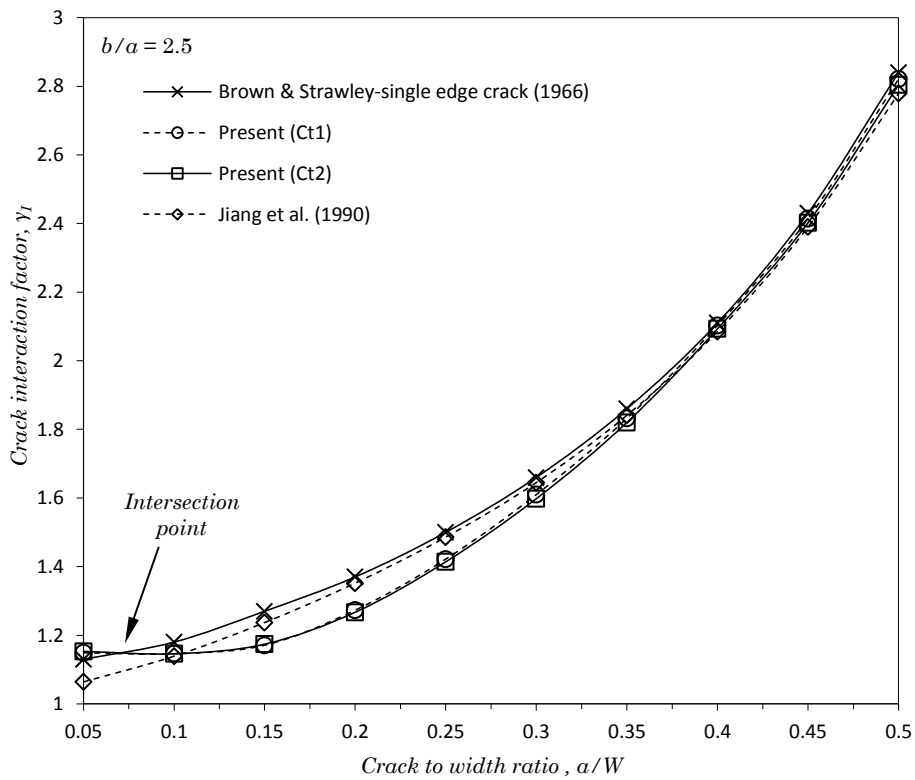


(b)

Figure 2. Elastic crack interaction factor: (a) $b/a = 3$, and (b) $b/a = 2.5$.

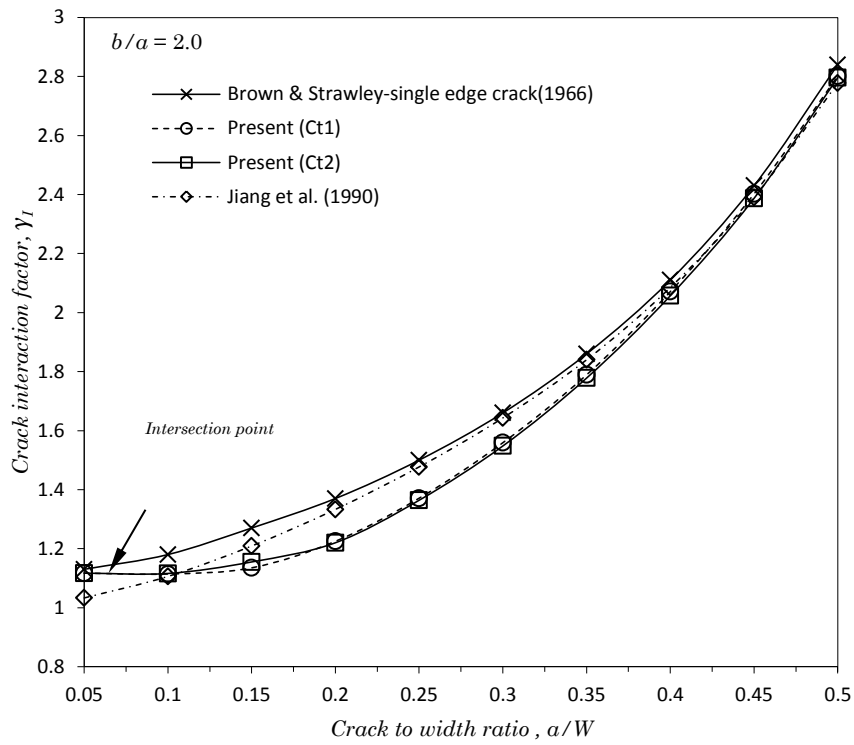

(a)

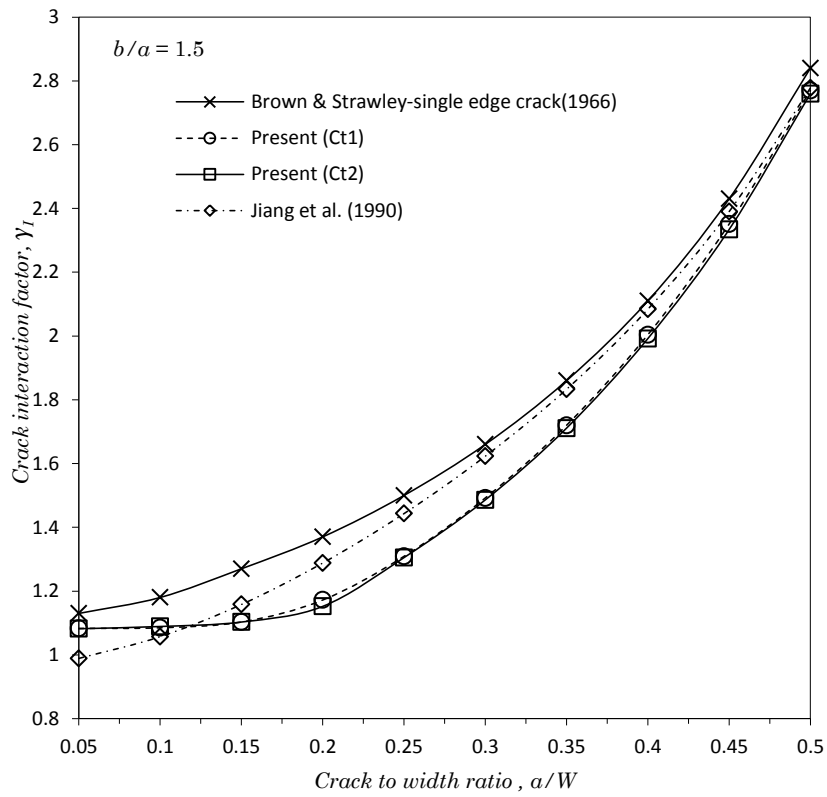

(b)

Figure 3. Elastic crack interaction factor: (a) $b/a = 2.0$, and (b) $b/a = 1.5$.

In order to validate the numerical model, the comparison is made with single crack SIF reference K_{Iref} (Brown and Strawley, 1966) Eq. (3) expressed as $f_I(K_{Iref})$. Good agreement was obtained, which provides confidence on the FE modeling and CIL interaction analysis of shielding effects. When compared with the condition of CIL claimed by Jiang et al. (1990), denoted as $F'_n(K_I)$, the present numerical model shows a significant improvement in the reduction of errors as a/W increases, as shown in Table 2.

Table 2. Crack interaction factor at ($b/a = 3.0$).

a/W	Analytical	Analytical	Present	
	$f_I(K_{Iref})$	$F'_n(K_I)$	$\gamma_{I \rightarrow CIL}(Ct_1)$	$\gamma_{I \rightarrow CIL}(Ct_2)$
0.05	1.133	1.085	1.178	1.178
0.1	1.184	1.158	1.174	1.173
0.15	1.266	1.251	1.214	1.205
0.2	1.373	1.358	1.311	1.305
0.25	1.505	1.486	1.457	1.449
0.3	1.665	1.645	1.638	1.628
0.35	1.864	1.842	1.851	1.838
0.4	2.113	2.086	2.111	2.096
0.45	2.432	2.392	2.424	2.408
0.5	2.843	2.799	2.817	2.816

CONCLUSION

An alternative solution for the elastic CIL for multiple parallel and equal edge strip cracks in a finite continuum body has been presented based on FE analysis. The close agreement with well-known analytical solutions for single edge cracks in a finite body validates the proposed solution for further applications for CIL analysis for closer crack distance, which involves higher crack interaction. Meanwhile, the compliance with recommended ASME codes, BSI codes, and JSME FFS codes provides additional evidence corroborating the present CIL prediction. Finally, it can be concluded that the CIL for equal and parallel edge cracks is depicted best at $b/a \geq 3$ because the crack interaction factor is approximately the normalized SIF value of a single edge crack with zero crack interaction.

ACKNOWLEDGMENTS

The authors wish to thank Dr. Mostafa Jamshidian and Prof. Dr. Masanori Kikuchi for crack interaction mechanic consultation. This research is supported by Fundamental Research Grant Scheme (FRGS), Ministry of Higher Education, Malaysia. All authors declare that there are no conflicts of interest that may arise as a result of this research.

REFERENCES

Arakere, N.K., Knudsen, E.C., Wells, D., McGill, P. and Swanson, G.R. 2008. Determination of mixed-mode stress intensity factors, fracture toughness and

- crack turning angle for anisotropic foam material. *International Journal of Solids and Structures*, 46: 4936-4951.
- ASME. 1998. ASME Boiler and Pressure Vessel Code, Section XI. New York, USA.
- ASME. 2004. ASME Boiler and Pressure Vessel Code, Section XI. New York, USA.
- ASME. 2007. 579-1 / FFS-1 Fitness-for-service, Section 9, American Society of Mechanical Engineers. New York, USA.
- Banks-Sills, L. 2010. Update: Application of the finite element method to linear elastic fracture mechanics. *Applied Mechanics Reviews*, 63: 1-17.
- Brown, W.F. and Strawley, J.E. 1966. ASTM STP 410.
- BSI. 1991. British Standard Institute, PD 6493, Section 8. Guidance on methods for assessing the acceptability of flaws in fusion welded structures.
- BSI. 1997. British Standard Institute, BS7910, Section 8. Guidance on methods for assessing the acceptability of flaws in structures.
- BSI. 2005. British Standard Institute, BS7910. Guidance on methods for assessing the acceptability of flaws in metallic structures.
- Burdekin, F.M. 1982. The role of fracture mechanics in the safety analysis of pressure vessels. *International Journal of Mechanical Sciences*, 24(4): 197-208.
- Chang, R. 1982. On crack-crack interaction and coalescence in fatigue. *Engineering Fracture Mechanics*, 16(5): 683-693.
- Chen, Y.Z. 1987. Plane problem of two rows of periodic crack. *Theoretical and Applied Fracture Mechanics*, 7: 185-188.
- Chen, Y.Z. 2007. Integral equation methods for multiple crack problems and related topics. *ASME Journal of Applied Mechanics*, 60: 172-194.
- Chen, Y.Z. and Wang, Z.X. 2012. Solution of multiple crack problem in a finite plate using coupled integral equations. *International Journal of Solids and Structures*, 49: 87-94.
- Choi, H.J. 1997. Mode I interaction of a periodic array of parallel cracks in a functionally graded nonhomogeneous plane. *KSME International Journal*, 11(3): 239-248.
- Domínguez Almaraz, G.M., Guzmán Tapia, M., Tapia Silva, E.E. and Cadenas Calderón, E. 2010. Fatigue life prediction based on macroscopic plastic zone on fracture surface of AISI-SAE 1018 steel. *International Journal of Automotive and Mechanical Engineering*, 1: 29-37.
- Dwyer, J.F. 1997. Edge function analysis of crack interaction in anisotropic materials. *Engineering Fracture Mechanics*, 56(2): 233-248.
- Feng, Y. and Jin, Z. 2009. Thermal fracture of functionally graded plate with parallel surface cracks. *Acta Mechanica Solida Sinica*, 22(5): 453-464.
- Gorbatikh, L. and Kachanov, M. 2000. A simple technique for constructing the full stress and displacement fields in elastic plates with multiple cracks. *Engineering Fracture Mechanics*, 66: 51-63.
- Gorbatikh, L., Lomov, S. and Verpoest, I. 2007. On stress intensity factors of multiple cracks at small distances in 2-D problems. *International Journal of Fracture*, 143: 377-384.
- Han, X., Ellyin, F. and Xia, Z. 2002. Interaction among interface, multiple cracks and dislocations. *International Journal of Solids and Structures*, 39: 1575-1590.
- Henshell, R.D. and Shaw, K.G. 1975. Crack tip finite elements are unnecessary. *International Journal for Numerical Methods in Engineering*, 9(3): 495-507.
- Iida, K. 1983. Shapes and coalescence of surface fatigue cracks. Paper presented at the International Symposium on Fracture Mechanics, Beijing, China.

- Jiang, Z.D., Petit, J. and Bezzine, G. 1990. Fatigue propagation of two parallel cracks. *Engineering Fracture Mechanics*, 37(5): 1139-1144.
- Jiang, Z.D., Petit, J., and Bezzine, G. 1991. Stress intensity factors of two parallel 3D surface cracks. *Engineering Fracture Mechanics*, 40(2): 345-354.
- Jiang, Z.D., Petit, J. and Bezzine, G. 1992. An investigation of stress intensity factors for two unequal parallel cracks in a finite width plate. *Engineering Fracture Mechanics*, 42(1): 129-138.
- Jiang, Z.D., Zeghloul, A., Bezzine, G. and Petit, J. 1990. Stress intensity factor of parallel cracks in a finite width sheet. *Engineering Fracture Mechanics*, 35(6): 1073-1079.
- JSME. 2000. JSME Fitness-for-Service Code S NA1-2000.
- JSME. 2008. JSME Fitness-for-Service Code S NA1-2008.
- Kachanov, M. 1987. Elastic solids with many cracks: a simple method of analysis. *International Journal of Solid Structures*, 23(1): 23-43.
- Kachanov, M. 1993. Elastic solids with many cracks and related problems. *Advances in Applied Mechanics*, 30: 259-445.
- Kachanov, M. 2003. On the problems of the crack interactions and crack coalescence. *International Journal of Fracture*, 120: 537-543.
- Kachanov, M. and Laures, J.P. 1988. Strong three dimensional interaction of several arbitrarily located penny-shaped cracks. *International Journal of Fracture*, 37: R63-R68.
- Kachanov, M. and Montagut, E. 1986. Interaction of a crack with certain microcrack arrays. *Engineering Fracture Mechanics*, 25(5/6): 625-636.
- Kachanov, M., Montagut, E.L.E. and Laures, J.P. 1990. Mechanics of crack-microcrack interactions. *Mechanics of Materials*, 10: 59-71.
- Kamal, M., Rahman, M.M. and Rahman, A.G.A. 2012. Fatigue life evaluation of suspension knuckle using multi body simulation technique. *Journal of Mechanical Engineering and Sciences*, 3: 291-300.
- Kamaya, M. 2003. A crack growth evaluation method for interacting multiple cracks. *JSME International Journal*, 46(1): 15-23.
- Kamaya, M. 2008a. Growth evaluation of multiple interacting surface cracks. Part II: Growth evaluation of parallel cracks. *Engineering Fracture Mechanics*, 75: 1350-1366.
- Kamaya, M. 2008b. Growth evaluation of multiple interacting surface cracks. Part I: Experiments and simulation of coalesced crack. *Engineering Fracture Mechanics*, 75: 1336-1349.
- Kamaya, M., Miyokawa, E. and Kikuchi, M. 2010. Growth prediction of two interacting surface cracks of dissimilar sizes. *Engineering Fracture Mechanics*, 77: 3120-3131.
- Leek, T.H. and Howard, I.C. 1994a. Estimating the elastic interaction factor of two coplanar surface cracks under Mode I load. *International Journal of Pressure Vessels and Piping*, 60: 307-321.
- Leek, T.H. and Howard, I.C. 1994b. Rules for the assessment of interacting surface cracks under Mode I load. *International Journal of Pressure Vessels and Piping*, 60: 323-339.
- Leek, T.H. and Howard, I.C. 1996. An examination of methods of assessing interacting surface cracks by comparison with experimental data. *International Journal of Pressure Vessels and Piping*, 68: 181-201.

- Li, D.F., Li, C.F., Shu, S.Q., Wang, Z.X. and Lu, J. 2008. A fast and accurate analysis of the interacting cracks in linear elastic solids. *International Journal of Fracture*, 151: 169-185.
- Moussa, W.A., Bell, R. and Tan, C.L. 1999. The interaction of two parallel non-coplanar identical surface cracks under tension and bending. *International Journal of Pressure Vessels and Piping*, 76: 135-145.
- Murakami, Y. 1976. A simple procedure for the accurate determination of stress intensity factors by finite element method. *Engineering Fracture Mechanics*, 8: 643-655.
- Murakami, Y. and Nasser, S.N. 1982. Interacting dissimilar semi-elliptical surface flaws under tension and bending. *Engineering Fracture Mechanics*, 16(3): 373-386.
- O'donoghue, P.E., Nishioka, T. and Atluri, S.N. 1984. Multiple surface cracks in pressure vessel. *Engineering Fracture Mechanics*, 20(3): 545-560.
- Orlowsky, B., Saenger, E.H., Gueguen, Y. and Saphiro, S.A. 2003. Effects of parallel cracks distributions on effective elastic properties- A numerical study. *International Journal of Fracture*, 124: 171-178.
- Parker, A.P. 1999. Stability of arrays of multiple edge cracks. *Engineering Fracture Mechanics*, 62: 577-591.
- R6. 2006. Nuclear Electric: Assessment of the integrity of structures containing defects, Revision 4. Gloucester, British Energy Generation Ltd.
- Ratwani, M. and Gupta, G.D. 1974. Interaction between parallel cracks in layered composites. *International Journal of Solids and Structures*, 10: 701-708.
- Saha, T.K. and Ganguly, S. 2005. Interaction of penny-shaped cracks with an elliptic crack under shear loading. *International Journal of Fracture*, 131: 267-287.
- Sankar, R. and Lesser, A.J. 2006. Generic overlapping cracks in polymers: modeling of interaction. *International Journal of Fracture*, 142: 277-287.
- Tada, H., Paris, P. C. and Irwin, G.R. 2001. *The stress analysis of cracks handbook*. New York: ASME Press.
- Xuan, F.Z., Si, J. and Tu, S.T. 2009. Evaluation of C^* integral for interacting cracks in plates under tension. *Engineering Fracture Mechanics*, 76: 2192-2201.
- Yang, Y.H. 2009. Multiple parallel symmetric mode III cracks in a functionally graded material plane. *Journal of Solid Mechanics and Materials Engineering*, 3(5): 819-830.
- Yildirim, B., Kutlu, O. and Kadioglu, S. 2011. Periodic crack problem for a functionally graded half-plane an analytic solution. *International Journal of Solids and Structures*, 48: 3020-3031.
- Yokobori, T., Sawaki, Y. and Nakanishi, S. 1979. Criterion for brittle fracture of notched or cracked specimens based on combined micro-and macro crack mechanics-II. *Engineering Fracture Mechanics*, 12: 125-141.
- Zulkifli, A., Ariffin, A.K. and Rahman, M.M. 2011. Probabilistic finite element analysis on vertebra lumbar spine under hyperextension loading. 3: 256-264.