
ZnO nanorods on reduced graphene sheets with excellent field emission, gas sensor and photocatalytic properties

Rujia Zou^a, Guanjie He^a, Kaibing Xu^a, Qian Liu^a, Zhenyu Zhang^b and Junqing Hu^{a,*}

^aState Key Laboratory for Modification of Chemical Fibers and Polymer Materials, College of Materials Science and Engineering, Donghua University, Shanghai 201620, China

^bCenter of Super-Diamond and Advanced Films (COSDAF), Department of Physics and Materials Science, City University of Hong Kong, Hong Kong

E-mail: hu.junqing@dhu.edu.cn

I. The reduced graphene sheets' preparation

0.01 g of graphite oxide sheets were ultrasonically dispersed into 10 mL of absolute ethanol in a capped bottle, followed by ultrasonic stirring for 1 h to form a homogeneous suspension. The homogeneous suspension was spin-coated on a SiO₂/Si substrate at 1000 rpm over 2 min, and then thermally reduced at 650 °C for 30 min under a 100 sccm H₂ gas flow. Figs. S1a and b reveal that the as-grown reduced graphene sheets (rGss) are multi-layered (≤ 8 nm) with a mean area of ~ 10 -300 μm^2 .

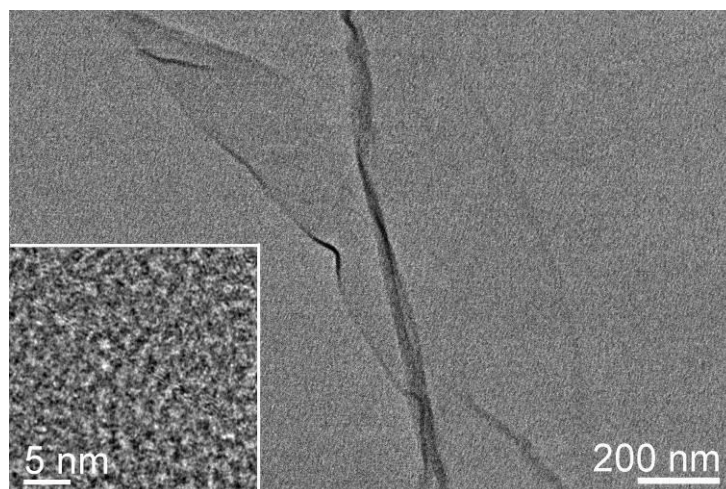


Fig. S1 TEM image shows a rGs; the inset shows that the rGs is multi-layered.

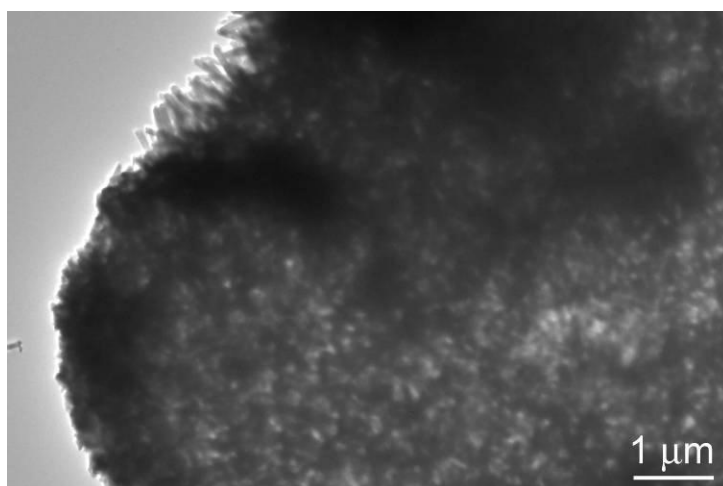


Fig. S2 TEM images show that the ZnO nanorod arrays are assembled on the graphene sheets' surfaces.

II. Synthesis of ZnO Nanorods

The Ni foam substrates were put in a mixed solution consisting of $\text{Zn}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$ (0.025 M), hexamethylenetetramine (0.025 M), and 50 mL de-ionized water. After being stirred, the mixture was subjected to a hydrothermal process at 95 °C for 8 h in a 60 mL autoclave. After reactions, the Ni foam substrates were removed from the solution, and the as-obtained product in solution was washed successively with deionized water and ethanol to remove any residual ionic species, and finally dried in vacuum at 60 °C for 12 h. Fig. S3a shows a low-magnification SEM image of the primary ZnO nanorods, which are well controllable, high yield, and high reproducibility. The nanorods have a diameter of 50~80 nm and length of 1~2 μm, with a relative smooth surface, as shown in Fig. S3b.

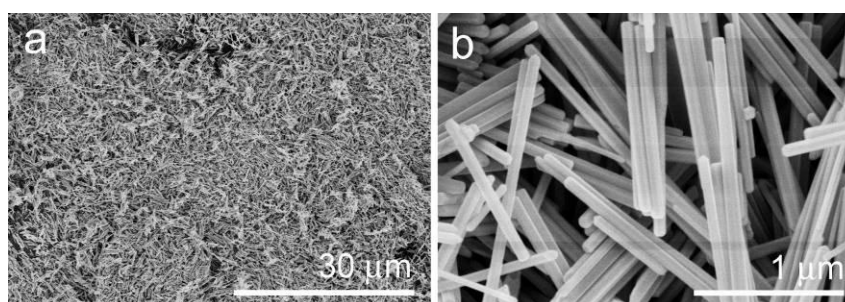


Fig. S3 (a) and (b) SEM image showing the ZnO nanorod.